

## ABx Rare Earth Resources Exceed 50 Million Tonnes

Block model completed for entire Deep Leads-Rubble Mound rare earth deposit

Model estimates 52 million tonnes averaging 817 ppm total rare earth oxides (TREO), from 39% of the mineralised outline

Resource has remarkably high proportion of dysprosium + terbium, averaging 4.4% of TREO, and some blocks exceed 6%

ABx Group (ASX: ABX) ("ABx" or "the Company") is pleased to announce that the Company and its consultants have completed the first comprehensive block model resource estimation of the Deep Leads-Rubble Mound rare earth resources. The full resources report is attached.

The resource estimate exceeds 50 million tonnes at approximately the same grade as previous smaller-scale resource estimates (Table 1). The cut-off grade is 350 ppm TREO-CeO<sub>2</sub>. The resource has the highest proportion of dysprosium + terbium (4.4% of TREO) of any clay-hosted rare earths resource in Australia. The relative proportion of rare earth oxides in the resource estimate is shown in Figure 1.

The resource model is based on data from 407 drillholes across the resource area and covers 39% of the identified mineralised outline. Furthermore, because it models all intercepts to date, the resource estimates highlights four high grade zones that warrant follow-up (Figure 2).

The exploration potential is self-evident and exploratory drilling is currently in full swing.

**Table 1: Mineral resources at Deep Leads – Rubble Mound (350 ppm cut-off grade)**

Resource Category	Million Tonnes	Avg depth (m)	Avg base (m)	Avg thickness (m)	TREO ppm	TREO-CeO <sub>2</sub> ppm	Perm Mag ppm	Permanent Magnet REOs				Key Ratios	
								Nd <sub>2</sub> O <sub>3</sub> ppm	Pr <sub>6</sub> O <sub>11</sub> ppm	Tb <sub>2</sub> O <sub>7</sub> ppm	Dy <sub>2</sub> O <sub>3</sub> ppm	PermMag TREO %	Tb+Dy TREO %
Inferred	45	4.3	12.1	7.8	806	623	211	140	36	5.1	30	26%	4.4%
Indicated	7	4.3	11.2	6.9	886	696	232	153	38	5.8	34	26%	4.5%
<b>Totals</b>	<b>52</b>	<b>4.3</b>	<b>12.0</b>	<b>7.7</b>	<b>817</b>	<b>633</b>	<b>214</b>	<b>142</b>	<b>36</b>	<b>5.2</b>	<b>31</b>	<b>26%</b>	<b>4.4%</b>

### Other Rare Earth oxides

### Low radioactivity

Resource Category	CeO <sub>2</sub> ppm	Er <sub>2</sub> O <sub>3</sub> ppm	Eu <sub>2</sub> O <sub>3</sub> ppm	Gd <sub>2</sub> O <sub>3</sub> ppm	Ho <sub>2</sub> O <sub>3</sub> ppm	La <sub>2</sub> O <sub>3</sub> ppm	Lu <sub>2</sub> O <sub>3</sub> ppm	Sm <sub>2</sub> O <sub>3</sub> ppm	Tm <sub>2</sub> O <sub>3</sub> ppm	Yb <sub>2</sub> O <sub>3</sub> ppm	Y <sub>2</sub> O <sub>3</sub> ppm	U <sub>3</sub> O <sub>8</sub> ppm	ThO ppm
Inferred	182	17	8.8	32	6.0	121	2.2	32	2.3	14	175	1.7	6.4
Indicated	190	19	10.2	36	6.7	130	2.4	35	2.6	16	204	1.7	6.3
<b>Totals</b>	<b>183</b>	<b>17</b>	<b>9.0</b>	<b>33</b>	<b>6.1</b>	<b>122</b>	<b>2.2</b>	<b>33</b>	<b>2.4</b>	<b>15</b>	<b>179</b>	<b>1.7</b>	<b>6.4</b>


**Parameters** Block cut-off grade (cog) = 350ppm TREO-CeO<sub>2</sub> Minimum thickness = 2 metres Search ellipse = 120m (Ind), 250m(Inf) Density = 1.9 tonnes/cubic metre  
TREO = total rare earth elements as oxides. TREO-CeO<sub>2</sub> = TREO minus cerium oxide

**Commenting on the resource estimate, ABx Group Managing Director and CEO Mark Cooksey said:**

"This block-modelling of resources is another significant step towards commercial assessment. It geostatistically models almost twice the tonnage of earlier polygonal estimates at similar grades to give guidance to ABx's exploration of an extensive area of ionic adsorption clay rare earth mineralisation.

"Equally as important, ABx is now focusing on identifying higher grades, and the block model has confirmed four high grade rare earth zones in accessible sites that warrant infill drilling. ABx's resource is exceptionally enriched in permanent magnet rare earths, especially dysprosium and terbium, which have the highest supply risk and are almost exclusively produced from ionic adsorption clay rare earth deposits.

"ABx is focused on creating a rare earths project that can address looming supply shortages of these critical minerals".

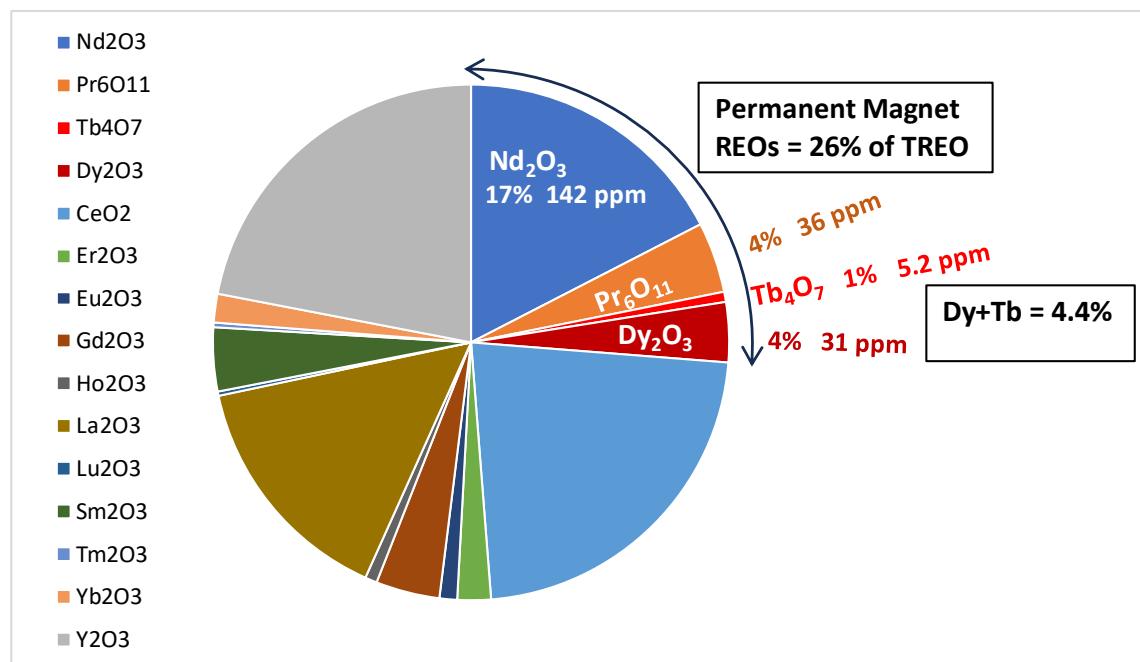

**Figure 1: Relative proportion of rare earth oxides in resource estimate**

The map of the resource model results (Figure 2) shows 'REE Accumulation' for each resource block, which is the grade (TREO) x thickness (metres). The four main high grade rare earth zones identified by this resource model are (1) Deep Leads, (2) Rubble Mound, (3) Alluvial Flats and (4) Leech Scrub, which is the company's newest prospect area.

#### **Location and Infrastructure**

ABx's IAC deposits are located in accessible pine plantations near highways, rail lines, airports, international shipping ports, grid hydropower and cities with major engineering capabilities and heavy industries (Figure 3).

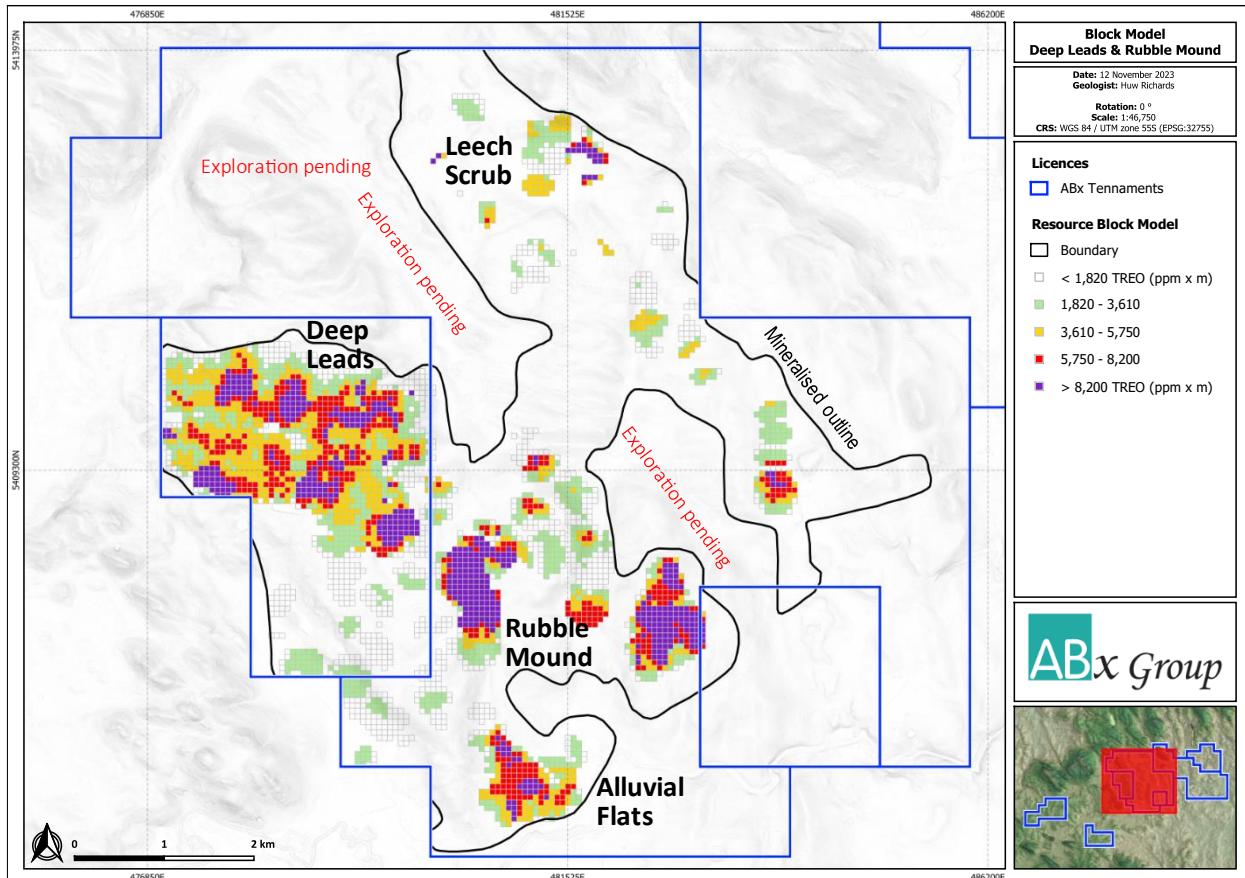


Figure 2: Map of block model showing the zones of high REE enrichment as the purple, red and orange blocks

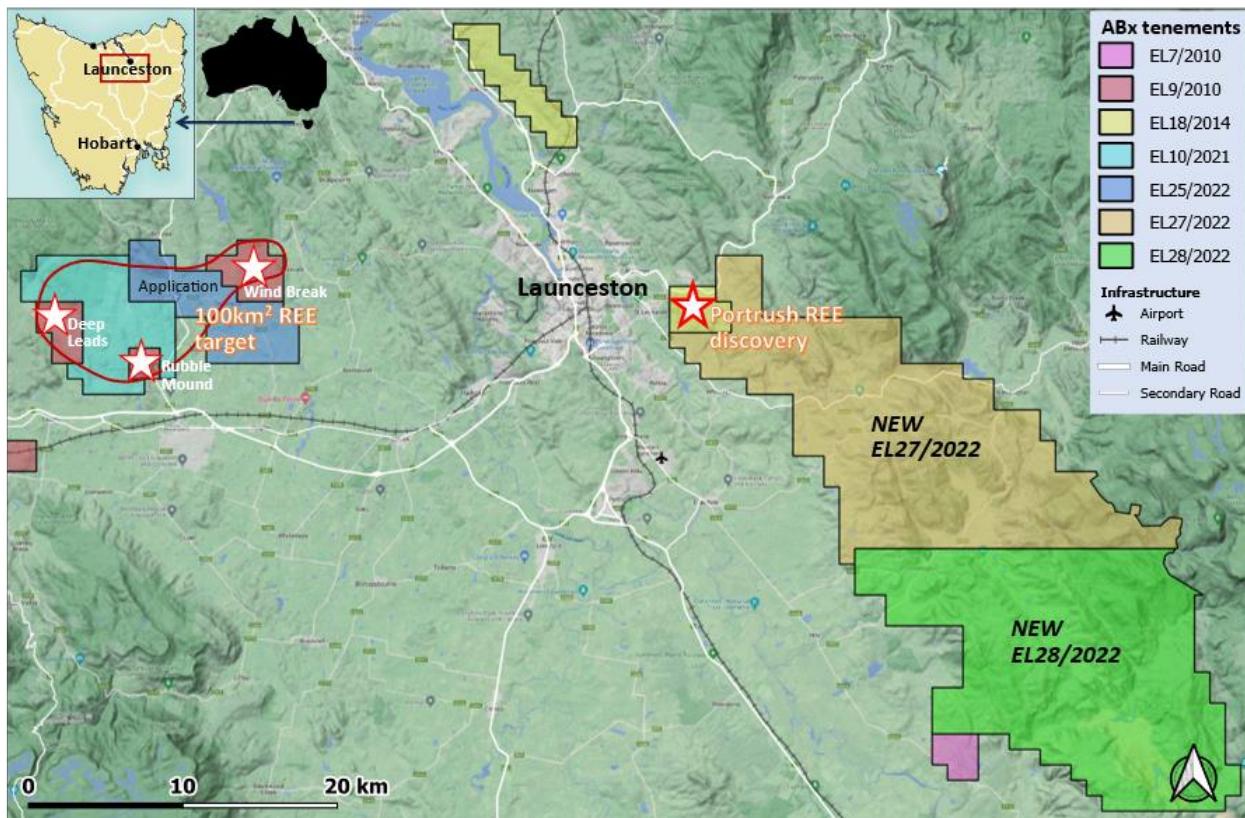


Figure 3: Location of ABx Exploration Projects in northern Tasmania

**Table 2 - Summary of resource estimation information in accordance with LR 5.8.1**

<b>Geology and geological interpretation</b>	REE mineralisation occurs in clay layers that overlie a Jurassic age dolerite basement in a district with some residual weathered Tertiary age alkali basalt. Jurassic age tholeiitic dolerite and Tertiary age bauxite-laterite are the main bedrock geological units. Paleochannels host thicker clay zones which host the rare earth element mineralisation.
<b>Sampling and sub-sampling techniques</b>	Sampling was at 1 metre intervals. Subsampling for assaying is by quartering the clay samples twice and each time, mixing diagonally opposite quarters. Assay results from resampling correspond satisfactorily.
<b>Drilling techniques</b>	RC aircore and push-tube coring used.
<b>Criteria used for classification, including drill and data spacing and distribution.</b>	Indicated Resources are those blocks with grades above the cut-off grade that were estimated based on a minimum 4 samples within 120 metres. Inferred Resources are those blocks with grades above the cut-off grade that were estimated based on a minimum 4 samples within 250 metres.
<b>Sample analytical method</b>	Assay samples are analysed by standard NATA-approved induction coupled plasma analytical methods for rare earth elements at ALS labs in Brisbane (method ME-MS81) and LabWest in Perth (method MMA04). Interlab comparisons proved satisfactory.
<b>Estimation methodology</b>	The centroid of each 1 metre sample is accurately located in Easting, Northing and RL coordinates. Because the clay horizon drapes the topography, estimation is by two runs of horizontal circular search ellipses. The first search ellipse is 120 metres horizontally and 2 metres vertically to define Indicated Resources. The second search ellipse is at 250 metres to estimate Inferred Resources. Clay density is typically 2 tonnes per cubic metre, but some samples exhibit density loss, so a density of 1.9 tonnes per cubic metre was applied globally.
<b>Cut-off grade</b>	Block cut-off grade is 350 ppm TREO - CeO <sub>2</sub> which is equivalent to 250 to 300 ppm TREO – CeO <sub>2</sub> in drillholes. A separation between background and mineralised grades exists at 190-260ppm TREO-CeO <sub>2</sub> . See Fig 10.
<b>Mining and metallurgical methods and parameters, and other modifying factors</b>	None applicable at this resource-drilling stage. Production and rehabilitation strategies are being reviewed. Deposits of this type are mined in China but under very different jurisdictions. The land is freehold hardwood and pine plantations.

The complete resource report with required data and JORC Appendix 1 information is attached.

This announcement is approved for release by the board of directors.

### For further information please contact:

Dr Mark Cooksey  
 MD & CEO, ABx Group  
 Mobile: +61 447 201 536  
 Email: [mcooksey@abxgroup.com.au](mailto:mcooksey@abxgroup.com.au)  
 Website: abxgroup.com.au

### Media

Chapter One Advisors  
 David Tasker / Alex Baker  
[dtasker@chapteroneadvisors.com.au](mailto:dtasker@chapteroneadvisors.com.au) / [abaker@chapteroneadvisors.com.au](mailto:abaker@chapteroneadvisors.com.au)  
 T: +61 433 112 936 / +61 432 801 745

## About ABx Group Limited

ABx Group (ABX) is a uniquely positioned, high-tech Australian company delivering materials for a cleaner future.

The two current areas of focus are:

- Creation of an ionic adsorption clay rare earth project in northern Tasmania
- Establishment of a plant to produce hydrogen fluoride and aluminium fluoride from recycled industrial waste, via its 83%-owned subsidiary, Alcore

There is also a legacy business:

- Mining and enhancing the value of bauxite resources for cement, aluminium and fertilisers.

We only operate where welcomed and we apply best practices to restore any disturbed land to a better condition than we found it.

## Qualifying statements

### Disclaimer Regarding Forward Looking Statements

This ASX announcement (Announcement) contains various forward-looking statements. All statements other than statements of historical fact are forward-looking statements. Forward-looking statements are inherently subject to uncertainties in that they may be affected by a variety of known and unknown risks, variables and factors which could cause actual values or results, performance, or achievements to differ materially from the expectations described in such forward-looking statements.

ABx does not give any assurance that the anticipated results, performance, or achievements expressed or implied in those forward-looking statements will be achieved.

### Competent Persons Statement

The information in this report that relate to Exploration Information and Mineral Resources are based on information compiled by Ian Levy who is a member of The Australasian Institute of Mining and Metallurgy and the Australian Institute of Geoscientists. Mr Levy is a qualified geologist and a director of ABx Group Limited.

Mr Levy has sufficient experience, which is relevant to the style of mineralisation and type of deposit under consideration and to the activity, which he is undertaking to qualify as a Competent Person as defined in the 2012 Edition of the Australasian Code for Reporting of exploration Results, Mineral Resources and Ore Reserves. Mr Levy has consented in writing to the inclusion in this report of the Exploration Information in the form and context in which it appears.

\* \* \*

## REE Resources Report for Deep Leads-Rubble Mound

### Executive summary

A geostatistical block model of the Deep Leads-Rubble Mound rare earth element (REE) resources in ABx's tenements EL9/2010 and EL10/2021 in northern Tasmania has estimated the following JORC-compliant Inferred and Indicated Resources at a block cut-off grade (cog) of 350 ppm TREO-CeO<sub>2</sub>:

**Table 1: Mineral Resources at Deep Leads-Rubble Mound: 350ppm cog**

Resource Category	Million Tonnes	Avg depth (m)	Avg base (m)	Avg thickness (m)	TREO ppm	TREO-CeO <sub>2</sub> ppm	Perm Mag ppm	Permanent Magnet REOs				Key Ratios	
								Nd <sub>2</sub> O <sub>3</sub> ppm	Pr <sub>6</sub> O <sub>11</sub> ppm	Tb <sub>4</sub> O <sub>7</sub> ppm	Dy <sub>2</sub> O <sub>3</sub> ppm	PermMag TREO %	Tb+Dy TREO %
Inferred	45	4.3	12.1	7.8	806	623	211	140	36	5.1	30	26%	4.4%
Indicated	7	4.3	11.2	6.9	886	696	232	153	38	5.8	34	26%	4.5%
<b>Totals</b>	<b>52</b>	<b>4.3</b>	<b>12.0</b>	<b>7.7</b>	<b>817</b>	<b>633</b>	<b>214</b>	<b>142</b>	<b>36</b>	<b>5.2</b>	<b>31</b>	<b>26%</b>	<b>4.4%</b>


### Other Rare Earth oxides

Resource Category	CeO <sub>2</sub> ppm	Er <sub>2</sub> O <sub>3</sub> ppm	Eu <sub>2</sub> O <sub>3</sub> ppm	Gd <sub>2</sub> O <sub>3</sub> ppm	Ho <sub>2</sub> O <sub>3</sub> ppm	La <sub>2</sub> O <sub>3</sub> ppm	Lu <sub>2</sub> O <sub>3</sub> ppm	Sm <sub>2</sub> O <sub>3</sub> ppm	Tm <sub>2</sub> O <sub>3</sub> ppm	Yb <sub>2</sub> O <sub>3</sub> ppm	Y <sub>2</sub> O <sub>3</sub> ppm	U <sub>3</sub> O <sub>8</sub> ppm	ThO ppm
Inferred	182	17	8.8	32	6.0	121	2.2	32	2.3	14	175	1.7	6.4
Indicated	190	19	10.2	36	6.7	130	2.4	35	2.6	16	204	1.7	6.3
<b>Totals</b>	<b>183</b>	<b>17</b>	<b>9.0</b>	<b>33</b>	<b>6.1</b>	<b>122</b>	<b>2.2</b>	<b>33</b>	<b>2.4</b>	<b>15</b>	<b>179</b>	<b>1.7</b>	<b>6.4</b>

Parameters Block cut-off grade (cog) = 350ppm TREO-CeO<sub>2</sub> Minimum thickness = 2 metres Search ellipse = 120m (Ind), 250m(Inf) Density = 1.9 tonnes/cubic metre  
TREO = total rare earth elements as oxides. TREO-CeO<sub>2</sub> = TREO minus cerium oxide

This resource is a confirmed ionic adsorption clay-hosted REE deposit (IAC REE) which is rare in Australia. It also has the highest ratio of the most critical REE species, Dysprosium + Terbium to TREO (Dy+Tb/TREO) at over 4.4%.

The area estimated by the block model is 39% of the mineralised outline identified by exploration to date.

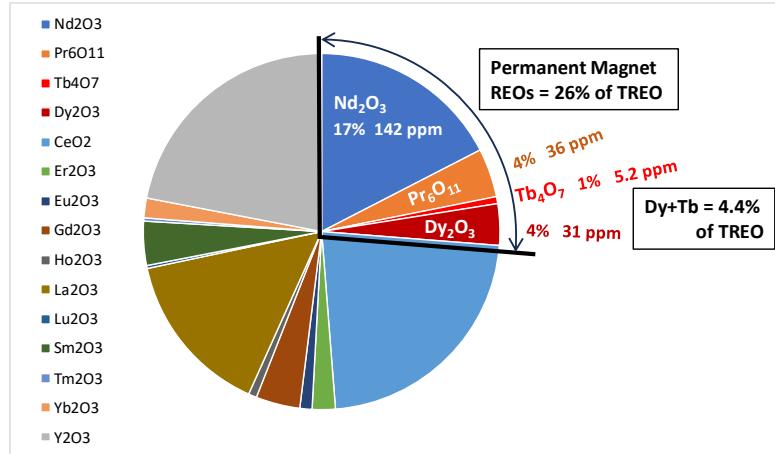

**Figure 1:** Pie chart showing the relative proportions of each rare earth element oxide

#### Notes:

The main revenue-earning Permanent Magnet REOs are high, being 26% of total rare earth oxides (TREO)

Critical REOs of Dy+Tb are, on average, 4.4% of TREO and has some areas exceeding 6% of TREO. This is the highest concentration ratio of Dy+Tb in Australia and high by world standards.

Uranium & Thorium grades are low (see Table 1) which is a preferred outcome.

**Large Deposit:** This resource block-model estimates 52 million tonnes, which is almost twice the tonnage of earlier polygonal estimates, and has similar grades to those smaller-scale polygonal estimates.

**High Leach Recoveries:** This resource has very high extractions of REE from clays under relatively benign leach conditions around pH 4, which proves the mineralisation to be an ionic adsorption clay (IAC) type.

**Dy+Tb-Rich:** ABx's resource is exceptionally enriched in permanent magnet rare earths, especially dysprosium (Dy) and terbium (Tb), which are the most valuable rare earths and are almost exclusively produced from IAC REE deposits, mainly in southern China and lately in Myanmar.

**High Grade Exploration Targets:** This new resource model gives guidance to ABx's exploration of an extensive area of ionic adsorption clay (IAC) REE mineralisation. Importantly, the resource estimate identifies four high grade REE zones in accessible sites that warrant infill drilling for feasibility studies.

The following map of the resource model shows “REE Accumulation” for each resource block, which is the TREO grade x metres thickness (ppm x m).

The four main high grade REE zones identified by this resource model are shown in Figure 2 below as (1) Deep Leads, (2) Rubble Mound, (3) Alluvial Flats and (4) Leech Scrub, which is the company’s newest prospect area.

The exploration potential is self-evident and exploratory drilling is currently on-going.

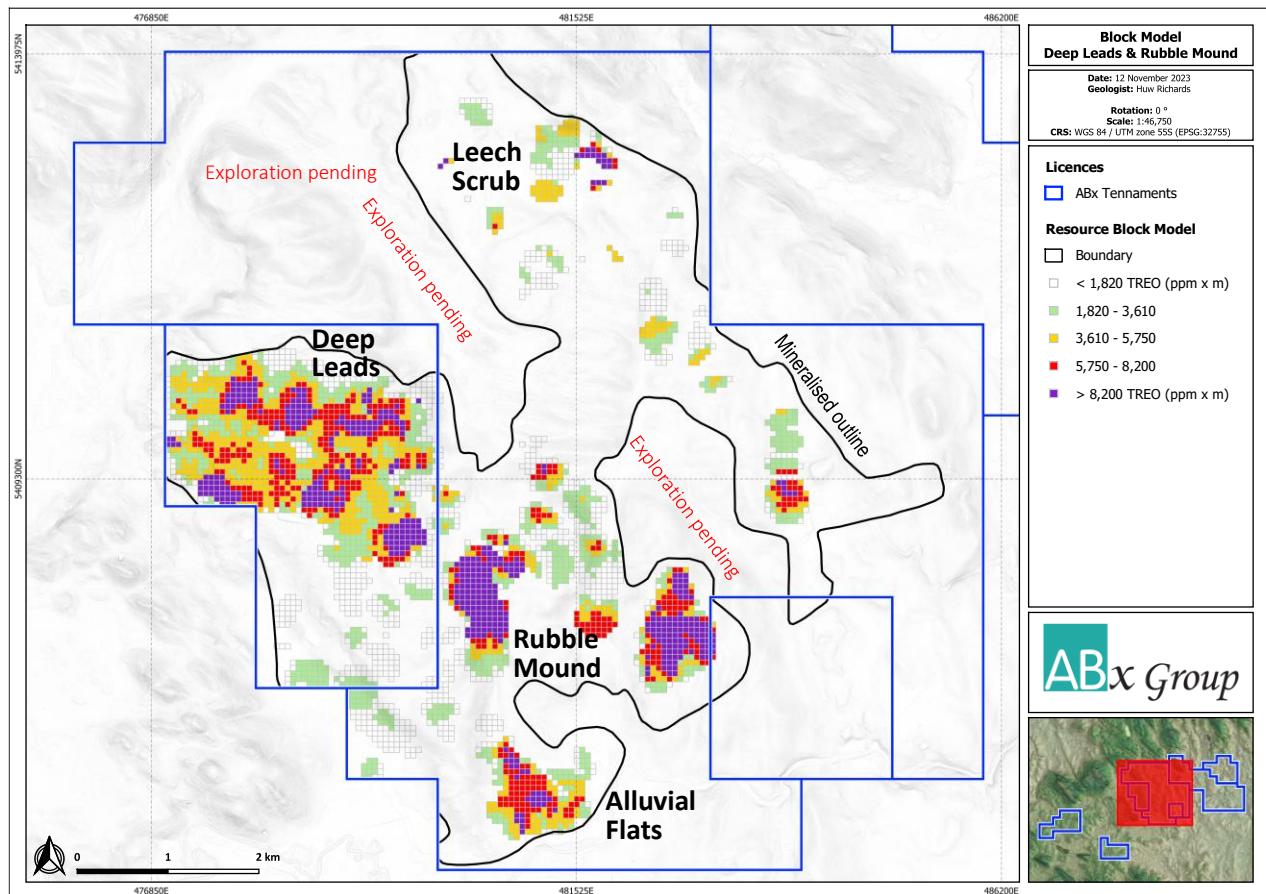


Figure 2: Map of block model showing the zones of high REE enrichment as the purple, red and orange coloured blocks.

This resource model is based on the following data from 407 drillholes across the resource area:

Drilling used in resource estimate
1,919 metres Deep Leads
1,922 metres Rubble Mound
<b>3,841 metres total</b>

Table 2: Statistics of metres drilled and the number of assays from the 407 drillholes used in this resource estimate

Assays used in resource estimate
1,219 assays Deep Leads
1,124 assays Rubble Mound
<b>2,343 assay samples total</b>

## Deposit significance

ABx is in the early stages of expanding the size of its clay-hosted Rare Earth Elements (REE) resource in northern Tasmania that is more enriched in the most important REE species, Dy and Tb, than any other Australian REE resource. Dy & Tb are in critical short supply.

Rare Earth Elements (REE), especially the permanent magnet REE species, Pr, Nd, Tb & Dy, are strategically important minerals for magnets, electronics, IT, communications, renewable energy-green transition technologies and military applications. Current supply is dominated by China.

ABx's ionic adsorption clay REE deposit (IAC REE) has achieved high extraction rates of up to 88% of REE using benign, low-cost processing leaching at pH4, confirming it to be a IAC REE deposit which are rare and important. At present Dy & Tb is mainly sourced from IAC REE deposits in southern China and Myanmar.

## Deposit Geology

This resource largely occurs in clays of variable thickness up to 40 metres overlaying Tasmanian dolerite, which is a stacked series of igneous sills.

**Bedrock dolerite:** The dolerite has intruded as hundred-metre-thick, columnar-jointed sills as part of the Ferrar Dolerite, which is the world's 5<sup>th</sup>-largest igneous magmatic event that intruded the crust during the Jurassic geological era (190-180 Ma) when Australia was in the final stages of breaking away from the rest of Gondwana.

Whilst the dolerite is classified as a tholeiite, which is typically rich in aluminium, low in potassium and more typically found in ocean floor settings, many of the Tasmanian dolerite features are enigmatic.

**Tertiary basalts:** The region also has 20 to 30Ma old alkali basalts (see Figure 3) but, in the resource area, these are only found as rare rubble rocks in creeks.

**Bauxite-Laterite:** These basalts and the oldest plateaus of dolerite have been bauxitised or lateritised, probably during the Tertiary wet periods, most of which has been eroded away – see Figure 4.

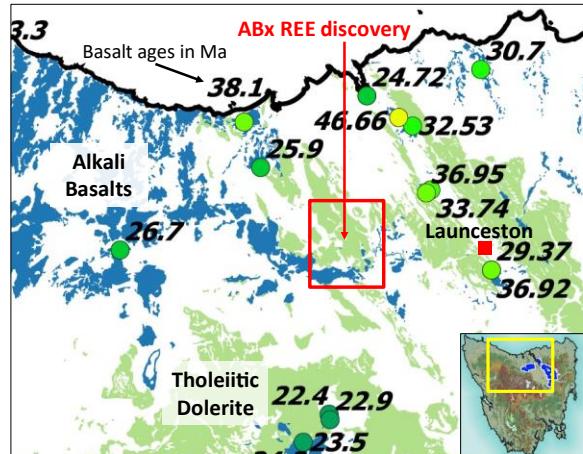


Figure 3: Dolerite and basalt in northern Tasmania.  
Source: Mineral Resources Tasmania map

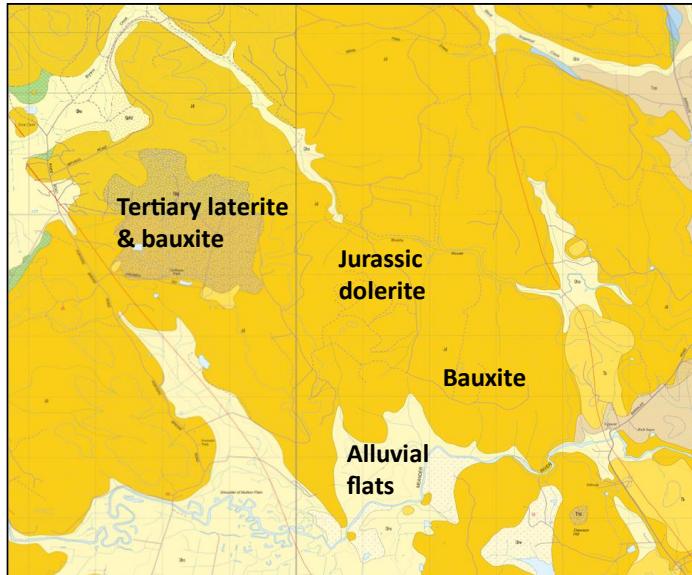


Figure 4 (left): Geological map of the current resource area

Source: Mineral Resources Tasmania maps & ABx mapping

Outcrop in the area is poor to moderate with occasional bars of bedrock dolerite rock. A lot of the area is strewn with dolerite boulders “floating” in heavy clay soils that have often been deeply ploughed for plantation forestry.

Undulations in bedrock topography are not always mirrored by the current surface topography, with some channels in the bedrock being totally concealed. Channels are often strongly mineralised.

## Economic Setting

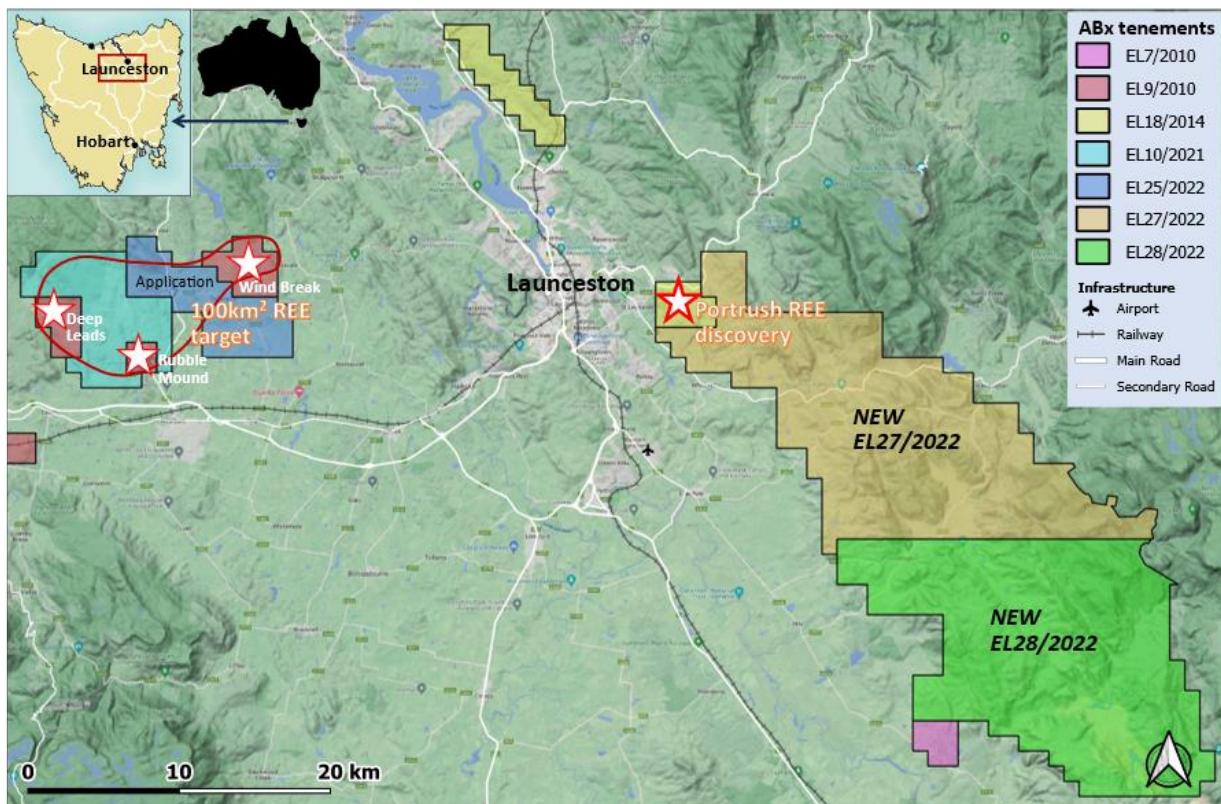


Figure 5: Location of ABx Exploration Projects in northern Tasmania

ABx has 4 REE discovery project areas in northern Tasmania at Deep Leads, Rubble Mound, Wind Break and Portrush, and is expanding its tenement holdings significantly (see Figure 5 above) to capitalise on its exploration knowledge and first-mover advantages.

The resource estimate presented here relates to only two of ABx's known REE discoveries, namely Deep Leads and Rubble Mound west of Launceston, which have been drilled sufficiently for a resource estimation by block modelling methods.

This resource is ideally located (see Figure 5) with regards:

1. Transport: major highways, rail, export ports and airport. Sealed roads to the project
2. Electricity: hydro and renewable power grid with lowest-quartile industrial electricity costs
3. Water: abundant town water, dam water, permanent rivers and groundwater
4. Accessibility: most of the resource is in freehold pine plantations and scrubland
5. Housing: modern towns and cities within 40 minutes drive of the project area
6. Industry: heavy engineering in Launceston and Tasmania's large mining sector
7. Workforce: skilled workforces, with two major smelters in region
8. Zoning: 3 hard-rock quarries operate nearby for the construction industry

There are no known barriers to developing a project at this location, subject to the normal approval processes. ABx has operated in Tasmania since 2010 and is well known for its strict adherence to its paramount corporate policy to apply the best practices for land management and rehabilitation; to leave the land better than they found it and to only operate where welcomed.

## Tenements

These resources occur on two contiguous Exploration Licence tenements, namely EL9/2010 Deloraine-Deep Leads covering an area of 13,600 hectares (136km<sup>2</sup>) and EL10/2021 Brushy Rivulet-Rubble Mound covering an area of 5,100 hectares (51km<sup>2</sup>).

Figure 6 below shows the tenement boundaries and an outline of the area that has been explored to date and found to have mineralisation with elevated REE grades. Only a small proportion of the mineralised area has been sufficiently drilled for resource estimation.

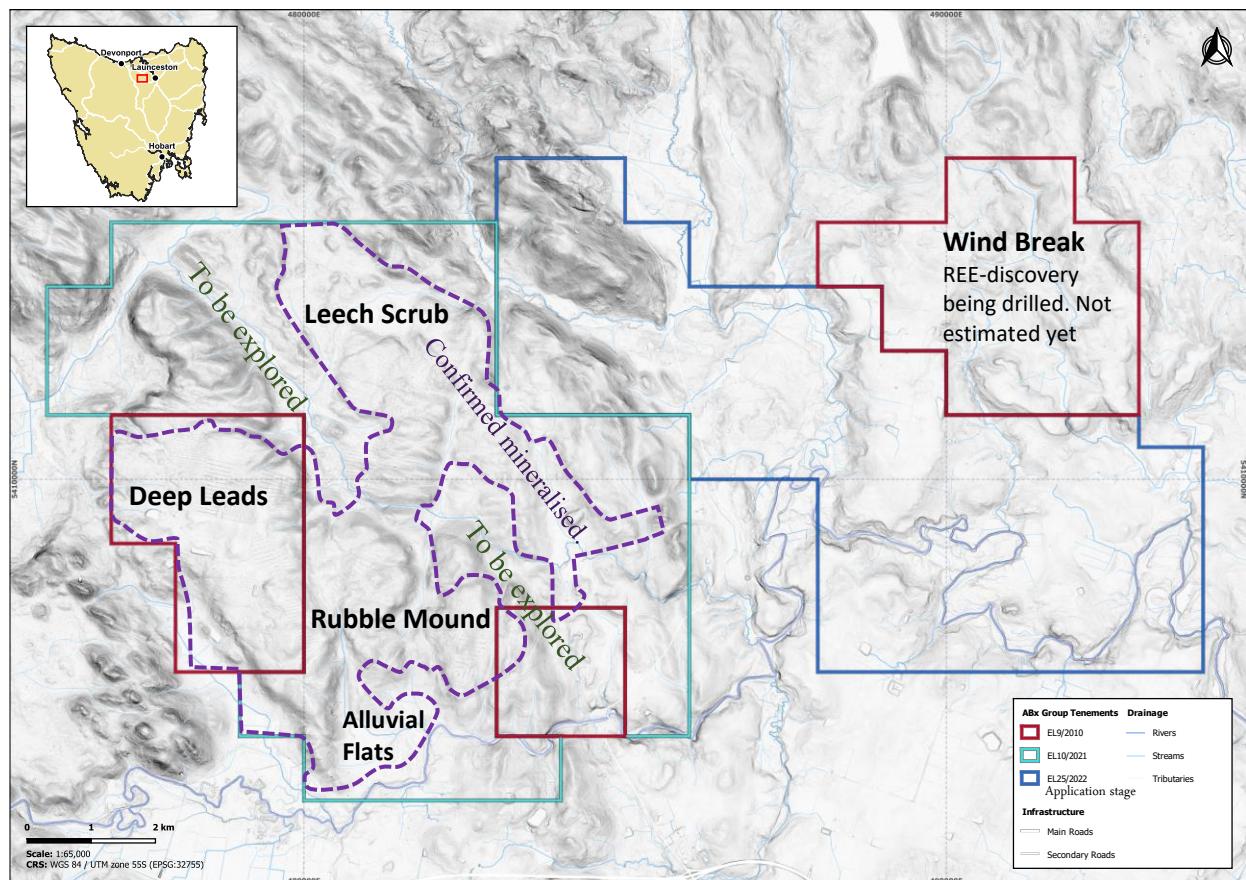


Figure 6: Tenements & topography of Deep Leads, Rubble Mound and Wind Break REE discoveries and mineralised area to date

### Drilling Techniques

Drilling was by 100mm diameter aircore reverse circulation holes and push-tube coring, using an RC Rig provided by Edrill Tasmania.



Figure 7: Example of the mixed drilling environment of hard rock boulders, wet clays and bedrock

In some locations, the holes must penetrate a mixture of clay, boulders and water, with the boulders being a mixture of weathered and very hard bedrock. This is a difficult, mixed drilling environment – see Figure 7.

An aircore cutter bit is used to drill clays and, when hard rock is encountered, the drill string is withdrawn which allows water into the hole, and a hammer bit is fitted.

In wet areas, the compressor has been operated at high pressure to keep the formation dry for efficient drilling. However, tests have shown that the groundwater and fine suspended clays that are being repelled by the high drilling pressure is carrying REE which could lead to an underestimation of REE grade in some places. Specialised clay coring equipment may be needed for infill drilling for the estimation of Measured Resources category.

No duplicate holes have been drilled to date. Five well-holes were drilled next to selected holes and the geological correspondence between holes was strong. Grade correspondence could not be tested because the well holes were drilled with an oversized hammer to ream and flush the chips out of the holes.

## Sampling & Assaying

Sampling has been done at 1 metre intervals. Each sample is quartered 2 or 3 times to collect a 0.5kg subsample for assaying and the rest is stored at the ABx Research Lab in Western Junction near the Launceston Airport. Samples are geologically logged, photographed and samples placed in chip trays.

Assaying has been done by two commercial laboratories, ALS in Brisbane and LabWest in WA. The ALS analytical method is coded ME-MS81™ involving lithium borate fusion followed by acid dissolution and ICP-AES measurement (a proprietary method of inductively coupled plasma with atomic emission spectroscopy). The LabWest method is coded MMA04, involving sample digestion in an HF-based acid mixture under high pressure and temperature in a microwave apparatus for determination of 61 elements including Rare-Earths by a combination of ICP-MS (inductively-coupled plasma and Mass Spectrometry) and ICP-OES (ICP and Optical Emission Spectrometry).

For comparison, 13 duplicate samples were also analysed using LabWest's AF02 method. Correlation was near-perfect, except for cerium (Ce) especially for samples with very high cerium values.

Whilst this test was not definitive, the analytical methods were considered to be acceptable for resource estimation purposes.

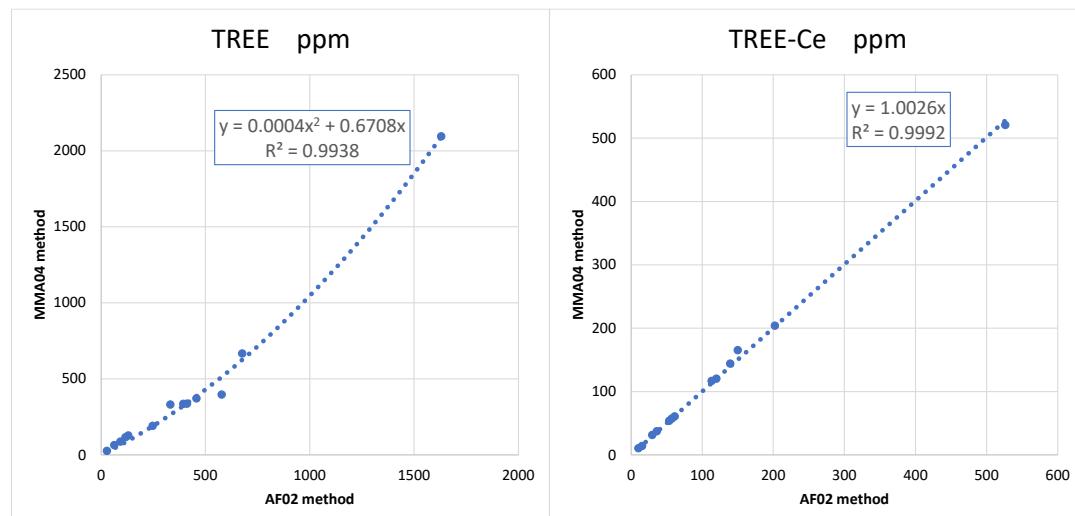


Figure 8: Graphs comparing values for total rare earths (TREE) and TREE-Ce for two different analytical methods.

**Oxide conversion factors** for converting the elemental values that are provided by the laboratories to oxides were based on atomic weights and are as follows (rare earths highlighted in yellow):

Metal	Ag	Al	As	As	Ba	Be	Bi	Ca	Cd	Ce	Ce	Co	Cr	Cs	Cu	Dy	Er	Eu
Oxide	Ag <sub>2</sub> O	Al <sub>2</sub> O <sub>3</sub>	As <sub>2</sub> O <sub>3</sub>	As <sub>2</sub> O <sub>5</sub>	BaO	BeO	Bi <sub>2</sub> O <sub>5</sub>	CaO	CdO	Ce <sub>2</sub> O <sub>3</sub>	Ce <sub>2</sub> O <sub>3</sub>	Co <sub>3</sub> O <sub>4</sub>	Cr <sub>2</sub> O <sub>3</sub>	Cs <sub>2</sub> O	CuO	Dy <sub>2</sub> O <sub>3</sub>	Er <sub>2</sub> O <sub>3</sub>	Eu <sub>2</sub> O <sub>3</sub>
Conversion	1.074	1.890	1.320	1.534	1.117	2.776	1.191	1.399	1.142	1.171	1.228	1.272	1.462	1.060	1.252	1.148	1.143	1.158
Metal	Fe	Fe	Ga	Gd	Ge	Hf	Hg	Ho	In	k	La	Li	Lu	Mg	Mn	Mn	Mo	Na
Oxide	FeO	Fe <sub>2</sub> O <sub>3</sub>	Ga <sub>2</sub> O <sub>3</sub>	Gd <sub>2</sub> O <sub>3</sub>	GeO <sub>2</sub>	HfO <sub>2</sub>	HgO	Ho <sub>2</sub> O <sub>3</sub>	In <sub>2</sub> O <sub>3</sub>	K <sub>2</sub> O	La <sub>2</sub> O <sub>3</sub>	Li <sub>2</sub> O	Lu <sub>2</sub> O <sub>3</sub>	MgO	MnO	MnO <sub>2</sub>	Mo <sub>3</sub>	Na <sub>2</sub> O
Conversion	1.287	1.430	1.344	1.153	1.441	1.179	1.080	1.146	1.209	1.205	1.173	2.153	1.137	1.658	1.291	1.583	1.500	1.348
Metal	Nb	Nd	Ni	P	Pb	Pb	Pr	Pr	Rb	Re	S	Sb	Sc	Se	Sm	Sn	Sr	Ta
Oxide	Nb <sub>2</sub> O <sub>5</sub>	Nd <sub>2</sub> O <sub>3</sub>	NiO	P <sub>2</sub> O <sub>5</sub>	PbO	Pb <sub>2</sub> O <sub>3</sub>	Pr <sub>2</sub> O <sub>3</sub>	Pr <sub>6</sub> O <sub>11</sub>	Rb <sub>2</sub> O	ReO	SO <sub>3</sub>	Sb <sub>2</sub> O <sub>5</sub>	Sc <sub>2</sub> O <sub>3</sub>	SeO <sub>3</sub>	Sm <sub>2</sub> O <sub>3</sub>	SnO <sub>2</sub>	SrO	Ta <sub>2</sub> O <sub>5</sub>
Conversion	1.431	1.166	1.273	2.292	1.077	1.154	1.170	1.208	1.094	1.086	2.497	1.328	1.534	1.608	1.160	1.270	1.183	1.221
Metal	Tb	Tb	Te	Th	Ti	Tl	Tm	U	U	U	V	W	Y	Yb	Zn	Zr		
Oxide	Tb <sub>2</sub> O <sub>3</sub>	Tb <sub>4</sub> O <sub>7</sub>	TeO <sub>3</sub>	ThO <sub>2</sub>	TiO <sub>2</sub>	Tl <sub>2</sub> O <sub>3</sub>	Tm <sub>2</sub> O <sub>3</sub>	UO <sub>2</sub>	UO <sub>3</sub>	U <sub>3</sub> O <sub>8</sub>	V <sub>2</sub> O <sub>5</sub>	WO <sub>3</sub>	Y <sub>2</sub> O <sub>3</sub>	Yb <sub>2</sub> O <sub>3</sub>	ZnO	ZrO <sub>2</sub>		
Conversion	1.151	1.176	1.376	1.138	1.668	1.117	1.142	1.134	1.202	1.179	1.785	1.261	1.270	1.139	1.245	1.351		

Table 3: Conversion factors applied to convert elemental values to oxides. Rare earths are highlighted in yellow.

## Estimation Methodology

A review of data by consultants and the Competent Person concluded that block modelling interpolation is the most appropriate estimation method at this stage. The block model interpolation procedure comprised the following:

1. Validation of the digital data by reference to original assay certificates
2. Examination of selected cross sections to assess continuity of grades and geology
3. Using photos of sample chip trays to look for continuity of structure and clay layers
4. Elimination of old bauxite holes that were incompletely sampled and/or assayed
5. Elimination of old bauxite holes that stopped at depths too shallow to test the REE horizon
6. Population statistics of assay data from holes that tested the REE horizon
7. Conversion of all drill hole collar heights to heights from the official LiDAR data. LiDAR stands for Light Detection and Ranging which uses a pulsed laser to accurately measure land surface heights
8. Provision of a final set of data suitable for block modelling
9. Drafting an outline of the area that has been explored and determined to be mineralised
10. Agreement on the model blocks to be 60m x 60m x 2m thick aligned with the true-north survey grid
11. Agreement on the search ellipses for Indicated Resources (120m) and Inferred Resources (250m) and the interpolation method (inverse distance squared – ID2)
12. Agreement that the minimum number of samples for a grade estimate is 3 for the entire model and 4 for the limit of Inferred Resources
13. Gravimetric tests on samples of the heavy clays (SG 2.65 t/m<sup>3</sup>) and dolerite (SG 2.5 to 3.0 t/m<sup>3</sup>) that host the REE and selection of a general density factor of 1.9 dry tonnes per cubic metre in-situ
14. Conversion of LiDAR data to a precise model of the land surface to constrain blocks
15. Generation of the block model for the Mineral Resource estimation and
16. Sorting the block model estimates into Resource categories according to JORC definitions.

## Block modelling parameters applied – Table 4

True north grid	Cell Dimensions	Origin	Number of Blocks	Indicated Resources Search Ellipse	Inferred Resources Search Ellipse
X Easting	60m	477000	150	120m	250m
Y Northing	60m	5405150	150	120m	250m
Z RL (LiDAR)	2m	322	81	2m	4m

Interpolation method: Inverse Distance Weighted (Squared)

Block Model orientated north south

Maximum number of samples from one hole 2

Minimum number of samples within search ellipse 3 Minimum 4 for Resources

Maximum number of samples 12

Resource modelling: Skandus Pty Ltd, Gems 4.11 software. QGIS & LiDAR by Terra Geospatial UK

### Proportion of mineralised area with grade estimates

Area of blocks with the mineralised outline: 31.748 km<sup>2</sup>

Area of blocks with grade estimates: 12.481 km<sup>2</sup>

∴ Proportion of mineralised outline with grade estimates = **39% of the mineralised outline area**

## Comparing hole grades and block grades

Previous resource estimate statements have been based on polygonal methods applying a cut-off grade to define the downhole intercept thickness and grade. This block-model resource estimate is based on a block modelling process whereby the grade of each 3-dimensional block, 60m x 60m x 2m is interpolated algorithmically from assays within the search ellipses.

A comparison was made between the interpolated block grades and actual hole grades that occur within each block that has been intersected by a drillhole. This method was developed and named “Jackstabbing” by I Levy & G Robinson in 1993-94 and is useful for testing block models versus the raw drill data.

The correlation between the grade of blocks and the corresponding drill sample grades displays the normal correlation pattern – see Figure 9 below. Like most block models, low grade blocks tend to be higher grade than their corresponding drillhole grades and the high-grade blocks are lower grade than their corresponding drillhole grades. Overall, the total average grades of blocks with drill assays in them and corresponding drillhole grades are within 2% of each other, which is an acceptable Jackstabbing result.


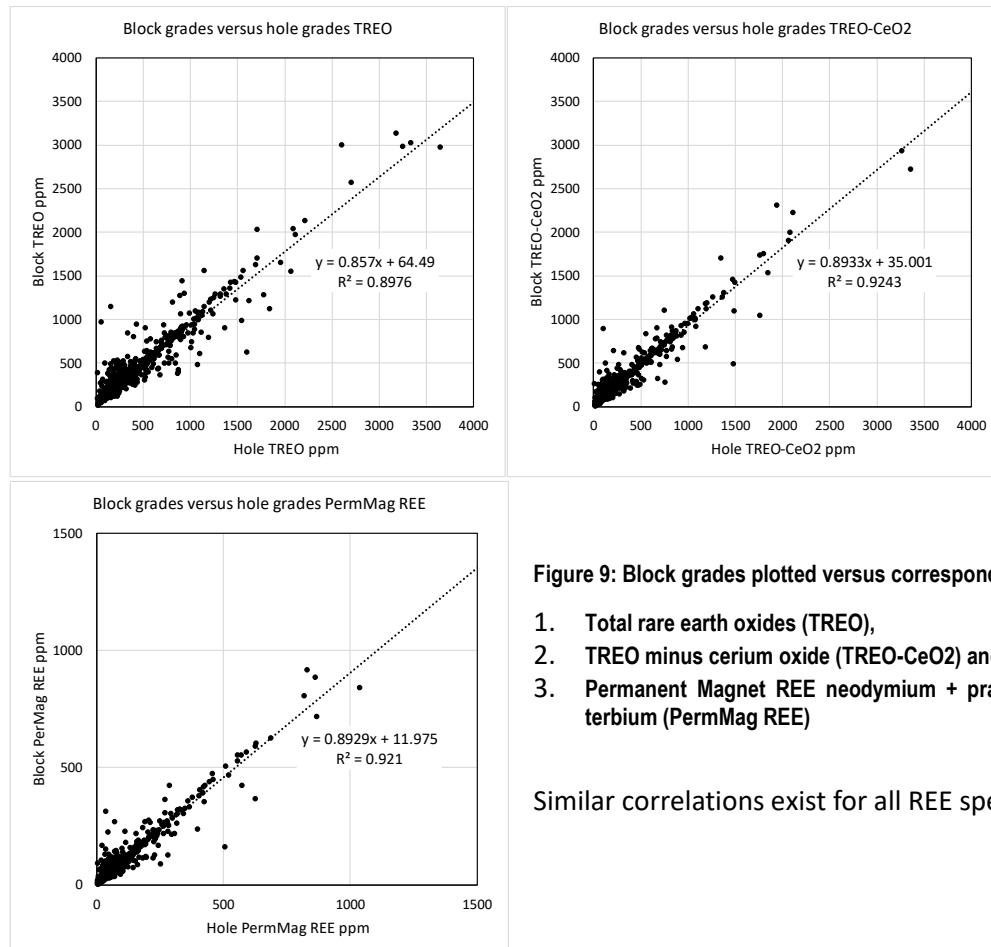


Figure 9: Block grades plotted versus corresponding hole grades for:

1. Total rare earth oxides (TREO),
2. TREO minus cerium oxide (TREO-CeO<sub>2</sub>) and
3. Permanent Magnet REE neodymium + praseodymium + dysprosium + terbium (PermMag REE)

Similar correlations exist for all REE species.

### Selecting the optimum block Cut-Off Grade (cog)

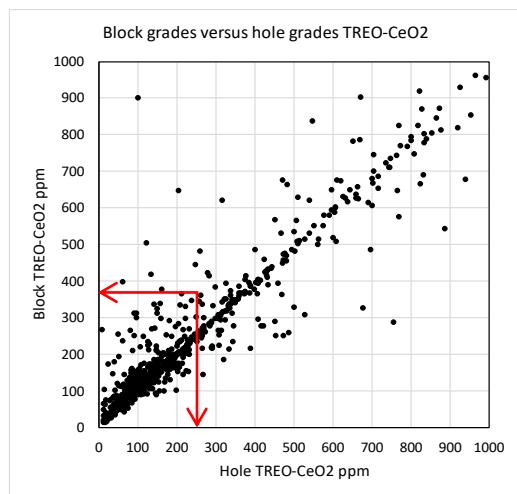

This correlation between hole and block grades is particularly important for the application of a block cut-off grade. At these lower grades, block grades tend to be scattered at grades well above the corresponding hole grades – see Figure 10 (left).

For previous resource estimates using the polygonal method, ABx applied a hole cut-off grade of 250ppm TREO-CeO<sub>2</sub>. However, the equivalent block cut-off grade may need to be higher, possibly higher than 350ppm TREO-CeO<sub>2</sub>, to avoid overstating tonnages.

For this estimation, a 350ppm TREO-CeO<sub>2</sub> block cut-off grade is applied.

Figure 10: Lower grade block grades plotted versus corresponding hole grades for TREO-CeO<sub>2</sub>

## RESOURCE ESTIMATES

### 1. At 350ppm TREO-CeO<sub>2</sub> cut-off grade (cog)

The block model REEBLOCKSV1.9 has been interrogated by the Competent Person and is considered sufficient and satisfactory for the following resource statement:

**Table 5: Mineral Resources at Deep Leads-Rubble Mound: 350ppm cog**

Resource Category	Million Tonnes	Avg depth (m)	Avg base (m)	Avg thickness (m)	TREO ppm	TREO-CeO <sub>2</sub> ppm	Perm Mag ppm	Permanent Magnet REOs				Key Ratios	
								Nd <sub>2</sub> O <sub>3</sub> ppm	Pr <sub>6</sub> O <sub>11</sub> ppm	Tb <sub>4</sub> O <sub>7</sub> ppm	Dy <sub>2</sub> O <sub>3</sub> ppm	PermMag TREO %	Tb+Dy TREO %
Inferred	45	4.3	12.1	7.8	806	623	211	140	36	5.1	30	26%	4.4%
Indicated	7	4.3	11.2	6.9	886	696	232	153	38	5.8	34	26%	4.5%
<b>Totals</b>	<b>52</b>	<b>4.3</b>	<b>12.0</b>	<b>7.7</b>	<b>817</b>	<b>633</b>	<b>214</b>	<b>142</b>	<b>36</b>	<b>5.2</b>	<b>31</b>	<b>26%</b>	<b>4.4%</b>


Other Rare Earth oxides

Low radioactivity

Resource Category	CeO <sub>2</sub> ppm	Er <sub>2</sub> O <sub>3</sub> ppm	Eu <sub>2</sub> O <sub>3</sub> ppm	Gd <sub>2</sub> O <sub>3</sub> ppm	Ho <sub>2</sub> O <sub>3</sub> ppm	La <sub>2</sub> O <sub>3</sub> ppm	Lu <sub>2</sub> O <sub>3</sub> ppm	Sm <sub>2</sub> O <sub>3</sub> ppm	Tm <sub>2</sub> O <sub>3</sub> ppm	Yb <sub>2</sub> O <sub>3</sub> ppm	Y <sub>2</sub> O <sub>3</sub> ppm	U <sub>3</sub> O <sub>8</sub> ppm	ThO ppm
Inferred	182	17	8.8	32	6.0	121	2.2	32	2.3	14	175	1.7	6.4
Indicated	190	19	10.2	36	6.7	130	2.4	35	2.6	16	204	1.7	6.3
<b>Totals</b>	<b>183</b>	<b>17</b>	<b>9.0</b>	<b>33</b>	<b>6.1</b>	<b>122</b>	<b>2.2</b>	<b>33</b>	<b>2.4</b>	<b>15</b>	<b>179</b>	<b>1.7</b>	<b>6.4</b>

Parameters Block cut-off grade (cog) = 350ppm TREO-CeO<sub>2</sub> Minimum thickness = 2 metres Search ellipse = 120m (Ind), 250m(Inf) Density = 1.9 tonnes/cubic metre

TREO = total rare earth elements as oxides. TREO-CeO<sub>2</sub> = TREO minus cerium oxide

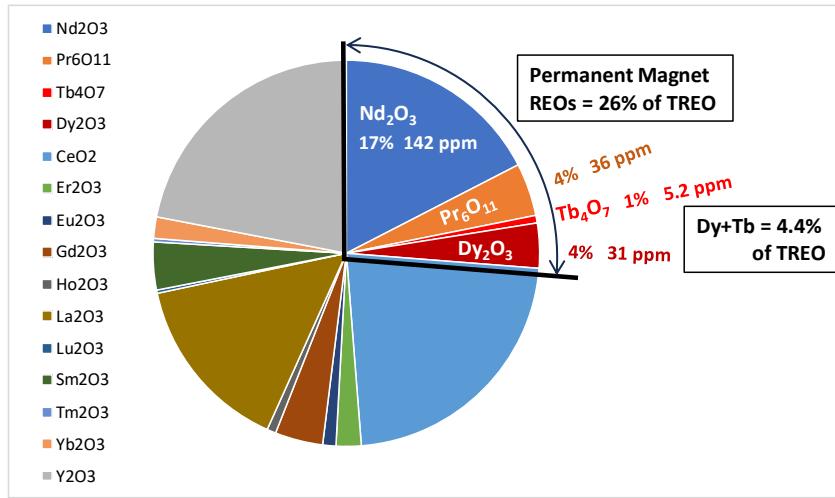

**Figure 11: Pie chart showing the relative proportions of the 14 rare earth element oxides**

**Notes:**

The main revenue-earning Permanent Magnet REOs are high, being 26% of total rare earth oxides (TREO)

Critical REOs of Dy+Tb are, on average, 4.4% of TREO and has some areas exceeding 6% of TREO. This is the highest concentration ratio of Dy+Tb in Australia and are high by world standards.

Uranium & Thorium grades are very low which is preferred.

### 2. Higher grade resources using 450ppm TREO-CeO<sub>2</sub> cut-off grade (cog)

**Table 6: Mineral Resources at Deep Leads-Rubble Mound 450ppm cog**

Resource Category	Million Tonnes	Avg depth (m)	Avg base (m)	Avg thickness (m)	TREO ppm	TREO-CeO <sub>2</sub> ppm	Perm Mag ppm	Permanent Magnet REOs				Key Ratios	
								Nd <sub>2</sub> O <sub>3</sub> ppm	Pr <sub>6</sub> O <sub>11</sub> ppm	Tb <sub>4</sub> O <sub>7</sub> ppm	Dy <sub>2</sub> O <sub>3</sub> ppm	PermMag TREO %	Tb+Dy TREO %
Inferred	29	n.a.	n.a.	n.a.	939	747	255	169	43	6.1	36	27%	4.5%
Indicated	5	n.a.	n.a.	n.a.	1,019	820	273	181	45	6.8	40	27%	4.6%
<b>Totals</b>	<b>34</b>	<b>n.a.</b>	<b>n.a.</b>	<b>n.a.</b>	<b>951</b>	<b>759</b>	<b>257</b>	<b>171</b>	<b>43</b>	<b>6.2</b>	<b>37</b>	<b>27%</b>	<b>4.5%</b>

Other Rare Earth oxides

Low radioactivity

Resource Category	CeO <sub>2</sub> ppm	Er <sub>2</sub> O <sub>3</sub> ppm	Eu <sub>2</sub> O <sub>3</sub> ppm	Gd <sub>2</sub> O <sub>3</sub> ppm	Ho <sub>2</sub> O <sub>3</sub> ppm	La <sub>2</sub> O <sub>3</sub> ppm	Lu <sub>2</sub> O <sub>3</sub> ppm	Sm <sub>2</sub> O <sub>3</sub> ppm	Tm <sub>2</sub> O <sub>3</sub> ppm	Yb <sub>2</sub> O <sub>3</sub> ppm	Y <sub>2</sub> O <sub>3</sub> ppm	U <sub>3</sub> O <sub>8</sub> ppm	ThO ppm
Inferred	191	20	10.6	38	7.1	145	2.5	39	2.8	17	208	1.7	6.2
Indicated	199	22	12.1	43	7.9	155	2.8	42	3.1	18	240	1.6	6.2
<b>Totals</b>	<b>192</b>	<b>20</b>	<b>10.8</b>	<b>39</b>	<b>7.2</b>	<b>146</b>	<b>2.6</b>	<b>39</b>	<b>2.8</b>	<b>17</b>	<b>213</b>	<b>1.7</b>	<b>6.2</b>

Parameters Block cut-off grade (cog) = 450ppm TREO-CeO<sub>2</sub> Minimum thickness = 2 metres Search ellipse = 120m (Ind), 250m(Inf) Density = 1.9 tonnes/cubic metre

TREO = total rare earth elements as oxides. TREO-CeO<sub>2</sub> = TREO minus cerium oxide

This higher-grade resource is significant but needs to be tested for continuity by infill drilling and tested for metallurgical performance – see discussion following.

## GRADE-TONNAGE DISTRIBUTION

Table 6 above shows that there is potential for higher grades. The cut-off grade units used for this deposit is “TREO-CeO<sub>2</sub>” which is the total of all rare earth oxide species except for cerium oxide, which is not targeted by ABx and can be undesirable in REE concentrates.

As the cut-off grade is increased, the size of the deposit that is above the cut-off grade reduces but the average grades of the resources increase. Figure 12 summarises the data for this block model.

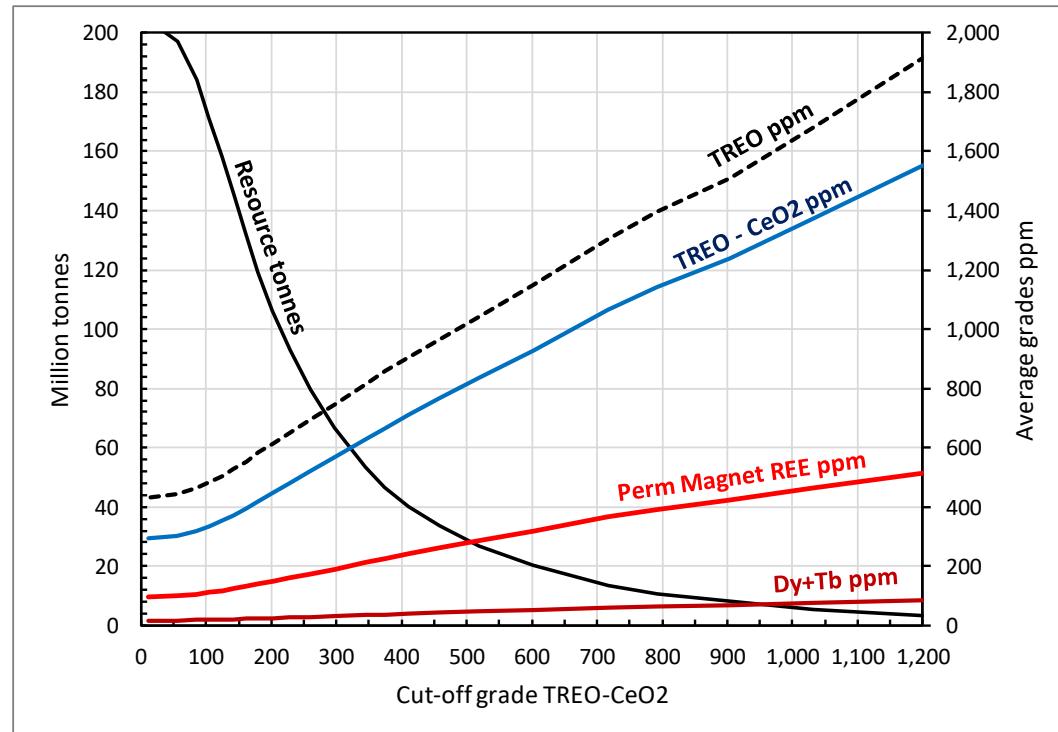


Figure 12: Grade-tonnage graph showing reduction in resource tonnages and increasing is average resource grade as the cut-off grade increased. Note the inflection in the rate of rising grades between 150 to 200 ppm cut-off grades.

**Significance of grade-tonnage:** As ABx moves into an economic assessment of these REE resources, its focus is on the tonnages that are readily accessible as well as having attractive grades and feasible metallurgy:

1. TREO is important in that processing will recover all REE into a bulk concentrate
2. TREO-CeO<sub>2</sub> is the more important grade because it excludes cerium which is not highly valuable
3. Permanent Magnet REE (Nd, Pr, Dy & Tb) are the most valuable REE
4. Dy & Tb are the most highly priced of all the REE species. They are in critically short-supply and are predominantly sourced from ionic adsorption clay REE deposits such as this one.

This is a widespread, broad-acre style of resource, extending across a diverse landscape and resource continuity becomes a key factor in future economic-engineering assessments. Infill drilling will be focussed on prospective areas.

One of the major benefits of this resource block model is that it maps the distribution of high-grade sections of the deposit.

## DISTRIBUTION OF RESOURCE GRADE-THICKNESSES AND EXPLORATION POTENTIAL

To summarise the distribution of REE, the following map, Figure 13, shows the “REE Accumulation” across the deposit based on the resource block model data. The units used are the thickness of the REE formation multiplied by the grade, so the units are expressed as REE ppm x metres (ppm x m).

This shows where the REE mineralisation is most abundant (the purple, red and orange zones in Figure 13) and where it is weakest (the light green and grey zones), often because of rock outcrop and thin clay. Channels of higher-grade and thicker REE-clay mineralisation are evident in this map.

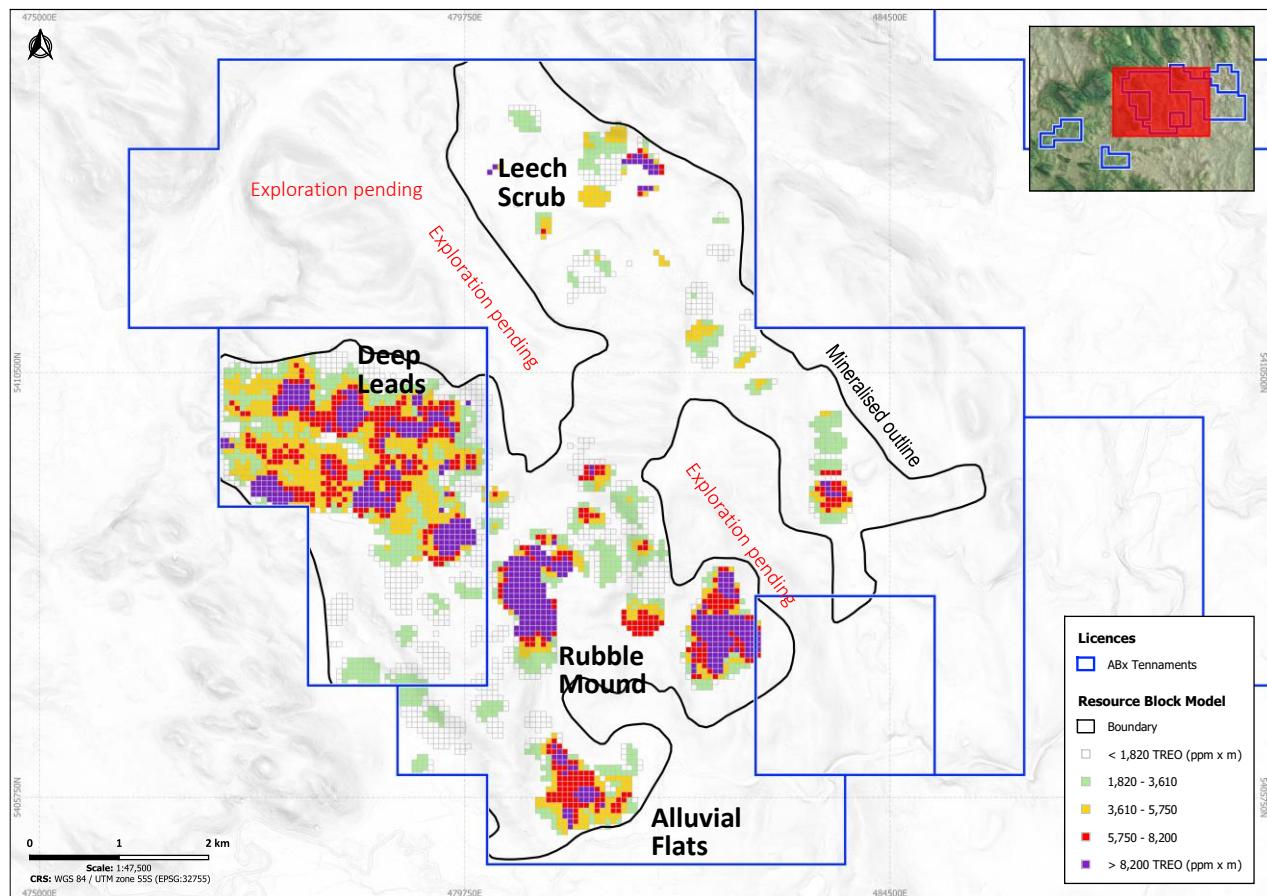



Figure 13: Map of REE accumulation across the area and areas where exploration is pending.

The resources block model covers 39% of the mineralised outline area which is the area of some form of exploration carried out to date and will be expanded as exploration continues.

### Patterns of mineralisation and their prospectivity

There are four different zones of stronger REE mineralisation:

1. **Deep Leads** is a thin clay layer with channels of thicker and higher-grade mineralisation. Exploration may extend this prospect to the north.
2. **Rubble Mound** is a thicker clay deposit and has very thick mineralised intercepts in places with some holes ending still in mineralised clay. There are large areas in the Rubble Mound zone that have not been drilled yet. This may be the most strongly mineralised zone discovered to date.
3. **Alluvial Flats** is a mixture of clay-hosted REE shedding off Rubble Mound and alluvial hosted REE which may actually be detrital in nature.
4. **Leech Scrub** is an emerging prospect and has had the two highest-grade thick drill intercepts to date (see Figure 14 and Tables 7 & 8 overleaf). Drilling is planned to extend the exploratory drilling of this prospect to the west.

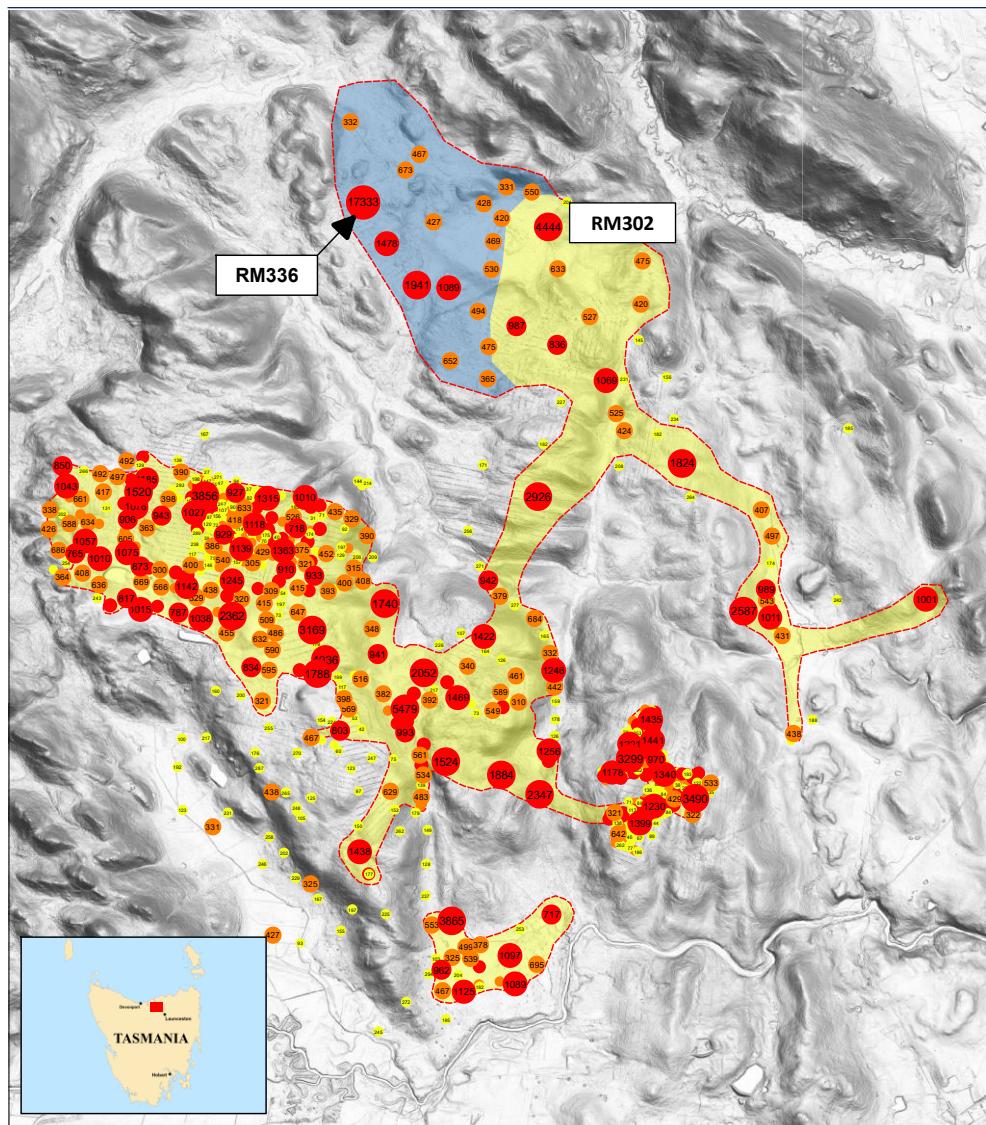

**Figure 14:** Map of maximum TREO grades in each hole and highlighting the Leech Scrub high-grade discovery holes RM336 & RM302  
see assays in Tables 7 & 8 below



From (m)	To (m)	TREO ppm	TREO-CeO <sub>2</sub> ppm	Perm Mag ppm	Nd <sub>2</sub> O <sub>3</sub> ppm	Pr <sub>6</sub> O <sub>11</sub> ppm	Tb <sub>4</sub> O <sub>7</sub> ppm	Dy <sub>2</sub> O <sub>3</sub> ppm	Tb+Dy TREO %	Ce <sub>2</sub> O ppm	Er <sub>2</sub> O <sub>3</sub> ppm	Eu <sub>2</sub> O <sub>3</sub> ppm	Gd <sub>2</sub> O <sub>3</sub> ppm	Ho <sub>2</sub> O <sub>3</sub> ppm	La <sub>2</sub> O <sub>3</sub> ppm	Lu <sub>2</sub> O <sub>3</sub> ppm	Sm <sub>2</sub> O <sub>3</sub> ppm	Tm <sub>2</sub> O <sub>3</sub> ppm	Yb <sub>2</sub> O <sub>3</sub> ppm	Y <sub>2</sub> O <sub>3</sub> ppm	ThO <sub>2</sub> ppm	U <sub>3</sub> O <sub>8</sub> ppm
1	2	952	363	101	63	17	3	19	2.3%	590	12	3	15	4	71	2	12	2	10	131	6.5	1.6
2	3	6,719	5,564	2,074	1,423	376	40	235	4.1%	1,155	125	69	244	44	1,366	16	282	17	108	1,218	4.7	1.7
3	4	17,333	16,847	6,189	4,176	1,056	138	819	5.5%	486	435	227	818	153	3,589	55	877	59	369	4,076	5.0	3.1
4	5	12,894	12,644	4,081	2,718	664	99	600	5.4%	251	359	148	603	122	2,709	45	566	48	293	3,670	5.1	3.4
5	6	4,817	4,642	1,333	874	211	35	213	5.1%	175	137	48	214	45	971	17	181	18	107	1,568	4.8	1.9
6	7	4,285	4,102	1,324	883	218	32	191	5.2%	183	114	48	196	38	868	14	190	15	93	1,203	5.7	1.7
7	8	2,078	1,987	580	380	94	15	91	5.1%	92	59	21	92	20	405	7	81	8	46	669	4.8	1.2
8	9	2,167	2,061	667	446	110	16	95	5.1%	106	56	25	97	19	433	7	98	8	48	603	5.3	1.6
1	9	6,406	6,026	2,044	1,370	343	47	283	4.7%	380	162	74	285	56	1,301	20	286	22	134	1,642	5.2	2.0

Hole RM336 location 479970E 5412965N 236mRL

From (m)	To (m)	TREO ppm	TREO-CeO <sub>2</sub> ppm	Perm Mag ppm	Nd <sub>2</sub> O <sub>3</sub> ppm	Pr <sub>6</sub> O <sub>11</sub> ppm	Tb <sub>4</sub> O <sub>7</sub> ppm	Dy <sub>2</sub> O <sub>3</sub> ppm	Tb+Dy TREO %	Ce <sub>2</sub> O ppm	Er <sub>2</sub> O <sub>3</sub> ppm	Eu <sub>2</sub> O <sub>3</sub> ppm	Gd <sub>2</sub> O <sub>3</sub> ppm	Ho <sub>2</sub> O <sub>3</sub> ppm	La <sub>2</sub> O <sub>3</sub> ppm	Lu <sub>2</sub> O <sub>3</sub> ppm	Sm <sub>2</sub> O <sub>3</sub> ppm	Tm <sub>2</sub> O <sub>3</sub> ppm	Yb <sub>2</sub> O <sub>3</sub> ppm	Y <sub>2</sub> O <sub>3</sub> ppm	ThO <sub>2</sub> ppm	U <sub>3</sub> O <sub>8</sub> ppm
2	3	724	300	104	70	17	2	15	2.4%	424	9	4	13	3	60	1	16	1	9	78	6.9	2.2
3	4	1,648	628	245	167	43	5	31	2.1%	1,020	18	9	28	6	128	2	38	3	19	133	6.2	1.9
4	5	2,932	1,660	773	545	155	11	63	2.5%	1,271	30	25	67	11	378	4	118	5	33	218	7.1	2.2
5	6	1,222	805	334	230	63	6	36	3.4%	416	19	11	33	6	176	3	54	3	21	144	7.0	2.1
6	7	1,723	1,422	460	286	76	13	85	5.7%	301	47	19	69	16	232	6	72	7	46	448	7.0	2.0
7	8	4,444	4,014	902	496	124	36	246	6.3%	430	153	41	197	53	452	18	146	20	121	1,911	6.4	2.0
8	9	3,269	2,893	742	442	112	25	162	5.7%	376	98	31	140	35	446	12	113	14	82	1,182	6.2	2.0
9	10	1,408	1,219	320	195	50	10	65	5.3%	189	39	13	57	14	212	5	47	5	33	474	6.3	1.9
10	11	640	540	150	95	24	4	27	4.9%	100	15	6	26	6	107	2	23	2	14	189	6.1	1.5
11	12	421	348	95	59	15	3	18	4.9%	73	11	4	16	4	61	1	15	1	10	131	5.1	1.5
12	13	453	375	103	65	16	3	19	4.8%	77	12	4	18	4	68	2	16	2	10	137	5.2	1.3
2	13	1,717	1,291	385	241	63	11	70	4.4%	425	41	15	60	14	211	5	60	6	36	459	6.3	1.9

**Table 7**  
Assays from hole RM336  
location in Figure 14

From (m)	To (m)	TREO ppm	TREO-CeO <sub>2</sub> ppm	Perm Mag ppm	Nd <sub>2</sub> O <sub>3</sub> ppm	Pr <sub>6</sub> O <sub>11</sub> ppm	Tb <sub>4</sub> O <sub>7</sub> ppm	Dy <sub>2</sub> O <sub>3</sub> ppm	Tb+Dy TREO %	Ce <sub>2</sub> O ppm	Er <sub>2</sub> O <sub>3</sub> ppm	Eu <sub>2</sub> O <sub>3</sub> ppm	Gd <sub>2</sub> O <sub>3</sub> ppm	Ho <sub>2</sub> O <sub>3</sub> ppm	La <sub>2</sub> O <sub>3</sub> ppm	Lu <sub>2</sub> O <sub>3</sub> ppm	Sm <sub>2</sub> O <sub>3</sub> ppm	Tm <sub>2</sub> O <sub>3</sub> ppm	Yb <sub>2</sub> O <sub>3</sub> ppm	Y <sub>2</sub> O <sub>3</sub> ppm	ThO <sub>2</sub> ppm	U <sub>3</sub> O <sub>8</sub> ppm
2	3	724	300	104	70	17	2	15	2.4%	424	9	4	13	3	60	1	16	1	9	78	6.9	2.2
3	4	1,648	628	245	167	43	5	31	2.1%	1,020	18	9	28	6	128	2	38	3	19	133	6.2	1.9
4	5	2,932	1,660	773	545	155	11	63	2.5%	1,271	30	25	67	11	378	4	118	5	33	218	7.1	2.2
5	6	1,222	805	334	230	63	6	36	3.4%	416	19	11	33	6	176	3	54	3	21	144	7.0	2.1
6	7	1,723	1,422	460	286	76	13	85	5.7%	301	47	19	69	16	232	6	72	7	46	448	7.0	2.0
7	8	4,444	4,014	902	496	124	36	246	6.3%	430	153	41	197	53	452	18	146	20	121	1,911	6.4	2.0
8	9	3,269	2,893	742	442	112	25	162	5.7%	376	98	31	140	35	446	12	113	14	82	1,182	6.2	2.0
9	10	1,408	1,219	320	195	50	10	65	5.3%	189	39	13	57	14	212	5	47	5	33	474	6.3	1.9
10	11	640	540	150	95	24	4	27	4.9%	100	15	6	26	6	107	2	23	2	14	189	6.1	1.5
11	12	421	348	95	59	15	3	18	4.9%	73	11	4	16	4	61	1	15	1	10	131	5.1	1.5
12	13	453	375	103	65	16	3	19	4.8%	77	12	4	18	4	68	2	16	2	10	137	5.2	1.3
2	13	1,717	1,291	385	241	63	11	70	4.4%	425	41	15	60	14	211	5	60	6	36	459	6.3	1.9

**Table 8**  
Assays from hole RM302  
location in Figure 14

**Table 9 - Summary of resource estimation information in accordance with LR 5.8.1**

<b>Geology and geological interpretation</b>	REE mineralisation occurs in clay layers that overlie a Jurassic age dolerite basement in a district with some residual weathered Tertiary age alkali basalt. Jurassic age tholeiitic dolerite and Tertiary age bauxite-laterite are the main bedrock geological units. Paleochannels host thicker clay zones which host the rare earth element mineralisation.
<b>Sampling and sub-sampling techniques</b>	Sampling was at 1 metre intervals. Subsampling for assaying is by quartering the clay samples twice and each time, mixing diagonally opposite quarters. Assay results from resampling correspond satisfactorily.
<b>Drilling techniques</b>	RC aircore and push-tube coring used.
<b>Criteria used for classification, including drill and data spacing and distribution.</b>	Indicated Resources are those blocks with grades above the cut-off grade that were estimated based on a minimum 4 samples within 120 metres. Inferred Resources are those blocks with grades above the cut-off grade that were estimated based on a minimum 4 samples within 250 metres.
<b>Sample analytical method</b>	Assay samples are analysed by standard NATA-approved induction coupled plasma analytical methods for rare earth elements at ALS labs in Brisbane (method ME-MS81) and LabWest in Perth (method MMA04). Interlab comparisons proved satisfactory.
<b>Estimation methodology</b>	The centroid of each 1 metre sample is accurately located in Easting, Northing and RL coordinates.  Because the clay horizon drapes the topography, estimation is by two runs of horizontal circular search ellipses. The first search ellipse is 120 metres horizontally and 2 metres vertically to define Indicated Resources. The second search ellipse is at 250 metres to estimate Inferred Resources.  Clay density is typically 2 tonnes per cubic metre, but some samples exhibit density loss, so a density of 1.9 tonnes per cubic metre was applied globally.
<b>Cut-off grade</b>	Block cut-off grade is 350 ppm TREO - CeO <sub>2</sub> which is approximately equivalent to 250 to 300 ppm TREO – CeO <sub>2</sub> in drillholes.  A statistical separation between background and mineralised grades exists at 190-260ppm TREO-CeO <sub>2</sub> . See Figure 10.
<b>Mining and metallurgical methods and parameters, and other modifying factors</b>	None applicable at this resource-drilling stage. Production and rehabilitation strategies are being reviewed. Deposits of this type are mined in China but under very different jurisdictions. The land is freehold hardwood and pine plantations.

**Additional information:** Figure 15 below shows the location of all drill holes, as at 15 October 2023. Appendix 1 shows the JORC Table 1 report. Table 5 at the end of this report lists the drillhole coordinate locations and assays used for the block modelling being reported this Resources Report.

## About ABx Group Limited

ABx Group (ABX) is a uniquely positioned, high-tech Australian company delivering materials for a cleaner future.

The three current significant projects are:

- Creation of an ionic adsorption clay rare earth project in northern Tasmania
- Establishment of a plant to produce hydrogen fluoride and aluminium fluoride from recycled industrial waste, via its 83%-owned subsidiary, Alcore
- Mining and enhancing the value of bauxite resources for cement, aluminium and fertilisers.

We only operate where welcomed and we apply best practices to restore any disturbed land to a better condition than we found it.

## Qualifying statements

### Disclaimer Regarding Forward Looking Statements

This ASX announcement (Announcement) contains various forward-looking statements. All statements other than statements of historical fact are forward-looking statements. Forward-looking statements are inherently subject to uncertainties in that they may be affected by a variety of known and unknown risks, variables and factors which could cause actual values or results, performance, or achievements to differ materially from the expectations described in such forward-looking statements.

ABx does not give any assurance that the anticipated results, performance, or achievements expressed or implied in those forward-looking statements will be achieved.

## Competent Persons Statement


The information in this report that relate to Exploration Information and Mineral Resources are based on information compiled by Ian Levy who is a member of The Australasian Institute of Mining and Metallurgy and the Australian Institute of Geoscientists. Mr Levy is a qualified geologist and a director of ABx Group Limited.

Mr Levy has sufficient experience, which is relevant to the style of mineralisation and type of deposit under consideration and to the activity, which he is undertaking to qualify as a Competent Person as defined in the 2012 Edition of the Australasian Code for Reporting of exploration Results, Mineral Resources and Ore Reserves. Mr Levy has consented in writing to the inclusion in this report of the Exploration Information in the form and context in which it appears.

## Consultants

The geostatistical consultants that created the resource block model were: block modelling by Skandus Pty Ltd using GEMS 4.11 software; QGIS & LiDAR modelling by Terra Geospatial, UK.

-----0000000-----

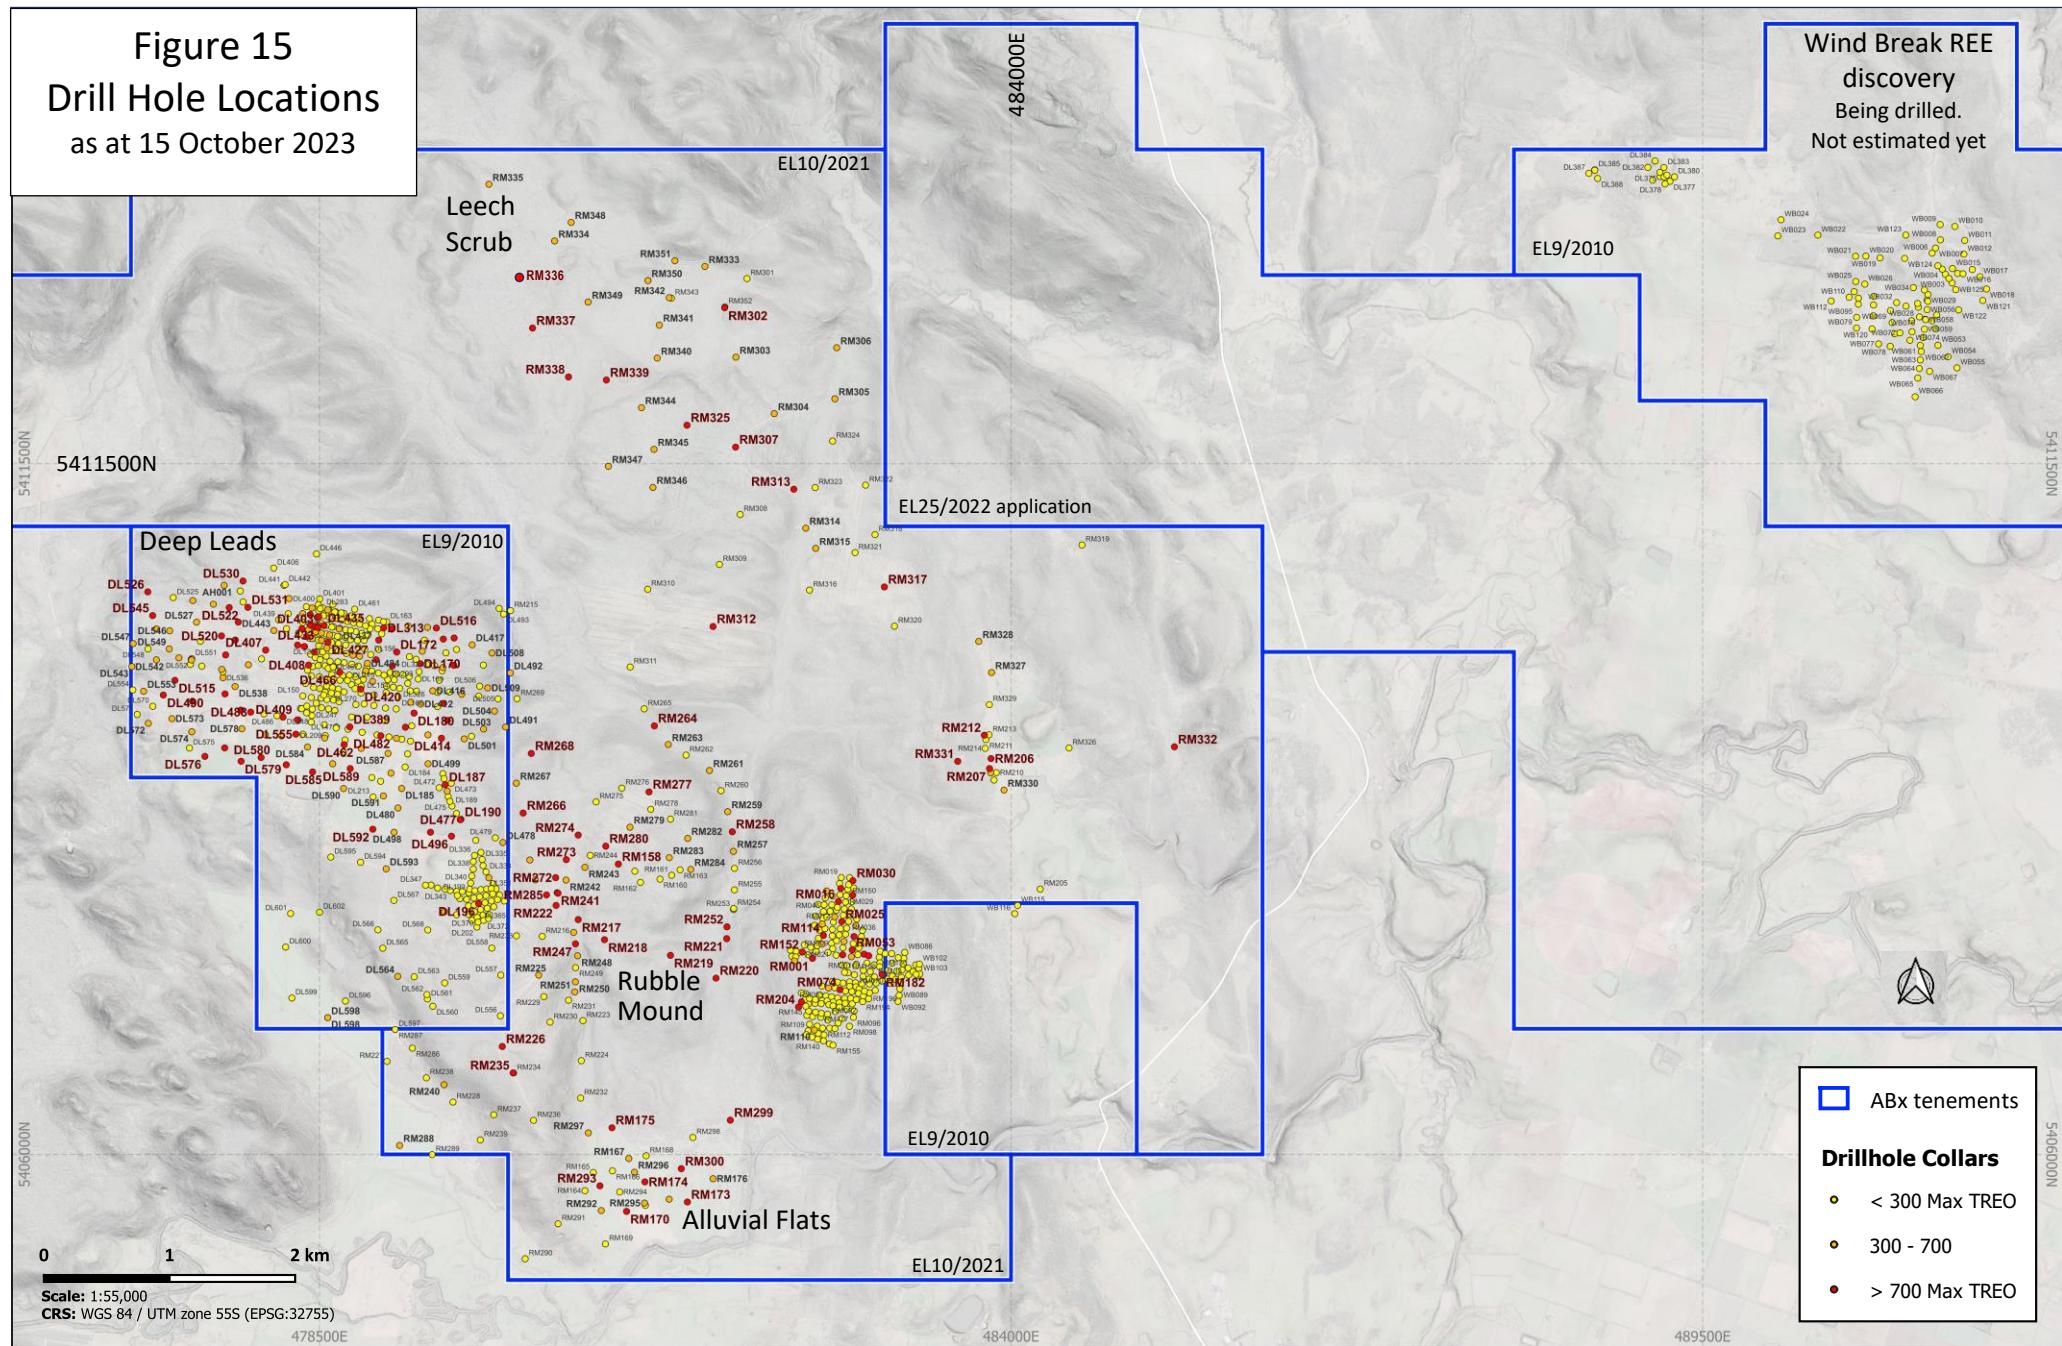

**Section 1 Sampling Techniques and Data****(Criteria in this section apply to all succeeding sections.)**

Criteria	JORC Code explanation	Commentary
Sampling techniques	<ul style="list-style-type: none"> <li>Nature and quality of sampling (eg cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc). These examples should not be taken as limiting the broad meaning of sampling.</li> <li>Include reference to measures taken to ensure sample representivity and the appropriate calibration of any measurement tools or systems used.</li> <li>Aspects of the determination of mineralisation that are Material to the Public Report.</li> <li>In cases where 'industry standard' work has been done this would be relatively simple (eg 'reverse circulation drilling was used to obtain 1 m samples from which 3 kg was pulverised to produce a 30 g charge for fire assay'). In other cases more explanation may be required, such as where there is coarse gold that has inherent sampling problems. Unusual commodities or mineralisation types (eg submarine nodules) may warrant disclosure of detailed information.</li> </ul>	<ul style="list-style-type: none"> <li>1m drill hole samples from reverse circulation aircore and pushtube core drilling to 37.5 metres maximum depth but typically to 12 metres depth</li> <li>Subsample obtained by quartering sent to commercial labs using NATA-approved REE analytical methods</li> <li>Drill sample weights can vary due to difference in moisture and different mixes of bedrock chips which can be dense and hard or rotted and light.</li> <li>Groundwater samples can contain high REE grades and ionic adsorption clays and be removed from the hole area by operation at high pressure (250 psi)</li> </ul>
Drilling techniques	<ul style="list-style-type: none"> <li>Drill type (eg core, reverse circulation, open-hole hammer, rotary air blast, auger, Bangka, sonic, etc) and details (eg core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc).</li> </ul>	<ul style="list-style-type: none"> <li>Reverse circulation aircore chip sampling and push-tube coring. Grades of core samples correspond well with aircore sample grades.</li> </ul>
Drill sample recovery	<ul style="list-style-type: none"> <li>Method of recording &amp; assessing core and chip sample recoveries and results assessed.</li> <li>Measures taken to maximise sample recovery &amp; ensure representative nature of the samples.</li> <li>Whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.</li> </ul>	<ul style="list-style-type: none"> <li>Drill sample weights vary due to heterogeneity, ground conditions and drilling method. No relationship between sample weight and grade</li> <li>Clay-washing and/or airpressure removal of groundwater &amp; clay may undersample the ionic clay REE in places.</li> </ul>
Logging	<ul style="list-style-type: none"> <li>Whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, mining studies and metallurgical studies.</li> <li>Whether logging is qualitative or quantitative. Core (or costean, channel, etc) photography.</li> <li>The total length and percentage of the relevant intersections logged.</li> </ul>	<ul style="list-style-type: none"> <li>Geologically logged by senior geologists. Every sample photographed.</li> <li>Photos, logs and assays entered into ABx's proprietary ABacus database.</li> </ul>
Sub-sampling techniques and sample preparation	<ul style="list-style-type: none"> <li>If core, whether cut or sawn and whether quarter, half or all core taken.</li> <li>If non-core, whether riffled, tube sampled, rotary split, etc and whether sampled wet or dry.</li> <li>For all sample types, the nature, quality and appropriateness of the sample preparation technique.</li> <li>Quality control procedures adopted for all sub-sampling stages to maximise representivity of samples.</li> <li>Measures taken to ensure that the sampling is representative of the in situ material collected, including for instance results for field duplicate/second-half sampling.</li> <li>Whether sample sizes are appropriate to the grain size of the material being sampled.</li> </ul>	<ul style="list-style-type: none"> <li>Chips are subsampled using industry-standard quartering method in accordance with ISO standards for fine damp clay material.</li> <li>Reassaying corresponds well</li> </ul>
Quality of assay data and laboratory tests	<ul style="list-style-type: none"> <li>The nature, quality and appropriateness of the assaying and laboratory procedures used and whether the technique is considered partial or total.</li> <li>For geophysical tools, spectrometers, handheld XRF instruments, etc, the parameters used in determining the analysis including instrument make and model, reading times, calibrations factors applied and their derivation, etc.</li> <li>Nature of quality control procedures adopted (eg standards, blanks, duplicates, external lab checks) &amp; whether acceptable levels of accuracy (ie lack of bias) &amp; precision have been established.</li> </ul>	<ul style="list-style-type: none"> <li>Assaying done at NATA-registered commercial labs using induction coupled plasma methods for rare earth elements at ALS labs in Brisbane (method ME-MS81) and LabWest in Perth (method MMA04). Interlab assays corresponded well.</li> <li>Desorption extraction tests by ANSTO at Lucas Heights, Sydney NSW with ANSTO's assays done at ALS Brisbane.</li> </ul>
Verification of sampling and assaying	<ul style="list-style-type: none"> <li>The verification of significant intersections by either independent or alternative company personnel.</li> <li>The use of twinned holes.</li> <li>Documentation of primary data, data entry procedures, data verification, data storage (physical and electronic) protocols.</li> <li>Discuss any adjustment to assay data.</li> </ul>	<ul style="list-style-type: none"> <li>Assaying done at NATA-registered commercial laboratories of ALS Brisbane Australia and Labwest Minerals Analysis Pty Ltd in Western Australia.</li> <li>Redrilled holes correlated closely</li> <li>Duplicate interlab assays corresponded well.</li> <li>No adjustment of assay data done.</li> </ul>

## APPENDIX 1 : JORC Code, 2012 Edition – Table 1 report

Criteria	JORC Code explanation	Commentary
Location of data points	<ul style="list-style-type: none"> <li>Accuracy and quality of surveys used to locate drill holes (collar and down-hole surveys), trenches, mine workings and other locations used in Mineral Resource estimation.</li> <li>Specification of the grid system used.</li> <li>Quality and adequacy of topographic control.</li> </ul>	<ul style="list-style-type: none"> <li>GPS hole locations confirmed within 1m.</li> <li>Grid Coords CRS:WGS84/UTM zone 55s (EPSG:32755)</li> <li>Topographic control by Lidar to within 0.25m</li> </ul>
Data spacing and distribution	<ul style="list-style-type: none"> <li>Data spacing for reporting of Exploration Results.</li> <li>Whether the data spacing and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the Mineral Resource and Ore Reserve estimation procedure(s) and classifications applied.</li> <li>Whether sample compositing has been applied.</li> </ul>	<ul style="list-style-type: none"> <li>Drilling typically at 50 to 105 metre spacing on mineralised prospects</li> <li>Geological continuity is established by drill pattern</li> <li>Grade continuity is not yet established beyond 80m</li> <li>Sample compositing not applied</li> </ul>
Orientation of data in relation to geological structure	<ul style="list-style-type: none"> <li>Whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the deposit type.</li> <li>If the relationship between the drilling orientation and the orientation of key mineralised structures is considered to have introduced a sampling bias, this should be assessed and reported if material.</li> </ul>	<ul style="list-style-type: none"> <li>Vertical holes through horizontal clay is appropriate</li> <li>Clay layer draped over topography and accumulates in gullies. Vertical holes is the appropriate orientation.</li> </ul>
Sample security	<ul style="list-style-type: none"> <li>The measures taken to ensure sample security.</li> </ul>	<ul style="list-style-type: none"> <li>Samples collected and bagged at every hole site and assembled onto pallets daily, shipped to lab weekly.</li> </ul>
Audits or reviews	<ul style="list-style-type: none"> <li>The results of any audits or reviews of sampling techniques and data.</li> </ul>	<ul style="list-style-type: none"> <li>Several audits confirmed reliability</li> </ul>

**Section 2 Reporting of Exploration Results** (Criteria listed in the preceding section also apply to this section.)

Criteria	JORC Code explanation	Commentary
Mineral tenement and land tenure status	<ul style="list-style-type: none"> <li>Type, reference name/number, location and ownership including agreements or material issues with third parties such as joint ventures, partnerships, overriding royalties, native title interests, historical sites, wilderness or national park and environmental settings.</li> <li>The security of the tenure held at the time of reporting along with any known impediments to obtaining a licence to operate in the area.</li> </ul>	<ul style="list-style-type: none"> <li>Satisfactory to excellent. All tenements are in force, unencumbered and securely held by ABx</li> <li>All drilling is on freehold land with access approvals by landholders</li> </ul>
Exploration done by other parties	<ul style="list-style-type: none"> <li>Acknowledgment and appraisal of exploration by other parties.</li> </ul>	<ul style="list-style-type: none"> <li>ABx is the first company to explore for Rare Earth Elements in northern Tasmania. No prior work has been done by other parties</li> </ul>
Geology	<ul style="list-style-type: none"> <li>Deposit type, geological setting and style of mineralisation.</li> </ul>	<ul style="list-style-type: none"> <li>Bauxite deposit formed on Lower Tertiary basalts overlying Jurassic dolerite</li> </ul>
Drill hole Information	<ul style="list-style-type: none"> <li>A summary of all information material to the understanding of the exploration results including a tabulation of the following information for all Material drill holes: <ul style="list-style-type: none"> <li>easting and northing of the drill hole collar</li> <li>elevation or RL (Reduced Level – elevation above sea level in metres) of the drill hole collar</li> <li>dip and azimuth of the hole</li> <li>down hole length and interception depth</li> <li>hole length.</li> </ul> </li> <li>If the exclusion of this information is justified on the basis that the information is not Material and this exclusion does not detract from the understanding of the report, the Competent Person should clearly explain why this is the case.</li> </ul>	<ul style="list-style-type: none"> <li>GPS location.</li> <li>LiDAR topography provided by government</li> <li>Lidar topography contoured at 1m height intervals</li> <li>All holes are short straight vertical holes</li> </ul>
Data aggregation methods	<ul style="list-style-type: none"> <li>In reporting Exploration Results, weighting averaging techniques, maximum and/or minimum grade truncations (eg cutting of high grades) and cut-off grades are usually Material and should be stated.</li> <li>Where aggregate intercepts incorporate short lengths of high grade results and longer lengths of low grade results, the procedure used for such aggregation should be stated and some typical examples of such aggregations should be shown in detail.</li> <li>The assumptions used for any reporting of metal equivalent values should be clearly stated.</li> </ul>	<ul style="list-style-type: none"> <li>Assays from labs converted to oxides by atomic wts</li> <li>Intercept summaries, if and when presented, are length-weighted arithmetic averages</li> <li>Total Rare Earth Oxides (TREO) is sum of all rare earth oxides. TREO-CeO<sub>2</sub> is TREO minus Cerium oxide. PermMag= Nd<sub>2</sub>O<sub>3</sub> + Pr<sub>6</sub>O<sub>11</sub> + Dy<sub>2</sub>O<sub>3</sub> + Tb<sub>4</sub>O<sub>7</sub></li> </ul>

## APPENDIX 1 : JORC Code, 2012 Edition – Table 1 report

Criteria	JORC Code explanation	Commentary
<i>Relationship between mineralisation widths &amp; intercept lengths</i>	<ul style="list-style-type: none"> <li>These relationships are particularly important in the reporting of Exploration Results.</li> <li>If the geometry of the mineralisation with respect to the drill hole angle is known, its nature should be reported.</li> <li>If it is not known and only the down hole lengths are reported, there should be a clear statement to this effect (eg 'down hole length, true width not known').</li> </ul>	<ul style="list-style-type: none"> <li>Mineralisation typically 3 to 8 metres thick and drillholes are sampled at 1 metre intervals</li> <li>Horizontal layers drilled by vertical holes means intercept thickness is true thickness</li> </ul>
<i>Diagrams</i>	<ul style="list-style-type: none"> <li>Appropriate maps and sections (with scales) and tabulations of intercepts should be included for any significant discovery being reported. These should include, but not be limited to a plan view of drill hole collar locations and appropriate sectional views.</li> </ul>	<ul style="list-style-type: none"> <li>N.A. Diagrams presented give appropriate information</li> </ul>
<i>Balanced reporting</i>	<ul style="list-style-type: none"> <li>Where comprehensive reporting of all Exploration Results is not practicable, representative reporting of both low and high grades and/or widths should be practiced to avoid misleading reporting of Exploration Results.</li> </ul>	<ul style="list-style-type: none"> <li>All new results are reported in this report and reference made to previous tabulation of data</li> </ul>
<i>Other substantive exploration data</i>	<ul style="list-style-type: none"> <li>Other meaningful, material exploration data should be reported including: geological observations; geophysical survey results; geochemical survey results; bulk samples – size and method of treatment; metallurgical test results; bulk density, groundwater, geotechnical and rock characteristics; potential deleterious or contaminating substances.</li> </ul>	<ul style="list-style-type: none"> <li>N.A. Information provided is appropriate.</li> </ul>
<i>Further work</i>	<ul style="list-style-type: none"> <li>The nature and scale of planned further work (eg tests for lateral extensions or depth extensions or large-scale step-out drilling).</li> <li>Diagrams clearly highlighting the areas of possible extensions, including the main geological interpretations and future drilling areas, provided this information is not commercially sensitive.</li> </ul>	<ul style="list-style-type: none"> <li>Step-out drilling over a wider area has been planned, work plans submitted and new drill rig configurations have been developed.</li> </ul>

**Section 3 Estimation & Reporting of Mineral Resources**

Criteria	JORC Code explanation	Commentary
<i>Database integrity</i>	<ul style="list-style-type: none"> <li>Measures taken to ensure data has not been corrupted by, for example, transcription or keying errors, between its initial collection &amp; its use for Mineral Resource estimation purposes. Data validation procedures used.</li> </ul>	<ul style="list-style-type: none"> <li>Random QA-QC checks done on each drill campaign</li> <li>Rare data or lab errors noted if conflicts with geological logging.</li> <li>Lab data entered electronically. Written logs &amp; sample photos also in database</li> </ul>
<i>Site visits</i>	<ul style="list-style-type: none"> <li>Comment on any site visits undertaken by the Competent Person &amp; outcome of those visits. If no site visits, why.</li> </ul>	<ul style="list-style-type: none"> <li>Competent person visited all sites at discovery, mapping, drilling, bulk sampling &amp; mining. All satisfactory.</li> </ul>
<i>Geological interpretation</i>	<ul style="list-style-type: none"> <li>Confidence in (or conversely, the uncertainty of) the geological interpretation of the mineral deposit.</li> <li>Nature of the data used &amp; of any assumptions made.</li> <li>Effect, if any, of alternative interpretations on Mineral Resource estimation.</li> <li>The use of geology in guiding &amp; controlling Mineral Resource estimation.</li> <li>Factors affecting continuity both of grade &amp; geology.</li> </ul>	<ul style="list-style-type: none"> <li>Geology is single clay strata. Drillholes determine degree of variation, especially where concealed by soil or covering layers.</li> <li>Outcrops mapped &amp; sampled. Drillholes complete the subsurface mapping.</li> <li>Outlines can vary estimate by 10% to 15%. 2 different methods used to check</li> <li>Method 1 = geological model outlines. Method 2 = voronoi polygons</li> <li>Continuity assumed to be semi random or highly variable, as normal for laterites</li> </ul>
<i>Dimensions</i>	<ul style="list-style-type: none"> <li>Extent &amp; variability of Mineral Resource expressed as length (along strike), plan width, &amp; depth below surface to the upper &amp; lower limits of Mineral Resource.</li> </ul>	<ul style="list-style-type: none"> <li>REE clay channels 100 to 450m wide meander over 1 to 2km strike. REE mineralisation thickness varies from 1 to 33 metres. Overburden varies from 0 to 10m.</li> </ul>
<i>Estimation &amp; modelling techniques</i>	<ul style="list-style-type: none"> <li>Nature &amp; appropriateness of estimation technique(s) applied &amp; key assumptions, including treatment of extreme grade values, domaining, interpolation parameters &amp; maximum distance of extrapolation from data points. If a computer assisted estimation method was chosen include a description of computer software &amp; parameters used.</li> <li>Check estimates, previous estimates &amp;/or mine production records &amp; whether Mineral Resource estimate takes appropriate account of such data.</li> <li>The assumptions made regarding recovery of by-products.</li> <li>Deleterious elements or other non-grade variables of economic significance</li> <li>In the case of block model interpolation, the block size in relation to the average sample spacing &amp; the search employed.</li> <li>Any assumptions behind modelling of selective mining units.</li> <li>Assumptions about correlation between variables.</li> <li>Description of geological interpretation used to control resource estimates.</li> <li>Discussion of basis for using or not using grade cutting or capping.</li> <li>Process of validation, checking process used, comparison of model data to drill hole data, &amp; use of reconciliation data if available.</li> <li>Are tonnages dry basis or natural moisture, &amp; method of moisture determination.</li> </ul>	<ul style="list-style-type: none"> <li>Method 1: Block model 25m x 25m horizontally inside geological boundaries. Thickness set by intercepts in holes. Grades interpolated Gemcom software by inverse distance squared methods. Search ellipse 250m along strike by 150m.</li> <li>Method 2: each drill sample is allocated an area half way to next holes, to a limit of 80 metres. Tonnage is density x area x sample length. Samples meeting grade cutoffs accumulated by tonnage weighting. Good correlation with Method 1.</li> <li>Good consistency between initial estimates &amp; re-estimations after additional drilling.</li> <li>By-products not reported. Viability not dependent on by-products.</li> <li>No deleterious elements known at this resource stage. CaO may affect yields.</li> <li>Blocks 60m x 60m x 2m suits irregular drill spacing of 50 to 100m and geological shapes.</li> <li>No assumptions of (1) selective mining unit or (2) correlation between variables</li> <li>Blocks are kept inside lease boundaries and surface topography.</li> <li>No cutting of high grades at this early stage. Spike high grades very rare.</li> <li>2 estimation methods correspond reasonably.</li> <li>Dry density factor applied so tonnages and grades are on a dry basis.</li> </ul>

## APPENDIX 1 : JORC Code, 2012 Edition – Table 1 report

Criteria	JORC Code explanation	Commentary
<i>Cut-off parameters</i>	<ul style="list-style-type: none"> <li>The basis of the adopted cut-off grade(s) or quality parameters applied.</li> </ul>	<ul style="list-style-type: none"> <li>350ppm TREO-CeO2 block cut-off-grade selected. To be adjusted to suit economics when known</li> </ul>
<i>Mining factors or assumptions</i>	<ul style="list-style-type: none"> <li>Assumptions made regarding mining methods, minimum dimensions &amp; dilution. It is necessary as part of determining reasonable prospects for eventual economic extraction to consider potential mining methods, but the assumptions made regarding mining methods &amp; parameters when estimating Mineral Resources may not be rigorous. Where this is the case, this should be reported with an explanation of the basis of the mining assumptions made.</li> </ul>	<ul style="list-style-type: none"> <li>Nil at this early stage but methods historically used in Tasmania have been assessed. It is likely that a hybrid method will be required in this socio-economic-environmental setting and it would be inappropriate to speculate at the resource estimation stage.</li> </ul>
<i>Metallurgical factors or assumptions</i>	<ul style="list-style-type: none"> <li>Basis for assumptions or predictions regarding metallurgical amenability. It is always necessary as part of the process of determining reasonable prospects for eventual economic extraction to consider potential metallurgical methods, but the assumptions regarding metallurgical treatment processes &amp; parameters made when reporting Mineral Resources may not always be rigorous. Where this is the case, this should be reported with an explanation of the basis of the metallurgical assumptions made.</li> </ul>	<ul style="list-style-type: none"> <li>Desorption tests done on 78 representative samples by ANSTO indicate good potential for high extraction rates. Mineralogy studies ongoing. ABx has established its own testing procedures at its Research Lab, near Launceston Airport</li> </ul>
<i>Environmental factors or assumptions</i>	<ul style="list-style-type: none"> <li>Assumptions made regarding possible waste &amp; process residue disposal options. It is always necessary as part of the process of determining reasonable prospects for eventual economic extraction to consider the potential environmental impacts of the mining &amp; processing operation. While at this stage the determination of potential environmental impacts, particularly for a greenfields project, may not always be well advanced, the status of early consideration of these potential environmental impacts should be reported. Where these aspects have not been considered this should be reported with an explanation of the environmental assumptions.</li> </ul>	<ul style="list-style-type: none"> <li>Rehabilitation strategy is under assessment by a senior industry expert with considerable experience in Tasmania.</li> <li>All options must meet ABx's paramount policy to always leave the land better than found and only operate where welcome.</li> <li>ABx has applied for a research grant for devising the optimum production and rehabilitation methods in Tasmania</li> </ul>
<i>Bulk density</i>	<ul style="list-style-type: none"> <li>Whether assumed or determined. If assumed, the basis for the assumptions. If determined, the method used, whether wet or dry, the frequency of the measurements, the nature, size &amp; representativeness of the samples.</li> <li>The bulk density for bulk material must have been measured by methods that adequately account for void spaces (vugs, porosity, etc), moisture &amp; differences between rock &amp; alteration zones within the deposit.</li> <li>Bulk density assumptions used in the evaluation process of the different materials.</li> </ul>	<ul style="list-style-type: none"> <li>Measured densities by volumetric methods from pit samples. However lower density samples found in drill samples led to a 15% reduction in global density assumption to 1.9 dry tonnes per cubic metre.</li> <li>N.A. Clays are compacted</li> <li>No assumptions used. Gravimetric measurements done.</li> </ul>
<i>Classification</i>	<ul style="list-style-type: none"> <li>Basis for classification of the Mineral Resources into varying confidence categories.</li> <li>Whether appropriate account has been taken of all relevant factors (ie relative confidence in tonnage/grade estimations, reliability of input data, confidence in continuity of geology &amp; metal values, quality, quantity &amp; distribution of the data).</li> <li>Whether the result appropriately reflects the Competent Person's view of deposit.</li> </ul>	<ul style="list-style-type: none"> <li>Minimum 4 samples in: (1) Indicated 120m search ellipse (2) Inferred 250 search ellipse</li> <li>Resources will not be classified as measured until mining and/or clay-coring experience is gained sufficient to correlate resource predictions with actual production outcomes. Data variability is similarly high in holes and in mine openings in these environments.</li> <li>Estimation results appropriately reflects Competent Persons' views of the deposit</li> <li>None done to date. In progress by independent companies.</li> </ul>
<i>Audits or reviews</i>	<ul style="list-style-type: none"> <li>Results of any audits or reviews of Mineral Resource estimates.</li> </ul>	<ul style="list-style-type: none"> <li>All Competent Persons do manual, volume-based checks of estimates to be satisfied with results from estimations methods</li> <li>Competent Persons have signed approvals for publicly released resource reports</li> <li>No objections to date &amp; comments are welcomed</li> </ul>
<i>Discussion of relative accuracy/ confidence</i>	<ul style="list-style-type: none"> <li>Where appropriate a statement of the relative accuracy &amp; confidence level in the Mineral Resource estimate using an approach or procedure deemed appropriate by the Competent Person. For example, the application of statistical or geostatistical procedures to quantify the relative accuracy of the resource within stated confidence limits, or, if such an approach is not deemed appropriate, a qualitative discussion of the factors that could affect the relative accuracy &amp; confidence of the estimate.</li> <li>Statement should specify whether it relates to global or local estimates, &amp; if local, state the relevant tonnages, which should be relevant to technical &amp; economic evaluation. Documentation should include assumptions made &amp; the procedures used.</li> <li>Statements of relative accuracy &amp; confidence of the estimate should be compared with production data, where available.</li> </ul>	<ul style="list-style-type: none"> <li>Each deposit is estimated individually.</li> <li>It will always be done in accordance with industry practice &amp; common sense checking. This will be a constant task as this project develops further.</li> </ul>

END

Table 5: Drill Data used

Hole ID	WGS 84 UTM 55 S				RL	Permanent Magnet REE				Dy+Tb																		
	From (m)	To (m)	Metres (m)	Hole depth (m)		East	North	Sample mid RL (LiDAR)	TREO ppm	TREO CeO <sub>2</sub> ppm	Perm Mag ppm	Tb <sub>4</sub> O <sub>7</sub> ppm	Dy <sub>2</sub> O <sub>3</sub> ppm	Dy+Tb TREO %	CeO <sub>2</sub> ppm	Er <sub>2</sub> O <sub>3</sub> ppm	Eu <sub>2</sub> O <sub>3</sub> ppm	Gd <sub>2</sub> O ppm	Ho <sub>2</sub> O <sub>3</sub> ppm	La <sub>2</sub> O <sub>3</sub> ppm	Lu <sub>2</sub> O <sub>3</sub> ppm	Sm <sub>2</sub> O <sub>3</sub> ppm	Tm <sub>2</sub> O ppm	Yb <sub>2</sub> O <sub>3</sub> ppm	Y <sub>2</sub> O <sub>3</sub> ppm	ThO <sub>2</sub> ppm	U <sub>3</sub> O <sub>8</sub> ppm	
AH001	1	2	1	9	477742	5410529	281.1	165	97	27	17	5	0.7	4.8	3.3%	68	3	1	4	1	20	0	4	0	3	32	6.7	1.8
AH001	2	3	1	9	477742	5410529	280.1	162	97	28	17	5	0.7	4.7	3.3%	64	3	1	4	1	20	0	4	0	3	33	6.6	1.7
AH001	3	4	1	9	477742	5410529	279.1	218	151	44	28	7	1.2	8.1	4.3%	67	5	2	7	2	27	1	7	1	4	51	6.6	1.8
AH001	4	5	1	9	477742	5410529	278.1	320	198	58	37	9	1.6	10.8	3.9%	122	7	3	10	2	35	1	9	1	6	68	6.3	1.7
AH001	5	6	1	9	477742	5410529	277.1	416	209	61	39	10	1.8	11.1	3.1%	207	7	3	10	2	37	1	8	1	6	72	5.8	1.5
AH001	6	7	1	9	477742	5410529	276.1	345	245	66	41	9	2.1	13.9	4.7%	100	9	3	13	3	37	1	10	1	8	94	5.9	1.2
AH001	7	8	1	9	477742	5410529	275.1	378	306	83	51	12	2.8	17.9	5.5%	72	11	4	16	4	44	1	13	2	10	117	6.1	1.5
AH001	8	9	1	9	477742	5410529	274.1	492	390	105	62	15	3.7	24.3	5.7%	102	15	5	22	5	54	2	17	2	14	148	5.3	1.3
DL162	6	7	1	9	478481	5410275	295.4	1163	928	320	210	48	10.1	52.8	5.4%	235	29	18	64	9	140	3	56	4	22	262	5.8	1.7
DL162	7	8	1	9	478481	5410275	294.4	1152	926	320	209	48	9.9	52.6	5.4%	226	30	18	63	10	141	4	55	4	22	260	5.9	1.7
DL162	8	9	1	9	478481	5410275	293.4	1222	1090	355	230	52	11.5	61.9	6.0%	133	36	21	72	11	155	4	61	5	28	342	5.4	1.4
DL167	4	5	1	6	479226	5409600	304.2	667	450	195	143	42	2.2	8.1	1.6%	216	3	7	16	1	176	0	27	0	2	22	6.1	2.1
DL167	5	6	1	6	479226	5409600	303.2	305	181	71	51	14	1.1	5.1	2.0%	124	3	3	7	1	62	0	10	0	2	21	5.9	2.2
DL170	3	4	1	5	479301	5409906	297.3	958	161	53	35	9	1.4	7.0	0.9%	797	5	3	8	2	35	1	9	1	4	41	6.3	2.0
DL170	4	5	1	5	479301	5409906	296.3	2108	450	161	107	29	4.3	21.3	1.2%	1658	13	8	24	5	92	2	30	2	12	102	5.5	1.7
DL172	4	5	1	6	479114	5409999	296.4	239	149	48	29	7	1.7	10.0	4.9%	90	6	3	9	2	23	1	8	1	5	44	5.3	1.6
DL172	5	6	1	6	479114	5409999	295.4	728	501	180	118	31	4.8	25.9	4.2%	227	15	8	29	5	102	2	28	2	13	117	5.1	1.4
DL176	0	1	1	9	479481	5409875	305.6	58	38	13	9	2	0.3	1.9	3.7%	20	1	1	2	0	8	0	2	0	1	10	18.8	3.0
DL176	1	2	1	9	479481	5409875	304.6	61	44	16	10	3	0.4	2.3	4.4%	17	1	1	2	0	9	0	2	0	1	11	20.0	2.9
DL176	2	3	1	9	479481	5409875	303.6	27	19	7	5	1	0.2	1.0	4.5%	7	1	0	1	0	3	0	1	0	1	5	8.4	2.3
DL176	4	5	1	9	479481	5409875	301.6	24	16	6	4	1	0.2	0.9	4.4%	7	1	0	1	0	3	0	1	0	1	4	10.0	2.8
DL176	5	6	1	9	479481	5409875	300.6	19	13	5	3	1	0.1	0.7	4.3%	6	0	0	1	0	2	0	1	0	0	3	8.4	3.1
DL176	6	7	1	9	479481	5409875	299.6	91	27	10	6	2	0.3	1.7	2.1%	64	1	0	1	0	5	0	2	0	1	6	6.7	2.3
DL176	7	8	1	9	479481	5409875	298.6	203	24	8	5	1	0.2	1.5	0.9%	179	1	0	1	0	4	0	1	0	1	6	3.7	1.5
DL176	8	9	1	9	479481	5409875	297.6	541	122	43	27	7	1.1	7.3	1.6%	419	5	2	6	1	24	1	7	1	5	28	4.8	1.4
DL180	4	5	1	6	479252	5409513	303.1	627	410	132	91	24	3.1	14.7	2.8%	217	9	7	21	3	111	1	22	1	6	96	5.6	2.1
DL180	5	6	1	6	479252	5409513	302.1	910	239	83	56	13	2.4	11.8	1.6%	671	7	5	15	3	38	1	16	1	6	65	6.5	1.8
DL185	2	3	1	9	479153	5408913	304.0	15	8	3	2	1	0.1	0.4	3.4%	6	0	0	0	2	0	0	0	0	2	8.9	2.8	
DL185	3	4	1	9	479153	5408913	303.0	32	16	6	3	1	0.2	1.3	4.8%	15	1	0	1	0	3	0	1	0	1	4	8.5	2.4
DL185	4	5	1	9	479153	5408913	302.0	98	41	14	8	2	0.5	3.9	4.5%	57	2	1	2	1	6	0	2	0	2	10	10.9	2.7
DL185	5	6	1	9	479153	5408913	301.0	78	45	18	11	3	0.5	3.4	5.0%	33	2	1	3	1	7	0	3	0	2	9	7.5	2.7
DL185	6	7	1	9	479153	5408913	300.0	170	108	43	29	7	1.0	6.3	4.3%	62	3	2	6	1	19	0	7	0	3	23	8.3	2.7
DL185	7	8	1	9	479153	5408913	299.0	229	141	56	37	9	1.3	8.4	4.2%	88	4	3	8	2	25	1	8	1	4	30	8.5	2.5
DL185	8	9	1	9	479153	5408913	298.0	486	416	152	100	25	3.5	23.2	5.5%	70	12	7	23	4	71	2	21	2	9	114	10.2	2.9
DL187	3	4	1	7	479500	5408943	300.1	70	46	16	11	3	0.3	2.2	3.6%	24	1	1	2	0	11	0	2	0	1	10	5.2	1.6
DL187	4	5	1	7	479500	5408943	299.1	737	128	45	28	8	1.0	6.7	1.0%	609	4	2	6	1	29	1	6	1	5	30	6.3	1.3
DL187	5	6	1	7	479500	5408943	298.1	1996	178	56	37	10	1.7	8.6	0.5%	1818	6	3	9	2	37	1	10	1	6	46	3.9	1.1
DL187	6	7	1	7	479500	5408943	297.1	3169	319	102	63	16	3.6	18.9	0.7%	2850	13	6	18	4	54	2	20	2	14	84	3.7	1.1
DL190	3	4	1	9	479625	5408667	302.2	290	206	67	44	13	1.3	8.6	3.4%	84	4	3	9	2	63	0	8	1	3	46	6.4	1.8
DL190	4	5	1	9	479625	5408667	301.2	1114	148	48	31	8	1.2	7.6	0.8%	965	4	2	8	1	30	0	6	1	3	44	6.6	1.0
DL190	5	6	1	9	479625	5408667	300.2	868	176	63	40	11	1.6	10.0	1.3%	692	5	3	10	2	32	1	8	1	4	49	7.2	1.7
DL190	6	7	1	9	479625	5408667	299.2	2530	1240	578	401	115	9.7	51.9	2.4%	1290	19	25	68	8	270	2	77	2	13	178	6.0	2.0
DL190	7	8	1	9	479625	5408667	298.2	4036	2156	960	679	172	16.7	93.2	2.7%	1879	35	39	116	15	496	4	129	4	24	333	4.9	1.9
DL190	8	9	1	9	479625	5408667	297.2	2604	1940	831	581	147	15.5	86.8	3.9%	665	34	35										

DL390	15	16	1	16	478922	5409764	299.7	345	153	49	31	7	1.6	9.2	3.1%	192	5	3	9	2	27	1	8	1	4	45	7.2	1.9
DL391	5	6	1	10	479474	5409850	301.3	27	16	5	3	1	0.2	0.9	3.8%	11	1	0	1	0	3	0	1	0	1	5	10.2	2.9
DL391	6	7	1	10	479474	5409850	300.3	26	14	4	2	1	0.1	0.7	3.3%	12	1	0	1	0	3	0	1	0	1	4	10.9	2.9
DL391	7	8	1	10	479474	5409850	299.3	32	13	4	2	1	0.1	0.7	2.7%	18	1	0	1	0	3	0	1	0	1	4	9.7	2.7
DL391	8	9	1	10	479474	5409850	298.3	170	29	10	6	2	0.2	1.4	1.0%	141	1	0	1	0	6	0	1	0	1	7	6.9	2.7
DL391	9	10	1	10	479474	5409850	297.3	174	27	9	6	2	0.2	1.3	0.9%	146	1	0	1	0	6	0	1	0	1	7	6.4	2.7
DL392	5	6	1	10	479568	5409893	297.4	81	41	14	9	2	0.3	2.0	2.8%	40	1	1	2	0	9	0	2	0	1	10	3.8	1.3
DL392	6	7	1	10	479568	5409893	296.4	155	93	30	20	5	0.7	4.0	3.0%	61	3	1	4	1	22	0	4	0	3	26	4.0	1.0
DL392	7	8	1	10	479568	5409893	295.4	625	419	137	92	26	2.9	16.3	3.1%	206	10	5	18	4	105	1	17	2	8	112	4.1	1.0
DL392	8	9	1	10	479568	5409893	294.4	1887	1782	710	493	126	14.6	76.8	4.8%	105	43	27	86	15	405	5	97	6	36	351	3.6	0.9
DL392	9	10	1	10	479568	5409893	293.4	989	938	380	259	73	7.6	40.3	4.8%	51	22	14	45	8	212	3	52	3	20	179	4.3	1.1
DL393	4	5	1	7	479359	5410196	281.8	377	277	90	60	17	2.0	11.4	3.6%	99	7	3	12	2	67	1	12	1	6	76	5.0	1.1
DL393	5	6	1	7	479359	5410196	280.8	382	288	96	64	18	2.1	11.7	3.6%	95	7	4	12	2	70	1	12	1	6	76	5.2	1.2
DL393	6	7	1	7	479359	5410196	279.8	365	289	92	61	17	2.2	12.4	4.0%	76	8	4	13	3	66	1	12	1	6	83	5.0	1.1
DL394	7	8	1	12	478559	5410030	302.6	125	57	14	9	3	0.4	2.5	2.3%	68	2	1	2	1	18	0	2	0	2	15	4.5	1.3
DL394	8	9	1	12	478559	5410030	301.6	192	28	9	5	2	0.3	1.5	0.9%	163	1	0	1	0	7	0	1	0	1	7	4.9	1.2
DL394	9	10	1	12	478559	5410030	300.6	321	52	19	12	3	0.5	3.0	1.1%	269	2	1	3	1	10	0	3	0	2	12	5.6	1.7
DL394	10	11	1	12	478559	5410030	299.6	252	112	43	29	7	1.1	5.8	2.7%	140	3	2	6	1	19	0	7	0	3	26	6.8	1.9
DL394	11	12	1	12	478559	5410030	298.6	249	68	25	17	4	0.6	3.5	1.6%	181	2	1	3	1	16	0	4	0	2	13	6.1	1.7
DL395	5	6	1	14	478963	5410184	299.6	75	23	8	5	2	0.2	0.9	1.4%	51	1	0	1	0	7	0	1	0	1	5	11.7	2.3
DL395	6	7	1	14	478963	5410184	298.6	24	11	3	2	1	0.1	0.5	2.4%	14	0	0	0	0	3	0	1	0	0	3	9.5	2.6
DL395	7	8	1	14	478963	5410184	297.6	44	14	5	3	1	0.1	0.6	1.7%	30	0	0	1	0	3	0	1	0	0	4	8.6	2.3
DL395	8	9	1	14	478963	5410184	296.6	45	15	5	3	1	0.1	0.7	1.8%	30	1	0	1	0	4	0	1	0	1	4	9.3	2.3
DL395	9	10	1	14	478963	5410184	295.6	134	25	8	5	2	0.2	1.2	1.1%	109	1	0	1	0	6	0	1	0	1	6	8.2	1.8
DL395	10	11	1	14	478963	5410184	294.6	102	22	8	5	1	0.2	1.1	1.3%	80	1	0	1	0	5	0	1	0	1	5	8.6	1.9
DL395	11	12	1	14	478963	5410184	293.6	270	69	23	15	4	0.6	4.0	1.7%	201	2	1	3	1	13	0	3	0	3	18	5.4	1.3
DL395	12	13	1	14	478963	5410184	292.6	265	108	39	25	7	0.9	5.1	2.3%	157	3	2	5	1	25	1	5	1	3	25	5.9	1.4
DL395	13	14	1	14	478963	5410184	291.6	233	85	32	21	6	0.7	4.2	2.1%	149	2	1	4	1	19	0	4	0	3	18	5.6	1.3
DL396	2	3	1	6	479009	5410241	299.6	22	11	4	3	1	0.1	0.6	2.9%	10	0	0	1	0	3	0	1	0	0	2	7.6	2.8
DL396	3	4	1	6	479009	5410241	298.6	54	25	10	7	2	0.2	1.1	2.3%	29	1	0	1	0	6	0	1	0	1	5	7.5	3.2
DL396	4	5	1	6	479009	5410241	297.6	60	9	3	2	1	0.1	0.5	0.9%	51	0	0	0	0	2	0	0	0	0	2	7.4	3.0
DL396	5	6	1	6	479009	5410241	296.6	54	15	5	3	1	0.1	0.8	1.7%	39	0	0	1	0	3	0	1	0	1	4	7.5	3.0
DL397	1	2	1	6	479075	5410182	302.4	113	67	23	15	4	0.5	3.2	3.3%	46	2	1	3	1	16	0	3	0	2	15	5.6	1.7
DL397	2	3	1	6	479075	5410182	301.4	103	63	21	14	4	0.5	3.1	3.5%	40	2	1	3	1	14	0	3	0	2	16	5.8	2.2
DL397	3	4	1	6	479075	5410182	300.4	354	303	81	45	9	4.1	22.5	7.5%	51	11	6	25	5	32	1	15	1	7	118	4.5	1.7
DL397	4	5	1	6	479075	5410182	299.4	1315	315	102	67	18	2.4	14.8	1.3%	1000	10	4	14	3	73	2	14	1	10	82	4.8	1.2
DL397	5	6	1	6	479075	5410182	298.4	267	141	35	20	5	1.4	8.3	3.6%	125	5	2	8	2	20	1	6	1	4	59	3.8	1.0
DL398	1	2	1	3	479204	5410206	304.8	131	76	19	12	3	0.7	4.0	3.6%	55	3	1	4	1	13	0	3	0	2	30	4.0	1.1
DL398	2	3	1	3	479204	5410206	303.8	158	69	21	14	4	0.5	3.2	2.4%	89	2	1	3	1	16	0	3	0	2	19	7.6	1.9
DL399	2	3	1	7	478576	5410309	302.4	38	16	5	3	1	0.1	0.9	2.7%	21	1	0	1	0	4	0	1	0	1	4	11.8	2.0
DL399	3	4	1	7	478576	5410309	301.4	40	18	6	4	1	0.2	1.0	2.8%	22	1	0	1	0	4	0	1	0	1	4	11.0	2.0
DL399	4	5	1	7	478576	5410309	300.4	45	15	5	3	1	0.1	0.8	2.2%	30	1	0	1	0	3	0	1	0	1	4	9.2	2.4
DL399	5	6	1	7	478576	5410309	299.4	60	13	4	3	1	0.1	0.7	1.3%	47	0	0	1	0	3	0	1	0	1	3	8.1	2.5
DL399	6	7	1	7	478576	5410309	298.4	35	10	3	2	1	0.1	0.5	1.6%	26	0	0	0	0	2	0	1	0	0	2	8.3	2.5
DL400	2	3	1	5	478490	5410376	298.9	27	14	4	3	1	0.1	0.8	3.6%	13	1	0	1	0	3	0	1	0	1	3	7.1	2.1
DL400	3	4	1	5	478490	5410376	297.9	13	7	2	1	0	0.1	0.5	4.4%	6	0	0	0	0	1	0	0	0	0	2	6.3	2.2
DL400	4	5	1	5	478490	5410376	296.9	24	8	3	2	0	0.1	0.5	2.4%	15	0	0	0	0	2	0	0	0	0	2	8.1	3.2
DL401	0	1	1	2	478502	5410243	301.1	27	13	4	2	1	0.1	0.8	3.2%	14	0	0	1	0	2	0	1	0	1	4	8.0	2.8
DL401	1	2	1	2	478502	5410243	300.1	23	11	3	2	1	0.1	0.7	3.5%	11	0	0	1	0	2	0	1	0	1	3	8.7	2.8
DL402	2	3	1	6	478426	5410296	298.4	145	8	2	2	0	0.1	0.4	0.3%	138	0											

DL409	4	5	1	10	478209	5409481	298.4	129	89	32	22	5	0.8	4.5	4.1%	40	2	2	5	1	20	0	5	0	2	20	7.7	1.8
DL409	5	6	1	10	478209	5409481	297.4	513	49	17	11	3	0.5	2.9	0.7%	464	2	1	3	1	8	0	3	0	1	13	3.5	1.2
DL409	6	7	1	10	478209	5409481	296.4	1291	119	40	26	7	1.1	6.3	0.6%	1172	4	2	6	1	24	1	6	1	3	31	5.2	1.8
DL409	7	8	1	10	478209	5409481	295.4	1205	478	156	102	27	4.0	23.8	2.3%	727	14	7	26	5	95	2	23	2	12	136	5.5	1.5
DL409	8	9	1	10	478209	5409481	294.4	1766	1185	371	240	62	9.4	58.8	3.9%	581	36	17	61	13	232	5	51	5	29	364	4.6	1.2
DL409	9	10	1	10	478209	5409481	293.4	935	548	191	125	31	5.1	30.0	3.7%	387	16	10	33	6	98	2	30	2	13	147	6.6	1.9
DL410	1	2	1	7	478533	5409657	304.1	177	100	34	22	6	0.8	5.0	3.3%	77	3	2	5	1	21	0	5	0	2	26	13.2	2.9
DL410	2	3	1	7	478533	5409657	303.1	61	31	10	6	2	0.3	1.9	3.6%	30	1	0	2	0	6	0	2	0	1	8	14.2	3.3
DL410	3	4	1	7	478533	5409657	302.1	77	45	14	8	2	0.5	3.0	4.4%	33	2	1	3	1	7	0	2	0	2	13	10.1	2.6
DL410	4	5	1	7	478533	5409657	301.1	98	55	19	12	3	0.5	3.1	3.7%	42	2	1	3	1	10	0	3	0	1	14	7.1	2.9
DL410	5	6	1	7	478533	5409657	300.1	165	54	19	12	3	0.5	2.8	2.0%	111	2	1	3	1	10	0	3	0	1	14	5.9	2.5
DL410	6	7	1	7	478533	5409657	299.1	92	43	15	10	3	0.4	2.1	2.7%	49	1	1	2	0	9	0	2	0	1	11	6.0	3.2
DL411	0	1	1	8	478951	5409937	309.2	155	63	30	24	3	0.4	2.6	2.0%	92	1	1	3	0	10	0	3	0	1	12	7.1	2.3
DL411	1	2	1	8	478951	5409937	308.2	114	51	23	17	3	0.4	2.2	2.3%	64	1	1	2	0	8	0	2	0	1	11	7.0	2.2
DL411	2	3	1	8	478951	5409937	307.2	111	59	22	16	3	0.4	2.4	2.6%	52	1	1	3	0	15	0	3	0	1	12	5.6	1.8
DL411	3	4	1	8	478951	5409937	306.2	653	446	149	99	39	2.0	9.3	1.7%	206	4	5	14	2	209	0	21	1	3	39	4.3	1.4
DL411	4	5	1	8	478951	5409937	305.2	331	197	71	49	13	1.4	7.7	2.8%	134	4	3	9	1	56	0	10	1	3	38	4.0	1.3
DL411	5	6	1	8	478951	5409937	304.2	670	228	108	87	10	1.7	9.3	1.6%	442	5	3	11	2	35	1	10	1	4	48	5.0	1.4
DL411	6	7	1	8	478951	5409937	303.2	1118	477	198	147	24	4.3	23.2	2.5%	641	12	8	26	4	74	1	25	2	9	117	5.0	1.4
DL411	7	8	1	8	478951	5409937	302.2	693	465	160	103	26	5.0	26.9	4.6%	228	15	9	29	5	70	2	29	2	11	132	5.6	1.4
DL412	0	1	1	7	479305	5409585	305.8	257	160	57	38	10	1.4	7.4	3.4%	96	4	3	8	1	36	0	9	1	3	38	10.2	2.2
DL412	1	2	1	7	479305	5409585	304.8	301	191	69	46	13	1.6	8.3	3.3%	110	4	3	9	1	52	0	11	1	3	36	9.9	2.3
DL412	2	3	1	7	479305	5409585	303.8	269	184	63	41	12	1.6	8.3	3.7%	85	4	3	10	1	48	0	10	1	3	41	6.3	1.6
DL412	3	4	1	7	479305	5409585	302.8	371	176	76	57	11	1.2	6.5	2.1%	195	3	3	8	1	43	0	9	0	3	30	5.3	1.3
DL412	4	5	1	7	479305	5409585	301.8	248	147	54	37	8	1.4	7.7	3.7%	101	4	3	8	2	23	0	8	1	4	41	5.6	1.5
DL412	5	6	1	7	479305	5409585	300.8	493	211	96	75	9	1.8	7.7	2.3%	281	6	3	11	2	25	1	11	1	4	53	5.6	1.2
DL412	6	7	1	7	479305	5409585	299.8	282	160	59	41	8	1.6	9.0	3.8%	122	5	3	10	2	19	1	9	1	4	48	5.0	1.8
DL413	0	1	1	15	479183	5409401	313.9	401	201	82	61	10	1.7	9.2	2.7%	200	5	3	10	2	35	1	11	1	4	48	6.3	1.9
DL413	1	2	1	15	479183	5409401	312.9	271	132	55	41	6	1.2	6.5	2.8%	139	4	2	7	1	19	0	7	0	3	33	7.2	2.1
DL413	2	3	1	15	479183	5409401	311.9	105	54	21	15	3	0.5	3.0	3.4%	51	2	1	3	1	8	0	3	0	2	14	5.2	1.9
DL413	3	4	1	15	479183	5409401	310.9	206	126	48	34	11	0.7	3.6	2.1%	80	2	2	5	1	46	0	7	0	1	13	5.7	1.6
DL413	4	5	1	15	479183	5409401	309.9	235	132	56	40	11	0.9	4.2	2.2%	103	2	2	6	1	41	0	8	0	2	15	6.8	1.5
DL413	5	6	1	15	479183	5409401	308.9	279	175	63	44	15	0.8	3.4	1.5%	104	1	2	5	1	82	0	8	0	1	12	7.2	1.8
DL413	6	7	1	15	479183	5409401	307.9	322	199	77	54	19	0.9	3.9	1.5%	123	2	3	6	1	88	0	10	0	1	12	7.0	2.0
DL413	7	8	1	15	479183	5409401	306.9	377	236	91	63	21	1.2	5.5	1.8%	141	2	3	8	1	98	0	12	0	2	18	7.4	2.3
DL413	8	9	1	15	479183	5409401	305.9	265	151	60	42	12	0.9	4.4	2.0%	114	2	2	6	1	55	0	7	0	2	16	6.2	2.1
DL413	9	10	1	15	479183	5409401	304.9	231	120	49	36	8	0.8	4.3	2.2%	111	2	2	5	1	35	0	6	0	2	18	6.8	2.1
DL413	10	11	1	15	479183	5409401	303.9	210	103	43	32	6	0.8	4.3	2.4%	107	2	2	5	1	24	0	5	0	2	19	7.1	1.9
DL413	11	12	1	15	479183	5409401	302.9	158	62	30	24	3	0.5	2.7	2.0%	95	2	1	3	1	10	0	3	0	1	12	6.2	1.9
DL413	12	13	1	15	479183	5409401	301.9	181	83	35	26	4	0.7	4.0	2.6%	98	2	1	4	1	13	0	4	0	2	20	6.1	1.9
DL413	13	14	1	15	479183	5409401	300.9	536	274	111	80	13	2.8	15.1	3.3%	263	8	5	16	3	35	1	16	1	6	72	6.1	1.6
DL413	14	15	1	15	479183	5409401	299.9	1544	1179	396	241	80	12.5	62.2	4.8%	365	29	28	78	11	179	3	91	4	20	339	5.6	1.6
DL414	0	1	1	3	479470	5409313	299.0	774	677	202	109	38	8.8	45.9	7.1%	96	23	16	48	8	93	2	48	3	15	218	8.2	2.2
DL414	1	2	1	3	479470	5409313	298.0	392	328	103	58	20	3.9	20.4	6.2%	65	10	7	22	4	49	1	7	99	9.2	2.3		
DL414	2	3	1	3	479470	5409313	297.0	646	549	180	105	37	6.3	32.6	6.0%	97	16	13	38	6	86	1	42	2	11	154	8.0	2.2
DL415	0	1	1	8	479484	5410102	290.6	196	147	49	30	10	1.5	7.9	4.8%	50	4	3	9	1	29	0	10	1	3	38	10.3	2.5
DL415	1	2	1	8	479484	5410102	289.6	37	27	9	5	2	0.3	1.5	4.8%	9	1	0	1	0	5	0	2	0	1	7	7.6	2.5
DL415	2	3	1	8	479484	5410102	288.6	75	58	19	11	4	0.6	3.4	5.2%	17	1	1	4	1	11	0	4	0	1	16	8.0	2.6
DL415	3	4	1	8	479484	5410102	287.6	122	94	31	19	6	0.9	4.8	4.7%	28	2	2	5	1	19</td							

DL424	5	6	1	8	478444	5410106	300.1	146	76	27	18	5	0.6	3.2	2.6%	70	2	1	4	1	21	0	4	0	1	13	6.2	1.7
DL424	6	7	1	8	478444	5410106	299.1	129	70	26	18	4	0.6	3.1	2.9%	59	2	1	4	1	18	0	4	0	1	13	5.3	1.7
DL424	7	8	1	8	478444	5410106	298.1	190	88	31	20	5	0.9	5.1	3.2%	102	3	2	5	1	16	0	6	0	2	21	5.7	1.6
DL425	8	9	1	15	478459	5409999	302.3	363	258	115	83	23	1.5	7.1	2.4%	105	2	5	12	1	86	0	17	0	2	19	6.4	1.8
DL425	9	10	1	15	478459	5409999	301.3	376	259	118	86	24	1.5	6.8	2.2%	117	2	5	12	1	87	0	17	0	1	15	6.4	1.8
DL425	10	11	1	15	478459	5409999	300.3	370	242	108	80	21	1.5	6.1	2.0%	128	2	5	12	1	82	0	17	0	1	14	6.7	1.8
DL425	11	12	1	15	478459	5409999	299.3	225	141	56	39	10	1.1	5.6	3.0%	84	3	3	8	1	37	0	9	0	2	23	6.6	1.8
DL425	12	13	1	15	478459	5409999	298.3	184	121	43	30	7	1.0	5.6	3.6%	63	3	2	7	1	26	0	7	0	2	29	6.1	1.7
DL425	13	14	1	15	478459	5409999	297.3	180	134	44	28	7	1.3	7.0	4.6%	46	4	2	8	1	25	0	7	1	3	39	5.4	1.5
DL425	14	15	1	15	478459	5409999	296.3	1646	1532	241	106	22	14.9	97.3	6.8%	113	66	16	83	22	88	7	39	8	42	921		
DL426	3	4	1	11	478514	5410093	302.0	223	142	52	35	8	1.3	7.1	3.8%	81	3	3	9	1	29	0	8	0	3	33	6.7	1.9
DL426	4	5	1	11	478514	5410093	301.0	270	163	57	38	9	1.6	8.2	3.6%	107	4	3	11	2	32	0	10	1	3	41	6.9	1.9
DL426	5	6	1	11	478514	5410093	300.0	201	112	37	24	6	1.1	6.0	3.5%	89	3	2	7	1	20	0	6	0	3	31	6.3	1.8
DL426	6	7	1	11	478514	5410093	299.0	318	230	68	44	10	2.1	11.8	4.4%	88	7	4	14	2	35	1	12	1	5	81	6.1	1.6
DL426	7	8	1	11	478514	5410093	298.0	435	349	100	64	14	3.1	17.7	4.8%	86	11	5	20	4	51	1	17	1	8	131	6.0	1.4
DL426	8	9	1	11	478514	5410093	297.0	552	467	131	84	19	4.2	23.5	5.0%	85	14	7	27	5	66	2	22	2	11	180	5.8	1.2
DL426	9	10	1	11	478514	5410093	296.0	601	535	160	105	23	4.9	27.3	5.4%	66	16	9	33	6	79	2	27	2	11	190	5.2	1.2
DL426	10	11	1	11	478514	5410093	295.0	538	451	133	86	19	4.0	23.2	5.1%	87	13	8	27	5	70	2	23	2	10	160	5.7	1.5
DL427	5	6	1	14	478567	5410078	301.5	149	108	37	25	6	0.8	5.1	4.0%	41	3	2	6	1	25	0	5	0	2	27	5.3	1.4
DL427	6	7	1	14	478567	5410078	300.5	189	128	43	29	7	1.0	6.2	3.8%	61	3	2	7	1	28	0	6	0	3	34	5.8	1.6
DL427	7	8	1	14	478567	5410078	299.5	577	462	190	132	31	4.1	22.7	4.6%	115	11	10	28	4	83	1	32	1	8	94	5.5	1.4
DL427	8	9	1	14	478567	5410078	298.5	2220	2085	635	395	93	22.0	125.1	6.6%	135	66	40	133	24	274	6	114	8	41	743	5.3	1.7
DL427	9	10	1	14	478567	5410078	297.5	1106	975	325	213	52	9.2	50.4	5.4%	131	26	18	58	10	154	3	59	3	18	302	5.2	1.4
DL427	10	11	1	14	478567	5410078	296.5	1033	949	290	183	43	9.6	54.1	6.2%	85	29	17	58	10	136	3	50	4	20	331	5.3	1.4
DL427	11	12	1	14	478567	5410078	295.5	547	501	159	103	25	4.7	25.6	5.5%	46	14	9	30	5	88	1	27	2	10	157	5.2	1.3
DL427	12	13	1	14	478567	5410078	294.5	1576	1529	282	168	38	10.9	65.2	4.8%	47	42	16	73	15	210	4	41	5	26	815	4.7	1.6
DL427	13	14	1	14	478567	5410078	293.5	1089	1035	212	124	28	8.8	51.9	5.6%	53	34	13	56	12	118	4	35	4	22	527	4.3	1.3
DL428	12	13	1	15	478643	5410124	295.2	176	90	27	17	4	0.9	5.6	3.7%	87	4	2	5	1	12	1	5	1	3	30	5.7	1.5
DL428	13	14	1	15	478643	5410124	294.2	267	128	41	26	6	1.2	7.2	3.2%	139	4	2	7	1	20	1	7	1	4	40	5.2	1.4
DL428	14	15	1	15	478643	5410124	293.2	235	146	49	31	8	1.4	8.1	4.0%	89	5	3	8	2	24	0	9	1	5	41	4.8	1.2
DL429	8	9	1	12	478580	5410135	297.7	179	80	23	14	4	0.7	4.4	2.9%	99	3	1	4	1	11	0	4	0	2	29	6.0	1.4
DL429	9	10	1	12	478580	5410135	296.7	191	86	27	17	4	0.8	4.8	2.9%	105	3	1	4	1	13	0	5	0	3	28	5.3	1.1
DL429	10	11	1	12	478580	5410135	295.7	155	105	36	23	6	1.1	6.1	4.6%	51	4	2	5	1	16	1	6	1	4	29	5.4	1.4
DL429	11	12	1	12	478580	5410135	294.7	464	341	123	79	20	3.5	20.4	5.2%	123	12	7	18	4	53	2	22	2	11	88	5.1	1.2
DL430	2	3	1	7	478515	5410151	302.1	66	43	16	11	3	0.3	1.9	3.4%	24	1	1	2	0	11	0	2	0	1	8	6.2	1.3
DL430	3	4	1	7	478515	5410151	301.1	77	45	15	10	3	0.4	2.1	3.2%	33	1	1	2	0	9	0	2	0	1	12	6.5	1.4
DL430	4	5	1	7	478515	5410151	300.1	584	128	44	29	7	1.3	7.4	1.5%	456	4	2	7	1	21	1	8	1	4	35	6.2	1.5
DL430	5	6	1	7	478515	5410151	299.1	518	145	52	33	8	1.5	8.6	1.9%	373	5	3	8	2	22	1	9	1	5	39	5.9	1.5
DL430	6	7	1	7	478515	5410151	298.1	574	317	116	77	18	3.2	17.6	3.6%	257	10	6	17	3	46	1	20	1	9	86	5.7	1.5
DL431	3	4	1	8	478474	5410129	299.3	287	176	61	40	9	1.8	10.2	4.2%	111	6	3	10	2	26	1	11	1	5	52	6.3	2.0
DL431	4	5	1	8	478474	5410129	298.3	245	145	50	33	8	1.4	8.3	4.0%	100	5	3	8	2	21	1	9	1	5	43	6.5	1.5
DL431	5	6	1	8	478474	5410129	297.3	441	266	90	58	14	2.7	15.5	4.1%	174	9	5	15	3	37	1	16	1	8	82	6.0	1.9
DL431	6	7	1	8	478474	5410129	296.3	189	146	39	24	6	1.4	7.9	4.9%	44	5	2	7	2	18	1	7	1	4	60	4.5	1.2
DL431	7	8	1	8	478474	5410129	295.3	370	230	73	46	11	2.5	13.8	4.4%	140	8	4	13	3	29	1	13	1	6	79	4.8	1.3
DL432	4	5	1	12	478466	5410199	298.6	114	70	22	14	3	0.7	4.1	4.1%	44	2	1	4	1	10	0	4	0	2	24	5.5	1.5
DL432	5	6	1	12	478466	5410199	297.6	102	69	19	12	3	0.6	3.5	4.0%	33	2	1	3	1	11	0	3	0	2	26	4.0	1.1
DL432	6	7	1	12	478466	5410199	296.6	202	159	38	22	5	1.7	9.8	5.7%	43	6	2	9	2	16	1	6	1	4	72	3.9	1.2
DL432	7	8	1	12	478466	5410199	295.6	140	89	26	17	4	0.9	5.1	4.3%	50	3	1	5	1	12	0	4	0	3	33	3.7	1.3
DL432	8	9	1	12	478466	5410199	294.6	2																				

DL437	11	12	1	13	478657	5410183	295.0	595	76	27	17	5	0.7	4.2	0.8%	518	2	1	4	1	18	0	4	0	2	16	7.1	1.5
DL437	12	13	1	13	478657	5410183	294.0	254	65	22	14	4	0.6	3.6	1.6%	189	2	1	3	1	14	0	4	0	2	15	6.4	1.5
DL438	1	2	1	3	478238	5410185	298.2	161	31	10	7	2	0.3	1.6	1.1%	130	1	0	2	0	7	0	2	0	1	7	9.6	1.8
DL438	2	3	1	3	478238	5410185	297.2	46	20	7	4	1	0.2	1.0	2.5%	26	1	0	1	0	5	0	1	0	1	5	10.1	2.6
DL439	4	5	1	7	478175	5410256	291.0	105	54	19	12	3	0.5	3.0	3.3%	50	2	1	3	1	11	0	3	0	2	13	6.3	1.9
DL439	5	6	1	7	478175	5410256	290.0	127	95	28	18	5	0.8	4.9	4.5%	32	3	1	5	1	17	0	4	0	3	32	3.9	1.0
DL439	6	7	1	7	478175	5410256	289.0	189	163	59	39	11	1.3	7.4	4.6%	26	5	2	8	2	31	1	9	1	4	42	5.6	2.1
DL440	5	6	1	8	478258	5410425	287.3	151	31	11	7	2	0.3	1.6	1.3%	120	1	0	2	0	6	0	2	0	1	8	5.4	1.8
DL440	6	7	1	8	478258	5410425	286.3	152	30	11	7	2	0.2	1.4	1.1%	122	1	0	1	0	6	0	2	0	1	7	6.1	2.0
DL440	7	8	1	8	478258	5410425	285.3	390	62	22	14	4	0.6	3.3	1.0%	328	2	1	3	1	12	0	4	0	2	15	4.8	1.7
DL441	1	2	1	8	478217	5410529	288.7	67	32	13	9	3	0.2	1.2	2.1%	34	1	0	1	0	9	0	2	0	1	5	7.9	2.9
DL441	2	3	1	8	478217	5410529	287.7	52	23	9	6	2	0.1	0.7	1.7%	30	0	0	1	0	7	0	1	0	1	3	8.5	2.7
DL441	3	4	1	8	478217	5410529	286.7	145	67	24	16	5	0.5	2.7	2.2%	78	2	1	3	1	18	0	3	0	2	14	10.5	1.7
DL441	4	5	1	8	478217	5410529	285.7	161	87	28	16	7	0.8	4.8	3.5%	74	3	1	5	1	19	0	6	0	3	21	5.5	1.7
DL441	5	6	1	8	478217	5410529	284.7	169	87	33	23	6	0.7	3.9	2.8%	82	2	1	4	1	19	0	5	0	2	18	5.8	2.1
DL441	6	7	1	8	478217	5410529	283.7	184	110	43	29	8	0.9	5.2	3.3%	74	3	2	6	1	23	0	6	0	3	23	5.3	1.9
DL441	7	8	1	8	478217	5410529	282.7	120	62	24	16	4	0.6	3.2	3.1%	59	2	1	3	1	12	0	4	0	2	13	6.4	2.1
DL442	2	3	1	9	478226	5410530	287.5	113	60	22	15	4	0.4	2.3	2.4%	54	1	1	3	0	16	0	3	0	1	12	14.1	2.4
DL442	3	4	1	9	478226	5410536	286.5	136	92	29	19	5	0.8	4.6	4.0%	44	3	1	5	1	17	0	4	0	3	27	4.5	1.1
DL442	6	7	1	9	478226	5410536	283.5	139	89	29	19	5	0.8	4.3	3.6%	49	3	1	4	1	17	0	4	0	3	27	5.4	1.4
DL442	7	8	1	9	478226	5410536	282.5	116	86	26	16	4	0.8	4.7	4.7%	29	3	1	4	1	15	0	4	0	3	28	3.7	1.0
DL443	2	3	1	8	478137	5410171	293.3	367	60	21	14	4	0.5	3.1	1.0%	307	2	1	3	1	12	0	3	0	2	14	5.0	1.2
DL443	3	4	1	8	478137	5410171	292.3	398	110	41	27	7	1.0	5.8	1.7%	289	3	2	6	1	21	0	7	1	3	24	4.9	1.4
DL443	4	5	1	8	478137	5410171	291.3	245	89	33	22	6	0.8	4.6	2.2%	156	3	1	5	1	17	0	5	0	3	21	3.9	1.6
DL443	5	6	1	8	478137	5410171	290.3	268	138	50	33	8	1.2	7.1	3.1%	130	4	2	7	2	26	1	8	1	4	34	3.1	1.4
DL443	6	7	1	8	478137	5410171	289.3	323	175	62	41	11	1.5	8.6	3.1%	149	5	3	9	2	33	1	10	1	4	45	5.6	1.6
DL443	7	8	1	8	478137	5410171	288.3	346	203	73	49	12	1.8	10.1	3.4%	144	6	3	11	2	38	1	11	1	5	52	5.7	1.7
DL444	2	3	1	8	477934	5409898	285.9	363	226	70	44	11	1.7	13.0	4.0%	137	7	3	10	2	44	1	9	1	6	75	7.0	2.0
DL444	3	4	1	8	477934	5409898	284.9	359	252	76	50	12	1.9	12.0	3.9%	107	8	3	12	3	47	1	11	1	7	83	5.9	1.6
DL444	4	5	1	8	477934	5409898	283.9	330	239	73	48	11	1.9	11.8	4.1%	90	7	3	12	3	43	1	11	1	7	80	5.8	1.7
DL444	7	8	1	8	477934	5409898	280.9	247	190	57	37	9	1.6	9.7	4.6%	57	6	3	10	2	32	1	9	1	5	64	5.2	1.5
DL445	0	1	1	8	478039	5409944	294.8	279	216	64	42	10	1.7	10.5	4.4%	63	7	3	11	2	38	1	9	1	6	74	6.4	2.1
DL446	1	2	1	7	478477	5410780	281.0	77	51	16	10	3	0.4	2.4	3.6%	27	2	1	2	1	11	0	2	0	2	15	9.4	2.5
DL446	2	3	1	7	478477	5410780	280.0	102	63	20	13	3	0.4	2.8	3.2%	39	2	1	3	1	15	0	2	0	2	18	10.7	2.3
DL446	3	4	1	7	478477	5410780	279.0	167	112	38	25	6	0.9	5.3	3.7%	55	3	1	5	1	24	1	5	0	3	30	4.4	1.2
DL447	3	4	1	8	478339	5410145	300.5	19	11	3	2	1	0.1	0.6	3.6%	8	0	0	0	0	3	0	0	0	1	3	6.2	1.7
DL447	5	6	1	8	478339	5410145	298.5	82	55	16	11	3	0.4	2.7	3.9%	27	2	1	2	1	10	0	2	0	2	18	6.3	1.8
DL447	6	7	1	8	478339	5410145	297.5	115	84	25	16	4	0.7	4.3	4.4%	32	3	1	4	1	14	0	4	0	3	28	4.2	1.1
DL448	4	5	1	11	478399	5410121	295.7	531	478	171	115	26	4.3	24.8	5.5%	53	14	8	27	5	75	2	28	2	12	134	5.8	1.7
DL448	10	11	1	11	478399	5410121	294.7	814	739	277	191	43	6.5	36.4	5.3%	76	19	13	40	7	121	2	45	3	17	194	5.5	1.5
DL449	2	3	1	7	478414	5410178	301.4	200	90	33	21	5	0.9	5.5	3.2%	110	3	2	5	1	15	1	5	1	4	22	5.1	1.4
DL449	3	4	1	7	478414	5410178	300.4	155	62	23	14	4	0.7	4.2	3.2%	93	3	1	4	1	10	1	4	0	3	13	5.3	1.4
DL449	4	5	1	7	478414	5410178	299.4	378	143	55	38	9	1.2	7.3	2.2%	235	4	3	7	1	25	1	9	1	5	33	5.2	1.8
DL449	5	6	1	7	478414	5410178	298.4	295	208	60	37	8	2.0	11.9	4.7%	86	7	3	12	2	29	1	9	1	7	78	4.7	1.4
DL449	6	7	1	7	478414	5410178	297.4	229	173	43	27	6	1.5	9.1	4.6%	55	6	2	9	2	22	1	7	1	5	75	4.3	1.2
DL450	4	5	1	19	478360	5410185	299.1	143	85	27	18	4	0.7	4.2	3.4%	58	3	1	4	1	14	0	4	0	3	27	4.9	1.4
DL450	5	6	1	19	478360	5410185	298.1	813	325	123	87	21	2.3	13.2	1.9%	488	8	4	14	3	71	1	17	1	8	73	5.1	1.7
DL450	6	7	1	19	478360	5410185	297.1	1158	606	333	236	59	5.6	32.9	3.3%	353	19	12	35	6	177	3	49	3	21	147	5.4	1.5
DL450	7	8	1	19	478360	5410185	296.1	1349	1144	479	338	87	7.9	46.4	4.0%	205	26	17	48	9	260	4	69	4	30	196	5.1	1.4
DL450	8	9	1	19	478360</td																							

DL457	6	7	1	10	478566	5410334	297.8	53	23	7	5	1	0.2	1.2	2.7%	31	1	0	1	0	4	0	1	0	1	7	7.1	2.9
DL457	7	8	1	10	478566	5410334	296.8	211	75	25	16	4	0.7	4.1	2.3%	136	2	1	4	1	14	0	4	0	2	21	6.6	2.2
DL457	8	9	1	10	478566	5410334	295.8	581	170	59	39	10	1.6	9.2	1.8%	412	5	3	9	2	31	1	10	1	5	45	6.2	1.6
DL457	9	10	1	10	478566	5410334	294.8	442	267	85	54	13	2.5	15.4	4.0%	175	9	4	14	3	44	1	13	1	9	82	5.5	1.6
DL458	4	5	1	10	478607	5410379	300.1	60	31	10	7	2	0.3	1.6	3.1%	29	1	0	1	0	6	0	2	0	1	9	7.1	1.8
DL458	7	8	1	10	478607	5410379	297.1	117	54	18	12	3	0.4	2.8	2.7%	64	2	1	3	1	11	0	3	0	2	14	7.8	2.2
DL458	8	9	1	10	478607	5410379	296.1	208	82	27	17	4	0.7	4.3	2.4%	127	3	1	4	1	16	0	4	0	3	22	6.8	1.8
DL458	9	10	1	10	478607	5410379	295.1	271	156	44	27	7	1.3	8.4	3.6%	115	5	2	8	2	24	1	7	1	5	59	4.7	1.2
DL459	5	6	1	8	478622	5410318	299.8	64	43	13	8	2	0.3	2.3	4.1%	21	1	1	2	0	8	0	2	0	2	14	9.5	2.8
DL459	6	7	1	8	478622	5410318	298.8	39	25	8	5	1	0.2	1.3	3.8%	14	1	0	1	0	5	0	1	0	1	8	7.3	2.4
DL459	7	8	1	8	478622	5410318	297.8	87	60	18	11	3	0.5	3.1	4.1%	27	2	1	3	1	10	0	3	0	2	21	5.1	1.4
DL460	5	6	1	7	478673	5410310	299.0	40	24	6	4	1	0.2	1.2	3.5%	16	1	0	1	0	5	0	1	0	1	8	13.4	2.7
DL460	6	7	1	7	478673	5410310	298.0	83	22	7	5	1	0.2	1.0	1.5%	61	1	0	1	0	5	0	1	0	1	6	8.3	3.1
DL461	4	5	1	7	478780	5410340	297.0	46	18	6	4	1	0.1	0.8	2.0%	28	1	0	1	0	4	0	1	0	1	5	10.5	2.9
DL461	5	6	1	7	478780	5410340	296.0	94	64	18	11	3	0.5	3.4	4.2%	30	2	1	3	1	11	0	3	0	2	23	4.5	1.3
DL462	8	9	1	15	478696	5409261	302.0	150	85	32	22	6	0.6	3.3	2.6%	65	2	1	4	1	24	0	5	0	1	15	6.5	2.0
DL462	9	10	1	15	478696	5409261	301.0	146	68	24	16	4	0.5	2.9	2.4%	77	2	1	3	1	19	0	4	0	1	14	6.1	1.8
DL462	10	11	1	15	478696	5409261	300.0	280	88	30	20	5	0.7	4.4	1.9%	192	2	2	5	1	21	0	5	0	2	19	6.3	1.8
DL462	11	12	1	15	478696	5409261	299.0	218	104	36	24	6	0.9	5.1	2.8%	114	3	2	5	1	24	0	6	0	3	24	6.8	1.9
DL462	12	13	1	15	478696	5409261	298.0	381	188	80	56	13	1.7	9.0	2.8%	193	4	4	11	2	33	1	14	1	3	35	10.1	2.5
DL462	13	14	1	15	478696	5409261	297.0	612	427	170	120	29	3.2	16.9	3.3%	185	8	7	22	3	106	1	27	1	7	76	9.2	2.7
DL462	14	15	1	15	478696	5409261	296.0	1549	1242	427	286	66	11.2	64.7	4.9%	307	34	20	73	13	220	4	67	5	29	351	8.3	2.4
DL463	2	3	1	6	478605	5409110	298.4	372	214	84	59	15	1.6	8.8	2.8%	158	4	4	11	2	51	0	14	1	4	40	7.0	2.2
DL463	3	4	1	6	478605	5409110	297.4	279	147	51	35	9	1.2	6.8	2.9%	132	4	2	7	1	30	1	8	1	3	38	4.6	1.3
DL463	4	5	1	6	478605	5409110	296.4	216	116	39	26	7	0.9	5.3	2.9%	101	3	2	6	1	23	0	6	0	3	32	4.5	1.4
DL464	1	2	1	14	478541	5409315	304.0	127	63	21	13	4	0.5	2.7	2.5%	64	2	1	3	1	20	0	3	0	2	12	9.0	2.2
DL464	5	6	1	14	478541	5409315	300.0	438	35	14	9	2	0.4	2.2	0.6%	403	1	1	2	0	7	0	3	0	1	6	7.1	2.1
DL464	6	7	1	14	478541	5409315	299.0	193	43	17	11	3	0.5	2.6	1.6%	149	1	1	2	0	9	0	3	0	2	7	7.3	2.2
DL464	7	8	1	14	478541	5409315	298.0	168	38	15	10	2	0.4	2.2	1.6%	130	1	1	2	0	8	0	3	0	1	7	7.4	2.3
DL464	8	9	1	14	478541	5409315	297.0	170	84	31	20	5	0.7	4.4	3.0%	86	2	1	4	1	18	0	5	0	2	19	9.1	2.5
DL464	9	10	1	14	478541	5409315	296.0	142	61	22	15	4	0.5	3.0	2.5%	80	2	1	3	1	13	0	4	0	2	13	11.7	3.3
DL464	10	11	1	14	478541	5409315	295.0	128	62	23	15	4	0.5	3.1	2.8%	65	2	1	3	1	12	0	3	0	2	15	11.5	3.0
DL464	11	12	1	14	478541	5409315	294.0	154	66	23	15	4	0.5	3.5	2.6%	89	2	1	3	1	13	0	3	0	2	17	12.2	2.8
DL464	12	13	1	14	478541	5409315	293.0	196	82	29	19	5	0.7	4.2	2.5%	113	2	1	4	1	16	0	4	0	2	21	12.1	2.8
DL465	8	9	1	10	478632	5409394	300.2	91	32	12	8	2	0.2	1.4	1.7%	59	1	0	1	0	9	0	2	0	1	6	8.1	2.5
DL465	9	10	1	10	478632	5409394	299.2	118	56	20	14	4	0.4	2.3	2.3%	62	1	1	3	1	15	0	3	0	1	11	6.3	3.0
DL466	5	6	1	23	478661	5409838	307.5	68	23	7	4	1	0.2	1.3	2.3%	45	1	0	1	0	5	0	1	0	1	6	5.2	1.6
DL466	6	7	1	23	478661	5409838	306.5	115	33	11	6	2	0.3	2.1	2.1%	82	1	1	2	0	7	0	2	0	1	8	4.9	1.5
DL466	7	8	1	23	478661	5409838	305.5	114	26	8	5	1	0.2	1.6	1.6%	87	1	0	1	0	6	0	1	0	1	6	4.4	1.0
DL466	8	9	1	23	478661	5409838	304.5	142	55	19	12	3	0.6	3.2	2.6%	86	2	1	3	1	13	0	3	0	2	13	5.0	1.0
DL466	9	10	1	23	478661	5409838	303.5	87	27	9	5	1	0.3	1.9	2.5%	60	1	0	1	0	5	0	2	0	1	7	5.0	0.9
DL466	10	11	1	23	478661	5409838	302.5	91	27	8	5	1	0.2	1.5	1.9%	65	1	0	1	0	5	0	2	0	1	7	6.6	1.5
DL466	11	12	1	23	478661	5409838	301.5	58	24	8	5	1	0.2	1.0	2.0%	35	1	0	1	0	6	0	1	0	1	6	8.3	1.3
DL466	12	13	1	23	478661	5409838	300.5	98	51	20	14	4	0.4	2.1	2.5%	47	1	1	2	0	12	0	3	0	1	11	8.4	1.5
DL466	13	14	1	23	478661	5409838	299.5	225	128	52	36	10	1.0	5.6	2.9%	96	2	2	7	1	31	0	8	0	2	22	7.8	2.4
DL466	14	15	1	23	478661	5409838	298.5	154	97	38	26	7	0.8	3.9	3.0%	57	2	2	5	1	24	0	6	0	2	18	7.0	1.9
DL466	15	16	1	23	478661	5409838	297.5	929	72	25	16	4	0.6	3.8	0.5%	857	2	1	4	1	15	0	4	0	2	17	7.7	1.9
DL466	16	17	1	23	478661	5409838	296.5	343	75	27	17	4	0.7	4.3	1.5%	268	2	1	4	1	14	0	4	0	3	18	7.0	1.9
DL466	17	18	1	23	478661	5409838	295.5	270	85	29	18	4	0.9	5.5	2.4%	184	3	2	5	1	14	0	5	0	3	23	6.6	1.7
DL466	18	19	1	23	478661	5409838	294.5	265</																				

DL473	4	5	1	6	479548	5408955	298.6	92	66	18	11	3	0.6	3.7	4.7%	26	2	1	3	1	10	0	3	0	2	25	3.9	1.0
DL474	6	7	1	10	479515	5408892	299.2	217	36	13	8	2	0.4	2.0	1.1%	181	1	1	2	0	7	0	2	0	1	8	6.6	2.8
DL474	7	8	1	10	479515	5408892	298.2	238	63	24	16	4	0.6	3.4	1.7%	176	2	1	4	1	12	0	4	0	2	13	7.3	2.9
DL474	8	9	1	10	479515	5408892	297.2	467	85	34	23	6	0.8	4.5	1.1%	382	2	2	4	1	18	0	6	0	3	15	6.5	2.3
DL474	9	10	1	10	479515	5408892	296.2	396	100	38	25	6	0.9	5.1	1.5%	296	3	2	5	1	20	0	6	0	3	20	6.6	2.3
DL475	1	2	1	6	479537	5408810	305.4	179	77	30	20	5	0.7	4.2	2.7%	102	2	1	4	1	15	0	5	0	3	15	7.6	2.5
DL475	2	3	1	6	479537	5408810	304.4	136	46	18	13	3	0.4	2.3	2.0%	90	1	1	2	0	9	0	3	0	2	9	6.0	1.9
DL475	3	4	1	6	479537	5408810	303.4	135	44	18	12	3	0.4	2.2	1.9%	91	1	1	2	0	8	0	3	0	1	8	5.7	2.0
DL475	4	5	1	6	479537	5408810	302.4	103	71	21	13	3	0.6	3.9	4.4%	32	2	1	4	1	12	0	3	0	3	25	3.4	1.0
DL476	1	2	1	4	479589	5408714	304.6	241	111	38	26	6	1.0	5.5	2.7%	130	3	2	6	1	23	0	6	0	3	29	6.3	1.5
DL476	2	3	1	4	479589	5408714	303.6	96	57	17	10	3	0.6	3.2	3.9%	39	2	1	3	1	10	0	2	0	2	19	3.3	0.9
DL477	1	2	1	7	479619	5408664	304.3	280	213	65	44	13	1.2	6.9	2.9%	66	3	3	8	1	83	0	8	0	3	38	6.9	1.8
DL477	2	3	1	7	479619	5408664	303.3	375	195	55	37	11	1.1	6.3	2.0%	180	3	2	8	1	80	0	8	0	3	35	6.7	1.7
DL477	3	4	1	7	479619	5408664	302.3	5615	345	124	79	19	3.8	21.2	0.4%	5270	10	7	21	4	58	1	22	1	10	88	5.4	1.4
DL477	4	5	1	7	479619	5408664	301.3	2265	441	152	99	24	4.3	24.3	1.3%	1824	13	9	26	5	74	2	27	2	12	121	5.4	1.4
DL477	5	6	1	7	479619	5408664	300.3	2579	1917	809	559	136	17.8	96.2	4.4%	662	41	43	116	17	326	5	146	6	37	373	5.1	1.3
DL477	6	7	1	7	479619	5408664	299.3	3174	2920	1048	683	156	30.9	177.3	6.6%	254	81	61	198	32	446	8	184	10	64	786	4.6	1.4
DL478	0	1	1	2	479959	5408483	287.2	516	416	153	103	24	3.9	22.0	5.0%	99	10	8	26	4	75	1	26	1	8	102	11.2	1.9
DL478	1	2	1	2	479959	5408483	286.2	168	83	28	18	5	0.8	4.5	3.1%	85	2	1	5	1	16	0	4	0	2	23	10.1	1.6
DL479	0	1	1	2	479898	5408520	292.3	101	77	24	15	4	0.7	4.3	4.9%	24	2	1	4	1	13	0	4	0	2	25	2.6	0.7
DL479	1	2	1	2	479898	5408520	291.3	96	71	23	14	4	0.6	4.2	5.0%	24	2	1	4	1	12	0	4	0	2	22	2.5	0.7
DL480	3	4	1	8	479124	5408758	300.8	209	118	41	27	7	1.1	6.8	3.8%	90	3	2	7	1	26	0	7	1	3	26	5.9	2.0
DL480	4	5	1	8	479124	5408758	299.8	250	152	54	35	9	1.5	8.4	4.0%	99	4	3	9	2	30	1	9	1	4	36	5.8	1.9
DL480	5	6	1	8	479124	5408758	298.8	374	255	91	61	15	2.3	13.1	4.1%	118	6	5	15	2	48	1	15	1	5	66	6.4	1.9
DL480	6	7	1	8	479124	5408758	297.8	590	337	118	79	19	2.9	16.8	3.3%	253	8	6	20	3	64	1	20	1	7	89	8.0	2.0
DL480	7	8	1	8	479124	5408758	296.8	520	298	105	71	17	2.7	15.1	3.4%	222	8	5	17	3	57	1	17	1	7	77	6.3	2.0
DL481	3	4	1	14	479112	5409312	310.4	83	51	17	11	3	0.3	2.0	2.7%	32	1	1	2	0	17	0	2	0	1	9	6.9	2.3
DL481	8	9	1	14	479112	5409312	305.4	215	115	38	25	7	0.9	5.1	2.8%	100	3	2	5	1	36	0	6	0	3	20	6.1	2.0
DL481	12	13	1	14	479112	5409312	301.4	290	102	30	19	5	0.7	4.5	1.8%	188	2	1	4	1	36	0	5	0	2	20	7.5	2.0
DL481	13	14	1	14	479112	5409312	300.4	309	137	42	27	6	1.2	7.4	2.8%	171	4	2	8	1	25	1	7	1	4	43	8.0	1.7
DL482	1	2	1	21	478987	5409332	314.1	231	147	65	46	13	1.0	4.5	2.4%	84	1	3	7	1	49	0	10	0	1	11	9.0	2.3
DL482	2	3	1	21	478987	5409332	313.1	401	300	137	101	24	2.5	10.1	3.1%	100	3	7	18	1	87	0	22	0	1	24	7.6	2.2
DL482	3	4	1	21	478987	5409332	312.1	201	154	64	45	13	0.9	4.2	2.6%	47	1	3	7	1	57	0	9	0	1	12	6.0	2.0
DL482	4	5	1	21	478987	5409332	311.1	125	78	31	22	6	0.6	2.9	2.7%	47	1	1	4	0	24	0	5	0	1	9	6.8	2.1
DL482	5	6	1	21	478987	5409332	310.1	104	56	20	14	4	0.3	1.5	1.7%	48	1	1	2	0	24	0	3	0	1	5	7.0	1.8
DL482	6	7	1	21	478987	5409332	309.1	92	45	16	11	3	0.3	1.7	2.2%	47	1	1	2	0	14	0	3	0	1	7	6.5	1.7
DL482	7	8	1	21	478987	5409332	308.1	100	43	15	10	3	0.3	1.8	2.2%	56	1	1	2	0	14	0	2	0	1	7	6.6	1.8
DL482	8	9	1	21	478987	5409332	307.1	202	103	38	26	8	0.6	3.4	2.0%	99	2	1	4	1	36	0	5	0	2	13	5.9	1.9
DL482	9	10	1	21	478987	5409332	306.1	146	77	28	20	6	0.4	2.2	1.8%	69	1	1	3	0	29	0	4	0	1	9	6.0	1.5
DL482	10	11	1	21	478987	5409332	305.1	152	60	20	14	4	0.4	2.2	1.7%	92	1	1	2	0	23	0	3	0	1	8	6.0	2.0
DL482	11	12	1	21	478987	5409332	304.1	197	125	43	30	9	0.6	2.7	1.7%	71	1	2	4	0	60	0	5	0	1	9	6.7	1.8
DL482	12	13	1	21	478987	5409332	303.1	126	66	22	15	4	0.4	2.4	2.3%	59	1	1	3	0	24	0	3	0	1	10	7.6	1.9
DL482	16	17	1	17	478868	5409850	319.1	389	252	100	69	16	2.3	11.9	3.7%	137	6	5	14	2	43	1	17	1	5	59	8.2	2.4
DL482	17	18	1	17	478868	5409850	318.1	425	250	94	64	15	2.3	12.3	3.5%	174	6	4	14	2	45	1	15	1	6	61	8.4	2.3
DL482	18	19	1	17	478868	5409850	317.1	724	565	216	146	32	6.0	31.9	5.2%	159	15	12	36	6	77	2	39	2	13	147	7.0	1.9
DL482	19	20	1	21	478897	5409332	296.1	866	767	226	145	31	7.7	42.6	5.8%	100	24	13	47	9	90	3	39	3	19	293	7.5	2.1
DL482	20	21	1	21	478897	5409332	295.1	640	509	164	107	24	5.1	27.9	5.2%	130	16	9	31	5	68	2	27	2	12	173	7.2	2.1
DL483	4	5	1	17	478868	5409850	310.8	148	109	31	19	4	1.1	6.0	4.8%	39	3	2	6	1	16	1	5	1	3	40	5.8	1.9
DL483	5	6	1	17	478868	5409850	307.8	144	86	26	16	4	0.8	4.4	3.6%	58	2	1	4									

DL488	4	5	1	6	477953	5409521	287.4	357	208	72	49	11	1.8	10.8	3.5%	149	6	3	12	2	35	1	11	1	6	59	6.5	2.0
DL488	5	6	1	6	477953	5409521	286.4	269	164	55	36	9	1.4	8.7	3.8%	105	5	3	9	2	28	1	8	1	5	48	5.8	1.9
DL489	0	1	1	5	477874	5409537	288.5	247	161	52	34	8	1.4	8.5	4.0%	86	5	2	8	2	28	1	8	1	4	50	6.0	1.8
DL489	1	2	1	5	477874	5409537	287.5	873	470	150	96	23	4.2	27.2	3.6%	403	15	7	25	5	74	2	23	2	14	152	6.3	1.8
DL489	2	3	1	5	477874	5409537	286.5	773	613	191	122	28	5.6	35.1	5.3%	160	21	9	35	7	88	3	30	3	17	208	7.0	1.9
DL489	3	4	1	5	477874	5409537	285.5	694	527	163	103	24	4.9	30.5	5.1%	168	18	8	30	6	76	2	26	2	15	180	6.6	1.7
DL489	4	5	1	5	477874	5409537	284.5	563	408	126	80	19	3.8	23.1	4.8%	155	14	6	25	5	58	2	21	2	11	138	6.0	1.5
DL490	0	1	1	4	477258	5409657	277.2	542	428	127	81	19	3.7	23.6	5.0%	114	14	6	23	5	65	2	19	2	12	153	7.2	1.7
DL490	1	2	1	4	477258	5409657	276.2	765	637	194	126	29	5.5	34.2	5.2%	128	21	8	35	7	91	3	31	3	18	225	6.5	1.7
DL490	2	3	1	4	477258	5409657	275.2	760	663	204	131	30	6.0	36.7	5.6%	97	22	9	38	8	92	3	34	3	19	232	6.6	1.7
DL490	3	4	1	4	477258	5409657	274.2	340	285	88	56	13	2.6	15.8	5.4%	55	10	4	16	3	42	1	16	1	8	96	6.8	1.8
DL491	0	1	1	5	479980	5409402	254.8	408	336	103	66	15	3.0	19.1	5.4%	72	11	4	19	4	48	1	16	2	10	117	5.6	1.5
DL491	1	2	1	5	479980	5409402	253.8	316	260	79	51	12	2.3	14.6	5.4%	56	9	3	14	3	39	1	12	1	8	90	5.8	1.3
DL491	2	3	1	5	479980	5409402	252.8	333	266	87	56	14	2.4	14.7	5.1%	67	9	4	14	3	42	1	14	1	8	83	5.2	1.4
DL491	3	4	1	5	479980	5409402	251.8	106	81	23	15	3	0.7	4.6	5.0%	25	3	1	4	1	12	0	4	0	3	30	2.4	0.7
DL492	0	1	1	8	480018	5409833	231.6	170	128	40	26	6	1.1	7.0	4.8%	42	4	2	7	1	21	1	6	1	4	40	3.8	0.9
DL492	1	2	1	8	480018	5409833	230.6	390	302	94	60	14	2.7	16.7	5.0%	88	10	4	17	3	45	1	15	1	9	102	4.7	1.2
DL492	2	3	1	8	480018	5409833	229.6	298	170	56	37	9	1.5	9.3	3.6%	128	6	2	9	2	30	1	8	1	5	50	4.2	1.1
DL492	3	4	1	8	480018	5409833	228.6	187	142	45	28	7	1.2	7.9	4.9%	45	5	2	7	2	25	1	7	1	4	45	4.3	1.0
DL492	4	5	1	8	480018	5409833	227.6	209	149	46	30	7	1.3	8.1	4.5%	59	5	2	8	2	25	1	7	1	5	48	3.7	1.0
DL492	5	6	1	8	480018	5409833	226.6	138	110	29	18	4	0.9	5.8	4.9%	29	4	1	5	1	15	1	4	1	3	45	2.8	0.7
DL492	6	7	1	8	480018	5409833	225.6	133	108	23	13	3	0.9	6.1	5.3%	25	5	1	5	1	11	1	4	1	4	53	2.1	0.5
DL493	0	1	1	6	479965	5410302	234.3	217	145	46	30	8	1.2	7.4	0.7%	72	5	2	7	2	27	1	7	1	4	43	4.0	0.9
DL493	1	2	1	6	479965	5410302	233.3	259	194	64	42	10	1.6	10.1	4.5%	66	6	3	10	2	38	1	10	1	6	53	3.5	0.6
DL493	2	3	1	6	479965	5410302	232.3	145	123	37	24	6	1.0	6.5	5.2%	22	4	2	7	1	22	1	6	1	4	40	3.0	0.7
DL493	3	4	1	6	479965	5410302	231.3	155	117	36	23	6	1.0	6.3	4.7%	38	4	1	6	1	23	1	5	1	3	36	3.5	0.8
DL493	4	5	1	6	479965	5410302	230.3	122	95	27	18	4	0.8	4.7	4.5%	27	3	1	5	1	18	0	4	0	3	32	3.0	0.7
DL493	5	6	1	6	479965	5410302	229.3	99	75	22	14	3	0.6	4.1	4.7%	24	3	1	4	1	12	0	3	0	2	26	2.6	0.7
DL494	0	1	1	4	479928	5410346	235.6	144	108	34	22	6	0.9	5.2	4.2%	36	3	1	5	1	22	0	5	0	3	32	4.0	1.0
DL494	1	2	1	4	479928	5410346	234.6	94	71	21	13	3	0.7	3.9	4.9%	23	2	1	4	1	12	0	3	0	2	24	2.2	0.5
DL494	2	3	1	4	479928	5410346	233.6	81	63	18	11	3	0.6	3.6	5.2%	18	2	1	3	1	9	0	3	0	2	23	2.0	0.5
DL494	3	4	1	4	479928	5410346	232.6	84	64	18	11	3	0.5	3.4	4.6%	20	2	1	3	1	10	0	3	0	2	24	2.4	0.6
DL495	2	3	1	4	479743	5408500	297.9	142	62	20	14	3	0.5	3.0	2.4%	80	2	1	3	1	13	0	3	0	2	17	5.8	1.9
DL495	3	4	1	4	479743	5408500	296.9	199	155	47	29	6	1.6	9.7	5.7%	43	6	2	10	2	24	1	8	1	4	51	3.7	1.1
DL496	3	4	1	6	479550	5408533	302.5	224	83	31	21	5	0.7	4.2	2.2%	141	2	1	4	1	16	0	5	0	2	19	5.0	1.2
DL496	4	5	1	6	479550	5408533	301.5	714	232	84	55	14	2.0	12.7	2.1%	482	7	4	13	2	42	1	13	1	7	58	4.6	1.2
DL496	5	6	1	6	479550	5408533	300.5	1788	1514	638	448	104	12.8	7.8	4.8%	274	35	31	88	12	290	5	111	5	34	265	3.5	0.9
DL497	0	1	1	6	479383	5408565	301.7	1693	1450	643	465	113	10.6	53.7	3.8%	243	25	27	82	9	320	3	106	4	23	207	4.3	1.2
DL497	1	2	1	6	479383	5408565	300.7	711	590	245	176	42	4.2	22.5	3.8%	121	11	10	32	4	130	1	38	2	10	107	4.9	1.5
DL497	2	3	1	6	479383	5408565	299.7	895	595	224	156	38	4.5	26.1	3.4%	300	14	9	31	5	120	2	34	2	11	144	6.6	1.9
DL497	3	4	1	6	479383	5408565	298.7	935	656	233	160	37	5.2	30.3	3.8%	279	17	10	35	6	121	2	35	2	12	183	7.5	1.9
DL497	4	5	1	6	479383	5408565	297.7	538	377	145	100	24	3.1	18.2	4.0%	161	10	7	21	4	68	1	24	1	8	89	4.9	1.4
DL497	5	6	1	6	479383	5408565	296.7	836	621	252	178	43	4.8	26.5	3.7%	216	14	11	33	5	127	2	40	2	12	124	5.1	1.5
DL498	1	2	1	4	479093	5408664	297.8	380	287	106	73	18	2.3	13.3	4.1%	93	7	5	17	2	52	1	17	1	6	72	6.2	1.5
DL498	2	3	1	4	479093	5408664	296.8	316	213	73	49	12	1.7	10.6	3.9%	103	6	3	11	2	40	1	11	1	5	61	5.0	1.4
DL498	3	4	1	4	479093	5408664	295.8	595	346	126	85	20	2.8	17.6	3.4%	249	10	6	18	3	66	1	18	1	8	90	5.9	1.7
DL499	2	3	1	6	479363	5409110	301.3	293	196	76	53	13	1.5	8.1	3.3%	97	5	3	11	2	40	1	12	1	4	43	6.8	1.8
DL499	3	4	1	6	479363	5409110	300.3	351	152	57	39	10	1.2	6.8	2.3%	199	4	2	7	1	34	0	9	1	3	34	6.8	2.1
DL499	4	5	1	6	479363	5409110	299.3	647	227	85	58	1																

DL506	4	5	1	5	479774	5409727	272.7	197	96	32	20	5	0.9	5.3	3.1%	102	3	1	5	1	19	0	5	0	3	27	4.5	1.3
DL507	2	3	1	5	479803	5409895	278.1	76	52	17	11	3	0.5	2.9	4.5%	24	2	1	3	1	11	0	3	0	1	14	5.8	1.9
DL507	3	4	1	5	479803	5409895	277.1	88	63	19	12	3	0.5	3.4	4.4%	24	2	1	3	1	11	0	3	0	2	21	4.1	1.3
DL507	4	5	1	5	479803	5409895	276.1	92	65	19	12	3	0.5	3.4	4.3%	26	2	1	3	1	11	0	3	0	2	23	3.5	0.9
DL508	6	7	1	22	479872	5409991	279.6	85	65	19	12	4	0.5	2.9	4.0%	20	2	1	3	1	15	0	3	0	2	19	7.2	1.7
DL508	7	8	1	22	479872	5409991	278.6	129	108	31	20	6	0.7	4.8	4.3%	21	3	1	5	1	27	0	4	0	3	33	7.1	1.6
DL508	8	9	1	22	479872	5409991	277.6	323	124	37	25	7	0.8	5.1	1.8%	199	3	1	5	1	34	0	4	1	3	35	5.6	1.4
DL508	9	10	1	22	479872	5409991	276.6	295	173	57	37	10	1.3	8.7	3.4%	121	5	2	8	2	41	1	7	1	5	44	5.4	1.4
DL508	10	11	1	22	479872	5409991	275.6	232	203	68	44	12	1.5	9.7	4.8%	29	6	2	9	2	48	1	9	1	5	53	5.2	1.2
DL508	11	12	1	22	479872	5409991	274.6	217	187	62	41	11	1.4	8.7	4.6%	30	6	2	8	2	43	1	8	1	5	50	4.5	1.0
DL508	12	13	1	22	479872	5409991	273.6	329	283	77	49	13	2.0	13.3	4.7%	45	9	3	12	3	52	1	9	1	8	108	4.9	1.1
DL508	13	14	1	22	479872	5409991	272.6	202	166	47	31	8	1.2	7.5	4.3%	36	5	2	7	2	34	1	6	1	4	59	5.2	1.4
DL508	14	15	1	22	479872	5409991	271.6	294	260	77	51	13	1.8	11.8	4.6%	34	8	3	11	3	54	1	10	1	7	85	4.4	1.2
DL508	15	16	1	22	479872	5409991	270.6	278	242	70	46	12	1.6	10.3	4.3%	36	7	2	10	2	52	1	9	1	6	83	4.2	1.0
DL508	16	17	1	22	479872	5409991	269.6	216	186	48	31	8	1.3	8.7	4.6%	30	6	2	8	2	34	1	6	1	5	74	3.7	0.9
DL508	17	18	1	22	479872	5409991	268.6	202	171	43	27	7	1.2	7.8	4.4%	32	5	2	7	2	32	1	6	1	4	69	3.4	0.8
DL508	18	19	1	22	479872	5409991	267.6	119	93	25	16	4	0.6	4.2	4.0%	26	3	1	4	1	18	0	3	0	2	35	3.8	0.8
DL508	19	20	1	22	479872	5409991	266.6	110	84	23	15	4	0.6	3.9	4.2%	25	3	1	4	1	16	0	3	0	2	30	3.8	0.8
DL508	20	21	1	22	479872	5409991	265.6	189	150	41	27	7	1.0	6.5	4.0%	39	5	1	6	1	30	1	5	1	4	55	3.8	0.9
DL509	1	2	1	7	479838	5409713	274.4	172	129	39	26	7	0.9	6.1	4.1%	43	4	1	5	1	28	0	5	1	3	41	4.3	1.2
DL509	2	3	1	7	479838	5409713	273.4	505	266	84	56	14	2.0	11.6	2.7%	240	7	3	11	3	58	1	11	1	7	80	4.0	1.0
DL509	3	4	1	7	479838	5409713	272.4	388	296	94	61	15	2.3	14.9	4.4%	93	9	3	13	3	59	1	13	1	8	89	4.7	1.1
DL509	4	5	1	7	479838	5409713	271.4	168	140	41	25	6	1.4	9.1	5.6%	28	5	2	8	2	20	1	7	1	5	50	2.7	0.8
DL509	5	6	1	7	479838	5409713	270.4	180	155	47	29	7	1.5	9.4	6.1%	24	6	2	8	2	23	1	7	1	5	53	2.8	0.8
DL510	1	2	1	5	479766	5409648	289.6	59	43	13	9	2	0.4	2.2	4.3%	16	1	1	2	0	9	0	2	0	1	13	6.5	1.9
DL510	2	3	1	5	479766	5409648	288.6	129	88	26	17	4	0.8	4.7	4.3%	40	3	1	4	1	15	0	4	0	3	30	4.1	1.1
DL510	3	4	1	5	479766	5409648	287.6	89	67	19	12	3	0.6	3.6	4.7%	23	2	1	3	1	10	0	3	0	2	24	3.2	0.9
DL511	0	1	1	7	479631	5409663	292.3	137	91	29	19	5	0.8	4.5	3.8%	47	3	1	5	1	17	0	5	0	2	27	6.9	1.5
DL511	1	2	1	7	479631	5409663	291.3	98	32	10	7	2	0.3	1.6	1.9%	66	1	0	2	0	6	0	2	0	1	9	4.0	1.3
DL511	2	3	1	7	479631	5409663	290.3	452	58	20	13	3	0.5	2.9	0.8%	394	2	1	3	1	12	0	3	0	1	15	3.9	1.6
DL511	3	4	1	7	479631	5409663	289.3	350	96	33	21	5	0.9	5.6	1.8%	254	3	2	5	1	18	0	5	0	3	26	3.9	1.4
DL511	4	5	1	7	479631	5409663	288.3	318	116	39	25	6	1.1	6.6	2.4%	202	4	2	6	1	22	1	6	1	4	31	3.6	1.1
DL511	5	6	1	7	479631	5409663	287.3	100	73	20	12	3	0.6	4.0	4.7%	27	3	1	4	1	10	0	3	0	2	28	2.5	0.7
DL511	6	7	1	7	479631	5409663	286.3	87	64	17	10	3	0.5	3.5	4.5%	24	2	1	3	1	9	0	3	0	2	26	2.5	0.7
DL512	1	2	1	4	479533	5409681	302.8	118	76	25	17	4	0.7	3.9	3.9%	41	2	1	4	1	15	0	4	0	2	21	5.8	1.9
DL512	2	3	1	4	479533	5409681	301.3	220	132	37	24	5	1.2	7.3	3.9%	87	4	2	7	2	19	1	6	1	4	49	3.2	0.9
DL512	3	4	1	4	479533	5409681	300.3	191	163	42	25	6	1.6	9.9	6.0%	27	6	2	11	2	18	1	7	1	4	69	3.0	0.8
DL513	1	2	1	4	479590	5410109	295.9	36	23	7	5	1	0.2	1.1	3.6%	13	1	0	1	0	5	0	1	0	1	6	7.3	2.5
DL513	2	3	1	4	479590	5410109	294.9	71	53	15	9	2	0.5	2.9	4.8%	18	2	1	3	1	8	0	2	0	2	20	2.6	0.8
DL514	1	2	1	6	479571	5410111	292.8	49	28	9	6	1	0.2	1.4	3.3%	21	1	0	1	0	6	0	1	0	1	8	7.4	2.9
DL514	2	3	1	6	479571	5410111	291.8	541	84	30	20	5	0.6	4.2	0.9%	457	3	1	4	1	17	0	4	0	3	20	5.1	1.6
DL514	3	4	1	6	479571	5410111	290.8	1222	598	239	162	40	5.4	31.4	3.0%	624	16	10	32	6	109	2	41	2	17	123	2.8	0.7
DL514	4	5	1	6	479571	5410111	289.8	590	427	151	98	24	4.1	24.7	4.9%	163	13	7	25	5	68	2	26	2	13	115	3.0	0.8
DL514	5	6	1	6	479571	5410111	288.8	644	439	175	118	31	3.8	22.7	4.1%	205	12	7	25	4	74	2	32	2	13	93	3.1	0.8
DL515	1	2	1	5	477350	5409773	280.0	1057	630	206	138	32	5.0	30.3	3.3%	427	19	7	31	6	117	2	29	3	17	192	6.1	2.0
DL515	2	3	1	5	477350	5409773	279.0	806	478	152	101	24	3.7	23.6	3.4%	328	14	6	24	5	87	2	23	2	13	150	6.5	1.9
DL515	3	4	1	5	477350	5409773	278.0	586	442	137	91	21	3.6	22.2	4.4%	144	14	5	22	5	73	2	21	2	12	149	5.8	1.6
DL515	4	5	1	5	477350	5409773	277.0	508	420	126	83	19	3.5	20.9	4.8%	87	13	5	21	5	71	2	19	2	11	145	5.8	1.6
DL516	0	1	1	5	479429	5410190	282.7	1010	136	54	37	9	1.1	6.9	0.8%	875	4	2	7	1	25	1	9	1	4	28	15.0	1.9
DL5																												

DL520	6	7	1	8	477720	5410127	281.2	884	839	205	101	22	11.3	70.7	9.3%	45	39	14	61	14	73	5	38	6	37	347	4.1	1.2
DL520	7	8	1	8	477720	5410127	280.2	1194	1145	352	211	49	13.2	78.4	7.7%	50	40	22	80	15	163	5	64	6	35	363	4.3	1.2
DL521	0	1	1	2	477854	5410237	291.6	1520	1446	426	255	60	15.9	94.8	7.3%	73	53	23	103	19	194	6	78	8	42	494	4.9	1.3
DL521	1	2	1	2	477854	5410237	290.6	903	775	238	145	34	8.0	51.0	6.5%	128	27	13	49	10	113	3	40	4	25	251	6.3	2.0
DL522	4	5	1	12	477781	5410353	284.4	611	459	133	81	20	4.1	27.1	5.1%	152	16	6	27	6	75	2	20	2	13	160	5.8	1.3
DL522	5	6	1	12	477781	5410353	283.4	446	381	110	66	17	3.6	24.4	6.3%	65	15	5	23	5	55	2	17	2	12	136	6.9	1.5
DL522	6	7	1	12	477781	5410353	282.4	512	448	125	76	19	4.0	26.4	5.9%	65	16	6	26	5	65	2	19	2	13	168	4.7	0.9
DL522	7	8	1	12	477781	5410353	281.4	979	877	248	155	38	7.0	48.3	5.7%	102	31	10	42	10	134	4	36	4	28	330	5.2	1.2
DL522	8	9	1	12	477781	5410353	280.4	1113	1030	318	206	53	8.1	51.3	5.3%	83	32	13	49	11	176	4	47	4	27	348	5.1	1.3
DL522	9	10	1	12	477781	5410353	279.4	934	833	263	173	43	6.4	40.2	5.0%	101	24	11	42	8	157	3	39	3	20	264	5.0	1.2
DL522	10	11	1	12	477781	5410353	278.4	704	601	174	109	28	5.1	33.1	5.4%	103	21	8	30	7	106	3	27	3	19	205	4.9	1.0
DL522	11	12	1	12	477781	5410353	277.4	696	639	181	114	27	5.4	34.2	5.7%	57	21	8	32	7	112	2	27	3	18	228	4.7	1.1
DL523	0	1	1	4	477655	5410380	283.8	190	167	47	29	7	1.4	8.7	5.3%	23	5	2	9	2	28	1	7	1	4	61	6.9	1.7
DL523	1	2	1	4	477655	5410380	282.8	337	298	83	52	13	2.4	15.4	5.3%	39	9	4	17	3	50	1	13	1	8	109	6.1	1.8
DL523	2	3	1	4	477655	5410380	281.8	497	214	61	39	10	1.7	10.8	2.5%	284	7	2	10	2	38	1	10	1	6	75	6.0	2.3
DL523	3	4	1	4	477655	5410380	280.8	289	161	48	31	8	1.2	8.1	3.2%	128	5	2	8	2	30	1	7	1	5	52	5.4	1.8
DL524	3	4	1	8	477492	5410409	282.3	196	129	37	24	6	1.1	6.8	4.0%	67	4	1	6	1	24	1	5	1	4	44	8.7	2.2
DL524	4	5	1	8	477492	5410409	281.3	464	219	72	47	12	1.6	10.3	2.6%	245	6	2	9	2	46	1	10	1	6	63	6.9	2.1
DL524	5	6	1	8	477492	5410409	280.3	395	233	76	51	12	1.6	10.9	3.2%	162	7	3	10	2	47	1	11	1	7	68	6.9	2.1
DL524	6	7	1	8	477492	5410409	279.3	492	386	129	86	21	3.0	18.5	4.4%	107	11	5	18	4	76	2	18	2	11	111	6.3	1.8
DL524	7	8	1	8	477492	5410409	278.3	422	329	108	72	18	2.5	15.6	4.3%	93	10	4	16	3	65	1	16	1	9	95	6.5	1.8
DL525	0	1	1	2	477336	5410433	287.3	219	115	35	23	6	0.9	5.5	2.9%	104	3	1	6	1	23	0	6	1	3	36	8.6	2.4
DL525	1	2	1	2	477336	5410433	286.3	266	178	57	38	10	1.3	8.7	3.8%	88	5	2	8	2	35	1	8	1	5	53	6.5	1.9
DL526	2	3	1	5	477134	5410478	289.8	472	170	58	40	10	1.1	7.0	1.7%	302	4	2	7	1	39	1	8	1	4	46	10.3	3.1
DL526	3	4	1	5	477134	5410478	288.8	356	171	58	40	10	1.1	7.3	2.4%	185	5	2	7	2	37	1	8	1	5	47	10.1	2.8
DL526	4	5	1	5	477134	5410478	287.8	850	265	91	61	16	1.9	11.8	1.6%	585	8	3	11	3	55	1	12	1	8	73	7.7	2.2
DL527	3	4	1	14	477522	5410237	285.2	198	46	15	10	3	0.4	2.4	1.4%	152	1	1	2	1	9	0	3	0	2	12	4.2	2.5
DL527	6	7	1	14	477522	5410237	282.2	182	91	32	22	5	0.7	4.4	2.8%	91	3	1	5	1	18	0	5	0	3	23	6.5	1.8
DL527	7	8	1	14	477522	5410237	281.2	233	115	39	26	6	0.9	6.0	3.0%	118	3	2	6	1	22	0	6	1	3	31	6.0	1.7
DL527	8	9	1	14	477522	5410237	280.2	242	116	39	26	6	0.9	5.6	2.7%	126	3	2	6	1	23	1	5	0	3	32	6.4	1.6
DL527	9	10	1	14	477522	5410237	279.2	239	125	42	28	7	1.0	6.0	2.9%	114	4	2	6	1	24	0	6	1	4	36	6.0	1.5
DL527	10	11	1	14	477522	5410237	278.2	165	102	32	21	5	0.9	5.7	4.0%	63	4	1	5	1	17	1	5	0	3	32	7.2	1.7
DL527	11	12	1	14	477522	5410237	277.2	255	155	43	26	7	1.3	8.4	3.8%	100	5	2	7	2	27	1	6	1	5	56	6.1	1.2
DL527	12	13	1	14	477522	5410237	276.2	242	202	55	35	9	1.6	10.5	5.0%	40	7	2	9	2	36	1	8	1	7	74	5.5	1.1
DL527	13	14	1	14	477522	5410237	275.2	417	386	96	59	15	2.8	18.8	5.2%	31	13	4	16	4	60	2	12	2	11	166	5.1	1.2
DL528	0	1	1	4	477892	5410398	286.7	197	111	35	23	6	0.9	5.5	3.3%	86	3	1	6	1	20	0	5	1	3	35	8.0	1.8
DL528	1	2	1	4	477892	5410398	285.7	164	100	30	19	5	0.8	5.0	3.6%	63	3	1	5	1	19	0	4	0	3	33	6.7	1.6
DL528	2	3	1	4	477892	5410398	284.7	191	152	37	22	5	1.4	9.2	5.5%	39	6	2	9	2	20	1	5	1	5	64	3.9	1.1
DL528	3	4	1	4	477892	5410398	283.7	183	147	36	21	5	1.4	8.8	5.6%	36	6	2	9	2	18	1	6	1	4	63	4.1	1.1
DL529	0	1	1	2	477870	5410485	287.0	129	94	27	17	4	0.8	5.1	4.5%	35	3	1	5	1	16	0	4	0	3	34	4.1	1.0
DL529	1	2	1	2	477870	5410485	286.0	577	61	21	13	3	0.5	3.2	0.6%	516	2	1	3	1	12	0	3	0	2	16	5.6	1.8
DL530	0	1	1	9	477892	5410565	289.6	82	50	15	9	2	0.4	2.5	3.6%	32	1	1	2	1	10	0	2	0	2	17	7.7	2.2
DL530	1	2	1	9	477892	5410565	288.6	59	35	10	6	2	0.3	1.8	3.7%	24	1	0	2	0	6	0	1	0	1	12	8.9	2.6
DL530	2	3	1	9	477892	5410565	286.6	577	21	11	7	2	0.3	2.1	0.4%	618	1	0	2	0	7	0	2	0	1	11	5.4	1.7
DL530	3	4	1	9	477892	5410565	286.6	515	181	66	44	11	1.5	9.4	2.1%	334	5	3	9	2	37	1	10	1	6	42	6.5	2.1
DL530	5	6	1	9	477892	5410565	284.6	313	195	71	47	12	1.7	9.9	3.7%	119	6	3	10	2	38	1	11	1	6	47	5.9	1.7
DL530	6	7	1	9	477892	5410565	283.6	367	204	73	48	13	1.7	10.3	3.3%	163	6	3	10	2	40	1	11	1	6	50	5.9	1.7
DL530	7	8	1	9	477892	5410565	282.6	397	298	102	67	17	2.5	15.6	4.5%	99	9	4	15	3	61	1	15	1	9	75	5.9	1.7
DL530	8	9	1	9	477892	5410565	281.6</																					

DL540	1	2	1	6	477490	5409607	281.3	627	406	112	71	15	3.4	21.8	4.0%	221	13	5	20	5	72	2	15	2	11	150	7.9	2.3
DL540	2	3	1	6	477490	5409607	280.3	781	610	163	101	25	4.7	31.7	4.7%	171	20	7	28	7	107	3	22	3	18	233	7.0	2.0
DL540	3	4	1	6	477490	5409607	279.3	1010	834	222	138	33	6.8	44.3	5.1%	176	28	9	39	10	132	4	32	4	25	329	6.9	2.2
DL540	4	5	1	6	477490	5409607	278.3	839	712	195	121	29	6.1	39.0	5.4%	127	24	9	36	8	108	3	31	3	21	274	6.4	2.1
DL540	5	6	1	6	477490	5409607	277.3	699	596	162	101	24	4.9	32.2	5.3%	102	20	7	30	7	92	3	25	3	17	231	6.8	1.9
DL541	0	1	1	2	477382	5409953	277.5	634	496	138	86	21	4.2	26.5	4.8%	138	16	6	25	6	83	2	21	2	14	183	7.8	2.0
DL541	1	2	1	2	477382	5409953	276.5	238	179	51	32	8	1.4	9.4	4.5%	59	6	2	8	2	31	1	7	1	5	65	6.2	1.8
DL542	0	1	1	2	477203	5409937	270.3	487	383	109	69	17	3.1	19.9	4.7%	104	12	5	19	4	70	2	16	2	10	135	8.1	2.2
DL542	1	2	1	2	477203	5409937	269.3	588	463	130	81	21	3.8	24.6	4.8%	125	15	6	23	5	80	2	19	2	13	168	7.0	2.0
DL543	2	3	1	14	477007	5409883	257.9	388	319	98	64	13	2.9	18.0	5.4%	70	11	4	17	4	49	2	15	2	10	107	7.4	2.2
DL543	3	4	1	14	477007	5409883	256.9	342	263	80	51	11	2.5	15.4	5.2%	79	9	4	15	3	41	1	12	1	8	89	8.1	2.5
DL543	4	5	1	14	477007	5409883	255.9	426	292	83	51	13	2.6	16.7	4.5%	133	11	4	15	4	47	2	13	2	10	104	8.6	2.3
DL543	5	6	1	14	477007	5409883	254.9	252	185	56	36	9	1.4	8.6	4.0%	66	5	2	8	2	38	1	8	1	5	60	6.7	2.4
DL543	6	7	1	14	477007	5409883	253.9	222	187	55	36	9	1.3	8.3	4.4%	35	5	2	8	2	38	1	8	1	5	62	6.6	2.7
DL543	7	8	1	14	477007	5409883	252.9	208	153	46	30	8	1.2	7.7	4.3%	54	5	2	7	2	29	1	7	1	5	50	6.8	2.2
DL543	8	9	1	14	477007	5409883	251.9	201	144	44	27	7	1.2	7.8	4.5%	57	5	2	7	2	26	1	7	1	5	47	6.7	1.7
DL543	9	10	1	14	477007	5409883	250.9	182	128	39	24	6	1.0	6.9	4.4%	53	4	2	6	1	23	1	6	1	4	43	6.7	1.6
DL543	10	11	1	14	477007	5409883	249.9	167	118	35	22	5	1.0	6.5	4.5%	49	4	2	6	1	20	1	5	1	4	39	6.5	1.5
DL543	11	12	1	14	477007	5409883	248.9	192	134	40	25	7	1.1	7.2	4.3%	58	5	2	6	1	23	1	6	1	4	45	6.6	1.7
DL543	12	13	1	14	477007	5409883	247.9	185	135	40	25	6	1.1	7.1	4.4%	51	5	2	6	2	24	1	6	1	4	44	6.2	1.5
DL543	13	14	1	14	477007	5409883	246.9	199	148	43	27	7	1.2	8.1	4.7%	51	5	2	7	2	25	1	6	1	5	52	5.9	1.3
DL544	1	2	1	3	477202	5410183	284.2	196	134	41	26	7	1.1	7.3	4.3%	62	5	2	7	2	24	1	6	1	5	43	9.0	2.5
DL544	2	3	1	3	477202	5410183	283.2	329	203	63	41	10	1.6	10.6	3.7%	126	6	2	10	2	37	1	9	1	6	65	8.3	2.5
DL545	0	1	1	4	477173	5410289	287.8	363	188	61	41	9	1.5	9.5	3.0%	174	6	2	9	2	36	1	9	1	5	57	10.8	3.5
DL545	1	2	1	4	477173	5410289	286.8	354	195	63	41	10	1.4	9.4	3.1%	160	6	2	9	2	38	1	9	1	6	59	9.0	2.7
DL545	2	3	1	4	477173	5410289	285.8	504	357	117	79	20	2.6	15.6	3.6%	147	10	4	16	3	76	1	16	1	9	104	8.0	2.3
DL545	3	4	1	4	477173	5410289	284.8	1043	649	226	155	38	4.7	29.0	3.2%	394	17	8	30	6	130	3	32	3	17	178	9.1	2.8
DL546	0	1	1	3	477308	5410168	286.3	661	223	78	54	11	1.7	10.7	1.9%	437	6	3	11	2	42	1	11	1	6	62	11.3	3.7
DL546	1	2	1	3	477308	5410168	285.3	233	89	30	20	5	0.7	4.2	2.1%	144	3	1	4	1	18	0	4	0	3	24	9.2	2.8
DL546	2	3	1	3	477308	5410168	284.3	199	133	40	26	6	1.1	6.8	4.0%	65	4	1	6	1	24	1	6	1	4	45		
DL547	1	2	1	2	477018	5410066	271.1	338	265	82	55	13	1.9	12.6	4.3%	73	8	3	13	3	50	1	12	1	7	85		
DL548	1	2	1	2	477136	5410024	279.2	202	123	35	23	6	0.8	5.1	2.9%	78	4	1	5	1	28	0	4	1	3	41	9.5	2.3
DL549	0	1	1	4	477305	5410024	281.9	307	103	30	20	5	0.7	4.5	1.7%	204	3	1	4	1	24	0	4	0	3	33	10.8	3.6
DL549	1	2	1	4	477305	5410024	280.9	485	194	56	38	10	1.1	7.5	1.8%	291	5	2	7	2	49	1	7	1	5	61	8.8	2.6
DL549	2	3	1	4	477305	5410024	279.9	469	309	95	64	16	2.0	13.3	3.3%	160	9	3	13	3	67	1	13	1	8	95	7.7	2.1
DL549	3	4	1	4	477305	5410024	278.9	368	228	70	46	12	1.6	9.8	3.1%	139	6	2	10	2	48	1	10	1	6	71	7.8	2.1
DL551	0	1	1	4	477484	5409946	279.1	288	204	65	43	11	1.6	9.7	3.9%	84	6	2	10	2	43	1	9	1	5	61	9.1	2.1
DL551	1	2	1	4	477484	5409946	278.1	261	168	54	36	10	1.3	7.9	3.5%	92	4	2	8	2	38	1	8	1	4	46	11.3	2.5
DL551	2	3	1	4	477484	5409946	277.1	149	105	31	20	5	0.8	5.3	4.1%	44	3	1	5	1	19	1	5	1	4	36	5.0	1.3
DL552	1	2	1	8	477479	5409939	277.4	296	209	64	41	10	1.9	11.8	4.6%	87	6	3	11	2	39	1	10	1	6	66	9.9	2.3
DL552	2	3	1	8	477479	5409939	276.4	140	94	28	18	5	0.8	5.2	4.3%	46	3	1	5	1	18	0	4	0	3	29	8.2	1.9
DL552	3	4	1	8	477479	5409939	275.4	266	198	59	37	9	1.7	11.4	4.9%	68	7	2	10	2	36	1	8	1	7	63	5.6	1.8
DL552	4	5	1	8	477479	5409939	274.4	221	162	44	28	7	1.3	8.3	4.4%	59	6	2	8	2	28	1	7	1	5	59	5.2	1.7
DL552	5	6	1	8	477479	5409939	273.4	157	111	33	21	5	0.9	5.8	4.3%	45	3	1	5	1	21	0	5	1	3	37	5.3	1.2
DL552	6	7	1	8	477479	5409939	272.4	147	104	32	20	5	0.9	5.4	4.3%	42	3	1	5	1	19	1	5	1	3	33	4.8	1.1
DL552	7	8	1	8	477479	5409939	271.4	169	124	38	25	6	1.0	6.3	4.3%	45	4	2	6	1	23	1	6	1	4	39	4.6	1.1
DL553	0	1	1	8	477101	5409686	277.0	345	275	78	51	11	2.0	13.7	4.6%	70	8	3	13	3	53	1	10	1	7	97	9.2	2.8
DL553	1	2	1	8	477101	5409686	276.0	680	592	178	115	28	5.0	30.8	5.3%	87	18	7	31	6	98	3	28	3	17	204	8.0	2.1
DL553	2	3	1	8	477101	5409686	275.0	679	610	177	110	27	5.4	34.2	5.													

DL563	3	4	1	5	479253	5407414	286.8	162	96	28	18	5	0.7	4.2	3.0%	66	2	1	4	1	24	0	3	0	3	29	8.4	2.2
DL563	4	5	1	5	479253	5407414	285.8	265	140	40	25	7	1.0	6.6	2.9%	125	4	2	6	1	28	1	5	1	4	48	7.1	1.9
DL564	1	2	1	6	479122	5407417	277.4	244	123	38	25	7	0.8	5.6	2.6%	120	3	1	5	1	30	1	5	0	3	36	9.5	2.7
DL564	2	3	1	6	479122	5407417	276.4	272	125	43	30	8	0.8	5.3	2.3%	146	3	2	5	1	29	0	6	0	3	32	10.1	2.6
DL564	3	4	1	6	479122	5407417	275.4	438	255	91	61	15	2.0	12.2	3.2%	184	7	4	12	2	54	1	13	1	7	64	9.4	3.0
DL564	4	5	1	6	479122	5407417	274.4	321	242	85	56	14	2.0	13.0	4.7%	79	7	4	13	2	46	1	13	1	7	63	7.7	2.2
DL564	5	6	1	6	479122	5407417	273.4	311	240	81	53	13	1.9	12.6	4.7%	71	8	3	13	2	46	1	12	1	7	67	8.7	2.5
DL565	1	2	1	4	479004	5407641	277.1	287	197	66	44	11	1.6	10.2	4.1%	90	6	3	10	2	40	1	10	1	5	53	11.5	3.0
DL565	2	3	1	4	479004	5407641	276.1	222	171	56	37	10	1.3	8.1	4.2%	51	5	2	8	2	37	1	8	1	4	47	11.8	2.7
DL565	3	4	1	4	479004	5407641	275.1	208	165	42	26	6	1.3	8.3	4.7%	43	5	2	8	2	26	1	6	1	4	69	5.6	1.5
DL566	1	2	1	3	478964	5407787	288.6	176	130	39	26	6	1.0	6.3	4.2%	46	4	1	7	1	26	0	6	1	4	41	9.5	2.9
DL566	2	3	1	3	478964	5407787	287.6	164	121	36	23	6	1.0	5.8	4.1%	43	4	2	6	1	23	1	5	1	3	40	7.0	1.8
DL567	1	2	1	4	479092	5408022	293.1	134	88	27	17	5	0.7	4.3	3.7%	46	3	1	4	1	19	0	4	0	3	26	7.9	2.7
DL567	2	3	1	4	479092	5408022	292.1	157	103	31	20	5	0.8	4.8	3.5%	54	3	1	5	1	23	0	4	0	3	32	8.3	2.6
DL567	3	4	1	4	479092	5408022	291.1	255	110	31	20	5	0.8	5.2	2.3%	145	3	1	5	1	23	0	4	0	3	37	6.7	2.1
DL568	1	2	1	3	479361	5407786	297.3	270	85	25	16	4	0.7	4.1	1.8%	185	3	1	4	1	18	0	3	0	2	27	7.7	2.2
DL568	2	3	1	3	479361	5407786	296.3	218	89	27	17	4	0.6	4.3	2.3%	130	3	1	4	1	19	0	4	0	3	28	7.0	1.9
DL569	1	2	1	8	479493	5407931	302.9	146	61	19	12	3	0.4	3.2	2.5%	85	2	1	3	1	12	0	3	0	2	19	6.7	2.0
DL569	2	3	1	8	479493	5407931	301.9	141	58	17	10	3	0.4	3.2	2.6%	84	2	1	3	1	10	0	2	0	2	19	6.6	1.8
DL569	3	4	1	8	479493	5407931	300.9	129	70	22	14	3	0.6	3.9	3.6%	58	3	1	3	1	12	0	3	0	3	22	5.6	2.5
DL569	4	5	1	8	479493	5407931	299.9	166	124	36	22	6	1.1	7.0	4.9%	42	5	1	6	2	20	1	5	1	5	44	6.1	2.8
DL569	5	6	1	8	479493	5407931	298.9	399	288	84	53	14	2.4	15.2	4.4%	111	10	3	13	3	51	1	12	1	10	98	6.0	2.4
DL569	6	7	1	8	479493	5407931	297.9	467	329	107	72	17	2.3	15.1	3.7%	138	9	4	15	3	66	1	15	1	9	97	6.4	1.9
DL569	7	8	1	8	479493	5407931	296.9	218	133	40	26	7	1.0	7.0	3.7%	86	5	2	6	1	23	1	6	1	4	44	6.3	2.0
DL570	1	2	1	4	477174	5409567	273.2	254	178	54	35	9	1.4	9.2	4.2%	76	6	2	8	2	35	1	8	1	5	56	6.3	1.5
DL571	2	3	1	7	477050	5409502	259.7	292	205	62	40	10	1.6	10.7	4.2%	87	7	2	10	2	36	1	9	1	7	67	7.1	2.0
DL571	4	5	1	7	477050	5409502	258.7	271	193	60	39	10	1.5	9.6	4.1%	78	6	2	9	2	36	1	9	1	6	62	8.1	2.0
DL571	5	6	1	7	477050	5409502	257.7	239	174	53	34	8	1.5	9.0	4.4%	65	6	2	9	2	31	1	8	1	6	57	7.9	1.9
DL571	6	7	1	7	477050	5409502	256.7	263	193	56	36	9	1.5	10.0	4.4%	70	7	2	9	2	32	1	8	1	6	68	8.0	2.3
DL572	3	4	1	7	477138	5409431	268.3	364	291	89	57	14	2.6	15.6	5.0%	73	10	3	16	3	47	1	15	1	9	95	8.1	2.4
DL572	4	5	1	7	477138	5409431	267.3	207	155	48	30	8	1.3	8.3	4.6%	52	5	2	8	2	27	1	8	1	5	49	7.3	2.0
DL572	5	6	1	7	477138	5409431	266.3	332	243	72	45	11	2.2	13.9	4.9%	89	9	3	13	3	36	1	12	1	8	84	7.7	2.1
DL572	6	7	1	7	477138	5409431	265.3	176	131	40	25	6	1.1	7.1	4.7%	46	5	2	7	1	22	1	6	1	4	43	6.3	1.7
DL573	2	3	1	11	477326	5409469	276.1	408	326	96	60	14	3.0	18.4	5.2%	82	11	4	19	4	48	2	17	1	10	115	8.0	1.7
DL573	3	4	1	11	477326	5409469	275.1	576	461	137	86	21	4.1	25.5	5.1%	115	15	6	26	5	70	2	24	2	14	160	12.0	2.9
DL573	4	5	1	11	477326	5409469	274.1	361	288	86	55	13	2.5	15.7	5.0%	72	9	4	16	3	45	1	14	1	9	99	8.0	2.1
DL573	5	6	1	11	477326	5409469	273.1	337	270	82	52	13	2.3	14.3	4.9%	68	9	3	15	3	44	1	13	1	8	90	8.1	2.2
DL573	6	7	1	11	477326	5409469	272.1	280	219	65	42	10	1.9	11.1	4.7%	61	7	3	11	2	36	1	11	1	7	76	7.6	1.9
DL573	7	8	1	11	477326	5409469	271.1	211	156	48	31	8	1.2	8.0	4.4%	55	5	2	8	2	27	1	8	1	5	50	6.8	1.7
DL573	8	9	1	11	477326	5409469	270.1	209	153	47	31	7	1.2	7.5	4.2%	56	5	2	7	2	27	1	7	1	5	51	7.1	1.7
DL573	9	10	1	11	477326	5409469	269.1	157	111	34	22	6	0.9	5.7	4.2%	46	4	1	5	1	20	1	5	1	3	36	6.2	1.7
DL574	3	4	1	11	477484	5409364	284.1	636	480	149	98	25	3.8	22.4	4.1%	156	14	6	24	5	94	2	22	2	12	152	5.7	1.7
DL574	4	5	1	11	477484	5409364	283.1	584	432	134	88	23	3.3	20.0	4.0%	152	12	5	21	4	89	2	21	2	11	132	6.0	1.6
DL574	5	6	1	11	477484	5409364	282.1	537	420	127	82	21	3.2	19.9	4.3%	117	12	4	21	4	85	2	20	2	11	134	6.0	1.7
DL574	6	7	1	11	477484	5409364	281.1	462	366	109	71	18	2.9	17.6	4.4%	96	11	4	18	4	73	1	16	1	9	118	7.2	2.0
DL574	7	8	1	11	477484	5409364	280.1	394	301	86	55	14	2.4	15.0	4.4%	93	9	3	15	3	56	1	12	1	8	105	5.8	2.7
DL574	8	9	1	11	477484	5409364	279.1	424	321	97	61	16	2.6	16.3	4.5%	102	9	4	17	3	61	1	14	1	9	105	6.3	1.7
DL574	9	10	1	11	477484	5409364	278.1	466	363	111	72	18	3.0	17.0	4.3%	102	10	4	18	4	70	1	17	1	10	117	6.2	1.8
DL574	10	11	1	11	477484	5409364	277.1	160	115	35	22	6	1.0	5.8	4.2%	45	4	1	6	1	22							

DL578	8	9	1	11	477883	5409388	282.8	234	174	51	33	8	1.4	9.1	4.5%	60	6	2	9	2	31	1	8	1	5	60	5.0	1.3
DL578	9	10	1	11	477883	5409388	281.8	176	131	37	24	6	1.0	6.5	4.3%	45	4	2	6	1	24	1	6	1	4	46	4.8	1.3
DL578	10	11	1	11	477883	5409388	280.8	145	106	31	20	5	0.8	5.4	4.3%	39	4	1	5	1	19	1	5	1	3	35	4.9	1.3
DL579	5	6	1	20	477876	5409130	297.6	257	46	12	7	2	0.4	2.2	1.0%	211	1	1	2	1	10	0	2	0	1	15	4.9	1.7
DL579	6	7	1	20	477876	5409130	296.6	564	71	21	14	4	0.4	2.5	0.5%	493	1	1	2	0	29	0	3	0	1	12	4.8	1.4
DL579	7	8	1	20	477876	5409130	295.6	274	65	19	13	4	0.4	2.3	1.0%	209	1	1	2	0	25	0	2	0	1	11	5.1	1.7
DL579	8	9	1	20	477876	5409130	294.6	165	65	19	12	3	0.6	3.3	2.3%	100	2	1	3	1	16	0	3	0	2	19	4.9	1.7
DL579	9	10	1	20	477876	5409130	293.6	150	53	15	10	3	0.4	2.6	2.0%	97	2	1	2	1	14	0	2	0	2	14	5.4	1.7
DL579	10	11	1	20	477876	5409130	292.6	236	103	30	20	6	0.7	4.0	2.0%	133	2	1	4	1	34	0	4	0	2	23	5.9	2.0
DL579	11	12	1	20	477876	5409130	291.6	272	185	51	32	8	1.4	8.7	3.7%	88	5	2	8	2	40	1	7	1	5	63	6.5	1.8
DL579	12	13	1	20	477876	5409130	290.6	128	69	22	14	4	0.5	3.0	2.7%	59	2	1	3	1	20	0	3	0	2	16	6.6	1.9
DL579	13	14	1	20	477876	5409130	289.6	112	82	22	14	3	0.6	4.0	4.1%	29	3	1	4	1	15	0	3	0	3	31	7.5	2.7
DL579	14	15	1	20	477876	5409130	288.6	128	100	24	15	4	0.8	5.1	4.6%	28	4	1	4	1	15	1	4	1	3	42	7.1	2.5
DL579	15	16	1	20	477876	5409130	287.6	129	75	23	15	4	0.6	3.5	3.1%	54	2	1	3	1	15	0	3	0	2	23	7.9	2.1
DL579	16	17	1	20	477876	5409130	286.6	130	81	24	15	4	0.7	4.2	3.7%	49	3	1	4	1	15	0	4	0	3	26	8.9	2.1
DL579	17	18	1	20	477876	5409130	285.6	98	70	22	14	4	0.6	3.6	4.4%	28	2	1	3	1	14	0	3	0	2	20	8.8	2.0
DL579	18	19	1	20	477876	5409130	284.6	248	181	59	38	10	1.4	9.1	4.2%	67	5	2	8	2	36	1	9	1	5	53	8.6	2.0
DL579	19	20	1	20	477876	5409130	283.6	744	524	200	139	35	3.9	22.4	3.5%	220	11	7	25	4	133	1	30	2	10	100	10.0	2.2
DL579	20	21	1	20	477876	5409130	282.6	1015	804	217	138	33	6.2	40.3	4.6%	211	26	8	36	9	159	4	30	4	23	290	10.2	2.5
DL580	2	3	1	14	478035	5409160	292.9	143	89	23	14	3	0.7	4.5	3.6%	54	3	1	4	1	15	1	3	0	3	35	14.4	2.9
DL580	3	4	1	14	478035	5409160	291.9	113	60	16	10	2	0.4	3.3	3.3%	53	2	1	2	1	11	0	2	0	2	23	15.2	2.9
DL580	4	5	1	14	478035	5409160	290.9	565	161	43	27	6	1.3	8.5	1.7%	404	6	1	7	2	27	1	6	1	5	62	13.7	2.8
DL580	5	6	1	14	478035	5409160	289.9	1200	364	129	88	22	2.8	17.2	1.7%	837	9	5	18	3	70	1	20	1	8	98	10.4	2.5
DL580	6	7	1	14	478035	5409160	288.9	1058	496	183	125	30	4.1	24.3	2.7%	563	13	8	26	5	90	2	29	2	12	127	7.8	2.1
DL580	7	8	1	14	478035	5409160	287.9	826	493	185	127	30	4.1	24.1	3.4%	333	13	8	26	5	92	2	29	2	12	120	7.9	2.1
DL580	8	9	1	14	478035	5409160	286.9	240	177	58	38	9	1.5	9.2	4.4%	64	5	2	9	2	31	1	9	1	5	54	5.6	1.5
DL580	9	10	1	14	478035	5409160	285.9	171	127	39	25	6	1.0	6.7	4.5%	44	4	2	6	1	22	1	6	1	4	42	5.2	1.4
DL580	10	11	1	14	478035	5409160	284.9	203	152	45	29	7	1.2	7.9	4.5%	51	5	2	7	2	27	1	7	1	5	52	6.0	1.7
DL580	11	12	1	14	478035	5409160	283.9	220	162	50	32	8	1.3	8.4	4.4%	58	5	2	8	2	29	1	8	1	5	53	7.2	1.9
DL580	12	13	1	14	478035	5409160	282.9	245	173	57	37	9	1.4	8.9	4.2%	73	5	2	8	2	33	1	8	1	5	51	9.8	2.6
DL580	13	14	1	14	478035	5409160	281.9	229	167	50	32	8	1.3	8.8	4.4%	62	5	2	8	2	29	1	8	1	5	57	7.6	2.3
DL581	2	3	1	10	478069	5409341	293.5	272	124	40	26	6	1.0	6.5	2.8%	148	4	2	6	1	25	0	6	0	4	36	8.3	2.4
DL581	3	4	1	10	478069	5409341	292.5	543	446	157	106	27	3.3	20.0	4.3%	97	11	6	21	4	95	1	22	2	9	117	10.4	2.3
DL581	4	5	1	10	478069	5409341	291.5	566	486	144	93	23	3.7	24.3	5.0%	81	16	6	22	5	84	2	21	2	14	169	9.8	2.2
DL581	5	6	1	10	478069	5409341	290.5	210	137	45	29	7	1.2	7.7	4.2%	75	5	2	7	2	24	1	7	1	4	39	6.8	2.5
DL581	6	7	1	10	478069	5409341	289.5	184	120	39	24	6	1.2	7.4	4.7%	64	4	2	7	1	19	1	6	1	4	37	6.9	2.1
DL581	7	8	1	10	478069	5409341	288.5	206	144	45	29	6	1.3	8.7	4.9%	62	5	2	8	2	21	1	7	1	4	47	7.1	1.9
DL581	8	9	1	10	478069	5409341	287.5	155	115	35	22	5	0.9	6.2	4.6%	40	4	1	5	1	19	1	5	1	3	39	5.2	1.4
DL581	9	10	1	10	478069	5409341	286.5	159	117	35	23	5	1.0	6.3	4.6%	43	4	1	6	1	19	1	6	1	4	40	5.0	1.4
DL582	3	4	1	14	478198	5409332	296.4	336	141	51	35	10	1.0	5.4	1.9%	195	3	2	6	1	42	0	8	0	2	25	6.0	1.6
DL582	4	5	1	14	478198	5409332	295.4	553	258	51	28	7	1.8	14.1	2.9%	295	12	2	8	4	32	2	7	2	13	127	12.3	2.4
DL582	5	6	1	14	478198	5409332	294.4	527	198	47	28	7	1.4	10.1	2.2%	329	8	2	7	2	32	1	6	1	8	83	10.4	2.1
DL582	6	7	1	14	478198	5409332	293.4	309	96	28	18	5	0.7	4.9	1.8%	213	3	1	4	1	18	1	4	1	3	31	10.3	2.5
DL582	7	8	1	14	478198	5409332	292.4	267	86	28	18	5	0.7	4.7	2.0%	181	3	1	4	1	16	0	5	0	3	25	9.6	3.2
DL582	8	9	1	14	478198	5409332	291.4	235	100	35	23	6	0.9	5.4	2.7%	135	3	2	5	1	18	0	5	0	3	27	10.3	2.6
DL582	9	10	1	14	478198	5409332	290.4	246	122	42	28	7	1.1	6.9	3.3%	123	4	2	7	1	20	1	7	1	4	34	9.7	2.5
DL582	10	11	1	14	478198	5409332	289.4	274	195	64	42	10	1.6	10.3	4.3%	78	6	2	10	2	32	1	9	1	5	62	8.1	2.3
DL582	11	12	1	14	478198	5409332	288.4	314	244	79	51	12	2.2	13.5	5.0%	70	7	3	13	3	38	1	12	1	6	80	7.0	1.9
DL582	12	13	1	14	478198	5409332	287.4	380	313	101	67	15	2.7	16.5	5.1%													

DL589	5	6	1	19	478744	5409071	296.6	289	156	55	36	8	1.6	9.3	3.8%	133	5	3	9	2	24	1	10	1	5	41	5.6	2.0
DL589	6	7	1	19	478744	5409071	295.6	725	532	195	134	32	4.5	24.8	4.0%	192	13	9	30	5	104	1	29	2	10	133	5.8	1.9
DL589	7	8	1	19	478744	5409071	294.6	1431	1173	501	358	85	9.3	48.3	4.0%	258	21	23	66	8	245	2	78	3	16	211	7.1	2.1
DL589	8	9	1	19	478744	5409071	293.6	1607	1384	561	398	92	11.4	59.5	4.4%	223	27	27	80	10	286	3	86	4	20	281	7.6	2.2
DL589	9	10	1	19	478744	5409071	292.6	1782	1595	621	437	99	13.5	70.7	4.7%	187	33	30	94	13	326	4	95	5	25	351	8.2	2.2
DL589	10	11	1	19	478744	5409071	291.6	2072	1915	625	419	96	16.8	93.6	5.3%	157	50	31	112	18	341	5	94	6	34	598	6.7	2.0
DL589	11	12	1	19	478744	5409071	290.6	2362	2235	630	401	92	20.2	116.5	5.8%	127	66	33	130	24	357	7	94	8	43	845	5.2	1.8
DL589	12	13	1	19	478744	5409071	289.6	1450	1380	350	219	50	11.5	68.6	5.5%	70	41	17	74	14	216	4	50	5	27	580	4.2	1.2
DL589	13	14	1	19	478744	5409071	288.6	401	350	91	59	14	2.6	15.3	4.5%	51	9	4	17	3	61	1	13	1	7	141	5.1	1.2
DL589	14	15	1	19	478744	5409071	287.6	335	277	75	49	12	2.1	12.5	4.4%	57	8	3	14	3	49	1	11	1	6	106	6.5	1.3
DL589	15	16	1	19	478744	5409071	286.6	269	205	60	39	10	1.6	9.8	4.2%	64	6	2	10	2	37	1	9	1	6	71	7.9	1.4
DL589	16	17	1	19	478744	5409071	285.6	263	203	56	36	9	1.6	10.2	4.5%	60	7	2	10	2	33	1	8	1	6	76	7.2	1.4
DL589	17	18	1	19	478744	5409071	284.6	257	201	53	33	8	1.6	10.6	4.7%	56	7	2	9	2	29	1	8	1	7	82	6.4	1.4
DL590	2	3	1	6	478692	5408912	295.5	414	352	99	64	14	2.9	17.7	5.0%	61	11	5	18	4	54	1	14	2	9	135	7.2	1.6
DL590	3	4	1	6	478692	5408912	294.5	455	366	111	73	17	3.1	17.9	4.6%	89	11	5	20	4	61	1	17	1	8	127	7.1	1.6
DL590	4	5	1	6	478692	5408912	293.5	189	136	42	28	7	1.1	6.9	4.3%	53	4	2	7	1	23	1	6	1	4	45	4.7	1.3
DL591	4	5	1	15	479008	5408853	305.7	106	82	24	15	4	0.6	3.7	4.0%	24	2	1	4	1	23	0	3	0	2	23	8.6	1.7
DL591	5	6	1	15	479008	5408853	304.7	159	114	35	24	7	0.6	2.9	2.2%	45	2	1	4	1	49	0	4	0	1	18	7.2	1.6
DL591	6	7	1	15	479008	5408853	303.7	213	91	28	19	6	0.5	2.7	1.5%	122	1	1	3	1	38	0	4	0	1	13	6.1	1.9
DL591	7	8	1	15	479008	5408853	302.7	282	89	26	16	5	0.6	3.6	1.5%	193	2	1	3	1	36	0	3	0	2	15	6.2	2.3
DL591	9	10	1	15	479008	5408853	300.7	111	73	23	14	4	0.6	3.9	4.1%	37	2	1	4	1	15	0	4	0	3	21	6.5	1.7
DL591	10	11	1	15	479008	5408853	299.7	342	187	58	37	9	1.7	10.1	3.4%	155	6	3	11	2	32	1	9	1	5	60	6.4	1.8
DL591	11	12	1	15	479008	5408853	298.7	456	389	117	76	17	3.5	20.6	5.3%	67	12	6	22	4	59	1	18	2	9	138	6.7	1.6
DL591	12	13	1	15	479008	5408853	297.7	632	454	141	91	20	4.2	24.6	4.5%	177	14	7	26	5	70	2	21	2	11	156	7.1	1.7
DL591	13	14	1	15	479008	5408853	296.7	304	251	79	52	12	2.2	12.9	5.0%	53	8	4	14	3	40	1	12	1	6	85	4.3	1.2
DL591	14	15	1	15	479008	5408853	295.7	196	154	47	31	7	1.3	8.0	4.7%	42	5	2	8	2	25	1	7	1	4	52	4.1	1.1
DL592	3	4	1	11	478924	5408589	295.9	400	334	114	77	17	3.1	16.6	4.9%	66	8	7	21	3	58	1	18	1	5	99	3.5	1.1
DL592	4	5	1	11	478924	5408589	294.9	247	181	62	42	10	1.6	8.4	4.1%	66	4	3	11	2	35	0	10	1	3	50	3.5	1.1
DL592	5	6	1	11	478924	5408589	293.9	368	291	98	67	15	2.5	13.0	4.2%	77	7	5	16	3	56	1	15	1	5	85	3.8	1.3
DL592	6	7	1	11	478924	5408589	292.9	252	177	55	36	9	1.5	9.0	4.2%	75	5	3	10	2	31	1	8	1	4	58	10.3	2.4
DL592	8	9	1	11	478924	5408589	290.9	267	177	57	37	9	1.6	9.0	3.9%	90	5	2	9	2	34	1	9	1	5	51	6.0	1.7
DL592	9	10	1	11	478924	5408589	289.9	834	619	205	138	34	4.9	28.8	4.0%	216	17	7	30	6	127	2	28	3	14	178	9.1	2.1
DL592	10	11	1	11	478924	5408589	288.9	412	314	95	62	15	2.6	15.6	4.4%	98	10	4	16	3	59	1	14	1	9	102	5.6	1.5
DL592	11	12	1	11	478924	5408589	287.9	238	182	51	33	8	1.5	9.5	4.6%	56	6	2	9	2	32	1	7	1	6	64	4.6	1.2
DL593	1	2	1	7	479030	5408273	293.5	246	177	57	37	9	1.5	9.1	4.3%	68	6	2	9	2	32	1	8	1	5	54	5.2	1.3
DL593	2	3	1	7	479030	5408273	292.5	321	205	74	50	13	1.6	9.5	3.5%	116	5	3	10	2	44	1	11	1	5	50	4.8	1.1
DL594	1	2	1	4	478827	5408325	290.4	200	110	39	26	6	1.0	5.8	3.4%	90	3	2	6	1	20	0	6	1	3	28	6.4	1.9
DL595	1	2	1	4	478850	5408367	278.2	160	118	37	24	6	1.0	5.9	4.3%	41	4	2	6	1	23	1	6	1	3	36	4.7	1.2
DL595	2	3	1	4	478850	5408367	277.2	142	97	30	20	5	0.8	5.2	4.2%	45	3	1	5	1	17	0	5	0	3	31	3.9	1.0
DL596	4	5	1	15	478706	5407221	281.6	231	182	62	41	10	1.5	9.8	4.9%	49	6	2	9	2	35	1	9	1	5	50	6.5	1.6
DL596	6	7	1	15	478706	5407221	281.6	180	133	44	29	7	1.1	6.8	4.4%	47	4	2	7	1	26	1	7	1	4	36	6.1	1.4
DL596	8	9	1	15	478706	5407221	284.6	191	144	46	30	7	1.2	7.7	4.6%	47	5	2	7	2	24	1	7	1	5	46	6.0	1.5
DL596	10	11	1	15	478706	5407221	286.6	154	112	34	22	6	0.9	5.6	4.2%	42	4	1	6	1	21	1	6	1	4	35	5.7	1.3
DL596	14	15	1	15	478706	5407221	286.7	174	127	38	24	6	1.0	6.9	4.6%	47	5	1	6	1	20	1	6	1	4	43	5.2	1.3
DL597	4	5	1	14	479101	5406994	219.1	258	187	53	34	9	1.4	8.7	3.9%	71	5	1	9	2	38	1	7	1	5	66	14.8	4.5
DL597	6	7	1	14	479101	5406994	217.1	174	116	38	25	7	0.8	4.9	3.3%	58	3	1	5	1	27	1	5	0	3	33	11.0	3.9
DL597	8	9	1	14	479101	5406994	215.1	243	159	53	35	9	1.1	6.7	3.2%	84	4	2	7	1	36	1	8	1	4	44	15.5	3.6
DL597	10	11	1	14	479101	5406994	213.1	236	155	52	35	9	1.1	6.6	3.3%	80	4	1	7	1	37	1	7	1	4	41	13.6	4.0
DL597	12	13	1	14</																								

RM016	8	9	1	10	482627	5408013	270.0	399	96	33	21	6	0.8	5.2	1.5%	303	3	1	4	1	19	1	5	1	4	24	3.7	1.0
RM016	9	10	1	10	482627	5408013	269.0	1198	528	229	156	49	3.7	20.3	2.0%	669	11	8	21	4	125	2	33	2	12	81	3.0	0.9
RM018	7	8	1	10	482646	5408117	272.3	56	18	6	4	1	0.1	0.8	1.6%	37	1	0	1	0	5	0	1	0	1	5	6.2	2.2
RM018	8	9	1	10	482646	5408117	271.3	1914	84	32	20	6	0.8	4.8	0.3%	1830	3	1	4	1	17	0	5	0	3	17	4.6	1.4
RM018	9	10	1	10	482646	5408117	270.3	526	114	42	27	7	1.1	6.4	1.4%	412	4	2	6	1	23	1	7	1	5	24	2.8	0.8
RM025	6	7	1	10	482654	5407853	274.7	247	55	20	13	4	0.4	2.7	1.3%	192	2	1	3	1	13	0	3	0	2	12	5.2	2.3
RM025	7	8	1	10	482654	5407853	273.7	239	79	27	17	5	0.7	3.9	1.9%	160	2	1	4	1	17	0	4	0	3	19	7.2	2.1
RM025	8	9	1	10	482654	5407853	272.7	844	117	46	30	8	1.1	6.3	0.9%	727	4	2	6	1	23	1	7	1	4	22	4.7	1.6
RM025	9	10	1	10	482654	5407853	271.7	815	470	181	122	31	4.0	22.8	3.3%	345	13	7	25	4	93	2	29	2	14	100	7.2	2.0
RM030	6	7	1	9	482742	5408179	268.7	1214	144	51	34	10	1.1	6.5	0.6%	1070	4	2	7	1	35	1	8	1	4	31	3.5	1.0
RM030	7	8	1	9	482742	5408179	267.7	1006	389	173	119	34	3.1	16.8	2.0%	617	8	7	19	3	83	1	28	1	9	57	3.1	0.9
RM030	8	9	1	9	482742	5408179	266.7	797	634	294	204	58	5.1	27.1	4.0%	163	13	11	31	5	130	2	48	2	15	82	2.7	0.7
RM032	5	6	1	7	482741	5408064	272.4	809	744	287	192	55	5.9	33.4	4.9%	66	17	11	35	6	182	3	46	3	18	137	1.1	0.3
RM032	6	7	1	7	482741	5408064	271.4	1619	1488	573	384	111	11.9	66.8	4.9%	131	34	22	70	13	365	5	91	6	36	273	2.3	0.6
RM039	6	7	1	9	482672	5407695	273.8	112	21	8	5	1	0.2	0.9	1.0%	91	1	0	1	0	5	0	1	0	1	4	8.8	3.3
RM039	7	8	1	9	482672	5407695	272.8	623	35	14	9	3	0.3	1.7	0.3%	588	1	1	2	0	8	0	2	0	1	6	6.4	2.3
RM039	8	9	1	9	482672	5407695	271.8	141	38	14	10	3	0.3	1.7	1.4%	103	1	1	2	0	9	0	2	0	1	8	9.2	3.3
RM044	8	9	1	12	482499	5407834	276.6	188	52	18	12	3	0.5	2.9	1.8%	136	2	1	3	1	9	0	3	0	2	14	7.1	2.2
RM044	10	11	1	12	482499	5407834	274.6	341	165	57	37	10	1.5	9.1	3.1%	176	6	3	8	2	29	1	10	1	6	43	7.4	2.2
RM044	11	12	1	12	482499	5407834	273.6	252	170	60	38	10	1.8	11.0	5.1%	82	6	3	10	2	25	1	10	1	7	43	4.9	1.3
RM049	7	8	1	12	482533	5408097	268.3	179	68	22	14	4	0.5	3.1	2.0%	111	2	1	3	1	15	0	3	0	2	18	5.3	1.6
RM049	8	9	1	12	482533	5408097	267.3	434	306	103	68	19	2.2	13.0	3.5%	128	8	4	14	3	70	1	14	1	8	81	4.7	1.1
RM049	9	10	1	12	482533	5408097	266.3	689	544	184	122	35	3.9	22.8	3.9%	145	14	6	24	5	125	2	25	2	13	144	4.0	0.7
RM049	10	11	1	12	482533	5408097	265.3	372	259	86	57	16	1.9	11.2	3.5%	113	8	3	11	2	60	1	12	1	7	67	6.5	1.5
RM049	11	12	1	12	482533	5408097	264.3	356	268	89	58	16	2.0	12.4	4.0%	88	7	3	12	3	58	1	13	1	7	73	5.3	1.2
RM051	5	6	1	7	482661	5407580	274.5	2070	1074	521	364	111	7.5	38.0	2.2%	996	16	17	47	6	254	2	79	2	15	114	6.3	1.7
RM051	6	7	1	7	482661	5407580	273.5	1149	1029	455	314	97	7.4	36.8	3.8%	120	19	14	46	7	252	3	66	3	19	146	8.3	2.3
RM052	3	4	1	10	482730	5407573	272.0	43	34	13	9	3	0.3	1.5	4.1%	9	1	0	2	0	8	0	2	0	1	7	5.7	1.6
RM052	6	7	1	10	482730	5407573	269.0	94	41	15	10	3	0.4	2.3	2.8%	53	1	1	2	0	7	0	3	0	1	9	7.3	3.5
RM052	8	9	1	10	482730	5407573	267.0	180	73	29	19	5	0.7	4.1	2.6%	108	2	1	4	1	13	0	4	0	2	16	7.0	2.8
RM052	9	10	1	10	482730	5407573	266.0	322	112	38	24	7	1.1	6.4	2.3%	210	4	1	6	1	19	1	6	1	4	30	6.0	2.4
RM053	3	4	1	6	482737	5407628	271.2	61	23	8	5	1	0.2	1.3	2.5%	37	1	0	1	0	4	0	1	0	1	7	11.5	3.1
RM053	4	5	1	6	482737	5407628	270.2	147	38	13	9	2	0.3	1.8	1.5%	109	1	0	2	0	8	0	2	0	1	9	10.0	2.8
RM053	5	6	1	6	482737	5407628	269.2	1104	473	221	154	46	3.4	17.4	1.9%	630	8	7	21	3	111	1	34	1	8	58	6.5	1.7
RM054	1	2	1	2	482745	5407678	273.0	48	23	8	5	2	0.2	1.1	2.8%	25	1	0	1	0	5	0	1	0	1	5	12.3	4.1
RM055	3	4	1	4	482751	5407734	270.9	970	824	309	210	61	5.7	32.7	4.0%	146	18	10	35	7	205	3	42	3	19	173	4.0	1.1
RM056	2	3	1	3	482765	5407821	273.5	360	238	88	58	17	2.0	11.7	3.8%	122	6	3	12	2	52	1	13	1	6	53	6.1	1.8
RM058	7	8	1	11	482770	5407514	267.2	106	39	13	9	2	0.3	1.9	2.1%	67	1	1	2	0	9	0	2	0	1	10	11.3	3.8
RM058	8	9	1	11	482770	5407514	266.2	214	35	12	8	2	0.3	1.7	0.9%	178	1	0	2	0	7	0	2	0	1	9	8.1	2.9
RM058	9	10	1	11	482770	5407514	265.2	157	36	13	9	2	0.3	1.7	1.3%	121	1	0	2	0	7	0	2	0	1	9	9.5	2.7
RM058	10	11	1	11	482770	5407514	264.2	178	41	14	10	3	0.3	1.9	1.3%	136	1	0	2	0	9	0	2	0	1	10	8.2	2.2
RM059	5	6	1	11	482826	5407465	268.8	113	87	31	21	6	0.6	3.4	3.5%	26	2	1	4	1	23	0	4	0	2	19	20.1	2.7
RM059	7	8	1	11	482826	5407465	266.8	56	42	14	10	3	0.3	1.9	3.9%	15	1	1	2	0	10	0	2	0	1	9	9.9	2.0
RM059	9	10	1	11	482826	5407465	264.8	170	41	14	9	3	0.4	2.0	1.4%	129	1	1	2	0	9	0	2	0	1	10	8.1	2.2
RM061	8	9	1	12	482754	5407429	266.1	42	29	10	7	1	0.2	1.5	4.1%	14	1	0	1	0	6	0	2	0	1	7	7.2	2.4
RM061	9	10	1	12	482754	5407429	265.1	50	33	11	7	2	0.3	1.8	4.2%	17	1	0	2	0	6	0	2	0	1	9	6.2	2.4
RM061	10	11	1	12	482754	5407429	264.1	156	36	12	8	2	0.3	1.8	1.3%	120	1	0	2	0	7	0	2	0	1	9	5.9	2.3
RM061	11	12	1	12	482754	5407429	263.1	107	41	15	10	2	0.4	2.4	2.6%	66	1	1	2	0	7	0	2	0	1	10	6.5	2.2
RM073	4	5	1	6	482683	5407301	268.7	228	61	21	14	4	0.5	2.8	1.4%	167	2	1	3	1	14							

RM167	13	14	1	26	480960	5405967	202.6	499	322	113	77	21	2.0	12.6	2.9%	177	8	2	12	2	88	1	15	1	8	72	23.3	5.3
RM167	14	15	1	26	480960	5405967	201.6	440	236	83	56	16	1.5	9.0	2.4%	205	5	2	9	2	67	1	12	1	5	50	11.9	4.3
RM167	15	16	1	26	480960	5405967	200.6	437	198	70	47	13	1.3	8.7	2.3%	238	6	1	8	2	46	1	10	1	6	50	15.3	4.3
RM167	17	18	1	26	480960	5405967	198.6	284	172	57	37	10	1.3	8.1	3.3%	113	5	1	7	2	36	1	8	1	5	49	18.8	4.1
RM167	19	20	1	26	480960	5405967	196.6	250	172	61	42	11	1.1	6.9	3.2%	77	4	1	7	1	42	1	9	1	4	41	11.2	3.5
RM167	21	22	1	26	480960	5405967	194.6	253	171	54	35	9	1.2	7.6	3.5%	82	4	1	7	2	38	1	7	1	4	52	12.5	3.9
RM167	22	23	1	26	480960	5405967	193.6	221	147	48	32	9	1.0	6.6	3.4%	74	4	1	6	1	34	1	7	1	4	41	12.3	3.6
RM167	23	24	1	26	480960	5405967	192.6	248	162	54	37	10	1.2	5.7	2.8%	85	5	1	7	1	37	1	8	1	4	44	12.6	3.6
RM167	24	25	1	26	480960	5405967	191.6	201	136	45	30	8	1.0	5.8	3.4%	65	4	1	6	1	30	1	6	1	4	37	11.3	3.5
RM170	5	6	1	12	480942	5405546	211.1	326	235	78	53	12	2.0	11.3	4.1%	91	6	4	12	2	46	1	12	1	5	68	6.3	2.1
RM170	6	7	1	12	480942	5405546	210.1	552	163	57	38	9	1.5	8.6	1.8%	389	4	3	9	2	27	1	9	1	4	46	5.7	2.0
RM170	7	8	1	12	480942	5405546	209.1	476	282	96	65	15	2.3	13.6	3.3%	193	7	5	15	3	53	1	14	1	6	83	6.1	1.9
RM170	8	9	1	12	480942	5405546	208.1	1125	797	352	259	60	5.5	26.7	2.9%	328	12	15	41	5	164	1	51	2	9	145	5.1	1.4
RM170	9	10	1	12	480942	5405546	207.1	571	401	155	111	26	2.9	15.8	3.3%	170	8	7	21	3	82	1	22	1	6	95	5.3	1.6
RM170	10	11	1	12	480942	5405546	206.1	699	480	181	132	30	3.8	15.4	2.7%	219	9	9	24	3	93	1	28	1	5	124	4.9	1.6
RM170	11	12	1	12	480942	5405546	205.1	420	297	102	70	17	2.4	13.1	3.7%	123	7	5	17	3	64	1	15	1	5	79	5.3	1.8
RM172	4	5	1	9	481281	5405643	213.2	196	106	37	25	8	0.6	3.4	2.1%	90	2	1	4	1	37	0	5	0	2	17	10.3	2.7
RM172	5	6	1	9	481281	5405643	212.2	581	358	122	86	28	1.8	7.2	1.5%	224	4	4	11	1	151	0	16	1	3	44	7.7	2.1
RM172	6	7	1	9	481281	5405643	211.2	520	337	128	90	25	2.0	11.3	2.6%	183	5	5	14	2	110	1	17	1	4	51	6.9	1.9
RM172	7	8	1	9	481281	5405643	210.2	604	411	153	109	28	3.2	13.4	2.8%	193	8	7	19	3	107	1	24	1	6	82	6.0	1.8
RM172	8	9	1	9	481281	5405643	209.2	373	266	93	64	16	1.9	10.6	3.3%	107	5	4	14	2	66	1	13	1	4	64	5.9	1.7
RM173	3	4	1	7	481426	5405621	215.1	106	69	23	16	4	0.5	2.7	3.0%	36	1	1	3	0	22	0	3	0	1	14	12.5	3.2
RM173	4	5	1	7	481426	5405621	214.1	90	50	16	11	3	0.4	1.7	2.4%	40	1	1	2	0	16	0	2	0	1	10	11.3	3.2
RM173	5	6	1	7	481426	5405621	213.1	797	315	134	96	25	2.1	10.9	1.6%	483	5	5	15	2	85	1	19	1	4	46	8.4	2.6
RM173	6	7	1	7	481426	5405621	212.1	1089	491	191	135	36	3.7	15.5	1.8%	598	10	8	22	3	136	1	29	1	7	84	6.7	2.0
RM174	10	11	1	18	481088	5405781	205.7	609	418	155	109	26	3.1	16.2	3.2%	190	8	7	21	3	108	1	23	1	7	84	7.4	2.4
RM174	11	12	1	18	481088	5405781	204.7	443	327	122	85	18	2.8	16.1	4.3%	115	8	6	20	3	51	1	20	1	6	89	7.1	2.2
RM174	12	13	1	18	481088	5405781	203.7	249	168	62	43	10	1.4	8.3	3.9%	81	4	3	10	2	28	1	10	1	3	44	8.7	1.9
RM174	13	14	1	18	481088	5405781	202.7	868	181	62	41	9	1.7	10.3	1.4%	687	6	3	11	2	22	1	9	1	6	58	7.0	2.1
RM174	14	15	1	18	481088	5405781	201.7	357	325	89	53	11	3.2	21.3	6.9%	31	14	5	18	5	27	2	13	2	14	137	11.6	2.9
RM174	15	16	1	18	481088	5405781	200.7	176	142	36	21	5	1.4	9.4	6.1%	33	7	2	7	2	11	1	6	1	6	63	11.7	2.6
RM174	16	17	1	18	481088	5405781	199.7	573	501	167	105	23	5.3	33.5	6.8%	72	19	9	31	7	47	3	32	3	20	164	10.3	3.7
RM174	17	18	1	18	481088	5405781	198.7	190	154	51	33	8	1.5	8.7	5.4%	36	5	2	8	2	22	1	8	1	5	48	10.7	3.0
RM175	4	5	1	10	480826	5406212	211.6	402	310	104	70	17	2.4	13.8	4.0%	92	8	3	15	3	70	1	14	1	7	85	14.5	3.2
RM175	5	6	1	10	480826	5406212	210.6	516	391	133	91	24	2.5	14.8	3.4%	125	9	3	18	3	101	1	18	1	7	97	14.3	3.1
RM175	6	7	1	10	480826	5406212	209.6	2499	1405	666	503	142	3.9	17.2	0.8%	1093	8	10	36	3	509	1	69	1	5	97	15.0	3.2
RM175	7	8	1	10	480826	5406212	208.6	3865	2114	971	742	206	4.2	18.7	0.6%	1750	8	12	49	3	834	1	87	1	4	144	13.0	3.5
RM175	8	9	1	10	480826	5406212	207.6	893	534	216	161	44	1.8	9.2	1.2%	359	5	4	17	2	190	1	22	1	4	74	11.5	3.1
RM175	9	10	1	10	480826	5406212	206.6	436	281	100	72	19	1.4	7.8	2.1%	155	4	2	11	2	80	1	12	1	4	66	11.4	3.6
RM176	4	5	1	9	481630	5405806	211.7	384	172	65	47	12	0.9	5.3	1.6%	212	3	2	6	1	52	0	8	0	2	32	7.2	2.1
RM176	5	6	1	9	481630	5405806	210.7	695	229	94	69	17	1.3	7.2	1.2%	467	4	3	10	1	62	0	12	0	3	38	6.1	1.8
RM176	6	7	1	9	481630	5405806	209.7	607	269	111	80	20	1.5	9.2	1.8%	338	4	4	11	2	74	0	14	1	4	45	7.1	2.0
RM176	7	8	1	9	481630	5405806	208.7	513	360	131	92	23	2.5	14.2	3.3%	152	8	5	18	3	97	1	17	1	6	73	6.9	1.7
RM176	8	9	1	9	481630	5405806	207.7	634	434	159	111	28	3.1	17.2	3.2%	200	8	7	21	3	118	1	22	1	7	87	6.6	1.8
RM182	8	9	1	10	482974	5407432	269.5	1565	288	101	70	19	2.1	9.9	0.8%	1278	7	4	11	2	68	1	15	1	7	72	2.7	0.8
RM182	9	10	1	10	482974	5407432	268.5	2325	642	263	187	53	4.3	20.0	1.0%	1683	14	9	23	4	150	2	39	2	14	121	4.3	1.2
RM183	4	5	1	6	482333	5407215	280.3	889	470	153	104	25	4.3	20.1	2.7%	419	16	7	24	5	79	2	27	2	13	142	4.5	1.3
RM183	5	6	1	6	482333	5407215	279.3	1778	940	307	208	51	8.5	40.3	2.7%	838	32	13	49	9	157	4	5					

RM217	17	18	1	23	480557	5407869	254.9	156	117	35	22	5	0.9	6.0	4.4%	39	4	1	6	1	21	1	5	1	4	39	6.6	1.8	
RM217	18	19	1	23	480557	5407869	253.9	212	161	46	29	8	1.3	8.0	4.4%	51	5	2	8	2	30	1	7	1	5	55	7.6	2.0	
RM217	19	20	1	23	480557	5407869	252.9	217	158	45	29	7	1.2	7.6	4.1%	59	5	2	7	2	29	1	7	1	5	55	6.9	1.7	
RM217	20	21	1	23	480557	5407869	251.9	257	183	56	37	9	1.5	9.4	4.2%	74	6	2	9	2	35	1	8	1	5	58	6.8	1.8	
RM217	21	22	1	23	480557	5407869	250.9	410	355	55	25	6	2.4	20.8	5.7%	55	20	2	10	6	23	4	7	3	21	205	6.1	1.8	
RM217	22	23	1	23	480557	5407869	249.9	251	195	52	32	8	1.6	10.2	4.7%	55	8	2	8	2	30	1	7	1	8	76	7.2	2.2	
RM218	3	4	1	9	480767	5407709	274.7	179	140	45	30	8	1.0	6.0	3.9%	39	4	2	6	1	31	1	6	1	4	40	7.2	2.1	
RM218	4	5	1	9	480767	5407709	273.7	311	253	81	54	14	1.9	11.9	4.4%	58	8	3	11	3	53	1	11	1	8	73	7.0	2.0	
RM218	5	6	1	9	480767	5407709	272.7	575	468	162	108	28	3.7	22.8	4.6%	107	14	6	22	5	92	2	23	2	14	128	8.0	2.5	
RM218	6	7	1	9	480767	5407709	271.7	1266	1021	388	267	73	7.1	40.4	3.8%	245	24	13	42	8	226	3	56	3	23	236	6.8	2.1	
RM218	7	8	1	9	480767	5407709	270.7	1524	1247	554	390	108	8.7	47.3	3.7%	276	23	18	52	8	289	4	83	3	24	189	6.8	2.0	
RM218	8	9	1	9	480767	5407709	269.7	1258	1029	448	315	87	7.3	39.7	3.7%	228	20	15	43	7	238	3	67	3	20	165	7.2	2.1	
RM219	0	1	1	1	481291	5407584	261.4	1884	1510	689	485	138	10.4	55.4	3.5%	373	27	22	64	10	354	4	103	4	26	206	7.0	2.0	
RM219	1	2	1	2	481291	5407584	260.4	312	250	114	80	23	1.7	9.2	3.5%	62	4	4	11	2	59	1	17	1	4	34	1.2	0.3	
RM220	0	1	1	5	481654	5407403	243.2	923	744	333	240	57	5.5	30.1	3.9%	179	14	12	34	5	168	2	50	2	14	111	9.1	2.4	
RM220	1	2	1	5	481654	5407403	242.2	540	447	158	108	28	3.1	19.3	4.1%	92	11	5	19	4	102	2	22	2	10	113	6.8	1.5	
RM220	2	3	1	5	481654	5407403	241.2	452	388	132	89	22	2.9	18.0	4.6%	64	10	5	17	4	82	2	19	2	10	105	6.2	1.7	
RM220	3	4	1	5	481654	5407403	240.2	2347	670	227	152	39	5.2	31.1	1.5%	1677	19	8	31	6	140	3	32	3	18	184	5.9	1.6	
RM220	4	5	1	5	481654	5407403	239.2	896	630	215	144	37	5.0	29.8	3.9%	267	17	8	29	6	121	3	33	2	16	178	5.1	1.4	
RM221	1	2	1	10	481739	5407717	229.8	283	215	70	47	11	1.7	10.7	4.4%	68	6	3	10	2	44	1	10	1	6	63	10.2	2.1	
RM221	2	3	1	10	481739	5407717	228.8	385	270	86	56	14	2.2	13.4	4.1%	116	8	3	12	3	56	1	13	1	8	78	6.7	1.3	
RM221	3	4	1	10	481739	5407717	227.8	444	307	101	65	16	2.7	17.0	4.4%	137	9	4	15	3	59	1	16	1	10	87	7.4	1.5	
RM221	4	5	1	10	481739	5407717	226.8	888	748	283	194	49	6.1	34.7	4.6%	141	18	11	38	6	163	2	43	3	16	164	6.4	1.6	
RM221	5	6	1	10	481739	5407717	225.8	1165	1027	383	264	66	8.3	45.2	4.6%	138	22	15	53	8	254	3	56	3	19	211	6.4	2.4	
RM221	6	7	1	10	481739	5407717	224.8	1556	1493	266	141	33	11.9	80.1	5.9%	64	57	11	66	19	153	7	38	7	41	828	6.0	1.8	
RM221	7	8	1	10	481739	5407717	223.8	944	851	213	132	32	6.8	42.5	5.2%	93	28	8	39	9	125	3	31	4	21	368	6.5	1.6	
RM221	8	9	1	10	481739	5407717	222.8	353	303	86	56	14	2.3	13.8	4.5%	49	9	4	14	3	61	1	12	1	7	107	6.3	1.3	
RM221	9	10	1	10	481739	5407717	221.8	262	216	56	36	8	1.5	9.8	4.3%	46	6	2	10	2	43	1	8	1	5	82	6.1	1.5	
RM222	1	2	1	16	480381	5407982	280.0	666	562	159	98	20	5.3	35.5	6.1%	104	21	7	31	7	75	3	25	3	18	212	11.1	1.6	
RM222	2	3	1	16	480381	5407982	279.0	730	578	179	116	28	4.7	29.7	4.7%	152	19	7	28	6	101	3	26	3	16	190	9.9	1.2	
RM222	3	4	1	16	480381	5407982	278.0	812	624	203	135	34	4.8	28.9	4.1%	188	18	8	29	6	118	3	31	3	16	189	9.7	1.3	
RM222	4	5	1	16	480381	5407982	277.0	993	690	243	165	42	5.4	31.3	3.7%	302	17	9	34	6	144	2	37	2	16	178	8.3	1.7	
RM222	5	6	1	16	480381	5407982	276.0	957	689	232	156	39	5.5	31.8	3.9%	268	18	9	34	6	141	3	35	3	16	191	8.8	1.7	
RM222	6	7	1	16	480381	5407982	275.0	675	511	140	87	20	4.3	28.1	4.8%	163	18	6	25	6	81	3	20	3	16	195	8.5	1.6	
RM222	7	8	1	16	480381	5407982	274.0	713	566	169	109	26	4.8	29.7	4.8%	147	18	7	29	6	97	2	25	3	16	195	8.8	1.6	
RM222	8	9	1	16	480381	5407982	273.0	648	468	135	87	20	4.0	23.8	4.3%	180	15	6	24	5	83	2	20	2	12	164	8.3	1.5	
RM222	9	10	1	16	480381	5407982	272.0	515	331	92	59	14	2.8	16.6	3.8%	184	11	4	16	4	55	2	14	2	10	122	7.2	1.6	
RM222	10	11	1	16	480381	5407982	271.0	549	370	104	66	15	3.1	19.3	4.1%	179	12	4	19	4	60	2	2	16	2	11	137	7.8	1.5
RM222	11	12	1	16	480381	5407982	270.0	527	379	110	70	17	3.2	19.6	4.3%	148	13	5	19	4	62	2	16	2	11	136	7.6	1.6	
RM222	12	13	1	16	480381	5407982	269.0	331	234	61	37	9	2.0	13.6	4.7%	98	9	3	12	3	34	1	10	1	8	93	7.1	1.6	
RM222	13	14	1	16	480381	5407982	268.0	268	183	45	26	6	1.7	11.5	4.9%	86	8	2	9	2	23	1	7	1	7	77	7.0	1.7	
RM222	14	15	1	16	480381	5407982	267.0	358	243	67	41	10	2.2	13.7	4.4%	115	9	3	12	3	37	1	10	1	8	92	7.3	1.8	
RM222	15	16	1	16	480381	5407982	266.0	207	156	40	24	6	1.4	9.3	5.2%	51	6	2	8	2	22	1	6	1	6	63	8.1	1.8	
RM223	2	3	1	11	480595	5407065	240.0	149	118	37	24	5	1.1	6.7	5.2%	30	4	2	7	1	20	1	6	1	4	36	3.1	0.7	
RM223	3	4	1	11	480595	5407065	234.0	98	72	21	13	3	0.6	3.9	4.6%	26	3	1	4	1	12	0	3	0	2	23	2.7	0.7	
RM223	9	10	1	11	480595	5407065	233.0	104	77	23	14	4	0.6	4.0	4.5%	26	3	1	4	1	13	0	3	0	3	27	2.9	0.7	
RM223	10	11	1	11	480595	5407065	232.0	81	62	17	11	3	0.5	3.4	4.9%	18	2	1	3	1	9	0	3	0	2	24	2.1	0.5	
RM224	1	2	1	6	480582	5406746	224.3	75	55	16	10	2	0.5	2.9	4.4%	20													

RM229	8	9	1	13	480284	5407256	292.5	131	78	26	17	4	0.6	4.4	3.8%	53	3	1	3	1	17	0	4	0	3	20	6.6	2.1
RM229	9	10	1	13	480284	5407256	291.5	129	76	25	17	4	0.6	3.8	3.4%	53	2	1	3	1	17	0	4	0	3	20	6.4	1.5
RM229	10	11	1	13	480284	5407256	290.5	122	87	29	18	5	0.7	5.0	4.7%	36	3	1	4	1	17	0	4	0	3	24	5.1	1.8
RM229	11	12	1	13	480284	5407256	289.5	145	92	30	19	5	0.8	4.8	3.8%	53	3	1	4	1	20	0	5	1	3	24	5.7	1.8
RM230	4	5	1	10	480334	5407053	275.9	143	105	29	19	5	0.6	4.2	3.4%	37	3	1	4	1	30	0	4	0	3	31	5.5	1.1
RM230	5	6	1	10	480334	5407053	274.9	177	94	29	18	5	0.7	4.7	3.0%	83	3	1	4	1	23	0	4	0	3	26	5.6	1.2
RM230	6	7	1	10	480334	5407053	273.9	200	118	35	23	6	0.8	5.2	3.0%	82	3	1	5	1	31	1	5	1	3	33	4.9	1.0
RM230	7	8	1	10	480334	5407053	272.9	262	212	73	51	14	1.3	7.2	3.3%	50	4	2	8	1	64	1	9	1	3	45	3.5	0.8
RM230	8	9	1	10	480334	5407053	271.9	227	171	57	39	11	1.0	6.4	3.3%	56	4	2	7	1	50	1	7	1	4	39	4.2	0.9
RM230	9	10	1	10	480334	5407053	270.9	234	172	56	37	10	1.2	6.8	3.4%	62	4	2	7	1	49	1	7	1	4	40	4.3	0.9
RM231	2	3	1	9	480481	5407227	256.3	139	115	34	22	6	0.8	5.2	4.3%	23	3	1	5	1	26	0	5	0	3	36	5.3	1.2
RM231	3	4	1	9	480481	5407227	255.3	179	152	44	28	8	1.0	7.1	4.5%	28	5	1	6	2	33	1	5	1	4	50	5.0	0.9
RM231	4	5	1	9	480481	5407227	254.3	179	143	43	28	7	0.9	6.2	4.0%	36	4	1	6	1	32	1	6	1	4	44	5.1	0.9
RM231	5	6	1	9	480481	5407227	253.3	144	112	33	22	6	0.8	5.0	4.0%	32	3	1	5	1	26	1	4	0	3	34	4.8	1.0
RM231	6	7	1	9	480481	5407227	252.3	174	115	35	23	6	0.9	5.5	3.7%	60	3	1	5	1	25	1	5	1	4	34	4.1	0.6
RM232	1	2	1	11	480577	5406448	220.8	128	103	34	22	6	0.8	4.9	4.5%	25	3	1	5	1	20	1	5	0	3	29	4.1	1.1
RM232	2	3	1	11	480577	5406448	219.8	237	213	46	26	7	1.8	11.7	5.7%	23	8	2	10	3	25	1	7	1	7	103	3.0	0.8
RM232	3	4	1	11	480577	5406448	218.8	119	94	23	15	3	0.7	4.4	4.2%	26	3	1	5	1	16	1	4	1	3	36	3.2	0.7
RM232	4	5	1	11	480577	5406448	217.8	78	56	17	11	3	0.4	2.6	3.8%	22	2	1	2	1	10	0	2	0	2	19	3.0	0.7
RM232	5	6	1	11	480577	5406448	216.8	84	62	18	12	3	0.5	3.2	4.3%	23	2	1	3	1	10	0	3	0	2	21	3.1	0.7
RM232	8	9	1	11	480577	5406448	213.8	78	58	17	10	3	0.4	3.2	4.7%	20	2	1	3	1	10	0	3	0	2	20		
RM232	10	11	1	11	480577	5406448	211.8	84	62	17	11	3	0.5	3.3	4.5%	21	2	1	3	1	10	0	3	0	2	22		
RM233	1	2	1	4	480066	5407740	305.4	116	79	24	16	4	0.6	3.7	3.7%	37	2	1	3	1	18	0	3	0	2	23	6.0	1.7
RM233	2	3	1	4	480066	5407740	304.4	155	44	14	9	2	0.3	2.1	1.6%	110	1	1	2	0	12	0	2	0	1	12	6.6	2.2
RM233	3	4	1	4	480066	5407740	303.4	247	52	16	11	3	0.3	2.4	1.1%	195	1	1	2	0	13	0	2	0	2	14	6.2	1.9
RM234	1	2	1	3	480043	5406648	296.5	177	77	24	16	4	0.6	3.6	2.4%	99	2	1	3	1	18	0	3	0	2	22	5.9	1.7
RM234	2	3	1	3	480043	5406648	295.5	95	70	19	12	3	0.4	2.9	3.5%	25	2	1	2	1	19	0	2	0	2	22	4.7	1.2
RM235	1	2	1	5	480039	5406649	296.5	77	50	14	9	2	0.3	2.1	3.2%	27	1	0	2	0	14	0	1	0	2	15	6.6	1.6
RM235	2	3	1	5	480039	5406649	295.5	240	160	50	34	9	1.0	6.5	3.1%	80	4	2	6	1	42	1	6	1	5	43	5.2	1.5
RM235	3	4	1	5	480039	5406649	294.5	373	163	53	36	9	1.1	6.9	2.1%	209	4	2	6	2	40	1	6	1	5	44	5.9	1.6
RM235	4	5	1	5	480039	5406649	293.5	868	267	93	62	16	2.0	12.6	1.7%	602	8	3	12	3	60	1	12	1	8	65	6.3	1.6
RM236	0	1	1	2	480202	5406271	285.9	172	93	30	20	5	0.6	4.1	2.7%	79	3	1	4	1	23	0	5	0	3	25	8.5	2.0
RM236	1	2	1	2	480202	5406271	284.9	225	126	43	28	7	1.0	6.6	3.4%	99	4	2	6	1	24	1	6	1	4	35	5.6	1.4
RM237	1	2	1	4	479886	5406315	241.7	140	82	27	18	5	0.7	3.8	3.2%	59	2	1	4	1	18	0	4	0	2	22	7.2	2.0
RM237	2	3	1	4	479886	5406315	240.7	197	89	29	19	5	0.6	4.2	2.4%	108	2	1	4	1	20	0	4	0	3	24	7.0	1.9
RM237	3	4	1	4	479886	5406315	239.7	91	65	17	11	3	0.5	3.4	4.3%	26	2	1	3	1	10	0	3	0	2	25	2.5	0.6
RM238	1	2	1	6	479350	5406610	220.2	115	68	21	14	4	0.5	3.1	3.1%	47	2	1	3	1	15	0	3	0	2	20	6.1	1.1
RM238	2	3	1	6	479350	5406610	219.2	148	101	33	22	5	0.8	5.0	4.0%	47	3	1	5	1	19	1	5	0	3	30	6.0	1.2
RM238	3	4	1	6	479350	5406610	218.2	182	119	39	26	6	1.0	6.0	3.9%	63	4	2	6	1	21	1	6	1	4	35	6.0	1.4
RM238	4	5	1	6	479350	5406610	217.2	229	174	54	35	9	1.3	8.7	4.3%	56	5	2	8	2	32	1	8	1	5	56	5.6	1.5
RM238	5	6	1	6	479350	5406610	216.2	177	126	39	25	6	1.0	6.3	4.1%	51	4	2	6	1	22	1	5	1	4	42	5.6	1.1
RM238	8	9	1	6	479350	5406610	213.2	147	113	32	20	5	0.9	5.8	4.6%	34	4	1	5	1	20	1	5	1	4	39		
RM239	0	1	1	3	479779	5406115	219.4	134	86	30	20	5	0.7	4.0	3.5%	47	2	1	4	1	18	0	5	0	2	22	9.9	1.8
RM239	2	3	1	3	479779	5406115	217.4	155	96	31	20	5	0.8	5.2	3.8%	59	3	1	5	1	18	0	5	0	3	29	3.5	0.8
RM240	2	3	1	13	479491	5406554	224.4	153	99	30	19	5	0.7	5.0	3.7%	54	3	1	4	1	20	0	4	0	3	30	6.4	1.3
RM240	3	4	1	13	479491	5406554	223.4	325	212	64	43	11	1.4	8.1	2.9%	113	6	2	8	2	49	1	8	1	6	65	8.0	1.6
RM240	4	5	1	13	479491	5406554	222.4	122	90	28	18	5	0.7	4.1	3.9%	32	3	1	4	1	19	0	4	0	3	27	4.2	0.9
RM240	5	6	1	13	479491	5406554	221.4	194	148	44	29	7	1.0	6.2	3.7%	46	4	2	6	1	33	1	6	1	4	47	4.3	1.1
RM240	6	7	1	13	479491	5406554	220.4	134	94	28	19	5	0.7	4.5	3.8%	40	3	1	4	1	20	0	4	0	3	30	4.3	0.9
RM240	7	8	1	13	479491	5406554	219.4	189	148	43	29	7	1.1</td															

RM245	8	9	1	14	480397	5408079	272.6	2009	1530	567	383	94	13.8	76.2	4.5%	479	32	26	95	12	354	3	94	4	27	314	7.4	2.2
RM245	9	10	1	14	480397	5408079	271.6	587	440	145	97	25	3.5	19.5	3.9%	147	10	6	25	4	113	1	21	1	8	105	9.8	2.2
RM245	10	11	1	14	480397	5408079	270.6	749	572	185	122	31	4.6	27.2	4.2%	177	14	8	31	5	130	2	30	2	11	154	8.2	1.7
RM245	11	12	1	14	480397	5408079	269.6	734	553	176	115	30	4.5	25.9	4.2%	181	14	8	31	5	127	2	28	2	11	149	8.7	1.5
RM245	12	13	1	14	480397	5408079	268.6	601	454	145	94	24	4.0	22.8	4.5%	147	12	7	25	4	95	2	22	2	10	131	8.6	1.4
RM245	13	14	1	14	480397	5408079	267.6	618	462	153	101	25	4.0	23.1	4.4%	157	12	7	26	4	103	1	25	2	10	119	9.1	1.7
RM246	2	3	1	9	480521	5407767	267.1	152	100	29	18	5	0.8	5.2	3.9%	52	3	1	4	1	21	0	5	0	3	30	5.5	1.5
RM246	3	4	1	9	480521	5407767	266.1	227	165	51	33	9	1.3	8.0	4.1%	62	5	2	7	2	36	1	7	1	4	49	4.4	1.0
RM246	4	5	1	9	480521	5407767	265.1	561	417	150	101	27	3.2	18.8	3.9%	144	9	5	20	3	102	1	22	1	8	94	5.1	1.3
RM246	5	6	1	9	480521	5407767	264.1	247	197	53	31	8	1.8	12.1	5.6%	50	8	2	10	3	30	1	8	1	7	74	5.6	1.6
RM246	6	7	1	9	480521	5407767	263.1	342	204	52	30	7	1.8	12.4	4.2%	138	8	2	10	3	29	1	8	1	8	82	5.8	1.8
RM246	7	8	1	9	480521	5407767	262.1	318	176	45	27	6	1.6	10.5	3.8%	141	7	2	8	2	23	1	8	1	7	71	5.4	1.6
RM246	8	9	1	9	480521	5407767	261.1	166	118	32	20	5	1.0	6.2	4.3%	48	4	1	5	1	19	1	5	1	4	44	5.2	1.5
RM247	3	4	1	33	480536	5407676	262.6	257	218	55	32	8	1.8	12.5	5.5%	39	8	2	10	3	37	1	8	1	7	85	7.7	1.7
RM247	4	5	1	33	480536	5407676	261.6	383	334	95	58	15	3.0	18.5	5.6%	49	12	4	17	4	59	2	14	2	10	117	8.2	2.1
RM247	5	6	1	33	480536	5407676	260.6	249	204	49	29	7	1.7	11.2	5.2%	45	8	2	10	3	32	1	8	1	7	83	8.5	2.0
RM247	6	7	1	33	480536	5407676	259.6	272	223	62	38	9	1.8	11.9	5.0%	49	8	2	10	3	41	1	9	1	7	79	7.4	1.8
RM247	7	8	1	33	480536	5407676	258.6	235	184	47	28	7	1.5	9.9	4.9%	51	7	2	9	2	31	1	7	1	6	72	8.4	2.1
RM247	12	13	1	33	480536	5407676	253.6	256	221	65	40	10	2.0	12.8	5.8%	36	8	2	11	3	41	1	10	1	9	69	8.1	2.5
RM247	13	14	1	33	480536	5407676	252.6	1654	1556	658	449	120	14.0	75.2	5.4%	98	33	24	86	13	324	4	107	5	29	273	7.4	2.7
RM247	14	15	1	33	480536	5407676	251.6	1196	1101	467	322	87	9.1	49.4	4.9%	95	22	16	56	9	240	3	72	3	21	190	7.3	2.7
RM247	15	16	1	33	480536	5407676	250.6	644	472	175	118	31	3.7	22.0	4.0%	172	12	6	23	4	100	2	27	2	11	111	6.8	2.1
RM247	16	17	1	33	480536	5407676	249.6	595	437	158	106	28	3.5	20.7	4.1%	158	12	5	21	4	90	2	24	2	11	109	7.6	2.3
RM247	17	18	1	33	480536	5407676	248.6	547	403	140	93	25	3.2	19.4	4.1%	145	11	5	19	4	81	2	21	2	10	107	8.5	2.6
RM247	18	19	1	33	480536	5407676	247.6	499	368	123	81	21	2.9	18.1	4.2%	131	11	4	17	4	72	1	19	2	10	106	9.3	2.8
RM247	19	20	1	33	480536	5407676	246.6	451	334	106	69	18	2.7	16.9	4.3%	117	10	4	16	4	63	1	16	1	10	104	10.1	3.1
RM247	20	21	1	33	480536	5407676	245.6	403	299	89	56	14	2.4	15.6	4.5%	104	10	3	14	3	54	1	13	1	9	102	11.0	3.3
RM247	21	22	1	33	480536	5407676	244.6	354	265	71	44	11	2.1	14.3	4.6%	90	9	2	12	3	44	1	11	1	9	100	11.8	3.6
RM247	22	23	1	33	480536	5407676	243.6	542	436	100	60	15	3.3	21.8	4.6%	107	15	3	19	5	70	2	15	2	14	189	11.8	3.7
RM247	23	24	1	33	480536	5407676	242.6	682	544	165	110	29	3.5	22.6	3.8%	138	15	5	23	5	117	2	23	2	14	173	13.8	3.2
RM247	24	25	1	33	480536	5407676	241.6	712	558	168	110	29	3.9	24.7	4.0%	155	16	5	24	5	116	2	24	2	15	180	12.6	3.3
RM247	25	26	1	33	480536	5407676	240.6	1175	979	304	204	52	6.5	41.2	4.1%	196	26	9	41	9	210	3	42	4	24	306	11.9	3.7
RM247	26	27	1	33	480536	5407676	239.6	906	711	226	150	39	5.0	31.6	4.0%	195	20	6	31	7	147	3	32	3	18	218	11.5	2.9
RM247	27	28	1	33	480536	5407676	238.6	948	728	249	168	44	5.0	31.6	3.9%	220	19	7	33	7	157	3	36	3	18	197	11.3	2.8
RM247	28	29	1	33	480536	5407676	237.6	793	612	211	142	37	4.3	26.9	3.9%	181	17	6	27	6	130	2	30	2	16	165	11.1	2.4
RM247	29	30	1	33	480536	5407676	236.6	679	488	175	120	31	3.5	21.3	3.7%	191	13	5	22	4	107	2	25	2	13	120	12.3	2.3
RM247	30	31	1	33	480536	5407676	235.6	803	621	214	145	37	4.5	27.5	4.0%	182	16	6	28	6	132	2	31	2	16	167	11.9	2.6
RM247	31	32	1	33	480536	5407676	234.6	987	819	294	201	52	6.0	35.7	4.2%	168	21	9	37	7	184	3	42	3	20	199	11.7	2.6
RM247	32	33	1	33	480536	5407676	233.6	986	737	279	192	50	5.3	31.1	3.7%	249	17	8	35	6	171	2	40	2	16	161	12.5	2.6
RM248	6	7	1	22	480553	5407581	250.5	443	327	93	58	15	2.6	16.9	4.4%	116	11	3	14	5	57	2	13	2	11	117	17.7	4.6
RM248	7	8	1	22	480553	5407581	250.4	489	370	103	64	17	2.9	19.1	4.5%	118	13	3	16	4	67	2	14	2	12	135	18.0	4.9
RM248	8	9	1	22	480553	5407581	250.3	534	414	114	71	19	3.2	21.2	4.6%	120	14	3	17	5	76	2	16	2	13	152	18.3	5.1
RM248	9	10	1	22	480553	5407581	250.2	482	353	100	63	16	2.7	18.1	4.3%	129	12	3	15	4	62	2	14	2	11	129	17.7	4.8
RM248	10	11	1	22	480553	5407581	249.0	430	293	86	55	14	2.3	15.0	4.0%	137	10	2	13	3	48	1	13	1	9	106	17.2	4.5
RM248	12	13	1	22	480553	5407581	249.0	207	133	39	25	7	1.0	6.5	3.6%	74	4	1	6	1	32	1	6	1	4	39	18.2	4.5
RM248	14	15	1	22	480553	5407581	247.0	233	147	43	28	8	1.0	6.4	3.2%	86	4	1	6	1	39	1	6	1	5	40	19.8	4.7
RM248	16	17	1	22	480553	5407581	245.0	206	125	37	24	6	0.9	5.9	3.3%	80	4	1	5	1	27	1	5	1	4	39	20.2	4.1
RM248	18	19	1	22																								

RM256	5	6	1	17	481801	5408277	213.1	105	72	23	16	4	0.5	2.8	3.1%	33	2	1	3	1	21	0	4	0	2	16	4.1	0.9
RM256	6	7	1	17	481801	5408277	212.1	89	66	19	12	3	0.5	3.3	4.3%	23	2	1	4	1	20	0	4	0	2	21	4.4	0.9
RM256	7	8	1	17	481801	5408277	211.1	115	82	29	20	5	0.6	3.6	3.6%	33	2	1	4	1	20	0	4	0	2	19	5.1	0.9
RM256	8	9	1	17	481801	5408277	210.1	120	89	29	19	5	0.7	4.1	4.0%	31	2	1	4	1	21	0	4	0	2	23	4.8	1.0
RM256	9	10	1	17	481801	5408277	209.1	91	65	21	14	4	0.5	3.1	4.0%	26	2	1	3	1	16	0	3	0	2	17	4.2	0.8
RM256	10	11	1	17	481801	5408277	208.1	103	72	24	16	4	0.5	3.3	3.7%	31	2	1	4	1	16	0	3	0	2	19	4.5	0.7
RM256	11	12	1	17	481801	5408277	207.1	105	71	24	16	4	0.5	3.3	3.7%	34	2	1	3	1	17	0	3	0	2	18	4.4	0.7
RM256	12	13	1	17	481801	5408277	206.1	92	62	20	13	4	0.5	2.9	3.7%	30	2	1	3	1	14	0	3	0	2	17	4.1	0.7
RM256	13	14	1	17	481801	5408277	205.1	98	68	22	15	4	0.6	3.2	3.9%	30	2	1	3	1	14	0	3	0	2	19	4.3	0.9
RM256	14	15	1	17	481801	5408277	204.1	103	71	23	15	4	0.5	3.2	3.7%	32	2	1	3	1	16	0	3	0	2	20	4.6	0.9
RM256	15	16	1	17	481801	5408277	203.1	94	65	21	14	4	0.5	3.1	3.8%	29	2	1	3	1	15	0	3	0	2	17	4.2	0.9
RM257	1	2	1	9	481792	5408412	218.6	294	146	44	27	7	1.2	7.8	3.1%	148	5	2	7	2	26	1	6	1	5	48	3.9	1.0
RM257	2	3	1	9	481792	5408412	217.6	154	124	35	21	5	1.2	7.6	5.7%	30	5	2	7	2	17	1	5	1	4	46	2.9	0.8
RM257	3	4	1	9	481792	5408412	216.6	218	194	57	35	8	2.0	11.9	6.3%	25	7	3	12	3	28	1	9	1	6	69	2.8	0.7
RM257	4	5	1	9	481792	5408412	215.6	222	176	53	35	9	1.4	8.7	4.5%	46	6	2	8	2	36	1	8	1	5	56	3.6	0.7
RM257	5	6	1	9	481792	5408412	214.6	358	315	93	59	15	2.5	16.0	5.2%	44	10	4	15	3	60	1	12	1	8	108	3.4	0.7
RM257	6	7	1	9	481792	5408412	213.6	442	406	138	93	24	3.0	18.1	4.8%	36	10	5	19	3	99	1	17	1	8	104	3.6	1.0
RM258	2	3	1	9	481783	5408568	218.3	267	232	83	56	14	1.9	11.5	5.0%	35	7	3	11	2	52	1	11	1	6	55	3.3	0.5
RM258	3	4	1	9	481783	5408568	217.3	193	174	60	40	11	1.2	7.7	4.6%	20	4	2	8	1	43	1	8	1	4	43	3.7	0.7
RM258	4	5	1	9	481783	5408568	216.3	250	225	72	48	12	1.6	9.9	4.6%	26	6	3	10	2	52	1	9	1	5	64	3.8	0.9
RM258	5	6	1	9	481783	5408568	215.3	501	475	86	47	10	3.6	24.9	5.7%	26	18	4	22	6	51	2	11	2	13	260	3.4	0.7
RM258	6	7	1	9	481783	5408568	214.3	1246	1203	201	104	23	9.0	65.0	5.9%	43	46	10	54	15	105	6	27	6	33	701	3.3	0.8
RM259	2	3	1	12	481747	5408728	214.3	127	101	25	16	4	0.7	4.9	4.4%	25	3	1	4	1	19	0	3	0	3	41	4.3	0.9
RM259	3	4	1	12	481747	5408728	213.3	142	106	31	19	5	0.9	6.1	5.0%	36	4	1	5	1	17	1	5	1	4	37	3.3	0.9
RM259	4	5	1	12	481747	5408728	212.3	232	196	44	24	6	1.7	12.2	6.0%	36	8	2	10	3	21	1	7	1	7	94	3.6	0.9
RM259	5	6	1	12	481747	5408728	211.3	332	248	56	32	7	2.2	14.8	5.1%	84	10	3	12	3	28	1	8	1	8	118	3.3	0.9
RM259	6	7	1	12	481747	5408728	210.3	261	186	51	32	8	1.5	9.9	4.4%	75	6	2	9	2	30	1	7	1	5	72	3.2	0.8
RM259	7	8	1	12	481747	5408728	209.3	242	183	49	30	8	1.5	9.8	4.6%	60	6	2	9	2	32	1	7	1	5	69	3.3	0.9
RM259	8	9	1	12	481747	5408728	208.3	241	184	50	31	8	1.5	9.8	4.7%	57	6	2	8	2	30	1	7	1	5	72	3.2	0.9
RM260	2	3	1	8	481694	5408895	217.4	165	132	35	22	5	1.0	6.5	4.6%	34	4	2	6	1	23	1	5	1	4	51	3.2	0.7
RM260	3	4	1	8	481694	5408895	216.4	129	98	27	17	4	0.7	4.7	4.2%	31	3	1	4	1	19	0	4	0	3	35	3.4	0.8
RM260	4	5	1	8	481694	5408895	215.4	128	98	29	19	5	0.7	4.7	4.2%	30	3	1	5	1	19	0	4	0	3	32	3.3	0.8
RM260	5	6	1	8	481694	5408895	214.4	150	120	33	20	5	1.0	6.3	4.9%	30	4	1	5	1	19	1	5	1	4	46	3.2	0.8
RM261	2	3	1	9	481602	5409056	220.8	89	63	21	14	4	0.5	2.9	3.8%	26	2	1	3	1	14	0	3	0	2	18	5.7	1.2
RM261	3	4	1	9	481602	5409056	219.8	223	120	43	29	7	1.0	6.3	3.3%	102	4	2	6	1	23	1	7	1	4	31	3.8	0.8
RM261	4	5	1	9	481602	5409056	218.8	286	225	82	53	13	2.2	13.9	5.6%	61	8	4	11	3	38	1	13	1	8	57	3.9	0.7
RM261	5	6	1	9	481602	5409056	217.8	182	147	50	32	8	1.3	8.6	5.4%	35	5	2	7	2	25	1	8	1	6	41	3.9	0.7
RM261	6	7	1	9	481602	5409056	216.8	248	199	70	46	13	1.5	9.5	4.5%	49	6	3	9	2	45	1	10	1	6	47	3.5	0.6
RM261	7	8	1	9	481602	5409056	215.8	684	648	270	194	52	3.7	20.5	3.5%	36	10	8	26	4	197	1	34	1	9	90	3.4	0.9
RM261	8	9	1	9	481602	5409056	214.8	588	541	219	155	42	3.3	19.2	3.8%	47	10	7	22	3	152	1	29	1	8	87	3.8	0.9
RM262	7	8	1	12	481415	5409178	214.9	147	122	41	27	7	1.0	5.8	4.6%	26	4	2	6	1	25	1	6	1	4	34	2.8	0.7
RM262	8	9	1	12	481415	5409178	213.9	277	251	77	51	12	1.8	12.1	5.0%	26	7	3	12	2	50	1	10	1	6	82	3.7	0.8
RM262	9	10	1	12	481415	5409178	212.9	139	119	41	28	7	0.9	5.3	4.4%	21	3	1	5	1	28	0	6	0	3	29	2.8	0.7
RM262	10	11	1	12	481415	5409178	211.9	226	192	48	30	7	1.4	9.2	4.7%	34	6	2	8	2	33	1	6	1	5	81	3.2	0.8
RM263	3	4	1	7	481274	5409263	222.0	372	345	109	73	19	2.4	14.9	4.6%	26	9	4	14	3	74	1	15	1	8	108	3.6	0.7
RM263	4	5	1	7	481274	5409263	221.0	379	318	109	74	19	2.2	13.4	4.1%	61	8	4	14	3	75	1	15	1	7	81	3.3	0.7
RM264	5	6	1	13	481163	5409412	220.8	942	772	233	152	39	6.0	37.0	4.6%	170	24	8	34	8	147	4	32	4	23	254	7.9	1.5
RM264	6	7	1	13	481163	5409412	219.8	752	619	200	134	33	4.7	28.9	4.5%	133	19	6	28	1	18	3	28	1	18	189	8.9	2.4
RM264	7	8	1	13	481163	5409412	218.8	802	690	217	143	35	5.4	33.3	4.8%	111	22	7	33	7	129	3	31</					

RM271	12	13	1	13	480217	5408185	269.0	212	157	49	30	7	1.4	9.6	5.2%	55	6	2	8	2	26	1	6	1	6	50	4.3	1.0
RM272	2	3	1	14	480378	5408203	276.5	90	66	22	14	3	0.6	3.9	5.0%	25	2	1	3	1	12	0	3	0	2	19	5.9	1.3
RM272	4	5	1	14	480378	5408203	274.5	383	213	80	53	14	1.8	11.0	3.3%	171	6	3	11	2	43	1	11	1	6	49	5.3	1.4
RM272	5	6	1	14	480378	5408203	273.5	554	395	153	106	27	3.2	18.0	3.8%	159	9	7	20	3	87	1	24	1	9	79	5.0	1.3
RM272	6	7	1	14	480378	5408203	272.5	1970	1715	656	453	118	13.1	72.6	4.4%	253	37	28	89	14	403	5	86	5	32	363	3.7	1.3
RM272	7	8	1	14	480378	5408203	271.5	1639	1455	533	358	91	12.2	71.8	5.1%	184	36	24	81	13	307	4	73	5	31	348	4.4	1.3
RM272	8	9	1	14	480378	5408203	270.5	993	915	301	195	48	8.0	48.8	5.7%	78	26	14	52	9	175	3	41	3	20	270	4.0	1.0
RM272	9	10	1	14	480378	5408203	269.5	1184	1120	369	244	60	9.5	55.5	5.5%	64	29	17	63	11	230	3	51	4	22	321	3.8	1.1
RM272	10	11	1	14	480378	5408203	268.5	5479	5397	1005	579	126	38.1	262.8	5.5%	82	161	51	269	59	760	15	128	19	99	2832	3.1	1.8
RM272	11	12	1	14	480378	5408203	267.5	3476	3390	676	398	87	24.2	167.0	5.5%	87	101	34	169	37	518	11	91	13	76	1664	3.2	1.5
RM272	12	13	1	14	480378	5408203	266.5	756	726	131	74	16	5.5	35.8	5.5%	30	25	7	36	9	90	3	18	3	18	386	2.8	0.9
RM273	4	5	1	16	480462	5408346	275.9	258	224	49	29	7	1.7	11.2	5.0%	34	7	2	11	3	34	1	7	1	6	103	6.0	2.6
RM273	5	6	1	16	480462	5408346	274.9	662	288	70	43	10	2.3	14.5	2.5%	375	10	3	14	3	48	2	10	1	10	117	4.8	1.2
RM273	6	7	1	16	480462	5408346	273.9	1715	1333	591	416	114	8.8	51.2	3.5%	382	24	21	56	9	313	3	89	3	27	196	4.0	1.2
RM273	7	8	1	16	480462	5408346	272.9	1147	1059	427	295	78	7.1	46.4	4.7%	88	22	16	46	8	242	3	61	3	24	209	3.1	1.1
RM273	8	9	1	16	480462	5408346	271.9	1397	1155	480	334	91	7.8	47.9	4.0%	241	23	18	50	8	264	4	70	4	26	208	3.8	1.3
RM273	9	10	1	16	480462	5408346	270.9	759	698	271	184	47	5.6	34.8	5.3%	61	17	11	34	6	147	3	43	3	20	143	3.4	1.0
RM273	10	11	1	16	480462	5408346	269.9	471	431	146	96	25	3.7	22.0	5.5%	40	13	6	22	4	86	2	23	2	14	112	3.3	0.9
RM273	11	12	1	16	480462	5408346	268.9	483	418	146	97	25	3.4	21.2	5.1%	65	12	6	20	4	83	2	22	2	13	107	3.3	0.9
RM273	12	13	1	16	480462	5408346	267.9	346	316	97	63	16	2.5	16.0	5.3%	30	10	4	15	3	65	2	14	1	11	94	3.0	0.9
RM273	13	14	1	16	480462	5408346	266.9	469	401	139	93	24	3.0	19.2	4.7%	67	10	6	19	4	84	2	21	2	11	105	2.9	1.0
RM273	14	15	1	16	480462	5408346	265.9	263	237	69	44	11	1.8	11.4	5.0%	26	7	3	11	2	51	1	10	1	8	73	3.3	0.9
RM274	2	3	1	7	480557	5408542	268.1	334	204	71	46	12	1.8	12.1	4.1%	130	6	3	10	2	37	1	12	1	8	52	6.4	2.2
RM274	3	4	1	7	480557	5408542	267.1	1370	1099	475	335	88	8.1	44.1	3.8%	271	18	17	56	7	266	2	75	3	18	161	4.4	1.9
RM274	4	5	1	7	480557	5408542	266.1	2052	1836	637	433	108	13.3	83.2	4.7%	216	41	24	93	16	407	5	93	6	36	480	6.0	2.6
RM275	1	2	1	5	480700	5408800	266.2	226	192	66	44	10	1.5	9.6	4.9%	35	5	2	9	2	42	1	10	1	5	50	7.3	2.1
RM276	1	2	1	5	480905	5408916	271.1	107	85	29	19	5	0.7	4.5	4.9%	22	2	1	4	1	17	0	4	0	3	23	6.3	1.9
RM277	2	3	1	7	481121	5408886	273.8	1284	854	395	276	78	5.8	34.8	3.2%	430	15	14	36	6	191	2	62	2	18	113	4.0	1.3
RM277	3	4	1	7	481121	5408885	272.8	1352	1204	520	358	99	8.6	54.1	4.6%	147	26	19	53	9	266	5	79	4	33	190	3.1	0.9
RM277	4	5	1	7	481121	5408885	271.8	1422	1358	556	380	103	9.6	62.5	5.1%	64	31	20	58	11	338	6	78	5	44	212	2.9	0.9
RM278	1	2	1	5	481135	5408747	271.1	164	127	55	38	11	1.0	5.5	3.9%	36	3	2	6	1	29	0	8	0	4	20	6.0	2.2
RM278	2	3	1	5	481135	5408747	270.1	154	83	28	17	5	0.6	4.6	3.4%	71	2	1	4	1	15	0	4	0	3	24	3.6	1.2
RM279	2	3	1	12	480969	5408605	276.9	340	273	93	60	14	2.4	15.8	5.4%	67	8	4	14	3	50	1	15	1	9	76	4.0	1.1
RM280	2	3	1	14	480777	5408454	281.3	92	23	8	5	1	0.2	1.3	1.6%	69	1	0	1	0	4	0	2	0	1	5	6.6	2.7
RM280	4	5	1	14	480777	5408454	279.3	268	136	49	32	8	1.1	7.3	3.1%	133	4	2	7	1	27	1	7	1	5	33	6.4	1.9
RM280	6	7	1	14	480777	5408454	277.3	185	127	45	30	7	1.1	4.4	5.7%	47	4	2	7	1	23	1	7	1	5	34	6.2	2.2
RM280	7	8	1	14	480777	5408454	276.3	390	320	109	72	17	2.5	17.1	5.0%	70	9	5	15	3	65	1	17	1	9	85	6.1	1.7
RM280	8	9	1	14	480777	5408454	275.3	2303	2228	595	359	86	18.6	130.8	6.5%	74	75	27	116	27	333	10	88	10	70	878	6.3	2.2
RM280	9	10	1	14	480777	5408454	274.3	778	722	174	106	24	5.4	39.3	5.7%	56	25	7	36	8	112	3	24	3	22	306	5.4	1.6
RM281	1	2	1	4	481291	5408669	265.0	126	100	28	18	4	0.8	5.5	5.0%	25	4	1	5	1	16	1	5	1	4	36	2.6	0.9
RM282	3	4	1	10	481428	5408515	266.2	239	157	54	33	8	1.5	10.7	5.1%	83	5	2	8	2	26	1	9	1	7	41	5.5	1.5
RM282	4	5	1	10	481428	5408515	265.2	369	273	106	69	19	2.3	16.1	5.0%	97	9	4	13	3	49	2	16	1	11	57	4.4	1.3
RM282	5	6	1	10	481428	5408515	264.2	277	222	80	49	13	2.1	15.7	6.4%	55	9	4	12	3	32	2	14	1	12	53	4.9	1.4
RM282	6	7	1	10	481428	5408516	263.2	461	362	147	98	26	2.9	19.2	4.8%	99	10	5	17	3	76	2	22	2	14	64	4.6	1.2
RM283	3	4	1	14	481282	5408362	275.4	397	211	81	53	14	1.9	13.2	3.8%	186	7	3	11	2	38	1	14	1	8	43	6.4	2.0
RM283	4	5	1	14	481282	5408362	274.4	589	400	169	116	30	3.1	19.5	3.8%	189	9	6	21	3	86	1	26	1	9	68	5.6	2.5
RM283	5	6	1	14	481282	5408362	273.4	293	272	109	75	18	2.3	13.9	5.5%	21	7	4	15	3	49	1	17	1	7	58	7.3	2.6
RM283	6	7	1	14	481282	5408362	272.4	300	246	89	58	14																

RM288	10	11	1	15	479137	5406071	204.3	205	164	49	31	8	1.2	8.4	4.7%	41	5	2	8	2	31	1	6	1	5	55	4.3	1.0
RM288	11	12	1	15	479137	5406071	203.3	181	143	43	28	7	1.1	7.0	4.5%	38	4	2	7	2	28	1	6	1	4	48	4.4	1.1
RM288	12	13	1	15	479137	5406071	202.3	192	147	43	28	7	1.1	7.3	4.4%	45	5	2	7	2	28	1	6	1	4	50	6.0	1.8
RM288	13	14	1	15	479137	5406071	201.3	177	118	40	27	7	0.9	5.3	3.5%	59	3	1	5	1	26	0	5	0	3	32	9.2	2.6
RM289	5	6	1	22	479395	5405998	208.9	90	64	20	13	3	0.5	3.1	3.9%	26	2	1	3	1	13	0	3	0	2	20	3.4	0.8
RM289	8	9	1	22	479395	5405998	205.9	93	71	23	15	3	0.6	4.0	4.9%	22	2	1	4	1	12	0	4	0	2	22	2.7	0.7
RM289	11	12	1	22	479395	5405998	202.9	68	47	15	10	2	0.4	2.5	4.3%	21	2	0	2	1	9	0	2	0	2	15	2.5	0.6
RM289	12	13	1	22	479395	5405998	201.9	71	49	16	10	3	0.4	2.5	4.1%	22	2	1	3	1	9	0	2	0	1	15	2.6	0.6
RM289	13	14	1	22	479395	5405998	200.9	70	49	15	10	3	0.4	2.6	4.3%	21	2	1	3	1	9	0	3	0	1	14	2.8	0.7
RM289	14	15	1	22	479395	5405998	199.9	65	45	14	9	2	0.4	2.3	4.2%	20	1	1	2	0	9	0	2	0	2	13	2.9	0.7
RM289	16	17	1	22	479395	5405998	197.9	83	63	18	12	3	0.6	3.5	5.0%	20	2	1	3	1	9	0	3	0	2	23	2.5	0.6
RM289	19	20	1	22	479395	5405998	194.9	65	45	14	9	2	0.3	2.3	4.1%	20	1	1	2	0	9	0	2	0	2	13	2.7	0.6
RM289	20	21	1	22	479395	5405998	193.9	63	42	13	8	2	0.3	2.0	3.7%	21	1	1	2	0	8	0	2	0	1	13	2.7	0.6
RM289	21	22	1	22	479395	5405998	192.9	70	53	16	10	2	0.5	3.0	5.0%	17	2	1	3	1	8	0	3	0	2	18	2.1	0.4
RM290	1	2	1	11	480136	5405169	212.4	159	100	34	24	6	0.6	3.7	2.7%	59	2	1	4	1	27	0	4	0	2	23	10.8	2.5
RM290	3	4	1	11	480136	5405169	210.4	245	208	47	28	7	1.5	10.1	4.7%	37	6	2	9	2	32	1	6	1	5	95	4.2	1.0
RM290	5	6	1	11	480136	5405169	208.4	195	160	39	24	6	1.1	7.3	4.3%	35	5	2	7	2	28	1	5	1	4	67	3.9	0.8
RM290	7	8	1	11	480136	5405169	206.4	156	128	28	17	4	0.9	5.7	4.2%	28	4	1	6	1	19	1	4	1	4	60	3.3	0.7
RM290	8	9	1	11	480136	5405169	205.4	125	93	25	17	4	0.7	4.3	4.0%	32	3	1	4	1	17	0	4	0	3	34	3.8	0.9
RM290	9	10	1	11	480136	5405169	204.4	113	87	23	14	3	0.6	4.2	4.3%	26	3	1	4	1	14	1	3	0	3	35	2.9	0.8
RM290	10	11	1	11	480136	5405169	203.4	111	84	22	13	3	0.7	4.6	4.8%	27	3	1	4	1	13	0	3	0	3	33	3.0	0.8
RM291	4	5	1	7	480397	5405447	233.7	228	144	45	29	7	1.3	8.3	4.2%	84	5	2	7	2	23	1	7	1	6	45	3.1	0.8
RM291	5	6	1	7	480397	5405447	232.7	272	200	69	44	11	1.9	12.0	5.1%	72	7	3	10	2	33	1	11	1	8	56	3.6	1.0
RM291	6	7	1	7	480397	5405447	231.7	271	202	67	43	11	1.8	11.9	5.1%	68	7	3	11	2	33	1	11	1	8	58	4.3	1.1
RM292	6	7	1	37	480741	5405553	211.6	171	119	37	24	6	1.0	6.5	4.4%	52	4	2	6	1	20	0	5	1	4	39	7.4	1.8
RM292	7	8	1	37	480741	5405553	210.6	178	135	35	21	5	1.1	7.5	4.8%	44	5	1	7	2	17	1	5	1	5	58	6.1	1.7
RM292	11	12	1	37	480741	5405553	206.6	210	155	47	30	8	1.2	8.5	4.7%	55	6	2	7	2	24	1	7	1	6	53	5.8	3.1
RM292	12	13	1	37	480741	5405553	205.6	256	170	60	39	10	1.3	8.9	4.0%	85	5	2	8	2	30	1	10	1	6	46	5.2	1.7
RM292	13	14	1	37	480741	5405553	204.6	228	160	53	33	9	1.5	9.6	4.8%	68	6	2	9	2	22	1	9	1	7	50	4.8	1.1
RM292	14	15	1	37	480741	5405553	203.6	207	128	48	32	8	1.2	7.0	4.0%	79	4	2	7	1	22	1	7	1	4	31	6.0	1.0
RM292	15	16	1	37	480741	5405553	202.6	144	88	32	21	6	0.8	4.9	4.0%	56	3	1	5	1	14	1	5	0	4	22	8.9	1.5
RM292	17	18	1	37	480741	5405553	200.6	138	95	32	20	5	0.9	5.7	4.8%	43	4	1	5	1	14	1	5	1	4	27	10.7	2.3
RM292	19	20	1	37	480741	5405553	198.6	92	67	23	14	3	0.8	5.2	6.6%	25	3	1	4	1	7	1	4	0	3	20	6.2	2.3
RM292	21	22	1	37	480741	5405553	196.6	323	115	41	27	7	1.0	6.1	2.2%	209	4	1	6	1	18	1	7	1	4	31	6.2	1.5
RM292	23	24	1	37	480741	5405553	194.6	153	87	29	18	5	0.8	5.3	4.0%	66	3	1	5	1	13	1	5	0	4	26	6.5	1.4
RM292	25	26	1	37	480741	5405553	192.6	231	155	56	36	9	1.3	8.9	4.4%	76	5	2	7	2	27	1	9	1	6	39	5.1	1.5
RM292	27	28	1	37	480741	5405553	190.6	325	269	82	50	12	2.6	17.4	6.2%	55	11	3	13	4	36	2	13	2	12	92	5.1	1.4
RM292	28	29	1	37	480741	5405553	189.6	365	313	95	59	15	2.6	17.8	5.6%	52	11	3	15	4	51	2	13	2	12	105	4.3	1.1
RM292	29	30	1	37	480741	5405553	188.6	348	286	90	58	15	2.3	15.0	5.0%	62	9	3	14	3	49	1	13	1	8	95	4.3	1.2
RM292	30	31	1	37	480741	5405553	187.6	345	289	91	59	15	2.2	14.3	4.8%	56	8	3	14	3	53	1	13	1	8	92	4.8	1.2
RM292	31	32	1	37	480741	5405553	186.6	343	291	92	61	16	2.1	13.5	4.6%	51	8	3	14	3	58	1	13	1	7	90	4.8	1.2
RM292	32	33	1	37	480741	5405553	185.6	332	290	87	54	14	2.5	16.6	5.8%	42	10	4	15	3	45	2	14	2	10	99	5.6	0.9
RM292	33	34	1	37	480741	5405553	184.6	321	289	82	48	12	2.9	19.7	7.0%	32	12	4	16	3	31	2	14	2	13	108	4.3	1.3
RM292	34	35	1	37	480741	5405553	183.6	394	292	91	56	14	2.7	17.6	5.1%	102	11	4	16	4	42	2	14	2	11	97	4.8	1.0
RM292	35	36	1	37	480741	5405553	182.6	467	296	99	65	17	2.4	15.5	3.8%	171	9	4	15	3	53	1	14	1	9	86	4.8	1.0
RM292	36	37	1	37	480741	5405553	181.6	448	339	108	66	17	3.3	21.2	5.5%	109	13	4	18	4	47	2	17	2	14	109	4.6	1.3
RM292	37	38	1	37	480741	5405553	180.6	430	383	117	68	17	4.1	26.9	7.2%	47	17	5	21	6	42	3	20	3	19	132	4.6	1.3
RM293	5	6	1	18	480730	5405750	212.2	229	168	53	34	9	1.4	8.7	4.4%	60	5	2	8	2	34	1	8	1	5	50	8.2	1.6
RM293	7	8	1	18	480730	5405750	209.2	115	90	23	14	4	0.8	5.3	5.2%	25	3	1	4	1</								

RM297	2	3	1	12	480638	5406171	217.8	553	504	131	77	18	4.7	31.8	6.6%	49	20	6	27	7	65	2	19	3	16	209	3.8	0.8
RM297	3	4	1	12	480638	5406171	216.8	477	430	111	64	15	4.0	27.4	6.6%	48	17	5	23	6	56	2	16	2	13	178	4.3	1.0
RM297	4	5	1	12	480638	5406171	215.8	393	343	97	62	15	2.6	16.6	4.9%	50	10	4	16	4	69	1	14	1	9	117	3.4	0.9
RM297	5	6	1	12	480638	5406171	214.8	238	206	57	37	9	1.6	10.0	4.9%	33	7	2	9	2	41	1	8	1	6	71	3.0	0.8
RM297	7	8	1	12	480638	5406171	212.8	121	162	49	32	8	1.2	8.1	4.4%	50	5	2	7	2	33	1	7	1	4	51	5.5	1.6
RM297	9	10	1	12	480638	5406171	210.8	110	83	25	16	4	0.6	4.2	4.3%	27	3	1	4	1	15	0	4	0	2	28	3.2	0.9
RM297	11	12	1	12	480638	5406171	208.8	112	82	24	15	4	0.6	4.4	4.5%	30	3	1	4	1	14	0	4	0	3	28	3.1	0.9
RM298	2	3	1	9	481470	5406134	210.6	140	86	25	16	4	0.7	4.5	3.7%	54	3	1	4	1	16	0	3	0	3	30	3.7	0.8
RM298	4	5	1	9	481470	5406134	208.6	253	198	64	43	11	1.4	8.6	3.9%	56	5	2	9	2	48	1	8	1	4	54	2.8	0.8
RM298	6	7	1	9	481470	5406134	206.6	121	93	25	16	4	0.6	4.5	4.3%	28	3	1	4	1	18	0	4	0	3	34	3.3	0.7
RM298	8	9	1	9	481470	5406134	204.6	94	70	20	12	3	0.5	3.5	4.3%	24	2	1	3	1	12	0	3	0	2	25	3.0	0.7
RM299	2	3	1	23	481768	5406272	209.6	170	125	36	23	6	1.0	6.1	4.2%	44	4	1	5	1	24	1	6	1	4	42	8.0	1.8
RM299	3	4	1	23	481768	5406272	208.6	170	126	34	21	5	0.9	6.3	4.2%	44	5	1	5	1	22	1	4	1	5	48	10.0	2.2
RM299	5	6	1	23	481768	5406272	206.6	175	128	38	24	7	0.9	5.9	3.9%	47	4	1	5	1	25	1	6	1	4	42	8.8	1.7
RM299	7	8	1	23	481768	5406272	204.6	203	144	43	28	7	1.0	7.4	4.1%	58	5	2	6	1	28	1	6	1	5	46	9.2	2.0
RM299	9	10	1	23	481768	5406272	202.6	369	259	91	62	16	1.8	11.5	3.6%	111	7	3	11	2	55	1	13	1	7	68	8.8	2.1
RM299	10	11	1	23	481768	5406272	201.6	543	380	126	84	21	3.0	18.0	3.9%	164	10	4	18	4	79	1	18	1	10	109	8.0	1.9
RM299	11	12	1	23	481768	5406272	200.6	717	501	160	105	26	4.2	24.6	4.0%	217	14	5	24	5	102	2	23	2	13	150	7.3	1.7
RM299	12	13	1	23	481768	5406272	199.6	506	347	97	62	15	2.7	17.0	3.9%	159	11	3	17	4	70	1	14	1	8	120	10.0	4.1
RM299	13	14	1	23	481768	5406272	198.6	671	556	117	72	17	3.5	24.8	4.2%	115	19	4	20	6	81	3	16	2	16	272	7.1	1.9
RM299	15	16	1	23	481768	5406272	196.6	152	111	31	20	5	0.7	5.0	3.8%	42	4	1	4	1	26	0	4	0	3	37	8.3	2.7
RM299	16	17	1	23	481768	5406272	195.6	153	90	27	17	5	0.6	4.0	3.0%	62	3	1	3	1	22	0	4	0	3	27	13.5	2.7
RM299	17	18	1	23	481768	5406272	194.6	415	285	98	66	17	2.1	12.3	3.5%	130	7	3	14	2	62	1	16	1	6	75	13.7	2.3
RM299	18	19	1	23	481768	5406272	193.6	119	73	16	9	2	0.6	4.0	3.8%	46	3	0	2	1	12	0	2	1	4	32	17.1	2.9
RM299	19	20	1	23	481768	5406272	192.6	139	92	23	14	4	0.6	5.0	4.0%	46	3	1	3	1	22	0	3	0	4	32	13.7	2.8
RM299	20	21	1	23	481768	5406272	191.6	551	213	79	56	15	1.1	7.3	1.5%	338	4	2	8	1	59	1	10	1	4	44	20.9	3.6
RM299	21	22	1	23	481768	5406272	190.6	314	165	54	37	10	1.1	6.4	2.4%	149	4	1	7	1	41	1	8	1	4	44	12.5	2.7
RM299	22	23	1	23	481768	5406272	189.6	296	176	57	39	10	1.2	7.0	2.8%	120	5	2	7	2	41	1	8	1	4	49	11.6	2.4
RM300	2	3	1	14	481377	5405886	211.2	119	76	24	17	4	0.5	2.9	2.8%	43	2	1	3	1	20	0	4	0	2	19	7.5	2.0
RM300	3	4	1	14	481377	5405886	210.2	114	73	23	15	4	0.5	3.1	3.1%	41	2	1	3	1	19	0	4	0	2	19	6.6	2.0
RM300	4	5	1	14	481377	5405886	209.2	131	90	28	17	4	0.8	5.4	4.7%	41	3	1	4	1	15	1	4	1	4	27	7.2	2.3
RM300	5	6	1	14	481377	5405886	208.2	117	75	23	14	4	0.6	4.3	4.2%	42	3	1	3	1	12	1	4	0	3	24	7.9	2.2
RM300	6	7	1	14	481377	5405886	207.2	135	96	24	14	3	1.0	6.7	5.7%	38	4	1	4	2	10	1	4	1	6	41	7.9	2.1
RM300	7	8	1	14	481377	5405886	206.2	293	259	44	17	4	2.6	20.7	7.9%	34	15	2	11	5	11	2	7	2	16	144	7.0	1.7
RM300	8	9	1	14	481377	5405886	205.2	411	363	134	90	22	3.0	18.5	5.2%	49	10	5	18	4	68	2	20	2	11	91	5.4	1.4
RM300	9	10	1	14	481377	5405886	204.2	959	904	372	259	66	6.8	39.5	4.8%	55	19	13	45	7	202	2	58	3	17	167	4.4	1.4
RM300	10	11	1	14	481377	5405886	203.2	1097	1040	429	301	76	7.8	44.3	4.7%	57	20	14	52	8	249	2	65	3	17	182	5.2	1.4
RM300	11	12	1	14	481377	5405886	202.2	474	431	164	112	28	3.3	20.4	5.0%	43	10	6	22	4	95	1	24	1	10	93	5.1	1.4
RM300	12	13	1	14	481377	5405886	201.2	367	329	124	84	21	2.6	15.7	5.0%	38	8	4	17	3	70	1	19	1	8	73	4.6	1.3
RM300	13	14	1	14	481377	5405886	200.2	97	72	27	18	5	0.5	2.7	3.3%	25	1	3	1	19	0	4	0	2	14	5.9	1.9	
RM301	3	4	1	11	481900	5412972	206.4	152	113	37	24	6	0.9	5.9	4.5%	39	4	1	5	1	21	1	6	1	3	34	4.5	1.2
RM301	4	5	1	11	481900	5412972	205.4	174	140	45	30	8	1.1	6.5	4.4%	35	4	2	6	1	27	1	6	1	4	43	4.6	1.2
RM301	5	6	1	11	481900	5412972	204.4	186	148	44	29	7	1.0	7.3	4.4%	38	5	2	7	2	27	1	7	1	4	50	5.0	1.2
RM301	6	7	1	11	481900	5412972	203.4	204	164	52	34	9	1.3	8.3	4.7%	40	5	2	8	2	31	1	9	1	5	50	4.9	1.3
RM301	7	8	1	11	481900	5412972	202.4	186	145	45	30	8	1.1	6.7	4.2%	42	4	2	7	1	27	1	7	1	4	46	4.5	1.2
RM302	2	3	1	15	481722	5412740	211.0	724	300	104	70	17	2.3	15.1	2.4%	424	9	4	13	3	60	1	16	1	9	78	6.9	2.2
RM302	3	4	1	15	481722	5412740	210.0	1648	628	245	167	43	4.7	30.5	2.1%	1020	18	9	28	6	128	2	38	3	19	133	6.2	1.9
RM302	4	5	1	15	481722	5412740	209.0	2932	1660	773	545	155	11.0	62.5	2.5%	1271	30	25	67	11	378	4	118	5	33	218	7.1	2.2
RM302	5	6	1	15	481722	5412740	208.0	1228																				

RM307	4	5	1	13	481809	5411630	232.0	289	133	46	29	8	1.1	7.6	3.0%	155	5	2	6	1	25	1	7	1	5	35	8.8	2.1
RM307	5	6	1	13	481809	5411630	231.0	359	202	72	47	12	1.9	12.0	3.9%	157	7	3	10	2	35	1	12	1	8	51	7.7	2.1
RM307	6	7	1	13	481809	5411630	230.0	514	376	140	93	25	3.2	19.4	4.4%	138	12	5	18	4	78	2	23	2	14	79	7.9	2.1
RM307	7	8	1	13	481809	5411630	229.0	415	316	118	77	22	2.6	16.4	4.6%	99	10	4	15	3	65	2	18	1	10	70	7.9	2.2
RM307	8	9	1	13	481809	5411630	228.0	428	334	123	81	21	2.8	18.2	4.9%	93	11	4	16	4	67	2	19	2	11	75	7.5	2.1
RM307	9	10	1	13	481809	5411630	227.0	440	340	122	81	21	2.8	18.3	4.8%	100	11	4	16	4	70	2	18	2	11	79	7.0	1.8
RM307	10	11	1	13	481809	5411630	226.0	374	295	104	68	18	2.4	15.8	4.9%	78	9	4	14	3	61	1	16	1	10	71	6.9	1.7
RM307	11	12	1	13	481809	5411630	225.0	157	118	35	22	6	0.9	6.2	4.5%	39	4	1	5	1	22	1	5	1	4	39	4.5	1.3
RM307	12	13	1	13	481809	5411630	224.0	320	257	84	55	15	1.9	12.7	4.6%	63	8	3	12	3	52	1	13	1	8	73	6.5	1.6
RM308	1	2	1	8	481846	5411094	244.6	104	80	26	17	4	0.7	4.2	4.6%	24	2	1	4	1	15	0	4	0	3	23	6.9	2.2
RM308	2	3	1	8	481846	5411094	243.6	82	61	20	13	3	0.6	3.1	4.4%	21	2	1	3	1	12	0	3	0	2	18	7.1	2.3
RM308	3	4	1	8	481846	5411094	242.6	227	123	43	29	7	0.9	6.0	3.1%	104	4	2	6	1	23	1	7	1	4	33	7.3	2.2
RM309	1	2	1	7	481681	5410696	252.9	162	111	36	23	6	0.9	6.1	4.4%	51	4	1	5	1	20	1	6	1	4	33	9.3	2.9
RM309	2	3	1	7	481681	5410696	251.9	69	34	11	7	2	0.3	1.9	3.1%	35	1	0	2	0	7	0	2	0	1	10	9.3	3.8
RM309	3	4	1	7	481681	5410696	250.9	149	84	26	17	4	0.6	4.2	3.3%	65	3	1	4	1	15	0	4	0	3	26	6.5	2.3
RM310	1	2	1	6	481110	5410499	225.0	171	122	36	23	6	1.0	6.3	4.3%	49	4	1	6	1	22	1	5	1	4	41	6.3	1.7
RM311	3	4	1	6	480971	5409880	213.4	256	158	47	30	8	1.3	8.0	3.6%	98	5	2	7	2	30	1	7	1	6	51	5.8	1.6
RM312	2	3	1	11	481630	5410202	229.8	246	169	52	34	9	1.1	7.3	3.4%	78	5	2	7	2	38	1	7	1	5	51	8.6	2.7
RM312	3	4	1	11	481630	5410202	228.8	185	132	43	29	7	0.9	6.1	3.8%	52	4	1	6	1	29	1	6	1	3	38	10.7	2.7
RM312	4	5	1	11	481630	5410202	227.8	426	287	92	61	15	2.1	13.9	3.8%	138	9	3	13	3	57	1	14	1	9	85	9.5	2.4
RM312	5	6	1	11	481630	5410202	226.8	496	395	133	87	22	3.3	20.6	4.8%	101	12	5	20	4	76	2	20	2	13	108	9.3	2.8
RM312	6	7	1	11	481630	5410202	225.8	779	652	234	157	40	5.0	31.1	4.6%	127	17	8	31	6	142	3	35	3	17	156	7.5	2.1
RM312	7	8	1	11	481630	5410202	224.8	1901	1661	639	440	112	13.2	74.4	4.6%	240	35	23	84	13	398	4	97	5	32	331	7.1	2.5
RM312	8	9	1	11	481630	5410202	223.8	2164	1973	582	367	88	17.4	109.5	5.9%	191	61	23	107	22	372	8	86	9	55	649	5.5	2.3
RM312	9	10	1	11	481630	5410202	222.8	2926	2797	658	369	85	26.5	177.3	7.0%	129	113	28	145	38	364	14	95	15	95	1232	5.9	1.9
RM312	10	11	1	11	481630	5410202	221.8	1329	1224	365	234	57	10.4	63.8	5.6%	105	37	13	64	13	230	5	54	5	32	405	5.9	1.6
RM313	1	2	1	6	482273	5411295	220.1	1069	944	293	190	47	7.8	48.2	5.2%	125	28	11	49	10	186	3	44	4	24	293	10.9	2.6
RM313	2	3	1	6	482273	5411295	219.1	265	222	69	44	11	2.0	11.4	5.0%	44	7	3	11	2	43	1	10	1	6	69	5.9	1.6
RM313	3	4	1	6	482273	5411295	218.1	208	169	49	31	8	1.4	8.8	4.9%	40	6	2	8	2	31	1	7	1	5	56	6.0	1.5
RM314	3	4	1	12	482368	5410985	210.5	408	338	104	67	16	2.8	18.2	5.2%	70	11	4	18	4	63	1	15	2	10	108	9.9	2.4
RM314	4	5	1	12	482368	5410985	209.5	478	387	124	80	20	3.4	21.6	5.2%	91	13	5	20	4	75	2	19	2	12	113	9.8	2.4
RM314	5	6	1	12	482368	5410985	208.5	403	291	87	56	14	2.4	14.9	4.3%	112	9	3	14	3	61	1	13	1	9	90	9.9	2.2
RM314	6	7	1	12	482368	5410985	207.5	525	442	109	67	17	3.2	22.3	4.9%	83	15	4	18	5	70	2	17	2	13	187	10.2	3.0
RM314	7	8	1	12	482368	5410985	206.5	501	420	103	62	16	3.3	21.7	5.0%	81	15	4	18	5	65	2	15	2	13	178	10.3	3.0
RM314	8	9	1	12	482368	5410985	205.5	294	231	64	40	10	1.9	12.0	4.7%	64	8	2	11	3	40	1	10	1	7	83	7.8	2.2
RM314	9	10	1	12	482368	5410985	204.5	309	230	59	36	9	1.9	12.0	4.5%	78	9	2	10	3	36	1	8	1	8	93	7.2	2.1
RM314	10	11	1	12	482368	5410985	203.5	380	303	76	46	11	2.4	16.1	4.8%	78	11	3	13	4	47	2	11	2	9	128	8.6	2.6
RM314	11	12	1	12	482368	5410985	202.5	243	188	51	32	8	1.6	9.8	4.7%	55	7	2	9	2	31	1	8	1	6	70	6.6	1.9
RM315	3	4	1	14	482446	5410824	209.6	424	355	89	56	14	2.6	16.8	4.6%	69	11	3	15	4	66	2	12	2	10	140	6.6	1.6
RM315	4	5	1	14	482446	5410824	208.6	377	322	70	42	10	2.3	15.7	4.8%	56	11	3	13	4	50	2	10	2	10	148	5.6	1.3
RM315	5	6	1	14	482446	5410824	207.6	311	258	63	39	9	1.9	12.8	4.7%	53	9	2	11	3	46	1	9	1	8	105	5.1	1.2
RM315	6	7	1	14	482446	5410824	206.6	189	152	39	24	6	1.2	7.4	4.6%	37	5	1	7	2	27	1	5	1	5	59	4.2	1.0
RM315	7	8	1	14	482446	5410824	205.6	149	118	30	19	5	1.0	6.0	4.7%	31	4	1	5	1	21	1	5	1	4	45	3.6	1.0
RM315	8	9	1	14	482446	5410824	204.6	144	112	30	19	5	0.9	5.9	4.7%	32	4	1	5	1	19	1	4	1	3	43	3.5	1.0
RM315	9	10	1	14	482446	5410824	203.6	115	87	24	15	4	0.8	4.9	4.9%	28	3	1	4	1	15	0	4	0	3	32	3.4	1.0
RM315	10	11	1	14	482446	5410824	202.6	103	76	23	15	3	0.6	4.0	4.5%	27	3	1	4	1	13	0	3	0	2	26	3.2	0.8
RM315	11	12	1	14	482446	5410824	201.6	104	77	22	14	4	0.6	3.9	4.3%	27	3	1	4	1	14	0	3	0	3	26	3.1	0.8
RM315	12	13	1	14	482446	5410824	200.6	108	82	24	15	4	0.6	4.4	4.7%	26	3	1	4	1	14	0	3	0	3	29	3.0	0.7
RM315	13	14	1																									

RM326	4	5	1	8	484462	5409236	190.7	166	131	37	24	6	1.0	7.0	4.8%	35	5	2	6	2	23	1	6	1	5	44	7.8	1.3
RM326	5	6	1	8	484462	5409236	189.7	242	186	56	36	9	1.6	9.8	4.7%	56	6	2	10	2	35	1	9	1	6	59	5.4	1.2
RM326	6	7	1	8	484462	5409236	188.7	163	122	35	22	6	1.0	6.4	4.6%	40	4	2	6	1	21	1	5	1	4	43	4.8	1.3
RM327	3	4	1	33	483845	5409836	189.3	152	101	32	20	5	0.9	5.7	4.3%	50	4	1	5	1	18	1	5	1	4	31	5.6	1.4
RM327	5	6	1	33	483845	5409836	187.3	168	88	29	18	4	0.8	5.9	4.0%	80	4	1	4	1	13	1	5	1	4	27	5.7	1.7
RM327	8	9	1	33	483845	5409836	184.3	216	128	43	28	7	1.0	6.7	3.5%	87	4	2	7	1	26	1	7	1	4	33	4.8	1.5
RM327	10	11	1	33	483845	5409836	182.3	279	210	65	42	11	1.8	10.9	4.6%	69	8	2	10	2	38	1	10	1	7	65	11.4	2.7
RM327	15	16	1	33	483845	5409836	177.3	127	63	23	16	4	0.4	2.2	2.0%	64	1	0	3	1	15	0	4	0	2	14	13.3	2.8
RM327	17	18	1	33	483845	5409836	175.3	114	35	12	7	2	0.3	1.7	1.8%	78	1	0	1	0	10	0	2	0	1	8	11.3	2.8
RM327	19	20	1	33	483845	5409836	173.3	189	46	15	9	2	0.4	3.3	2.0%	143	2	1	2	1	6	0	2	0	2	14	7.9	2.4
RM327	20	21	1	33	483845	5409836	172.3	253	169	62	40	10	1.6	10.4	4.7%	84	6	2	8	2	29	1	10	1	8	40	7.5	1.9
RM327	22	23	1	33	483845	5409836	170.3	408	355	115	70	17	3.7	24.2	6.8%	53	16	5	18	5	48	3	19	2	17	107	7.3	2.7
RM327	23	24	1	33	483845	5409836	169.3	446	388	123	78	19	3.5	22.7	5.9%	58	15	5	20	5	65	2	19	2	14	119	8.4	2.4
RM327	24	25	1	33	483845	5409836	168.3	484	422	132	86	22	3.3	21.1	5.0%	62	14	5	21	4	82	2	19	2	12	130	9.4	2.2
RM327	25	26	1	33	483845	5409836	167.3	412	336	104	68	17	2.7	16.8	4.7%	76	11	4	16	3	66	1	15	1	10	104	10.5	2.1
RM327	26	27	1	33	483845	5409836	166.3	341	250	77	49	13	2.0	12.5	4.3%	91	7	2	11	3	49	1	11	1	8	78	11.5	2.1
RM327	27	28	1	33	483845	5409836	165.3	337	253	79	51	14	2.0	12.8	4.4%	85	8	3	12	3	49	1	11	1	8	78	10.6	2.1
RM327	28	29	1	33	483845	5409836	164.3	334	256	81	52	14	2.0	13.1	4.5%	78	8	3	12	3	49	1	11	1	8	78	9.7	2.1
RM327	29	30	1	33	483845	5409836	163.3	283	196	63	40	11	1.6	10.6	4.3%	88	7	2	9	2	37	1	8	1	6	60	9.4	2.4
RM327	30	31	1	33	483845	5409836	162.3	497	416	135	91	22	3.3	18.5	4.4%	80	11	5	21	4	86	1	19	1	9	125	8.6	2.0
RM327	31	32	1	33	483845	5409836	161.3	328	265	78	51	12	2.2	12.9	4.6%	63	8	3	12	3	49	1	11	1	8	89	7.5	2.0
RM328	4	5	1	20	483743	5410083	190.0	407	293	90	59	15	2.2	13.8	3.9%	114	8	3	15	3	59	1	14	1	7	92	7.5	2.2
RM328	7	8	1	20	483743	5410083	187.0	258	204	57	36	9	1.8	10.7	4.8%	54	7	2	10	2	35	1	9	1	7	74	6.5	2.2
RM328	9	10	1	20	483743	5410083	185.0	235	152	47	30	8	1.2	7.8	3.8%	83	5	2	7	2	28	1	7	1	5	47	10.2	1.8
RM328	11	12	1	20	483743	5410083	183.0	219	139	43	28	7	1.1	7.3	3.8%	80	5	2	6	2	26	1	7	1	5	44	9.8	2.0
RM328	13	14	1	20	483743	5410083	181.0	236	161	48	31	8	1.3	8.0	3.9%	76	5	2	8	2	30	1	7	1	5	52	9.6	2.0
RM328	15	16	1	20	483743	5410083	179.0	207	138	42	26	7	1.1	7.6	4.2%	70	5	1	25	1	6	1	5	44	8.9	2.0		
RM328	17	18	1	20	483743	5410083	177.0	197	123	41	26	7	1.0	7.1	4.1%	74	4	1	6	1	23	1	6	1	5	34	9.3	1.8
RM329	3	4	1	15	483828	5409581	188.4	174	97	32	21	5	0.7	4.9	3.2%	77	3	1	4	1	19	0	5	0	3	28	8.5	2.0
RM329	5	6	1	15	483828	5409581	186.4	163	115	37	23	6	1.0	6.9	4.9%	48	5	1	5	1	18	1	5	1	5	36	7.4	2.9
RM329	7	8	1	15	483828	5409581	184.4	147	104	33	22	6	0.9	5.3	4.2%	43	4	1	5	1	18	1	5	1	4	32	8.2	1.9
RM329	9	10	1	15	483828	5409581	182.4	167	137	41	25	6	1.2	8.1	5.5%	30	6	1	7	2	20	1	5	1	6	48	6.2	2.0
RM329	10	11	1	15	483828	5409581	181.4	80	53	16	10	3	0.4	3.0	4.3%	28	2	1	2	1	11	0	3	0	2	15	10.4	2.1
RM329	11	12	1	15	483828	5409581	180.4	154	124	35	21	5	1.1	7.0	5.2%	30	5	1	6	2	19	1	5	1	5	45	6.5	2.0
RM329	12	13	1	15	483828	5409581	179.4	167	123	38	24	6	1.0	6.7	4.6%	44	4	1	6	1	22	1	6	1	4	39	6.5	1.6
RM329	14	15	1	15	483828	5409581	177.4	42	26	7	4	1	0.2	1.6	4.5%	16	1	0	1	0	4	0	1	0	2	9	9.5	2.1
RM330	2	3	1	16	483944	5408900	188.2	176	116	41	27	7	0.9	5.5	3.7%	60	3	1	5	1	25	1	6	0	3	29	13.2	2.2
RM330	3	4	1	16	483944	5408900	187.2	355	236	84	57	15	1.8	10.1	3.4%	119	6	4	12	2	54	1	13	1	5	56	4.8	1.4
RM330	4	5	1	16	483944	5408900	186.2	431	299	105	72	18	2.3	12.9	3.5%	133	7	5	15	3	68	1	16	1	5	73	5.2	1.5
RM330	5	6	1	16	483944	5408900	185.2	416	288	101	69	17	2.2	12.3	3.5%	128	6	5	15	2	67	1	15	1	5	70		
RM330	6	7	1	16	483944	5408900	184.2	400	277	96	66	16	2.1	11.8	3.5%	123	6	5	15	2	66	1	15	1	5	67	4.2	1.2
RM330	7	8	1	16	483944	5408900	183.2	286	196	68	47	12	1.5	8.1	3.3%	90	4	3	10	2	46	1	10	1	3	48	6.2	1.6
RM330	8	9	1	16	483944	5408900	182.2	171	115	40	28	7	0.8	4.4	3.1%	56	3	2	6	1	26	0	5	0	2	30	8.3	1.9
RM330	15	16	1	16	483944	5408900	175.2	54	23	6	4	1	0.2	1.3	2.8%	31	1	0	4	0	1	0	1	8	8.1	2.0		
RM331	2	3	1	8	483576	5409129	209.4	392	321	134	92	25	2.7	15.3	4.6%	71	8	5	15	3	65	1	21	1	9	59	5.0	1.2
RM331	3	4	1	8	483576	5409129	208.4	2587	584	200	122	32	6.3	39.6	1.8%	2002	23	9	30	8	92	3	33	3	24	160	3.5	1.1
RM331	4	5	1	8	483576	5409129	207.4	1550	785	302	204	53	6.6	38.6	2.9%	765	20	12	39	7	160	2	47	3	19	173	2.8	0.8
RM331	5	6	1	8	483576	5409129	206.4	919	827	362	251	64	7.2	39.5	5.1%	92	17	4	44	7	164	2	59	2	17	138	3.4	1.1
RM331	6	7	1	8	483576	5409129	205.4	641	475	195	34	34	4.2	23.5	4.3%													

RM336	6	7	1	9	479970	5412965	229.1	4285	4102	1324	883	218	31.6	191.1	5.2%	183	114	48	196	38	868	14	190	15	93	1203	5.7	1.7
RM336	7	8	1	9	479970	5412965	228.1	2078	1987	580	380	94	15.1	90.6	5.1%	92	59	21	92	20	405	7	81	8	46	669	4.8	1.2
RM336	8	9	1	9	479970	5412965	227.1	2167	2061	667	446	110	16.3	94.7	5.1%	106	56	25	97	19	433	7	98	8	48	603	5.3	1.6
RM337	0	1	1	4	480194	5412578	230.2	1478	1345	444	299	73	10.4	61.1	4.8%	133	36	16	62	13	279	4	62	5	30	395	6.8	1.9
RM337	1	2	1	4	480194	5412578	229.2	503	472	149	99	24	3.6	21.7	5.0%	30	13	6	22	5	100	2	20	2	11	143	9.0	2.3
RM337	2	3	1	4	480194	5412578	228.2	424	397	134	91	22	3.0	18.2	5.0%	27	11	5	19	4	84	1	21	1	9	108	7.9	2.5
RM337	3	4	1	4	480194	5412578	227.2	359	308	66	43	11	1.6	10.4	3.3%	151	7	2	10	2	40	1	9	1	6	64	5.2	1.5
RM338	0	1	1	10	480480	5412189	228.4	430	204	66	44	11	1.5	9.7	2.6%	227	6	2	9	2	42	1	10	1	6	59	9.1	2.6
RM338	1	2	1	10	480480	5412189	227.4	336	143	46	30	8	1.1	6.8	2.3%	193	4	2	7	1	32	1	6	1	4	39	8.3	2.2
RM338	2	3	1	10	480480	5412189	226.4	565	140	52	35	8	1.3	6.9	1.4%	425	4	2	7	1	32	0	9	1	3	30	6.9	2.1
RM338	3	4	1	10	480480	5412189	225.4	554	291	100	67	18	2.1	13.0	2.7%	263	8	3	12	2	67	1	14	1	7	75	7.4	1.9
RM338	4	5	1	10	480480	5412189	224.4	1941	951	428	301	90	5.7	31.3	1.9%	990	16	12	33	6	253	2	60	2	16	122	6.6	2.0
RM338	5	6	1	10	480480	5412189	223.4	1920	1502	684	488	145	8.3	42.9	2.7%	418	20	18	51	7	449	3	92	3	18	157	7.0	2.4
RM338	6	7	1	10	480480	5412189	222.4	1113	1010	419	297	81	6.2	33.5	3.6%	103	17	12	39	6	296	2	56	2	15	145	5.4	1.5
RM338	7	8	1	10	480480	5412189	221.4	1645	1564	635	450	120	10.3	55.0	4.0%	82	26	19	63	10	484	3	87	4	23	210	5.4	1.7
RM338	8	9	1	10	480480	5412189	220.4	1462	1370	521	367	97	8.7	47.4	3.8%	92	23	15	56	9	442	3	69	3	21	209	6.3	1.9
RM338	9	10	1	10	480480	5412189	219.4	1494	1414	542	383	103	8.8	47.7	3.8%	80	24	16	57	8	461	3	72	3	21	207	5.8	1.7
RM339	0	1	1	8	480781	5412165	232.6	561	478	176	122	33	3.1	18.5	3.9%	83	10	5	19	4	131	1	24	1	9	96	10.4	3.1
RM339	1	2	1	8	480781	5412165	231.6	321	249	95	66	18	1.6	8.7	3.2%	72	5	3	9	2	70	1	13	1	5	48	8.3	2.9
RM339	2	3	1	8	480781	5412165	230.6	1089	144	53	37	9	1.0	5.7	0.6%	945	3	2	6	1	38	1	7	0	3	29	7.3	2.6
RM339	3	4	1	8	480781	5412165	229.6	691	146	51	35	9	1.0	5.9	1.0%	544	4	2	6	1	36	1	7	1	4	35	7.7	2.4
RM339	4	5	1	8	480781	5412165	228.6	748	372	123	83	21	2.7	16.8	2.6%	376	10	4	16	3	87	1	17	1	9	100	7.4	2.1
RM339	5	6	1	8	480781	5412165	227.6	766	369	124	82	21	2.9	18.2	2.8%	397	12	5	17	4	75	2	18	2	11	101	6.4	1.7
RM339	6	7	1	8	480781	5412165	226.6	411	342	117	79	19	2.8	16.5	4.7%	69	10	4	17	3	69	1	18	1	8	93	4.5	1.3
RM339	7	8	1	8	480781	5412165	225.6	551	488	155	103	25	3.8	22.9	4.9%	63	13	6	24	5	98	2	23	2	11	148	4.8	1.5
RM340	0	1	1	18	481186	5412339	213.0	530	457	153	103	26	3.6	20.8	4.6%	73	13	5	22	4	98	2	22	2	11	126	8.7	2.3
RM340	1	2	1	18	481186	5412339	212.0	220	150	49	32	9	1.0	6.0	3.2%	70	4	1	6	1	35	1	7	1	4	41	12.2	3.4
RM340	2	3	1	18	481186	5412339	211.0	323	235	77	51	14	1.8	10.7	3.9%	88	7	2	10	2	53	1	11	1	6	65	12.9	3.4
RM340	3	4	1	18	481186	5412339	210.0	283	170	59	40	11	1.1	6.6	2.7%	113	4	1	7	1	43	1	8	1	4	42	14.3	3.5
RM340	4	5	1	18	481186	5412339	209.0	228	143	49	33	9	0.9	6.0	3.0%	85	4	1	5	1	35	0	7	1	4	36	13.4	3.3
RM340	5	6	1	18	481186	5412339	208.0	220	150	49	33	9	1.1	5.8	3.1%	70	4	1	6	1	36	1	7	1	4	41	15.1	4.2
RM340	6	7	1	18	481186	5412339	207.0	427	317	102	68	18	2.5	14.1	3.9%	110	9	3	14	3	71	1	15	1	7	90	13.5	3.9
RM340	7	8	1	18	481186	5412339	206.0	423	304	100	67	17	2.2	13.6	3.7%	119	8	3	14	3	68	1	15	1	7	83	11.7	3.2
RM340	8	9	1	18	481186	5412339	205.0	244	168	54	37	10	1.1	6.6	3.2%	76	4	1	7	1	40	1	8	1	4	47	12.9	4.2
RM340	9	10	1	18	481186	5412339	204.0	310	226	71	47	13	1.6	9.7	3.6%	84	6	2	10	2	51	1	10	1	6	68	15.7	3.7
RM340	10	11	1	18	481186	5412339	203.0	244	163	53	36	10	1.0	6.1	2.9%	81	4	1	7	1	38	1	7	1	4	45	15.5	3.5
RM340	12	13	1	18	481186	5412339	201.0	185	121	41	28	7	0.8	4.4	2.8%	64	3	1	5	1	29	0	7	0	3	30	12.3	4.4
RM340	14	15	1	18	481186	5412339	199.0	201	133	44	30	8	0.9	5.7	3.2%	68	4	1	5	1	31	1	6	1	4	36	11.9	3.9
RM340	17	18	1	18	481186	5412339	196.0	231	153	51	35	9	1.0	6.2	3.1%	78	4	1	6	1	36	1	6	1	4	42	12.8	5.4
RM341	0	1	1	34	481203	5412601	211.8	163	110	35	23	6	0.7	4.3	3.1%	53	3	1	4	1	28	0	5	0	3	29	11.9	2.8
RM341	1	2	1	34	481203	5412601	210.8	258	178	58	39	10	1.2	7.4	3.3%	80	5	2	8	2	42	1	8	1	4	49	13.3	4.1
RM341	2	3	1	34	481203	5412601	209.8	119	73	26	18	5	0.4	2.6	2.5%	46	2	1	3	1	21	0	3	0	2	15	8.9	1.3
RM341	3	4	1	34	481203	5412601	208.8	136	79	29	20	6	0.4	2.8	2.4%	56	2	1	3	1	23	0	4	0	2	16	8.6	1.5
RM341	4	5	1	34	481203	5412601	207.8	142	81	31	22	6	0.4	2.7	2.2%	62	1	1	3	0	24	0	4	0	1	13	9.4	1.4
RM341	5	6	1	34	481203	5412601	206.8	99	57	21	15	4	0.3	1.9	2.2%	42	1	1	2	0	16	0	3	0	1	11	5.7	1.1
RM341	6	7	1	34	481203	5412601	205.8	129	72	27	19	5	0.4	2.2	2.0%	58	1	1	3	0	22	0	4	0	1	13	10.2	2.6
RM341	7	8	1	34	481203	5412601	204.8	109	62	24	17	5	0.4	2.0	2.1%	47	1	1	2	0	18	0	3	0	1	11	7.8	1.4
RM341	8	9	1	34	481203	5412601	203.8	103	61	21	14	4	0.3	2.1	2.3%	42	1	1	2	0	17	0	3	0				

RM346	5	6	1	13	481152	5411309	249.7	47	21	6	4	1	0.2	1.2	2.9%	26	1	0	1	0	4	0	1	0	1	5	14.0	3.8
RM346	6	7	1	13	481152	5411309	248.7	56	20	6	4	1	0.2	1.1	2.2%	36	1	0	1	0	4	0	1	0	1	5	15.8	4.4
RM346	7	8	1	13	481152	5411309	247.7	148	26	8	5	1	0.2	1.4	1.1%	122	1	0	1	0	5	0	1	0	1	8	15.8	4.4
RM346	8	9	1	13	481152	5411309	246.7	254	48	16	11	3	0.3	2.2	1.0%	206	1	1	2	0	12	0	3	0	1	11	14.1	4.9
RM346	9	10	1	13	481152	5411309	245.7	365	92	32	21	6	0.7	4.4	1.4%	273	3	1	4	1	20	0	5	0	3	22	12.9	4.4
RM346	10	11	1	13	481152	5411309	244.7	ot rec'	0	0	0	0	0.0	0.0	#####	0	0	0	0	0	0	0	0	0	0	0.0	0.0	0.0
RM347	1	2	1	5	480798	5411478	243.9	327	248	87	60	15	1.7	10.2	3.7%	79	6	3	11	2	57	1	13	1	7	61	13.0	3.5
RM347	2	3	1	5	480798	5411478	242.9	343	234	78	54	14	1.4	9.1	3.1%	109	6	2	9	2	55	1	11	1	6	63	13.8	3.5
RM347	3	4	1	5	480798	5411478	241.9	384	257	84	57	15	1.7	11.1	3.3%	127	7	2	11	3	54	1	12	1	7	75	10.4	3.1
RM347	4	5	1	5	480798	5411478	240.9	652	446	150	101	26	3.0	19.8	3.5%	206	12	4	20	4	97	1	20	2	12	124	11.9	3.7
RM348	2	3	1	10	480502	5413419	227.2	107	77	25	16	4	0.5	3.5	3.7%	29	2	1	3	1	16	0	3	0	2	23	8.8	2.1
RM348	3	4	1	10	480502	5413419	226.2	167	126	41	27	7	0.9	5.5	3.8%	41	4	1	6	1	25	1	5	1	4	38	8.2	2.0
RM348	4	5	1	10	480502	5413419	225.2	253	181	58	38	10	1.3	8.3	3.8%	72	6	2	9	2	36	1	9	1	5	54	7.5	1.7
RM348	5	6	1	10	480502	5413419	224.2	326	257	82	54	15	1.8	11.9	4.2%	69	7	3	12	2	51	1	11	1	7	79	7.1	1.6
RM348	6	7	1	10	480502	5413419	223.2	423	341	112	74	19	2.6	16.0	4.4%	82	11	4	16	3	69	2	15	1	9	100	6.4	1.5
RM348	7	8	1	10	480502	5413419	222.2	467	368	122	83	20	2.7	16.0	4.0%	99	11	4	17	4	76	2	17	1	10	106	5.6	1.3
RM348	8	9	1	10	480502	5413419	221.2	465	333	109	74	18	2.4	14.7	3.7%	132	10	4	16	3	69	2	16	1	9	94	7.8	1.8
RM348	9	10	1	10	480502	5413419	220.2	401	299	91	60	15	2.2	14.6	4.2%	102	9	3	14	3	54	1	12	1	9	101	8.3	1.9
RM349	0	1	1	4	480636	5412785	218.2	334	272	73	45	11	2.2	13.7	4.8%	62	10	3	12	3	43	1	9	1	9	108	7.0	1.9
RM349	1	2	1	4	480636	5412785	217.2	378	321	84	51	13	2.6	17.4	5.3%	58	12	3	15	4	48	2	11	2	11	128	6.4	1.7
RM349	2	3	1	4	480636	5412785	216.2	427	357	99	62	15	3.0	18.6	5.1%	70	13	3	17	4	55	2	14	2	11	136	6.0	1.7
RM350	0	1	1	14	481112	5412956	214.8	200	146	44	28	8	1.1	6.4	3.7%	54	4	1	6	1	32	1	6	1	4	45	8.2	1.8
RM350	1	2	1	14	481112	5412956	213.8	184	137	43	28	8	1.0	6.2	3.9%	46	4	2	6	1	29	1	5	1	4	42	7.3	1.8
RM350	2	3	1	14	481112	5412956	212.8	363	240	91	63	18	1.4	8.8	2.8%	123	5	3	10	2	66	1	12	1	4	46	15.2	3.2
RM350	3	4	1	14	481112	5412956	211.8	389	247	92	65	18	1.5	8.2	2.5%	142	5	3	10	2	70	1	13	1	5	47	15.8	3.6
RM350	4	5	1	14	481112	5412956	210.8	428	315	98	65	18	2.3	12.9	3.5%	114	9	3	13	3	69	1	13	1	8	96	12.2	2.8
RM350	5	6	1	14	481112	5412956	209.8	322	206	72	50	14	1.4	7.6	2.8%	116	5	2	8	2	53	1	10	1	4	48	12.5	2.8
RM350	6	7	1	14	481112	5412956	208.8	278	176	63	44	12	1.0	5.6	2.4%	101	4	2	7	1	49	1	9	1	4	36	14.7	3.1
RM350	7	8	1	14	481112	5412956	207.8	285	185	64	44	12	1.1	7.0	2.8%	100	4	2	7	1	52	1	8	1	4	42	14.3	3.1
RM350	8	9	1	14	481112	5412956	206.8	275	194	63	42	12	1.3	7.3	3.1%	82	5	2	8	2	47	1	8	1	5	53	13.0	2.7
RM350	9	10	1	14	481112	5412956	205.8	254	177	56	37	10	1.2	7.6	3.4%	77	5	2	7	2	43	1	7	1	4	51	12.6	3.0
RM351	1	2	1	12	481327	5413114	216.2	197	128	44	30	8	0.8	4.9	2.9%	69	3	1	5	1	35	0	6	0	3	29	12.4	2.3
RM351	2	3	1	12	481327	5413114	215.2	132	88	28	19	5	0.5	3.5	3.1%	44	2	1	3	1	23	0	4	0	2	23	8.5	1.8
RM351	3	4	1	12	481327	5413114	214.2	200	112	34	23	6	0.7	4.2	2.5%	88	3	1	4	1	31	0	4	0	3	30	7.8	1.2
RM351	4	5	1	12	481327	5413114	213.2	230	163	56	38	11	1.1	6.1	3.1%	67	4	2	6	1	42	1	8	0	4	39	7.4	1.5
RM351	5	6	1	12	481327	5413114	212.2	331	270	99	69	19	1.8	10.1	3.6%	62	6	3	12	2	73	1	13	1	5	56	6.9	1.6
RM351	6	7	1	12	481327	5413114	211.2	287	226	76	52	14	1.6	8.8	3.6%	62	6	3	10	2	55	1	10	1	5	58	7.9	1.7
RM351	7	8	1	12	481327	5413114	210.2	287	224	69	46	12	1.5	9.1	3.7%	63	7	2	9	2	51	1	9	1	6	66	9.1	1.9
RM351	8	9	1	12	481327	5413114	209.2	309	235	68	44	12	1.6	10.1	3.8%	75	7	2	10	2	51	1	9	1	6	78	8.6	1.8
RM351	9	10	1	12	481327	5413114	208.2	246	196	47	29	8	1.4	8.6	4.0%	50	6	2	8	2	36	1	6	1	5	81	6.7	1.6
RM351	10	11	1	12	481327	5413114	207.2	188	145	36	23	6	1.0	6.1	3.8%	43	5	1	6	1	29	1	5	1	4	56	5.7	1.4
RM351	11	12	1	12	481327	5413114	206.2	301	255	75	50	13	1.7	10.7	4.1%	46	7	2	12	2	53	1	11	1	6	86	5.0	1.5

End of Table 5.

End of Report.