

NI 43-101 Technical Report Haile Gold Mine Lancaster County, South Carolina

Effective Date: June 30, 2020

Report Date: September 30, 2020

Report Prepared for

OceanaGold Corporation

Report Prepared by



SRK Consulting (U.S.), Inc.
1125 Seventeenth Street, Suite 600
Denver, CO 80202

SRK Project Number: 392900.290

Signed by Qualified Persons:

David Carr, BEng Metallurgical (Hons) (OceanaGold Chief Metallurgist)
Michael Kirby, PE, MEng Civil (OceanaGold Environmental Superintendent)
Tom Cooney, BEng (Hons) Mining, MMinMgt, MAusIMM (CP) (OceanaGold General Manager Project Development)
John Jory, MSc Mineral Exploration, BS Geology, CPG, AIPG (OceanaGold Director of Exploration, Haile)
Jonathan Moore, BSc Geology (Hons), MAusIMM(CP) (OceanaGold Chief Geologist)
Jay Newton Janney-Moore, PE (NewFields Project Manager I)
William Lucas Kingston P.G. Hydrogeology and Groundwater Management (NewFields Senior Hydrogeologist)
Joanna Poeck, BEng Mining, SME-RM, MMSAQP (SRK Senior Consultant, Mining Engineer)
Larry Standridge, PE, MSE Geotechnical (Call & Nicholas Principal Engineer, Geotechnical Engineer)
Matt Sullivan, BEng, RM-SME (SRK Senior Consultant, Mineral Economics)
David Bird, MSc., PG, RM-SME (SRK Principal Consultant, Geochemistry)
Fernando Rodrigues, BS Mining, MBA, MMSAQP, MAusIMM (SRK Principal Consultant, Mining Engineering)
John Tinucci, PhD, PE (SRK Principal Consultant, Geotechnical Engineer)
Brian S. Prosser, PE (SRK Principal Consultant)

Reviewed by:

Berkley Tracy MSc Geology, PG, CPG, PGeo (Principal Consultant, Resource Geologist)

Table of Contents

1	Summary	16
1.1	Property Description and Ownership	16
1.2	Geology and Mineralization	16
1.3	Status of Exploration; Development and Operations	16
1.4	Mineral Processing and Metallurgical Testing	17
1.5	Mineral Resource Estimate	17
1.5.1	Open Pit Mineral Resource Estimate	17
1.5.2	Underground Mineral Resource Estimate	18
1.5.3	Combined Open Pit and Underground Resource Estimate	19
1.6	Mineral Reserve Estimate	20
1.6.1	Open Pit Mineral Reserves Estimate	20
1.6.2	Underground Mineral Reserves Estimate	21
1.6.3	Combined Open Pit and Underground Reserves Estimate	22
1.7	Mining Methods	23
1.7.1	Open Pit Mining Methods	23
1.7.2	Underground Mining Methods	26
1.8	Recovery Methods	28
1.9	Project Infrastructure	29
1.10	Environmental Studies and Permitting	29
1.11	Capital and Operating Costs	29
1.12	Economic Analysis	31
1.13	Conclusions and Recommendations	31
1.13.1	Geology and Mineral Resources	31
1.13.2	Status of Exploration; Development and Operations	32
1.13.3	Mining and Reserves	32
1.13.4	Mineral Processing and Metallurgical Testing	33
1.13.5	Recovery Methods	33
1.13.6	Project Infrastructure	34
1.13.7	Environmental Studies and Permitting	34
1.13.8	Economic Analysis	34
2	Introduction	35
2.1	Terms of Reference and Purpose of the Report	35
2.2	Qualifications of Consultants	35
2.3	Details of Inspection	37
2.4	Sources of Information	38

2.5	Effective Date	38
2.6	Units of Measure	38
3	Reliance on Other Experts	39
4	Property Description and Location	40
4.1	Property Location	40
4.2	Ownership	42
5	Accessibility, Climate, Local Resources, Infrastructure and Physiography	44
5.1	Accessibility	44
5.2	Climate	44
5.3	Local Resources and Infrastructure	44
5.4	Physiography	44
5.5	Infrastructure Availability and Sources	44
6	History	45
7	Geological Setting and Mineralization	47
7.1	Regional Geology	47
7.2	Local Geology	50
7.2.1	Lithology	50
7.2.2	Structure	57
7.2.3	Mineralization and Alteration	59
8	Deposit Type	61
8.1	Haile Genetic Model	61
8.2	Haile Geological Model	62
9	Exploration	63
9.1	Pre-Romarco	63
9.2	Romarco	63
9.3	OceanaGold Exploration	63
9.3.1	Geologic Mapping and Surface Sampling	63
9.3.2	Geophysics	64
10	Drilling	65
10.1	Type and Extent	65
10.2	Sample Collection	66
10.3	Collar Locations and Downhole Surveys	68
10.4	Significant Results and Interpretation	68
11	Sample Preparation, Analysis and Security	70
11.1	Sample Preparation for Analysis	70
11.1.1	Off-Site Sample Preparation	71

11.2 Sample Analysis.....	72
11.3 Check Assays	73
11.4 Quality Assurance/Quality Control Procedures	74
11.4.1 Standards	74
11.4.2 Blanks.....	74
11.4.3 Duplicates.....	74
11.4.4 Actions and Results.....	74
11.5 Opinion on Adequacy (Security, Sample Preparation, Analysis).....	74
12 Data Verification.....	76
12.1 Data Validation of Pre-Romarco Holes.....	76
12.2 Verification of Romarco and OceanaGold Data.....	77
12.3 Romarco Data Verification	77
12.4 Horseshoe Data Verification 2016	78
12.5 Haile QA/QC ALS July 2017-July 2020	80
12.5.1 July 2017- July 2020 CRM Performance	80
12.5.2 Contamination Monitoring	85
13 Mineral Processing and Metallurgical Testing	86
13.1 Testing and Procedures	87
13.1.1 Comminution	87
13.1.2 Flotation and Cyanidation.....	90
13.1.3 Sample Representativeness	100
13.2 Recovery Estimate Assumptions	101
14 Mineral Resource Estimate	103
14.1 Open Pit Mineral Resources Estimate	103
14.1.1 Drillhole Database	104
14.1.2 Geologic Model Concepts	104
14.1.3 Lithology	105
14.1.4 Silicification.....	105
14.1.5 Pyrite	105
14.1.6 Grade Domain Construction.....	105
14.1.7 Compositing	106
14.1.8 Assay Cap Values	106
14.1.9 Multiple Indicator Gold Class Thresholds and Means.....	107
14.1.10 Variogram Analysis and Modeling	107
14.1.11 Block Model.....	107
14.1.12 Estimation Methodology Gold, Sulfur and Carbon.....	107
14.1.13 Estimation Methodology Silver.....	108

14.1.14	SG	109
14.1.15	Resource Classification	110
14.1.16	Model Validation	110
14.1.17	Resource Model Reconciliation	113
14.1.18	Mineral Resource Statement	114
14.2	Underground Mineral Resource Estimate.....	114
14.2.1	Horseshoe	114
14.2.2	Palomino Resource Estimate	126
14.3	Open Pit and Underground Combined Mineral Resource Statement.....	127
14.4	Relevant Factors	127
15	Mineral Reserve Estimate.....	129
15.1	Open Pit Mineral Reserve Estimate.....	129
15.1.1	Introduction.....	129
15.1.2	Conversion Assumptions, Parameters and Methods.....	130
15.1.3	Reserve Estimate	131
15.2	Underground Mineral Reserve Estimate.....	132
15.2.1	Introduction.....	132
15.2.2	Conversion Assumptions, Parameters and Methods.....	133
15.2.3	Reserve Estimate	135
15.3	Open Pit and Underground Combined Reserves Statement.....	136
16	Mining Methods.....	138
16.1	Open Pit Mining Methods.....	138
16.1.1	Current or Proposed Mining Methods	138
16.1.2	Parameters Relevant to Mine or Pit Designs and Plans	139
16.1.3	Optimization	146
16.1.4	Mine Design	149
16.1.5	Overburden/Geochemical	152
16.1.6	Mine Production Schedule	156
16.1.7	Mining Fleet and Requirements	164
16.1.8	Labor	166
16.1.9	Mine Dewatering	166
16.2	Underground Mining Methods.....	168
16.2.1	Cut-off Grade Calculations	169
16.2.2	Geotechnical	171
16.2.3	Hydrogeology and Mine Dewatering	188
16.2.4	Geochemical	188
16.2.5	Stope Optimization	198

16.2.6 Mine Design	198
16.2.7 Productivities	203
16.2.8 Mine Production Schedule	207
16.2.9 Mining Operations	210
16.2.10 Ventilation	217
16.2.11 Mine Services.....	223
16.3 Combined Open Pit and Underground Production Schedule	228
17 Recovery Methods	230
17.1 Processing Methods.....	230
17.2 Processing Flowsheet.....	232
17.3 Operational Results.....	234
17.4 Process Unit Costs.....	236
18 Project Infrastructure.....	239
18.1 Tailing Storage Facility.....	239
18.2 Overburden Storage.....	243
18.3 Potential Acid Generating (PAG) Overburden Storage Areas.....	245
18.4 Site Wide Water Management.....	248
18.5 Site Wide Water Balance	250
18.6 Surface Roads and Bridges.....	251
18.7 Underground Access.....	251
18.8 Ancillary Facilities.....	253
18.9 Power Supply	254
18.10 Water Supply.....	254
19 Market Studies and Contracts	255
20 Environmental Studies, Permitting and Social or Community Impact.....	257
20.1 Required Permits and Status	259
20.2 Environmental Studies	260
20.3 Environmental Issues.....	262
21 Capital and Operating Costs.....	263
21.1 Capital Cost Estimates.....	263
21.1.1 Basis for Capital Cost Estimates.....	263
21.2 Operating Cost Estimates	265
21.2.1 Basis for Operating Cost Estimates	266
22 Economic Analysis	270
22.1 Principal Assumptions and Input Parameters.....	270
22.2 Cashflow Forecasts and Annual Production Forecasts	270

22.2.1 Mine Production	270
22.2.2 Mill Production	272
22.2.3 Revenue	273
22.2.4 Operating and Capital Costs	274
22.2.5 Economic Results	275
22.3 Taxes, Royalties and Other Interests	279
22.4 Sensitivity Analysis	280
22.4.1 Operational Sensitivity	280
22.4.2 Gold Price Sensitivity	281
22.4.3 Consensus Pricing Model Result	282
22.4.4 Discount Rate Sensitivity	283
23 Adjacent Properties	285
23.1 Ridgeway Mine	285
23.2 Brewer Mine	285
23.3 Barite Hill Mine	286
24 Other Relevant Data and Information	287
25 Interpretation and Conclusions	288
25.1 Geology and Mineralization	288
25.2 Resource Estimation	288
25.2.1 Open Pit	288
25.2.2 Underground	288
25.3 Status of Exploration, Development and Operations	289
25.4 Mining and Reserves	289
25.4.1 Open Pit	289
25.4.2 Underground	289
25.5 Mineral Processing and Metallurgical Testing	290
25.6 Recovery Methods	290
25.7 Project Infrastructure	291
25.7.1 Underground Support Infrastructure	291
25.8 Environmental Studies and Permitting	291
25.9 Economic Analysis	291
26 Recommendations	292
26.1 Recommended Work Programs	292
26.1.1 Geology and Mineralization	292
26.1.2 Resource Estimation	292
26.1.3 Status of Exploration; Development and Operations	293
26.1.4 Mining and Reserves	293

26.1.5 Mineral Processing and Metallurgical Testing.....	294
26.1.6 Project Infrastructure	294
26.1.7 Environmental Study Results	295
26.1.8 Economic Analysis	296
26.2 Recommended Work Programs Costs	296
27 References.....	298
28 Glossary.....	304
28.1 Mineral Resources	304
28.2 Mineral Reserves	304
28.3 Definition of Terms	305
28.4 Abbreviations	306

List of Tables

Table 1-1: Open Pit Mineral Resources as of June 30, 2020.....	18
Table 1-2: Horseshoe Underground Mineral Resource Statement as of June 30, 2020, OceanaGold.....	19
Table 1-3: Palomino Underground Mineral Resource Statement as of June 30, 2020.....	19
Table 1-4: Haile Combined Open Pit and Underground Resource Statement as of as of June 30, 2020	20
Table 1-5: Haile Open Pit Mineral Reserves Estimate as of June 30, 2020	21
Table 1-6: Haile Horseshoe Underground Reserves Estimate as of June 30, 2020	22
Table 1-7: Reserve Statement for OceanaGold’s Haile Gold Mine as of June 30, 2020.....	22
Table 1-8: Major Equipment Required to Achieve the Mine Schedule.....	26
Table 1-9: Horseshoe Mine Production Annual Mining Schedule	28
Table 1-10: Total Capital Cost Summary (US\$000).....	30
Table 1-11: RoM Operating Cost Summary	30
Table 1-12: RoM Indirect Costs Summary	31
Table 2-1: Site Visit Participants.....	37
Table 7-1: Geological Summary of Major Gold Deposits of SE USA.....	50
Table 10-1: Haile Drilling Campaigns by Year, Owner and Lab.....	65
Table 12-1: Number of Standards Inserted by Year.....	77
Table 13-1: Bond Ball Mill Work Indices (Wi) for Haile Samples.....	87
Table 13-2: Bond Rod and Ball Mill Work Indices for Haile Composite	87
Table 13-3: Rod and Ball Mill Work Indices for Ledbetter Extension Samples	88
Table 13-4: Rod & Ball Mill Work and Abrasion Indices for Horseshoe Samples	88
Table 13-5: ALS Comminution Tests on Horseshoe Samples	88
Table 13-6: ALS Comminution Tests on Mill Zone Pit Samples.....	88
Table 13-7: ALS Comminution test results for 2018 Infill Sample Program	90

Table 13-8: RDi Whole-Ore Leach Test Results	91
Table 13-9: Flotation Test Results – Averages by Grind.....	92
Table 13-10: Flotation Test Results Average by Grade and Grind	92
Table 13-11: Flotation Tailing Leach Test Results Average by Grade and Grind	93
Table 13-12: Test Results for Flotation and Leaching.....	95
Table 13-13: Gold Recovery by Ore Zone and Ore Grade	96
Table 13-14: CIL Test Results for Fine Ground Flotation Concentrate	96
Table 13-15: Tests Results for Composites from Mill Zone and Snake areas	97
Table 13-16: Test Results for Horseshoe Samples.....	98
Table 13-17: Test Results for Horseshoe Samples.....	98
Table 14-1: Sample Numbers for Gold, Sulfur and Carbon	104
Table 14-2: Indicator Gold Class Thresholds and Means	107
Table 14-3: HA0520OLM Block Model Dimensions	107
Table 14-4: HGM16 Block Search Parameters	108
Table 14-5: HA0520OLM SG Assignment.....	110
Table 14-6: Resource Model Reconciliation.....	114
Table 14-7: Open Pit Total Mineral Resources as of 30 June 2020	114
Table 14-8: Densities Assigned in the Block Model	116
Table 14-9 Basic Statistics for 3 m Composites Within 1 g/t Au Indicator Shell	116
Table 14-10: HUG Grid Transformation Details	117
Table 14-11: Block Model Dimensions and Origin	118
Table 14-12: Au Grade Estimation Search Distances.....	118
Table 14-13: Ordinary Kriging Parameters.....	119
Table 14-14: Horseshoe Underground Mineral Resource Statement as of June 30, 2020	124
Table 14-15: Mineral Resource Sensitivity	125
Table 14-16: Palomino Underground Mineral Resource Statement as of June 30, 2020.....	127
Table 14-17: Haile Combined Open Pit and Underground Resource Statement June 30, 2020.....	127
Table 15-1: Haile Underground Coordinate Transformation Details	129
Table 15-2: Pit Optimization Parameters.....	130
Table 15-3: Haile Open Pit Reserve Checklist.....	130
Table 15-4: Haile Open Pit Mineral Reserves Estimate as of June 30, 2020	132
Table 15-5: Dilution ELOS Assumptions	135
Table 15-6: Mine Design Dilution Factors	135
Table 15-7: Haile Horseshoe Underground Reserves Estimate as of June 30, 2020	136
Table 15-8: Reserve Statement for OceanaGold’s Haile Gold Mine as of June 30, 2020	137
Table 16-1: ISA Recommendations for Near Surface Materials	142
Table 16-2: Mill Zone ISA Recommendations for Metasediments and Diabase Dikes.....	142

Table 16-3: Mill Zone ISA Recommendations for Metavolcanics.....	142
Table 16-4: ISA Recommendations for Metasediments and Diabase Dikes – Snake, Haile, Red Hill, and Ledbetter Pits.....	143
Table 16-5: ISA Recommendations for Metavolcanics – Snake, Haile, Red Hill, and Ledbetter Pits.....	143
Table 16-6: Summary of Rock Mass Properties.....	144
Table 16-7: Optimization Results for Selected Shell on \$75 Gold Price Increments	148
Table 16-8: Pit Optimization Parameters.....	149
Table 16-9: Grade Tonnage Curve within the Pit Design (not diluted).....	151
Table 16-10: Current Open Pit and Adopted UG Overburden Classification at Haile.....	153
Table 16-11: Cut-off Grade Calculation.....	156
Table 16-12: Phase Inventory (1/1/2022 to End of Mine Life)*	157
Table 16-13: Open Pit Production Summary.....	158
Table 16-14: Mine (UG + OP) and Mill Production Schedule.....	159
Table 16-15: LoM Yearly Bench Sinking Rates.....	162
Table 16-16: Rimpull Curve Representing Truck Speeds by Gradient	163
Table 16-17: Annual Truck Cycle Times and Distances	164
Table 16-18: Estimation of Scheduled Hours per Year for a Typical Year.....	164
Table 16-19: Factors in Estimation of Potential Operating Hours for a Typical Year.....	165
Table 16-20: Major Equipment Required to Achieve the Mine Schedule.....	166
Table 16-21: Labor Levels in 2021	166
Table 16-22: Underground Cut-off Grade Calculation.....	169
Table 16-23: Discontinuity Orientation Data for 2014 Geotechnical*	172
Table 16-24: Summary of the Laboratory Tests.....	172
Table 16-25: Summary of Point Load (IS_{50}) Test Results.....	174
Table 16-26: Summary of Strength Properties (m_i and σ_{ci}).....	175
Table 16-27: Summary of Elastic Properties (E_i and ν).....	175
Table 16-28: Summary of Rock Mass Quality by Domain.....	176
Table 16-29: Summary of Dilution ELOS Estimates	179
Table 16-30: Design Parameters for Different Drift Types	181
Table 16-31: Summary of Rock Quality for Each Ground Support Type	181
Table 16-32: Current Open Pit, and adopted UG Overburden Classification at Haile	189
Table 16-33: Backfill Samples	191
Table 16-34: Mine Design Summary – by Activity Type.....	203
Table 16-35: Productivity Rates	204
Table 16-36: Schedule Parameters for Underground Mining.....	204
Table 16-37: Material Characteristics.....	204
Table 16-38: Horseshoe Mine Production Annual Mining Schedule.....	207

Table 16-39: Detailed Mine Production Schedule	210
Table 16-40: LoM Backfill Quantities.....	215
Table 16-41: General Ventilation Modeling Parameters	218
Table 16-42: Cemented Rock Fill Equipment Load and Minimum Airflow Calculation	219
Table 16-43: Paste Fill Equipment Load and Minimum Airflow Calculation.....	219
Table 16-44: Main Fan Requirements	222
Table 16-45: Mine Labor by Year	227
Table 16-46: Owner and Contractor Workforce Distribution	227
Table 16-47: Mobile Equipment Fleet.....	228
Table 16-48: Combined Open Pit and Underground Production Schedule*	229
Table 17-1: Key Consumable Consumption Rates	237
Table 20-1: Mine Permits.....	258
Table 20-2: Environmental Permits	259
Table 20-3: Environmental Studies	260
Table 21-1: Total Capital Cost Summary (US\$000).....	263
Table 21-2: Open Pit Mining Equipment Capital Leasing – Indirect Costs	263
Table 21-3: Open Pit Mining Capital.....	264
Table 21-4: Underground Capital Cost Summary	264
Table 21-5: Other Capital	265
Table 21-6: RoM Operating Cost Summary	265
Table 21-7: RoM Indirect Costs Summary	266
Table 21-8: Open Pit Mining Cost Summary	267
Table 21-9: Underground Mining Cost Summary	267
Table 21-10: Summary of Process Operating Costs.....	268
Table 21-11: General and Administration Cost Summary (US\$000's).....	269
Table 21-12: Indirect Cost Summary.....	269
Table 22-1: Basic Model Parameters	270
Table 22-2: Life-of-Mine Production Summary.....	271
Table 22-3: Life-of-Mine Process Production Summary.....	272
Table 22-4: RoM Operating Cost Summary	274
Table 22-5: RoM Indirect Costs Summary	274
Table 22-6: Life-of-Mine Capital Costs (000's).....	275
Table 22-7: Indicative Economic Results	276
Table 22-8: RoM AISC Contribution	278
Table 22-9: Haile Tax Deductions (US\$000).....	280
Table 22-10: Indicative Economic Results (Consensus Pricing).....	283
Table 26-1: Environmental Studies	295

Table 26-2: Summary of Costs for Recommended Work.....	297
Table 28-1: Definition of Terms	305
Table 28-2: Abbreviations.....	306

List of Figures

Figure 1-1: Final Pit Design and Site Layout.....	24
Figure 1-2: LoM Production Schedule	25
Figure 1-3: Mine Production Schedule Colored by Year	28
Figure 4-1: General Location Map of the Haile Gold Mine	40
Figure 4-2: Site Map of the Haile Gold Mine. Background Imagery from Mar. 22, 2019	41
Figure 4-3: Land Tenure Map	43
Figure 7-1: Time Distribution of Major Geological Events in the Carolinas.....	48
Figure 7-2: District Geology of North-Central South Carolina (UTM NAD83 Z17N)	53
Figure 7-3: Geologic Map of the Haile Area with Gold Zones (UTM NAD83 Z17N)	54
Figure 7-4: Haile Stratigraphic Column	55
Figure 7-5: Plan View of Drillholes used for Resource Estimation, Gold Mineralization, and EOY 2019 Reserve Pit Limit (Sections A-A' and B-B' are Presented in Figure 7-6)	56
Figure 7-6: Cross-sections A-A' (NE-looking) and B-B' (NW-looking) with Geology, Gold Mineralization, and Pit Design	57
Figure 7-7: High Strain Fabrics in Core Samples.....	58
Figure 12-1: Box and Whiskers Plots for Horseshoe 2016 Standards and Blanks	78
Figure 12-2: Horseshoe AuFA_grav KML vs. ALS 0-53 g/t (n=253)	79
Figure 12-3: July 2017-Current CRM Analyses versus Expected Value (n=1,457)	81
Figure 12-4: July 2017-Current CRM Analyses versus Expected Value <4 g/t (n=1,444)	82
Figure 12-5: July 2017-Current, Control Chart, OxF125 (n=268).....	83
Figure 12-6: July 2017-Current, Control Chart, OxG124 (n=218)	83
Figure 12-7: July 2017-Current, Control Chart, SG84 (n=42)	84
Figure 12-8: July 2017-Current, Control Chart, HiSilk2 (n=63).....	84
Figure 12-9: July 2017-Current Blank Insertions (n=1,363)	85
Figure 13-1 Modelled vs Measured SAG Specific Energy Values	89
Figure 13-2: Overall Percent Recovery vs. Head Grade.....	100
Figure 13-3: Plant Gold Recovery Performance Jun-Aug 2020	102
Figure 14-1: Estimation Domains	106
Figure 14-2: Silver Gold Relationship for Gold Ranked Percentile Averaged Grades.....	109
Figure 14-3: Swath Plot with Mean Composite Gold Grade vs HA0520OLM Block Values	111
Figure 14-4: Swath Plot with Mean Composite Carbon Grade vs HA0520OLM Block Values.....	112
Figure 14-5: Swath Plot with Mean Composite Sulfur Grade vs HA0520OLM Block Values	112

Figure 14-6: Swath Plot with Mean Composite Silver Grade vs HA0520OLM Block Values.....	113
Figure 14-7: Log Normal Cumulative Distribution Plot of Gold Assays Above 2 g/t.....	117
Figure 14-8: Global Grade Tonnage Comparison between 2019 and 2020 Models	120
Figure 14-9: Upper Domain Easting Swath Plot.....	121
Figure 14-10: Lower Domain RI Swath Plot	122
Figure 14-11: Representative Cross Section with Estimated Au Grades (Viewing E90°).....	122
Figure 14-12: Representative Cross Section Showing Indicated Wireframe around Pass 1 Estimated Blocks (Viewing N90°E)	123
Figure 14-13: Representative Cross Section Showing Resource Classification (Viewing N90°E)	124
Figure 14-14 Sensitivity of Indicated Resource Tonnes and Grade to Cut-off.....	125
Figure 15-1: General Site Layout and Location of the UG Reserve Area	133
Figure 15-2: UG Design Sill Levels (local grid)	134
Figure 16-1: Haile Open Pit Naming Convention	138
Figure 16-2: Example Overall Analysis: Cross-Section LB4 for the Southeast Wall of the Ledbetter Pit.....	144
Figure 16-3: Example of 3D Overall Analysis: Northwest Corner of the Ledbetter Pit.....	145
Figure 16-4: Section View Through Critical Mass of 3D Overall Analysis of Northwest Corner of the Ledbetter Pit.....	146
Figure 16-5: Pit Optimization Tonnes by Revenue Factor	147
Figure 16-6: LoM Pit Design.....	150
Figure 16-7: Grade Tonnage Curve within Reserve Pit (Measured and Indicated Material)	151
Figure 16-8: Final Pit Design and Ultimate Overburden Storage Site Plan	155
Figure 16-9: Annual Production Schedule.....	160
Figure 16-10: Material Type Annual Schedule	161
Figure 16-11: Horseshoe Upper and Lower Mineralized Zones.....	168
Figure 16-12: Haile Underground Block Model and Mineralization Extents.....	170
Figure 16-13: Horseshoe Underground Model Grade/Tonne Curve Based on Au Cut-off	171
Figure 16-14: Horseshoe 2020 Underground Workings with As-Drilled Characterization Core Holes.....	173
Figure 16-15: Geotechnical Model Cross Section.....	174
Figure 16-16: Snake Pit Showing Slopes Above Proposed Horseshoe UG Portal Locations	177
Figure 16-17: Plan View of Planned Workings Showing Dikes (local grid)	177
Figure 16-18: Plan View of 930 Level Showing Proximity of Footwall Access Drifts to Planned Stopes	178
Figure 16-19: General Ground Support Drawing for Level Assesses and Decline Drifts with Arched Back	183
Figure 16-20: Sill Pillars (Red Stopes) to be Extracted Late in Mining Sequence	184
Figure 16-21: Plan View of Vertical Displacements Representing Surface Subsidence	185
Figure 16-22: Ground Support Drawing for Decline Drift at Portal 1.....	187
Figure 16-23: Horseshoe FS/PEA Lithological Distribution of Samples.....	190
Figure 16-24: NP/AP for Horseshoe Development Rock	194
Figure 16-25: NNP vs. Total Sulfur for Horseshoe Development Rock	194
Figure 16-26: Location of PEA and FS Geochemical Samples Color Coded using Haile Criteria.....	196

Figure 16-27: Level Cross Section of Stopes.....	199
Figure 16-28: Slope Cross Section	199
Figure 16-29: Underground Portal Location (shown in the OP coordinate system).....	200
Figure 16-30: Typical Level Section	201
Figure 16-31: Main Ramp Design Detail	201
Figure 16-32: Horseshoe Completed Mine Design, colored by activity type (looking South)	202
Figure 16-33: Mine Production Schedule Colored by Year (looking NW)	208
Figure 16-34: Ore Tonnes by Activity Type	209
Figure 16-35: All Material Tonnes	209
Figure 16-36: Crushing and Screening Plant for Backfill Aggregate.....	214
Figure 16-37: CRF Backfill Plant	215
Figure 16-38: Level Section Showing Planned Diamond Drilling from Footwall Access Drifts	216
Figure 16-39: Cross Section View of Development Rounds and Proposed Channel Sampling Locations ...	217
Figure 16-40: Ventilation System Layout.....	221
Figure 16-41: Dewatering System Layout	223
Figure 16-42: Portable Pumping Skids.....	225
Figure 16-43: Electrical System Layout.....	226
Figure 16-44: Combined Open Pit and Underground Production	228
Figure 17-1: Haile Process Flow Sheet.....	233
Figure 17-2: Mill Throughput Performance Since Startup	234
Figure 17-3: SAG Mill Utilization Since Startup	234
Figure 17-4: Flotation Circuit Recovery	235
Figure 17-5: Gold Recovery Performance Since Startup	236
Figure 17-6: Process Unit Cost History Since Startup	237
Figure 18-1: Tailing Storage Facility Layout.....	241
Figure 18-2: Tailing Storage Facility Typical Section	242
Figure 18-3: Overburden Storage Areas Plan.....	244
Figure 18-4: West PAG Overburden Storage Area	246
Figure 18-5: East PAG Overburden Storage Area Expansion	247
Figure 18-6: As Built Fresh Water Storage Dam.....	249
Figure 18-7: Portal Access	251
Figure 18-8: Production Portal Layout.....	252
Figure 18-9: Layout for Ventilation Portals Area	252
Figure 18-10: Underground Surface Infrastructure Detail	253
Figure 20-1: Reclamation Bond and Reclamation Bridge	262
Figure 22-1: Annual Open Pit Mine Production	271
Figure 22-2: Annual Open Pit and Underground Ore Production	272

Figure 22-3: Annual Process Plant Production	273
Figure 22-4: Project After-Tax Metrics Summary	277
Figure 22-5: Annual AISC Curve Profile.....	279
Figure 22-6: Operational Sensitivity Analysis.....	281
Figure 22-7: Gold Price Sensitivity Analysis.....	282
Figure 22-8: Discount Rate Sensitivity Analysis.....	284

Appendices

Appendix A: Certificates of Qualified Persons

Appendix B: LoM Annual Cash Flow Forecast

1 Summary

This National Instrument 43-101 (NI 43-101) Technical Report (Technical Report) was prepared for OceanaGold Corporation (OceanaGold) to a feasibility study (FS) level by SRK Consulting (U.S.), Inc. (SRK) on the Haile Gold Mine (Haile or Project). This report includes both open pit and underground mining components and a single economic analysis based on open pit and underground reserves as of June 30, 2020.

1.1 Property Description and Ownership

The Haile gold mine is 100% owned and operated by OceanaGold. Haile is located 5 km northeast of Kershaw in southern Lancaster County, South Carolina. The Haile property site is 30 km southeast of Lancaster, the county seat, and 80 km northeast of Columbia, the state capital of South Carolina. Haile Gold Mine Inc. (HGM) is a wholly owned subsidiary of OceanaGold Corporation (OceanaGold). As of June 30, 2020, HGM owns a total of 11,478 acres in South Carolina with no royalties. Of this total, 4,552 acres are within the mine permit boundary. Proposed expansion in the Supplemental Environmental Impact Statement (SEIS) will increase the mine property to 5,432 acres.

1.2 Geology and Mineralization

Haile is situated within the northeast-trending Carolina Terrane, also known as the Carolina Slate Belt, which also hosts the past-producing Ridgeway, Brewer and Barite Hill gold mines in South Carolina. Haile is the largest gold deposit (4.3 Moz resource) in the eastern USA. The Haile district consists of nine en echelon gold deposits within a 3.5 km by 1 km area. Haile occurs within a variably deformed ENE-trending structural zone at or near the contact between metamorphosed Neoproterozoic volcanic and sedimentary rocks. Haile is hosted in laminated siltstones and minor volcanic rocks of the upper Persimmon Fork Formation and is dissected by barren NNW-striking diabase dikes. Deformation includes brittle and ductile styles with ENE-trending foliation, faults, brecciation, and isoclinal folds. Sedimentary rocks are folded within an ENE-trending anticlinorium with a steep SE limb and a gentle NW limb. Gold mineralization dated at ~549 Ma (Mobley et al., 2014) postdates peak volcanism and predates the Alleghanian greenschist facies metamorphic deformation. Timing of gold mineralization coincides with a major tectonostratigraphic change from intermediate volcanism and tuffaceous and epiclastic sedimentation to basinal turbiditic sedimentation. Quartz-sericite-pyrite alteration is overprinted by regional greenschist facies metamorphism with carbonate-chlorite-pyrite alteration. Haile is classified as a low-sulfidation, sediment-hosted, disseminated, epithermal gold deposit.

1.3 Status of Exploration; Development and Operations

Resource definition drilling at Haile by Romarco Minerals and OceanaGold has increased the resources more than five-fold since 2007. Reserve growth has been stimulated by 3D geologic models, higher gold prices, and aggressive, deep drilling of a previously underexplored gold system. This is exemplified by pre-development of the Horseshoe underground reserve in 2017 (0.44 Moz) and announcement of a maiden Inferred resource at Palomino in 2020 (0.6 Moz). In-house core drilling continues by OceanaGold at about 15 km per year, focused on pit design margins and high-grade underground targets proximal to the sedimentary-volcanic contact. Underground development of the Horseshoe deposit in 2022 will provide access to underground drill stations along the prospective one km long Horseshoe-Palomino trend.

1.4 Mineral Processing and Metallurgical Testing

Samples of ore were collected by Haile Gold Mine, Inc. (HGM) for metallurgical testing which indicated that the ore will respond to flotation and direct agitated cyanide leaching technology to extract gold.

Comminution test work on mineralized samples was performed by RDi, and ALS Limited (ALS). Tests included Bond work indices and Sag Mill Comminution (SMC) and JK Drop Weight impact testing. The results of the test work were used for additional power modelling to predict circuit throughputs with a modified SABC grinding circuit that was subsequently commissioned in 2018.

Laboratory testing on ore composite samples demonstrated that the mineralization was readily amenable to flotation and cyanide leaching process treatment. A conventional flotation and cyanide leaching flow sheet can be used as the basis of process design.

The relative low variability of test work indicates that the different mineralized zones are similar in terms of ore grindability, mineral composition, and flotation and cyanide leaching response.

Overall gold recovery will be in the range of 65% to 92% dependent primarily on head grade to the mill and less related to which zone the ore is mined from.

The data developed in the test programs has been used to establish a relationship between overall gold recovery and head grade. Operating experience and metallurgical development programs have indicated this relationship is valid and is expected to be slightly exceeded over the LoM.

1.5 Mineral Resource Estimate

The Mineral Resources at Haile comprise both open pit and underground resources. Separate block models were generated for the open pit and underground areas.

OceanaGold knows of no existing environmental, permitting, legal, socio-economic, marketing, political, or other factors that might materially affect the Mineral Resource estimates.

1.5.1 Open Pit Mineral Resource Estimate

Drillhole data available in April 2020 were included in the HA0520OLM open pit resource estimate.

The assay coverage for gold covers all core and RC drilling. However, the collection of silver, carbon and sulfur assay data has largely been retrospective and is significantly sparser than for gold. Sulfur and carbon data are primarily used for the prediction of waste classification types. Sulfur grades are also used for mill feed sulfur estimates. Silver grade estimates are provided for metallurgical considerations (carbon stripping and electro-winning) as well as for revenue estimation, albeit silver is a minor contributor to revenue.

Gold estimation was constrained within implicitly modelled grade shells, approximating a 0.065 g/t gold indicator. Metasediment/metavolcanic contacts were not used to constrain gold estimation. Post-mineralization dikes were assigned zero grade.

Grades were estimated into 10mE x 10mN x 5mRI blocks using 2.5 m bench composites.

Grade estimation was done in Vulcan software, using Multiple Indicator Kriging (MIK) to produce E-Type estimates for gold.

MIK is well suited to estimating positively skewed grade distributions. Top caps of 50 g/t Au were used to temper mean grades for the top indicator class threshold.

Ordinary kriging was used for silver, sulfur and carbon estimates.

The Mineral Resources are classified as Measured, Indicated, Inferred Mineral Resources, based primarily on drillhole spacing.

The open pit Mineral Resources are shown in Table 1-1.

Table 1-1: Open Pit Mineral Resources as of June 30, 2020

Class	Tonnes (Mt)	Au Grade (g/t)	Contained Au (Moz)	Ag Grade (g/t)	Contained Ag (Moz)
Measured	3.2	1.35	0.14	2.61	0.27
Indicated	52.3	1.53	2.57	2.40	4.04
Measured & Indicated	56	1.52	2.71	2.41	4.30
Inferred	7.6	1.0	0.2	1.32	0.32

Source: OceanaGold

- Cut-off grade 0.45 g/t Au based on a gold price of US\$1,700/oz.
- Open pit resource is reported within a US\$1,700/oz optimized shell.
- Mineral Resources include Mineral Reserves and are reported on an in-situ basis.
- There is no certainty that Mineral Resources that are not Mineral Reserves will be converted to Mineral Reserves.
- All figures are rounded to reflect the relative accuracy and confidence of the estimates and totals may not add correctly.
- The open pit Mineral Resources were estimated under the supervision of Jonathan Moore, MAusIMM CP(Geo), a Qualified Person.

1.5.2 Underground Mineral Resource Estimate

Horseshoe

The Horseshoe resource estimation is based on the current drillhole database, interpreted lithologies, geologic controls and current topographic data. The resource estimate is supported by drilling and sampling current to April 22, 2020.

Gold estimation was constrained within implicitly modelled grade shells, approximating a 1.0 g/t gold indicator. The grade shells were constructed using interpreted trend planes of mineralization. Two dominant zones of mineralization were identified, an upper moderately northwest dipping zone and a lower near vertical zone.

Post-mineralization dikes were assigned zero grade. Metasediment/metavolcanic contacts were not used to constrain gold estimation.

Gold grades were estimated with Vulcan™ modelling software into 10mE x 10mN x 10mRI blocks (sub-blocked to 5mE x 5mN x 5mRI) using Ordinary Kriging with 3 m composites.

Densities, based upon core analyses, were assigned by rock type.

The Mineral Resources reported for the Horseshoe deposit are classified as Indicated and Inferred Mineral Resources, based primarily on drillhole spacing since all other supporting data is of good quality.

The Horseshoe Mineral Resource statement is based on the Ordinary Kriging (OK) model as presented in Table 1-2. The resource is not constrained within conceptual stope designs. A CoG of 1.26 g/t Au has been applied which assumes underground mining methods and is based on a gold price of US\$1,700/oz.

Table 1-2: Horseshoe Underground Mineral Resource Statement as of June 30, 2020, OceanaGold

Class	Tonnes (Mt)	Au Grade (g/t)	Contained Oz (Moz)
Measured	0.0	0.00	0.00
Indicated	3.3	4.95	0.53
Measured & Indicated	3.3	4.95	0.53
Inferred	2.1	4.4	0.3

Source: OceanaGold

- Cut-off grade 1.26 g/t Au based on a gold price of US\$1,700/oz.
- Spatially constrained by a 1 g/t Au indicator shell.
- Mineral Resources include Mineral Reserves and are reported on an in-situ basis.
- There is no certainty that Mineral Resources that are not Mineral Reserves will be converted to Mineral Reserves.
- All figures are rounded to reflect the relative accuracy and confidence of the estimates and totals may not add correctly.
- The underground Mineral Resources were estimated under the supervision of Jonathan Moore, MAusIMM CP(Geo), a Qualified Person.

Palomino

The Palomino resource estimation is based on the current drillhole database, interpreted lithologies, geologic controls and current topographic data. The resource estimation is supported by drilling and sampling current to November 11, 2019.

Gold estimation was constrained within implicitly modelled grade shells, approximating a 1.0 g/t gold indicator. Post-mineralization dikes were assigned zero grade. Metasediment / metavolcanic contacts were not used to constrain gold estimation.

Gold grades were estimated into 5mE x 5mN x 5mRI blocks with Vulcan™ modelling software using Ordinary Kriging on 3 m composites. Sub-blocking was not used.

Densities, based upon core analyses, were assigned by rock type.

The Mineral Resources reported for the Palomino deposit are classified as Inferred Mineral Resources, based primarily on drillhole spacing and geological understanding.

The Palomino Mineral Resource statement is presented in Table 1-3. The reported resource is constrained within a conceptual stope design based on a gold price of US\$1,700/oz, approximating a 1.37 g/t cut-off. All unclassified material within the conceptual design was assigned zero grade for the purposes of reporting.

Table 1-3: Palomino Underground Mineral Resource Statement as of June 30, 2020

Class	Tonnes (Mt)	Au Grade (g/t)	Contained Oz (Moz)
Measured	0.0	0.0	0.0
Indicated	0.0	0.0	0.0
Measured & Indicated	0.0	0.0	0.0
Inferred	6.9	2.7	0.6

Source: OceanaGold

- Cut-off grade 1.37 g/t Au based on a gold price of US\$1,700/oz.
- Mineral Resources are reported on an in-situ basis.
- There is no certainty that Mineral Resources that are not Mineral Reserves will be converted to Mineral Reserves.
- All figures are rounded to reflect the relative accuracy and confidence of the estimates and totals may not add correctly.
- The underground Mineral Resources were estimated under the supervision of Jonathan Moore, MAusIMM CP(Geo), a Qualified Person.

1.5.3 Combined Open Pit and Underground Resource Estimate

Table 1-4 presents the combined open pit and underground resource statement for the Haile Property.

Table 1-4: Haile Combined Open Pit and Underground Resource Statement as of as of June 30, 2020

Type	Class	Tonnes (Mt)	Au Grade (g/t)	Contained Au (Moz)	Ag Grade (g/t)	Contained Ag (Moz)
Open Pit	Measured	3.2	1.35	0.14	2.61	0.27
	Indicated	52.3	1.53	2.57	2.40	4.04
	Measured & Indicated	55.5	1.52	2.71	2.41	4.30
	Inferred	7.6	1.0	0.2	1.32	0.32
Underground	Measured	0.0	0.00	0.00		
	Indicated	3.3	4.95	0.53		
	Measured & Indicated	3.3	4.95	0.53		
	Inferred	9.0	3.1	0.9		
Combined	Measured	3.2	1.35	0.14	2.61	0.27
	Indicated	55.6	1.73	3.10	2.40	4.04
	Measured & Indicated	58.8	1.71	3.24	2.41	4.30
	Inferred	17	2.1	1.1	1.32	0.32

Source: OceanaGold

- Cut-off grades for the open pit, Horseshoe underground and Palomino underground are 0.45 g/t, 1.26 g/t and 1.37 g/t Au respectively, based on a gold price of US\$1,700/oz.
- Open pit resource is reported within a US\$1,700/oz optimized shell. Palomino is constrained within a conceptual stope design and Horseshoe underground is spatially constrained by a 1 g/t Au indicator shell.
- Mineral Resources include Mineral Reserves and are reported on an in-situ basis.
- There is no certainty that Mineral Resources that are not Mineral Reserves will be converted to Mineral Reserves.
- All figures are rounded to reflect the relative accuracy and confidence of the estimates and totals may not add correctly.
- The underground Mineral Resources were estimated under the supervision of Jonathan Moore, MAusIMM CP(Geo), a Qualified Person.

1.6 Mineral Reserve Estimate

1.6.1 Open Pit Mineral Reserves Estimate

The geological model was used without modification, as the block size in the model matched the SMU size of 10 m x 10 m x 5 m. This block size is currently considered appropriate for the loading units operating at Haile.

The open pit Ore Reserves are reported within a pit design based on open pit optimization results. The optimization included Measured, Indicated and Inferred Mineral Resource categories with a gold price of US\$1,500/oz Au. Subsequent to pit optimization, inferred material (approximately 10%) within the reserve pit was treated as waste and given a zero-gold grade. The overall pit slopes (interramp angle slopes) used for the design are based on operational level geotechnical studies and range from 32° to 45°. This includes a 5° allowance for ramps and geotechnical catch benches.

Measured Mineral Resources were converted to Proven Mineral Reserves and Indicated Mineral Resources were converted to Probable Mineral Reserves by applying the appropriate modifying factors, as described herein, to potential mining pit shapes created during the mine design process.

The open pit mine design process results in open pit mining reserves of 48.6 Mt with an average grade of 1.59 g/t. The Mineral Reserve statement, as of June 30, 2020 for the Haile Open Pit is presented in Table 1-5.

Table 1-5: Haile Open Pit Mineral Reserves Estimate as of June 30, 2020

Category	Tonnes (Mt)	Au (g/t)	Ag (g/t)	Au Contained (Moz)	Ag Contained (Moz)
Proven	3.01	1.37	2.54	0.13	0.25
Probable*	46.4	1.58	2.35	2.36	3.50
Proven + Probable	49.4	1.57	2.36	2.49	3.75

* Includes 722kt of stockpile material grading 1.23g/t Au and 1.78g/t Ag

Source: SRK

- Reserves are based on a US\$1,500/oz Au gold price.
- Open pit reserves are stated using a 0.45 g/t cut-off and assume full mine recovery.
- Metallurgical recoveries are based on a recovery curve $(1 - (0.2152 \cdot \text{Au grade}^{-0.3696})) + 0.025$ that equate to an overall recovery of 82%.
- Reserves are converted from resources through the process of pit optimization, pit design, production schedule and supported by a positive cash flow model.
- Reserves are inclusive of Mineral Resources. All figures are rounded to reflect the relative accuracy of the estimates. Totals may not sum due to rounding.
- 5% dilution at zero grade and 98% mining recovery was applied for 2020 and 2021 mine schedule. Remaining years open pit reserves are not diluted further to dilution inherent to the resource model and assume selective mining unit of 10 m x 10 m x 5 m.
- The open pit Mineral Reserves were estimated by Fernando Rodrigues, BS Mining, MBA, MMSAQP #01405, MAusIMM #304726 of SRK, a Qualified Person.

SRK knows of no existing environmental, permitting, legal, socio-economic, marketing, political, or other factors that might materially affect the open pit Mineral Reserve estimate.

1.6.2 Underground Mineral Reserves Estimate

The Project is currently being mined as an open pit mine. Mineralization extends down at depth and outside of the pit extents. This mineralization, not mined by the open pit, is assessed as an underground mine and is referred to as the Horseshoe deposit.

Based on the orientation, depth, and geotechnical characteristics of the mineralization, a transverse sublevel open stoping method (longhole) with ramp access is used. The stopes will be 20 m wide and stope length will vary based on mineralization grade and geotechnical considerations. A spacing of 25 m between levels is used. Cemented rock fill (CRF) will be used to backfill the stopes. There will be an opportunity for some non-cemented waste rock to be used in select stopes based on the mining sequence. The CRF will have sufficient strength to allow for mining adjacent to backfilled stopes.

The deposit has been divided into three production areas. The uppermost block extends from approximately the 930 m elevation to 1,030 m elevation and includes four stoping levels that will be mined bottom up. The mid-block extends from approximately the 850 m elevation to the 930 m elevation and includes three stoping levels that will be mined bottom up. The uppermost level in this block includes mining out of the sill. The lowest block extends from approximately the 780 m elevation to the 930 m elevation. It includes three stoping levels that are also mined bottom up. The uppermost level in this block also includes mining out of the sill. A lower extraction has been used for sill levels.

The underground mine design process resulted in underground mining reserves of 3.4 Mt (diluted) with an average grade of 3.78 g/t Au. The Mineral Reserve statement, as of June 30, 2020, for the Haile Horseshoe Underground is presented in Table 1-6.

This estimate is based on a mine design cut-off of 1.44 g/t Au. The numbers include a 94% to 100% mining recovery based on type of opening (Stope, development, etc.) to the designed wireframes in addition to a 0% to 10% unplanned dilution using zero grade for dilution.

Mineral reserves were classified using the 2014 CIM Definition standards.

Table 1-6: Haile Horseshoe Underground Reserves Estimate as of June 30, 2020

Category	Tonnes (Mt)	Au (g/t)	Ag (g/t)	Au Contained (Moz)	Ag Contained (Moz)
Proven	-	-	-	-	-
Probable	3.42	3.78	-	0.42	-
Proven + Probable	3.42	3.78	-	0.42	-

Source: SRK

- Reserves are based on a gold price of US\$ 1,500/oz. Metallurgical recoveries are based on a recovery $(1 - (0.2152 \cdot \text{Au grade}^{-0.3696})) + 0.025$ that equates to an overall recovery of 88%.
- Underground reserves are stated using a 1.44 g/t Au cut-off. The reserve estimate is based on a mine design using an elevated cut-off grade of 1.67 g/t Au, with adjacent lower grade stopes included in the design. Incremental material is included in the reserves based on an incremental stope cut-off grade of 1.29 g/t Au and an incremental development cut-off grade of 0.38 g/t Au.
- Mining recovery ranges from 94% to 100% depending on activity type. Sill levels use a 75% recovery. Mining dilution is applied using zero grade. The dilution ranges from 2% to 10% depending on activity type.
- Reserves are inclusive of Mineral Resources. All figures are rounded to reflect the relative accuracy of the estimates. Totals may not sum due to rounding.
- Mineral Reserves have been stated on the basis of a mine design, mine plan, and cash-flow model.
- The Mineral Reserves were estimated by Joanna Poeck, BEng Mining, SME-RM, MMSAQP #01387QP, a Qualified Person.

1.6.3 Combined Open Pit and Underground Reserves Estimate

Table 1-7 presents the combined open pit and underground resource statement for the Haile Property.

Table 1-7: Reserve Statement for OceanaGold's Haile Gold Mine as of June 30, 2020

Type	Category	Tonnes (Mt)	Au Grade (g/t)	Au Grade (g/t)	Au Contained (Moz)	Ag Contained (Moz)
OP	Proven	3.01	1.37	2.54	0.13	0.25
	Probable*	46.4	1.58	2.35	2.36	3.50
	<i>Proven + Probable</i>	49.4	1.57	2.36	2.49	3.75
UG	Proven	-	-	-	-	-
	Probable	3.42	3.78	-	0.42	-
	<i>Proven + Probable</i>	3.42	3.78	-	0.42	-
OP + UG	Proven	3.01	1.37	2.54	0.13	0.25
	Probable	49.8	1.73	2.19	2.77	3.50
	Proven + Probable	52.8	1.71	2.21	2.91	3.75

*Includes 722kt of stockpile material grading 1.23 g/t Au and 1.78 g/t Ag

Source: SRK


- Mineral Reserves are based on a gold price of US\$ 1,500/oz. Metallurgical recoveries are based on a recovery curve $(1 - (0.2152 \cdot \text{Au grade}^{-0.3696})) + 0.025$ that equates to an overall recovery of 82% for the open pit material and 88% for the underground material.
- Open pit Mineral Reserves are stated using a 0.45 g/t Au cut-off and assume full mine recovery. 5% dilution at zero grade and 98% mining recovery was applied for 2020 and 2021 mine schedule. Remaining years open pit reserves are not diluted further to dilution inherent to the resource model and assume selective mining unit of 10 m x 10 m x 5 m.
- Open pit reserves are converted from resources through the process of pit optimization, pit design, production schedule and supported by a positive cash flow model.
- Underground reserves are stated using a 1.44 g/t Au cut-off. The reserve estimate is based on a mine design using an elevated cut-off grade of 1.67 g/t Au, with adjacent lower grade stopes included in the design. Incremental material is included in the reserves based on an incremental stope cut-off grade of 1.29 g/t Au and an incremental development cut-off grade of 0.38 g/t Au. Mining recovery ranges from 94% to 100% depending on activity type. Sill levels use a 75% recovery. Mining dilution is applied using zero grade. The dilution ranges from 2% to 10% depending on activity type.
- Mineral Reserves are inclusive of Mineral Resources. All figures are rounded to reflect the relative accuracy of the estimates. Totals may not sum due to rounding.
- Mineral Reserves have been stated on the basis of a mine design, mine plan, and cash-flow model.
- The open pit Mineral Reserves were estimated by Fernando Rodrigues, BS Mining, MBA, MMSAQP #01405, MAusIMM #304726 of SRK, a Qualified Person. The underground Mineral Reserves were estimated by Joanna Poeck, BEng Mining, SME-RM, MMSAQP #01387QP, a Qualified Person.

1.7 Mining Methods

1.7.1 Open Pit Mining Methods

Haile is currently being mined using conventional open pit methods. The open pit is located in gently undulating topography intersecting natural drainages that will require diversion to withstand high rainfall events during the summer months. Overburden type is calculated from blasthole sulfur and carbon assays and informs the routing and placement of materials. Red PAG is sent to geomembrane-lined facilities where the material will be placed in lifts and compacted by haulage trucks. At the completion of each lift, the face will be covered with saprolite prior to dozing to reclaimed slope angles. Yellow PAG can be stored in a lined facility or below a prescribed water table within pits. Yellow material in-pit will be mixed with lime before placement in the pit void.

The open pit that forms the basis of open pit reserves and life of mine (LoM) production schedule is approximately 2.5 km from east to west, 1.25 km north to south with a maximum depth of 370 m. The design consists of multiple pushbacks with ramp locations targeting saddle points between the pit bottoms and also acting as catch benches for geotechnical purposes. Each bench has at least one ramp for scheduling. Generally, the number of benches mined within a pit phase within a given year fall below the one bench per month target bench sinking rate. Figure 1-1 illustrates the site layout and final pit design.

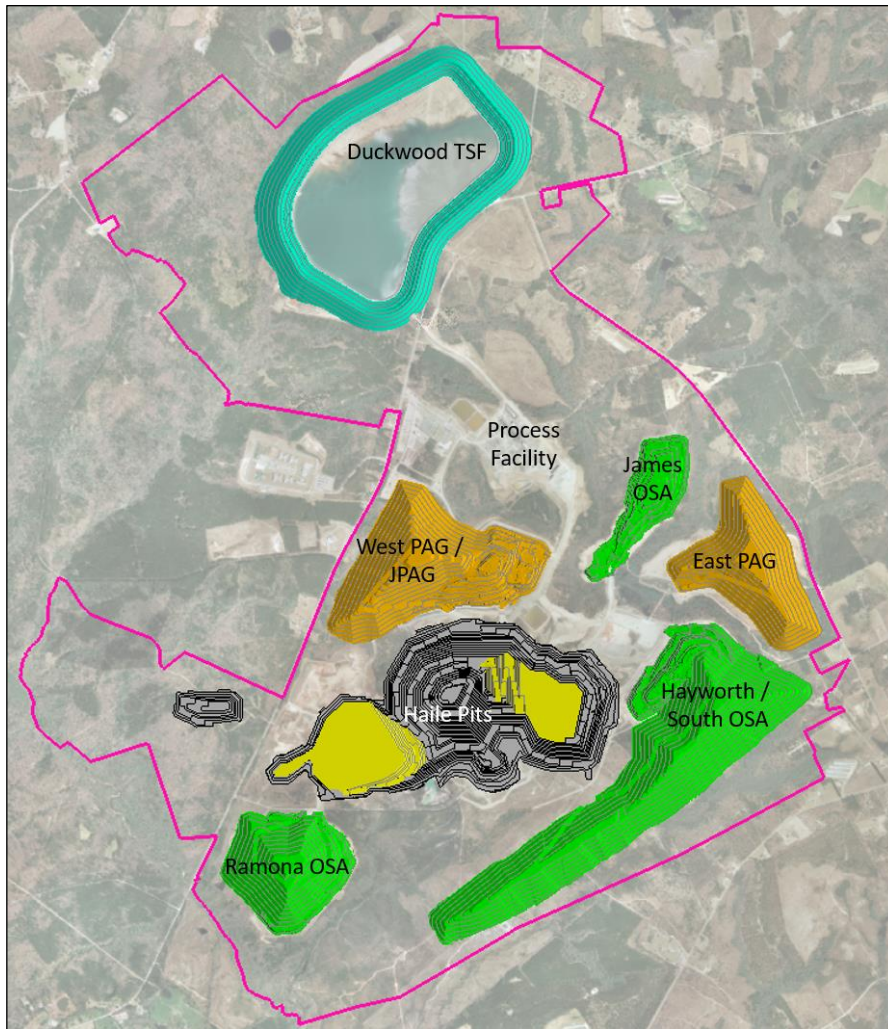


Yellow inside pits is backfill material.
Source: OceanaGold

Figure 1-1: Final Pit Design and Site Layout

2020 ore production rates are 4.0 million tonnes per annum (Mtpa) of ore delivered to the mill and 45 Mtpa of total material movement. Open pit production will stay around 4.0 Mtpa of ore and 45.0 Mtpa of total material movement through 2020 and 2021. Open pit ore production will decrease to about 3.5 Mtpa in 2022, after the Horseshoe underground mine has been started .

The mine production schedule (OP + UG) is summarized in Figure 1-2.

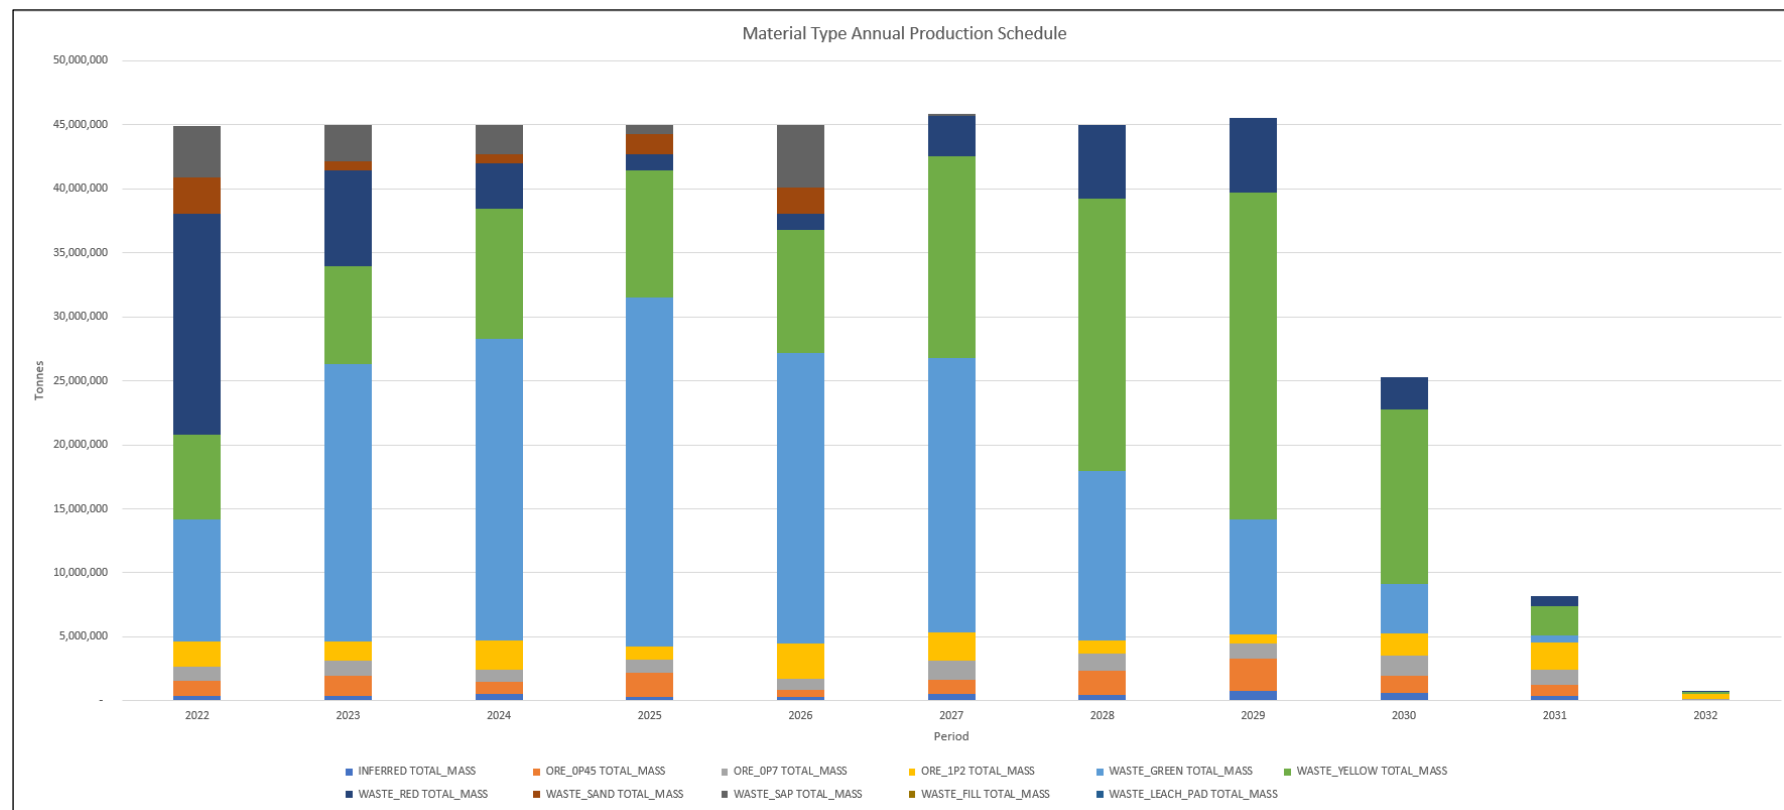

Source: SRK

Figure 1-2: LoM Production Schedule

The open pit loading and hauling equipment fleet consists of hydraulic excavators (Komatsu PC3000 and PC4000 models) and rigid frame haul trucks (CAT 777, CAT 785 and Komatsu 730). Blasthole drilling and wall control drilling is performed with a fleet of Sandvik DR410i and Epiroc D65 drills. Typical ancillary equipment, including track dozers, wheel dozers, motor graders and water trucks support the mining operation. Table 1-8 shows the major equipment required annually to achieve the mine schedule.

Table 1-8: Major Equipment Required to Achieve the Mine Schedule

Fleet	2021	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032	2033
PC4000 excavator	2	2	2	2	2	2	2	2	2	1	-	-	-
PC3000 excavator	1	1	1	1	1	1	1	1	1	1	1	1	-
Cat 993 loader	1	1	1	1	1	1	1	1	1	1	1	1	1
Cat 777 trucks	3	3	3	3	3	3	3	3	3	3	3	3	3
Cat 785 trucks	3	-	-	-	-	-	-	-	4	-	-	-	-
Komatsu 730 trucks	19	18	18	16	19	19	19	19	19	14	5	1	-
Sandvik DR410i drill	4	4	4	4	4	4	4	4	4	3	1	-	-
Epiroc D65 drill	3	3	3	3	3	3	3	3	3	2	1	1	-

Source: OceanaGold

1.7.2 Underground Mining Methods

Geotechnical

A geotechnical field characterization program has been undertaken to assess the expected rock quality. This program included logging core, laboratory strength testing, in situ stress measurements and oriented core logging of jointing. The results of this program have provided adequate quantity and quality of data for feasibility-level design of the underground workings.

A geotechnical assessment of the orebody shape and ground conditions has determined that longhole open stoping mining is an appropriate mining method. Stopes have been sized to maintain stability once mucked empty. A primary/secondary extraction sequence with tight backfilling allows optimization of ore recovery while maintaining ground stability. Primary stopes will be backfilled with cemented rockfill.

The design has been laid out using empirical design methods based on similar case histories. The stability of the design has been checked with 3D numerical stress-strain models of the workings which included consideration for mine-scale faulting. The modeling results confirm that stopes and access drifts are predicted to remain stable during active mining.

The 2020 updated underground design has conducted more detailed numerical modeling of the revised mine plan. These analyses used rock mass properties consistent with the geotechnical database, considering that no new data has been collected since 2017. Additional details of sill pillar extraction have been considered and a series of detailed ground support drawings have been developed for the underground workings and infrastructure. A detailed ground support design has been developed for the first portal and can be adopted for the second and third portal based on experience with ground conditions from the first portal. The updated design includes the main decline between the footwall of the Snake Pit and the Horseshoe orebody and the ground support design has

considered mining induced stresses as well as the presence of diabase dikes, especially at locations where the main decline crosses over ventilation declines with a sill in between.

Although the base case design considers cemented waste rock fill material for backfilling stopes, the option for using pastefill is still under consideration. There are operational and geotechnical advantages for using pastefill. However, until questions of environmental impact of cement encapsulated tailings waste can be fully addressed, the backfill design remains the use of cemented waste rock backfill of a specified 1 MPa strength. Pastefill would have a similar strength requirement, however, requires additional testing for cement contents.

Mine Design

Stope optimization was completed on prior versions of the model. Results from those prior runs were used for comparison during the mine design process. For the design, vertical slices were created through the orebody along 2 m strike length intervals. The model was then interrogated, filtered on cutoff, and then the slices were combined to create minable stopes. The mining method is transverse sublevel open stoping with cemented rockfill (CRF). Stope sizes, used in the optimization were 25 m high, 20 m wide, and varying stope length based on geotechnical considerations.

Each stope has a 4.5 m x 5 m access located at the bottom of the stope. Top accesses (also 4.5 m x 5 m) are designed to give access to stopes on the next level and to allow for backfilling. The stopes are drilled from the top and rings are blasted from the end of a stope toward the footwall access. The blasted material is remotely mucked from the stope access. A primary/secondary stoping sequence will be used. The stope accesses are connected to a level access located in waste material. The level accesses connect to the main ramp which is located in the footwall. Each level access is connected to the ventilation system. Ore will be remotely mucked from the bottom stope access using a 14.9-t LHD and loaded into 51-t trucks for haulage to surface.

The underground mine is accessed via a decline from the surface. The decline portal is located on an open pit bench approximately 70 m below the natural surface. Two ventilation drift portals are also located on an open pit bench.


The Horseshoe underground mine production schedule is based on the productivity rates developed from first principles which were adjusted based on benchmarking and the experience of OceanaGold personnel. The schedule was completed using Deswik scheduling software and is based on mining operations occurring 365 days/year, 7 days/week, with two 12 hour shifts each day. A production rate of approximately 2,000 t/d was targeted with ramp-up to full production as quickly as possible.

The underground permitting process is expected to be complete by mid-2021. Underground portal development is scheduled to begin in August 2021. Prior to portal development, open pit mining in the Snake Pit will have progressed sufficiently to allow access to the portal location. Portal development is required before the decline access can begin. First production from the stopes is scheduled to occur in January 2023 and will last through September 2027 based on the current Mineral Reserves. Table 1-9 shows the yearly production schedule and Figure 1-3 shows the mine production schedule colored by year.

Table 1-9: Horseshoe Mine Production Annual Mining Schedule

Year	Mineralized Tonnes (kt)	Au (g/t)	Waste Tonnes (kt)	Backfill Volume (m3)
2021			69.3	
2022	15.1	5.03	333.9	
2023	660.9	3.99	225.6	211,536
2024	750.9	4.07	128.1	263,313
2025	741.5	4.53	55.6	274,151
2026	738.2	3.26	7.1	293,306
2027	509.7	2.70	2.6	220,027
Total	3,416.3	3.78	822.1	1,262,333

Source: SRK

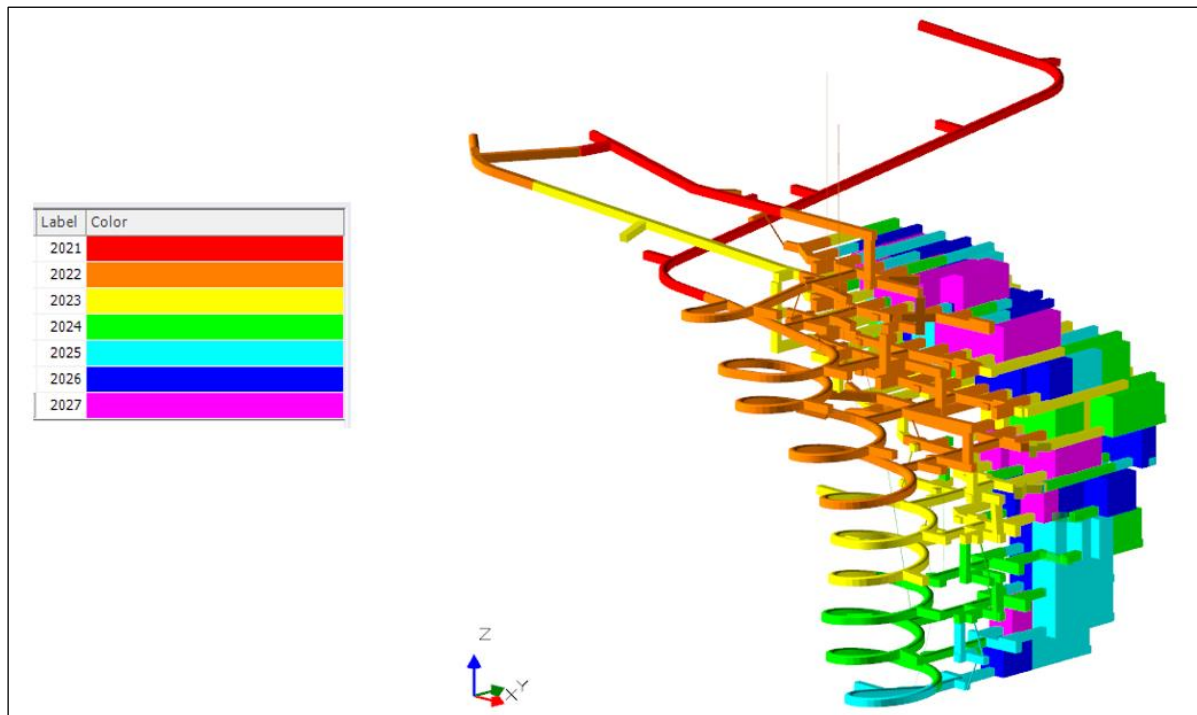

Source: SRK

Figure 1-3: Mine Production Schedule Colored by Year

1.8 Recovery Methods

The processing plant continues to utilize the conventional flowsheet developed in the feasibility study comprising:

- Primary Jaw Crushing
- Conventional SABC grinding circuit incorporating flash flotation on the cyclone underflow
- Rougher flotation
- Two stage concentrate regrind with a tower mill followed by an Isamill
- CIL leaching of reground concentrate and flotation tailings
- Carbon stripping, electrowinning and smelting of bullion
- Cyanide destruction

Additional equipment was installed in some areas of the plant between 2018-2020 to achieve the expanded capacity of 4.0 Mtpa.

1.9 Project Infrastructure

The permitted Duckwood Tailings Storage Facility (TSF) will be expanded to store plant tailings by raising the crest height. The existing permitted potentially acid generating (PAG) facilities will be expanded to store additional PAG material. Johnny's PAG (JPAG) Overburden Storage Area (OSA) will be expanded to the west (West PAG), and East PAG OSA will be expanded north and south of the existing footprint. The upper Haile Gold Mine Creek (HGMC) is reporting to the existing Fresh Water Storage Dam (FWSD) and is pumped around the proposed pits in a pipe and released into an unnamed tributary downstream of the pits.

The underground infrastructure required to support underground mining will include general buildings, upgrade and extension of the power lines and water supply. An underground run-of-mine (RoM) pad area will contain the stockpiles, CRF plant as well as a truck shop and laydown area.

1.10 Environmental Studies and Permitting

In late 2014, HGM received all of the major permits required for construction and operation of the current mine plan, including: Clean Water Act 404 Dredge and Fill Permit, Mine Operation Permit, 401 Water Quality Certification, TSF Dam Permit, North Fork Dam Permit, Air Permit (to construct), and various National Pollutant Discharge Elimination System (NPDES) Permits (wastewater treatment and storm water).

Haile is unique in that it occurs wholly on private land owned by HGM and does not impact federal/public (United States Department of the Interior Bureau of Land Management (BLM) or United States Forest Service (USFS)) lands that would be subject to projected modifications from these surface management agencies

There is a significant amount of existing background and environmental baseline data available for the Project. This data continues to be collected and reported to the regulators as part of operational controls. Additional data and environmental studies (Section 20.3) will be of technical interest to the federal and state agencies in evaluating a request to expand the current mining operation.

Permits currently held by the HGM may be kept, modified, terminated, or replaced during the expansion process.

OceanaGold will work closely with all key stakeholders to ensure that the permitting of the mine expansion meets all of the federal and state requirements.

1.11 Capital and Operating Costs

Capital Cost

The total LoM capital cost is US\$788 million as summarized in Table 1-10. Initial capital is \$484M, including open pit capitalized pre-strip. The sustaining capital cost thereafter is US\$246.1 million, which is primarily for surface infrastructure, open pit mine equipment replacements and underground development. Capital costs have been estimated with reference to actual experience in undertaking the same or similar works at Haile, quotations from suppliers and estimates provided by consultants with appropriate expertise.

Capital cost estimation is considered to be consistent with proposed development programs and ongoing requirements and undertaken to an appropriate level of estimation accuracy. It is likely though that over the life of the mine that actual expenditures will vary, due to modifications, upgrades, introduction of new technology and other unforeseen factors.

Table 1-10: Total Capital Cost Summary (US\$000)

Description	Initial Capex	Sustaining Capex	Total
Land Acquisitions	-	5,925	5,925
Permitting	-	1,542	1,542
On-Site Exploration Drilling	6,679	-	6,679
Op Capitalized Pre-Strip	281,838	-	281,838
Capital Leases: Sustaining	-	-	-
Capital Leases: Non-Sustaining	-	-	-
OP Mining PP&E	19,969	6,850	26,819
OP Tech Services PP&E	720	-	720
Pit Dewatering	15,868	-	15,868
Site Works	1,975	7,722	9,697
PAG Cell Development	-	88,077	88,077
TSF Lift Design	138,857	33,329	172,186
Underground Mining: Non-Sustaining	-	79,413	79,413
Underground Mining: Sustaining	17,091	-	7,091
Mill PP&E	793	13,020	13,814
Commercial	54	14	68
Total Net Capex	\$483,844	\$235,894	\$719,738
Reclamation/Closure ⁽¹⁾	-	68,280	68,280
Total LoM Net Capex	\$483,844	\$304,173	\$788,017

Source: SRK, 2020

(1) Captured as Capex in Cashflow

Operating Cost

The total LoM operating cost (excluding capitalized operating cost) is US\$1,499 million. Operating costs have been estimated with reference to actual operating experience at Haile, supplier quotations, estimates from consultants with appropriate expertise and otherwise estimated internally by appropriately credentialed OceanaGold people. The operating cost estimates include allowance for performance related improvement opportunities that have been identified.

Total life of mine operating costs, and the total RoM operating cost unit rate of US\$28.40/t processed are summarized in Table 1-11.

Table 1-11: RoM Operating Cost Summary

Description	US\$000's	US\$/t Ore Processed
OP Mining (\$/t rock mined) - All Material	909,308	2.00
OP Mining (\$/t rock mined) - Operational Material	627,469	2.05
UG Mining (\$/t ore mined)	161,073	47.15
Subtotal Mining (Operational Material Only)	788,542	14.94
Processing	526,811	9.98
G&A Cost	175,478	3.32
Refining/Freight Costs	8,213	0.16
Total Operating Costs	\$1,499,044	\$28.40

Source: SRK, 2020

There are several important cost items excluded from the operating cost of which are detailed in Table 1-12 that OceanaGold does not consider to be direct operating costs but which the operation does

incur. These include payments related to leasing arrangements of the open pit and underground mobile equipment fleets.

Table 1-12: RoM Indirect Costs Summary

Description	US\$000's	US\$/t Ore Processed
Endowment & Reclamation Fund	18,778	0.36
Environmental Bond	7,645	0.14
Interest Expense - Capital Leases	11,226	0.21
Principal Payment - Capital Leases: Sustaining	12,089	0.23
Principal Payment - Capital Leases: Non-Sustaining	108,810	2.06
Regional Business Units	18,032	0.34
Total Non-Operating Costs	176,580	\$3.35

Source: SRK, 2020

1.12 Economic Analysis

The Project consists of an operating mine with a mill processing 4.0 Mtpa of material. The mill is mainly fed by open pit ore. The mill feed will be supplemented with ore from a five-year UG 2,150 t/d max annual capacity high grade operation that begins production at the end of 2022.

The Project is expected to produce 2.47 million ounces of payable gold over a 14-year mine life at an average rate of 195 koz Au per year during full production years with a run-of-mine (RoM) all-in sustaining cost (AISC) of US\$799/oz.

The Project is expected to incur sustaining capital in the amount of US\$483.8 million over the modeled life and a non-sustaining capital spend, including closure costs, of US\$304.2 million for total capital expenditure of US\$788.0 million.

Project metrics using a constant US\$1,500 / oz gold price include pre-tax and after-tax NPV 5% values of US\$929.8 million and US\$891.9 million, respectively. Because the project is operational and is valued on a total project basis and not by an incremental analysis of the UG start up, an IRR value is not relevant in this analysis. In terms of sensitivity, the Project is not surprisingly most sensitive to gold grade and price, followed by operating costs and capital costs.

1.13 Conclusions and Recommendations

1.13.1 Geology and Mineral Resources

Open Pit

Haile 3D geologic models are updated twice per year using Maptek's Vulcan software, based largely on core drilling and pit mapping to reflect controls to mineralization. Geologic domains are used to guide gold grade interpolation. Exploration drilling has been accompanied by an industry standard QA/QC program showing good quality analytical results in terms of precision and accuracy. OceanaGold has conducted extensive core logging resulting in a high-quality geologic model. The results of the drilling, sampling, analytical testing, core logging and geologic interpretation provide good support for an industry standard resource estimation. New lithologic and structural interpretations aided by pXRF alteration zonation and geochemistry are being used to support geological interpretations and new drill targets. Lithology, alteration and mineralogical data are being integrated with geotechnical, overburden storage and metallurgical evaluations to optimize reserve growth, mill

recoveries and throughput. Rising gold prices drive potential pit expansions that will be evaluated with more drilling to assess economic potential.

Underground

OceanaGold completed an industry standard exploration drilling program to delineate the Horseshoe mineralization sufficient to support the current mineral resource estimation. The average drill spacing is approximately 25 m x 25 m within the Indicated Mineral Resource and 50 m x 50 m in the Inferred Mineral Resource. Exploration drilling has been accompanied by an industry standard QA/QC program showing good quality analytical results in terms of precision and accuracy. OceanaGold has conducted extensive core logging resulting in a high-quality geologic model. The results of the drilling, sampling, analytical testing, core logging and geologic interpretation provide good support for an industry standard resource estimation. The results of the mineral resource estimation define an Indicated Mineral Resource of 3.3 Mt at an average Au grade of 4.95 g/t containing 0.53 Moz of gold and an additional Inferred Mineral Resource of 2.1 Mt at an average Au grade of 4.4 g/t containing 0.3 Moz of gold at a 1.26 g/t Au cut-off. The Palomino underground resource is located about 1 km southwest of the Horseshoe reserve. The Palomino Inferred Mineral Resource includes 6.9 Mt at 2.77 g/t Au for 0.6 Moz at a 1.37 g/t Au cut-off. High level mine designs and economic and sensitivity analyses were subsequently completed.

1.13.2 Status of Exploration; Development and Operations

OceanaGold will continue to expand resources adjacent to open pit and underground reserves in the Haile district with development drilling and by regional greenfields exploration in the Carolina Terrane. Systematic target generation supported by mapping, drilling, geochemistry and geophysics is expected to yield new discoveries within 50 km of Haile during the next five to ten years. Interpretation of geophysical data and integration with geology and geochemistry will play an important role. It is worth noting that a blind gold deposit has never been discovered in the Carolina Terrane. An ‘exploration toolkit’ of diagnostic criteria for Haile-like deposits has been developed to drive exploration for potentially mineable deposits, supported by a plethora of historic data and exemplary community relations.

1.13.3 Mining and Reserves

Open Pit

The mine block model, geotechnical stability, pit design, phase design, dump design, production schedule and reserve estimation have been completed to a feasibility study standard. The Project confirms a positive cash flow using only Measured and Indicated Resources for the conversion of reserves using a US\$1,500/oz gold price. The mine design supports the style and size of equipment selected for operations. While subject to continual improvement, the mine plan implementation will require qualified staff and the integration of all mining and related disciplines for the successful execution of the Project.

The mine operating and capital costs have been estimated from first principles and operational knowledge from current mine operations. The equipment is sized to meet minimum SMU requirements that support the dilution and mine recovery factors while providing bulk earthwork capability for the expected production rates.

The LoM production schedule includes provision for careful control of potentially acid generating overburden and appropriate material handling costs have been included in the mining cost estimate. It is recommended that initiatives as identified in this report relating to open pit mining productivities and costs, grade control, ore loss and dilution and PAG waste definition and classification be pursued, including the development and implementation of appropriate project plans.

Underground

Longhole stoping is seen as the appropriate mining method for the deposit geometry. The large stope sizes minimize cost and grades are not overly diluted. Mine planning work considered revenue for Au and a cut-off grade (CoG) of 1.44 g/t Au was used. A detailed 3D mine design was completed around economically minable areas above cutoff grade.

The underground mine is accessed via a decline from the surface. The decline portal is located on an open pit bench approximately 80 m below the natural surface. Two ventilation drift portals are also located on an open pit bench. And emergency egress system is included in the design.

Tonnage and grades presented in the reserve include dilution and recovery and are benchmarked to other similar operations. Productivities were generated from first principles with inputs from mining contractors, blasting suppliers, and equipment vendors where appropriate. The productivities were also benchmarked to similar operations. Equipment used in this study is standard equipment used worldwide with only standard package/automation features.

A production schedule was generated using Deswik software. The schedule targeted 2,000 t/d.

1.13.4 Mineral Processing and Metallurgical Testing

A significant portion of equipment installed at the Haile process plant was designed conservatively enough (that is, with sufficient additional capacity) to readily accommodate expansion. A targeted debottlenecking project has increased plant capacity to a new target capacity of 4.0 Mtpa over the last three years.

No novel, experimental or unproven technologies are used for the Haile process plant. Gold production from conventional grinding, sulfide flotation and fine grinding followed by CIL treatment is able to achieve gold recoveries in excess of 82% for the majority of the sulfide ore treated.

1.13.5 Recovery Methods

There is no effective change to the existing plant recovery methods originally envisaged for the constructed plant or from the expansion activities undertaken.

The processing plant has been successfully operating since 2017 and is achieving targeted throughput rates, equipment utilization and gold production. Progressive ramp up has been achieved since mid-2018 to current levels. Ongoing improvement projects and process monitoring will continue to develop operating knowledge to maintain recovery and provide the basis for a first principals cost model to predict unit costs.

The existing Haile facilities have an ample site footprint to achieve a capacity of 4.0 Mtpa.

1.13.6 Project Infrastructure

The surface infrastructure required for the increase in open pit production as per the mine plan is straightforward as it is aligned with the current surface infrastructure requirements. The primary changes are increases in size to the main waste storage facilities such as the TSF and PAG OSAs. Major site water management facilities are in place.

The surface infrastructure required for the development of the underground Horseshoe deposit is straightforward and relatively minor. Consideration should be given into whether the crusher is required to support the CRF plant.

1.13.7 Environmental Studies and Permitting

Section 26.1.7 summarizes the environmental studies. The mine is currently operating as permitted.

1.13.8 Economic Analysis

The current metal price environment is extremely strong. If prices are forecast to remain elevated for long periods, the project reserves and resources should be updated and fed into an economic model at a revised price deck reflective of the long-term price forecasts

2 Introduction

2.1 Terms of Reference and Purpose of the Report

This National Instrument 43-101 (NI 43-101) Technical Report (Technical Report) was prepared for OceanaGold Corporation (OceanaGold) to a feasibility level by SRK Consulting (U.S.), Inc. (SRK) on the Haile Gold Mine (Haile or Project). This report includes both open pit and underground mining components and a single economic analysis based on open pit and underground reserves.

The quality of information, conclusions, and estimates contained herein is consistent with the level of effort involved in SRK's services, based on: i) information available at the time of preparation, ii) data supplied by outside sources, and iii) the assumptions, conditions, and qualifications set forth in this report. This report is intended for use by OceanaGold subject to the terms and conditions of its contract with SRK and relevant securities legislation. The contract permits OceanaGold to file this report as a Technical Report with Canadian securities regulatory authorities pursuant to NI 43-101 Standards of Disclosure for Mineral Projects. Except for the purposes legislated under provincial securities law, any other uses of this report by any third party is at that party's sole risk. The responsibility for this disclosure remains with OceanaGold. The user of this document should ensure that this is the most recent Technical Report for the property as it is not valid if a new Technical Report is issued.

This report provides Mineral Resource and Mineral Reserve estimates, and a classification of resources and reserves prepared in accordance with the Canadian Institute of Mining, Metallurgy and Petroleum (CIM) Standards on Mineral Resources and Reserves: Definitions and Guidelines, May 10, 2014 (CIM, 2014).

2.2 Qualifications of Consultants

The consultants preparing this technical report are specialists in the fields of geology, exploration, Mineral Resource and Mineral Reserve estimation and classification, underground mining, geotechnical, environmental, permitting, metallurgical testing, mineral processing, processing design, capital and operating cost estimation, and mineral economics.

SRK consultants employed in the preparation of this Technical Report have no beneficial interest in OceanaGold. The SRK consultants are not insiders, associates, or affiliates of OceanaGold. The results of this Technical Report are not dependent upon any prior agreements concerning the conclusions to be reached, nor are there any undisclosed understandings concerning any future business dealings between OceanaGold and SRK. The SRK consultants are being paid a fee for their work in accordance with normal professional consulting practice.

The following individuals, by virtue of their education, experience and professional association, are considered Qualified Persons (QP) as defined in the NI 43-101 standard and are members in good standing of appropriate professional institutions. QP certificates of authors are provided in Appendix A. The QPs are responsible for specific sections as follows:

- David Carr, BEng Metallurgical (Hons), OceanaGold Chief Metallurgist is the QP responsible for mineral processing, all of Sections 13 and 17, the process plant costs of section 21, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.

- Michael Kirby, PE, MEng Civil, (OceanaGold Environmental Superintendent), is the QP responsible for Environmental and Permitting, Section 20 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- Tom Cooney, BEng (Hons) Mining, MMinMgt, MAusIMM (CP), (OceanaGold General Manager Project Development and Studies) is the QP responsible for the Sections 16.1.1, 16.1.7, 16.1.8, 19, the open pit, underground, and other costs of section 21 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- John Jory, MSc Mineral Exploration, BS Geology, CPG, AIPG, (OceanaGold Director of Exploration, Haile), is the QP responsible for all of Sections 4, 5, 6, 7, 8, 9, 10, 11, 12, 16.1.5, 23, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- Jonathan Moore, BSc Geology (Hons), MAusIMM(CP), (OceanaGold Chief Geologist), is the QP responsible for open pit and underground Mineral Resources, Section 14 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- Jay Newton Janney-Moore, PE, (NewFields Project Manager I), is the QP responsible for tailing and overburden storage, Sections 18.1, 18.2, 18.3, 18.4, 18.5, 18.10, the Tailings/Overburden section of 21 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- William Lucas Kingston, P.G. Hydrogeology and Groundwater Management, (NewFields Senior Hydrogeologist) is the QP responsible for hydrogeology, Sections 16.1.9, 16.2.3, the hydrogeological portion of section of 16.1.2, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- Joanna Poeck, BEng Mining, SME-RM, MMSAQP, (SRK Principal Consultant, Mining Engineer), is the QP responsible for underground Mineral Reserves, all of Sections 2, 3, 24, 27, 28, the underground portions of Section 15 and 16.3, Section 16 opening statements, Sections 16.2, 16.2.1, 16.2.5, 16.2.6, 16.2.7, 16.2.8, 16.2.9, 16.2.11, 18.6, 18.7, 18.8, 18.9 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- Fernando Rodrigues, BS Mining, MBA, MMSAQP, MAusIMM, (Principal Consultant, Mining Engineering) is the QP responsible for open pit Mineral Reserves, the open pit portions of Section 15 and 16.3, Sections 16.1, 16.1.1, 16.1.3, 16.1.4, 16.1.6, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- Larry Standridge, PE, MSE Geotechnical, (Call & Nicholas Principal Engineer, Geotechnical Engineer) is the QP responsible for open pit geotechnical work, the geotechnical portion of Section 16.1.2 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- Matt Sullivan, BEng, RM-SME (SRK Senior Consultant, Mineral Economics), is the QP responsible for technical-economics Sections 22, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- David Bird, MSc., PG, RM-SME, (SRK Principal Consultant, Geochemistry), is the QP responsible for underground geochemistry, Section 16.2.4, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- John Tinucci, PhD, PE, (SRK Principal Consultant, Geotechnical Engineer), is the QP responsible for underground geotechnical information, Section 16.2.2 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
- Brian S. Prosser, PE (SRK Principal Consultant), is the QP responsible for ventilation, Section 16.2.10 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.

2.3 Details of Inspection

Site visits conducted by QPs are summarized in Table 2-1.

Table 2-1: Site Visit Participants

Personnel	Company	Expertise	Date(s) of Visit	Details of Inspection
Larry Standridge	Call & Nicholas	Geotechnical	November 29 and 30 2017 October 10 and 11 2018 January 14 to 16 2020	Review of existing pit slopes and examination of geotechnical drill core.
David Carr	OceanaGold	Metallurgy	Various visits in 2017, 2018 & 2019 March 8 to March 25 2020	Plant Commissioning support and plant investigations Plant Commissioning and ramp-up of operations to 4mtpa
Tom Cooney	OceanaGold	Mining	November 28 to December 7, 2018	Technical review of open pit mining, processing and infrastructure areas, including site tours.
Jay Newton Janney-Moore	NewFields	Geotechnical/ Infrastructure	Sept. 24-26, 2019	Inspection of the Duckwood TSF, PAG OSA, and geomembrane lined ponds
Joanna Poeck	SRK	UG Mining/ Infrastructure	February 6 and 7, 2017 March 12 to 14, 2019	Site tour of current mining and infrastructure
John Tinucci	SRK	Geotechnical	November 29 to December 1, 2016	Site tour of current mining, geotechnical drilling activities, and examination of core
William Lucas Kingston	NewFields	Hydrogeology and Groundwater Management	December 4 to 5, 2019	General site inspection, including dewatering system
Jonathan Moore	OceanaGold	Geology/Resources	January 13 to 28, 2020	Review of Resource and Reconciliation. Visited open pit.

John Jory and Michael Kirby are based in South Carolina and are on-site regularly.

2.4 Sources of Information

This report is based in part on internal Company technical reports, previous feasibility studies, maps, published government reports, Company letters and memoranda, and public information as cited throughout this report and listed in the References Section 27.

2.5 Effective Date

The effective date of this report is June 30, 2020.

2.6 Units of Measure

The Metric System for weights and units has been used throughout this report. Tonnes are reported in metric tonnes of 1,000 kg. Gold is reported in grams and troy ounces, where applicable (1 Troy ounce = 31.1035 grams). All currency is in U.S. dollars (US\$) unless otherwise stated.

3 Reliance on Other Experts

The Consultant's opinion contained herein is based on information provided to the Consultants by OceanaGold throughout the course of the investigations. SRK has relied upon OceanaGold and the work of other consultants in the project areas in support of this Technical Report.


The Consultants used their experience to determine if the information from previous reports was suitable for inclusion in this technical report and adjusted information that required amending. This report includes technical information, which required subsequent calculations to derive subtotals, totals and weighted averages. Such calculations inherently involve a degree of rounding and consequently introduce a margin of error. Where these occur, the Consultants do not consider them to be material.

SRK has relied upon OceanaGold for information regarding the surface land ownership/agreements as well as the mineral titles and their validity. Land titles and mineral rights for the project have not been independently reviewed by SRK and SRK did not seek an independent legal opinion for these items.

4 Property Description and Location


4.1 Property Location

The Haile gold mine is located 5 km northeast of Kershaw in southern Lancaster County, South Carolina, USA, in the north-central part of the state, as shown in Figure 4-1. Haile is 27 km southeast of Lancaster, the county seat, and is 80 km northeast of Columbia, the state capital. The geographic center of the mine is at 34° 34' 46" N latitude and 80° 32' 37" W longitude. Mineralized zones at Haile lie within an area extending from UTM NAD83 zone 17N coordinates 540000E to 544000E and 3825500N to 3827500N. Figure 4-2 shows a site map of the Haile Gold Mine.

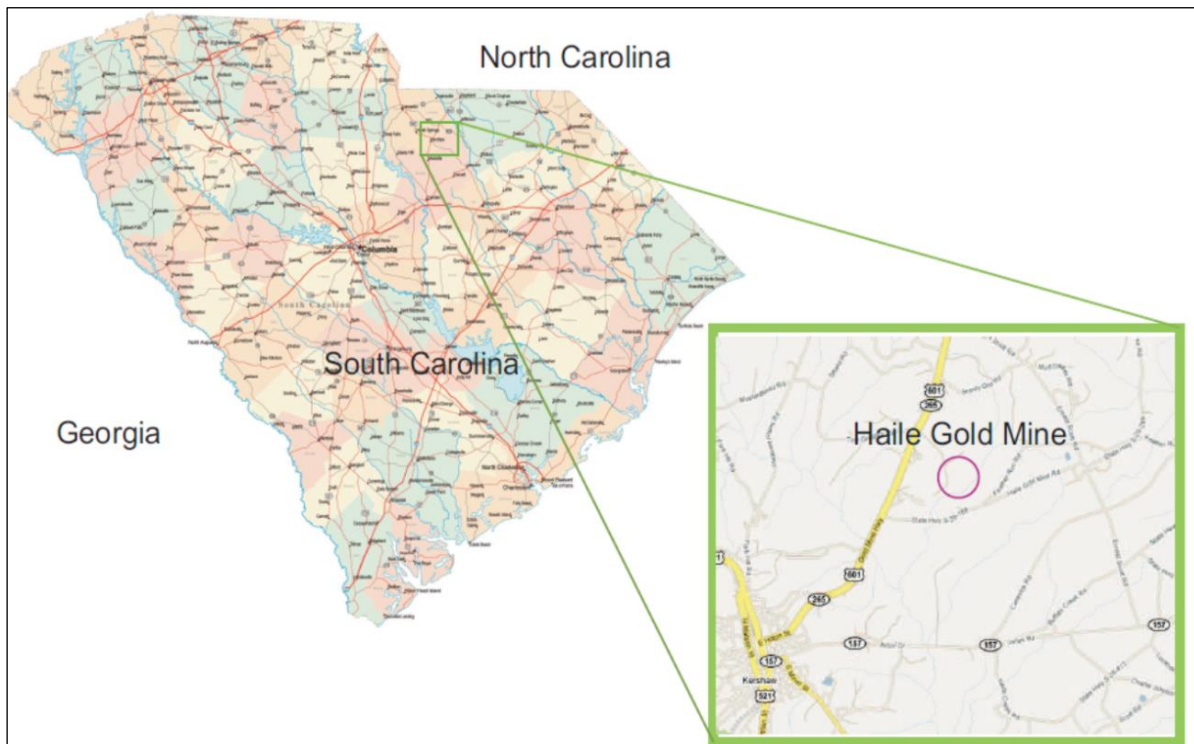

Source: State-Maps.org and Google Maps, 2014

Figure 4-1: General Location Map of the Haile Gold Mine

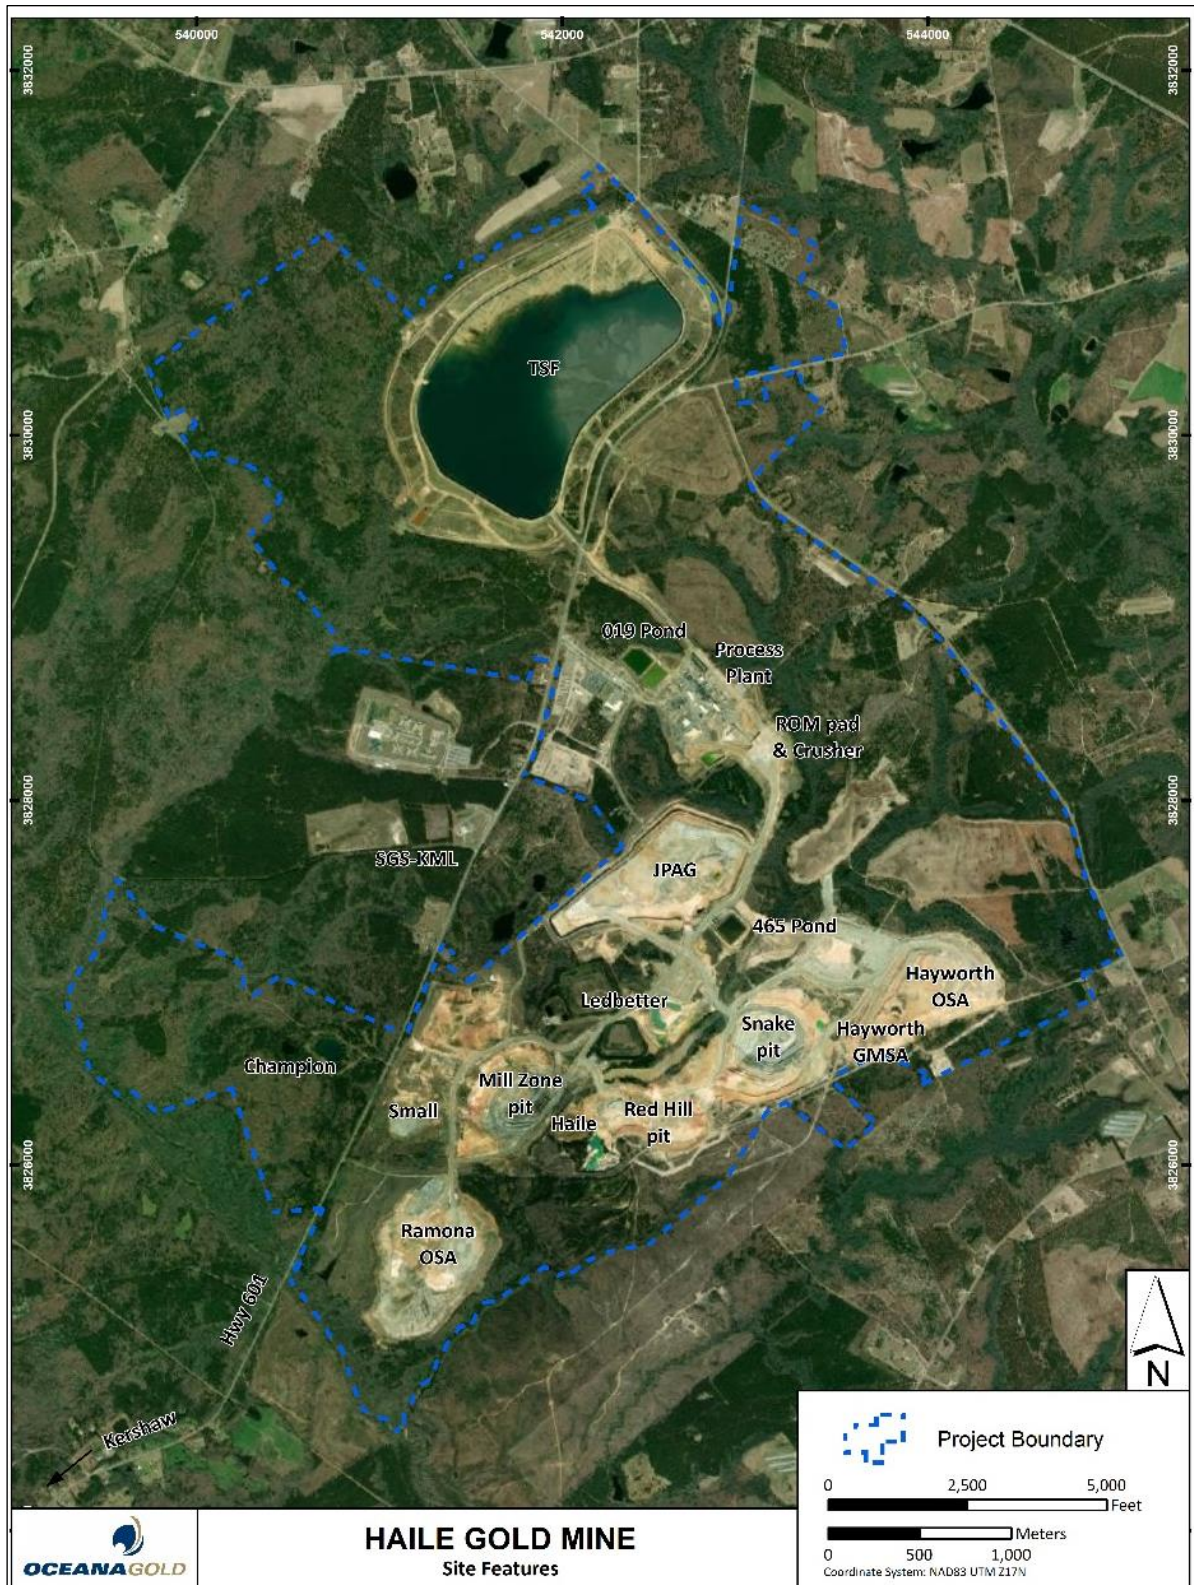


Source: OceanaGold

Figure 4-2: Site Map of the Haile Gold Mine. Background Imagery from Mar. 22, 2019

4.2 Ownership

Haile Gold Mine Inc. (HGM) is a wholly owned subsidiary of OceanaGold Corporation (OceanaGold). References in this document to OceanaGold refer to the parent company together with its subsidiaries, including HGM and Romarco Minerals Inc. As of June 30, 2020, HGM owns a total of 11,478 acres in South Carolina. Of this total, 4,552 acres are within the mine permit boundary. Proposed expansion in the Supplemental Environmental Impact Statement (SEIS) will increase the mine property to 5,432 acres. Figure 4-3 shows the Land Tenure map as of June 30, 2020, with Fee Simple (OGC owned) and leased properties, almost entirely in Lancaster County.

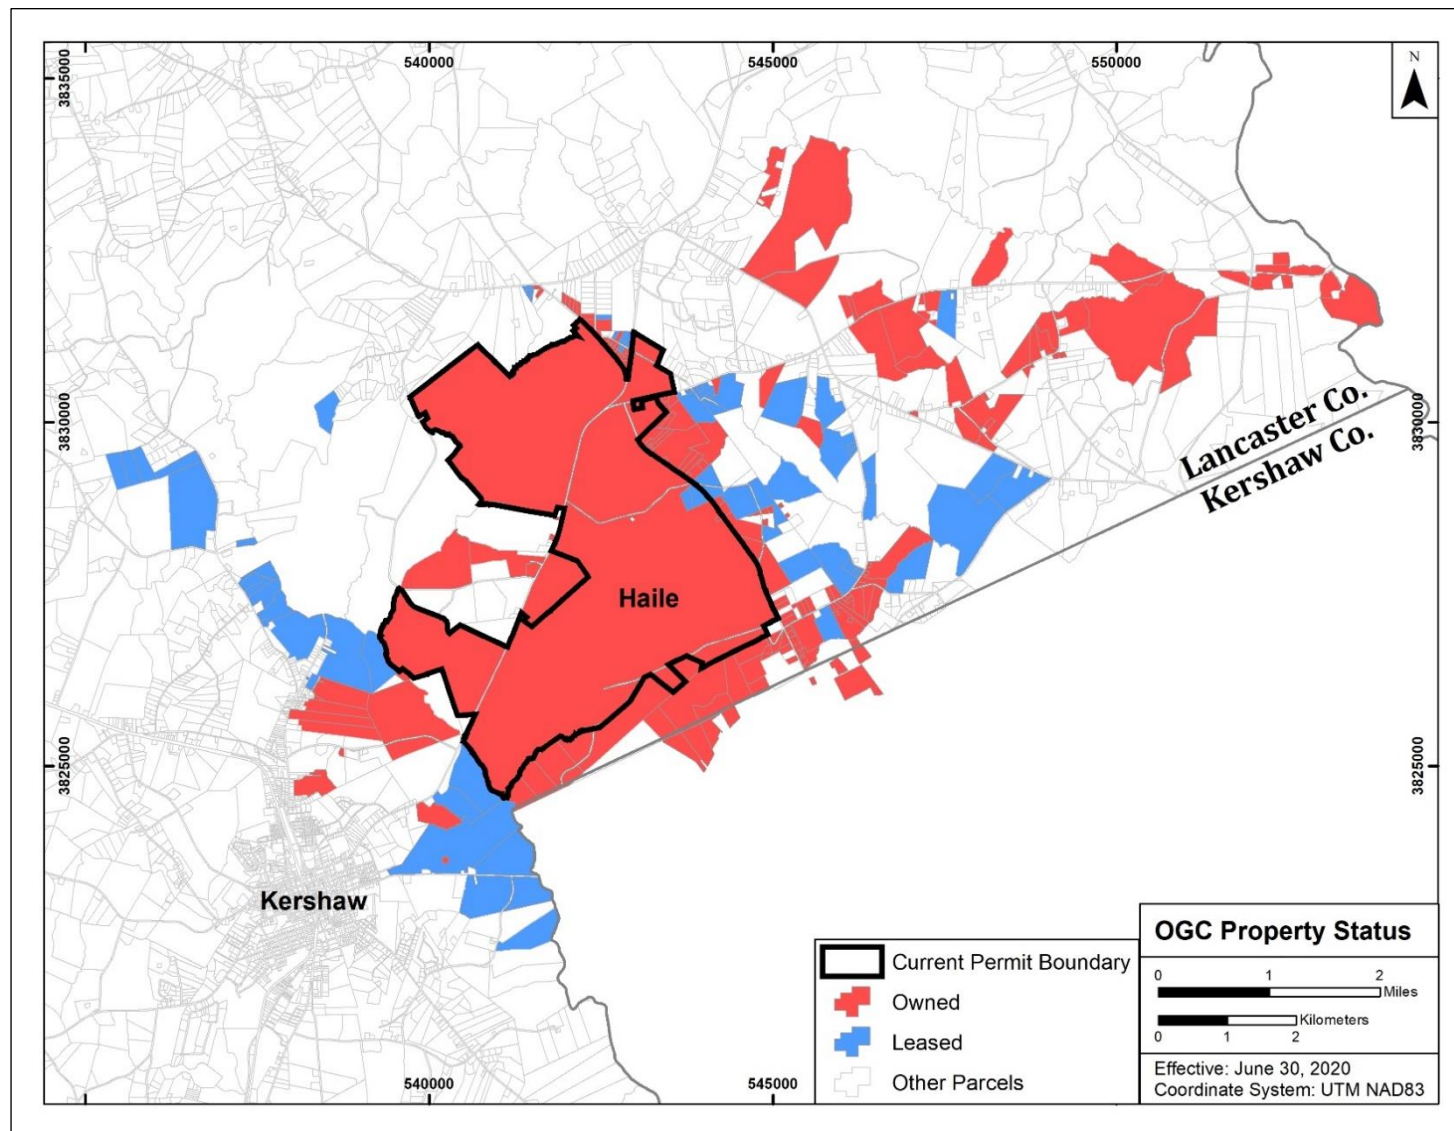

Source: OceanaGold

Figure 4-3: Land Tenure Map

5 Accessibility, Climate, Local Resources, Infrastructure and Physiography

5.1 Accessibility

The Haile property is easily accessible on paved roads and highways from U.S. Highway 601 to the mine entrance on Snowy Owl Road, located 5 km northeast of Kershaw, South Carolina. The major international airport at Charlotte, North Carolina, is an 80-minute drive from the mine.

5.2 Climate

The Haile area of South Carolina has a sub-tropical climate. Summers are hot and humid with daytime temperatures averaging 29°C to 35°C. Winters are mild and temperatures range from 0°C to 15°C. Average annual precipitation is 1,270 mm while annual evaporation is estimated at 760 mm. Rain is abundant throughout the year with January, March, and July being the wettest months. Snowfall is insignificant and averages less than 80 mm per year. South Carolina averages 50 days of thunderstorm activity and 14 tornadoes per year. The mine operating season is year-round.

5.3 Local Resources and Infrastructure

Local resources (labor force, manufacturing, supplies, housing, utilities, emergency services, etc.) and infrastructure are in place and are widely utilized at Haile. Numerous small communities exist around the Haile mine with populations ranging from 700 to 10,000 people. Power is available in the area via an existing 44 kV transmission grid with Duke Energy and a 69 kV transmission grid with Lynches River. The company utilizes both grids. Surrounding nearby land use is dominantly for agriculture and timber.

5.4 Physiography

The Haile Gold Mine and its surroundings occur within the Sand Hills sub-province of the Piedmont physiographic province of the southeastern United States. This province trends from southwest to northeast and is bound by the Coastal Plain to the southeast and the southern Appalachian Mountains to the northwest. Gentle topography and rolling hills, dense networks of stream drainages, and white sand to red brown saprolitic soils characterize the province. The mine elevation ranges from 120 m to 170 m above mean sea level. Topography is dissected by the perennial, southwest-flowing Haile Gold Mine Creek and by its intermittent tributaries. Haile Gold Mine Creek (HGMC) enters the southeast-flowing Little Lynches River 1.6 km southwest of the mine site. Gradients within the drainages are gentle to moderate (9 to 13%) and slopes above the drainages are gentle to nearly flat (less than 1%). The property is heavily wooded by pine and hardwood forests. Pine timber harvesting occurs frequently in and around the property area as each harvestable tract matures.

5.5 Infrastructure Availability and Sources

There are large industrial centers near the mine. Equipment and sources of logistical and professional expertise can be obtained from the major cities of Charlotte, N.C., and Columbia, S.C., which are both within one-hour travel of the mine. Multiple contractors provide skilled workers for the project. There is adequate labor for operations.

6 History

Gold was discovered in 1827 near Haile by Colonel Benjamin Haile, Jr. in gravels of Ledbetter Creek (now HGMC). This led to placer mining and prospecting until 1829, when lode deposits at the Haile-Bumalo pit site were found. Surface pit and underground work continued at the Haile-Bumalo site for many years. In 1837, a five-stamp mill was built (Newton et al., 1940). Gold production and pyrite-Sulfur mining for gunpowder continued through the Civil War from 1861 to 1865. General Sherman's Union troops invaded the area and burned down the operations near the war's end.

In 1882 a sixty-five-stamp mill was constructed by E.G. Spilsbury and operated continuously until a fatal boiler explosion killed the mine manager in 1908. During that time, Adolph Thies developed the Thies barrel chlorination extraction process and improved gold recovery from Haile sulfide ores (Pardee and Park, 1948). During the 26-year operation period, mining grew to include the Blauvelt, Bequelin, New Bequelin, and Chase Hill areas. From 1907 to 1913, an attempt to operate a cyanide plant to extract gold from mine tailings was unsuccessful. Pyrite used to produce sulfuric acid was mined at Haile from 1914 to 1918 (Newton et al., 1940).

From mid-1937 to 1942, larger-scale mining was undertaken by the Haile Gold Mines Company. The property then consisted of owned or leased ground totaling about 1,335 hectares (ha) (Newton et al., 1940). Most of the main pits were mined to the 46-m level with some underground operations at Haile-Bumalo reaching the 106-m level (Pardee and Park, 1948). The Red Hill Deposit was discovered by crude induced polarization techniques next to the Friday pyrite diggings (Newton et al., 1940). This fairly large operation was shut down by presidential decree in 1942 because of World War II. By this time, Haile had produced over US\$6.4 million worth of gold (in 1940 dollars) (Newton et al., 1940).

Starting in 1951, the Mineral Mining Company (Kershaw, South Carolina) mined Mineralite® from sericite-rich pits around Haile. This industrial product is a mixture of sericite, kaolinite, quartz, and feldspar and is used in manufacturing insulators and paint base. Mineralite mining ended in 1991.

In 1966, Earl Jones conducted exploration work in the area and eventually interested Cyprus Exploration Company (Cyprus) in the project. Cyprus worked Haile from 1973 to 1977. Numerous companies explored the Haile regional area in the 1970s and 1980s, including Amselco, Amax, Nicor, Callaghan Mining, Westmont, Asarco, Newmont, Superior Oil, Corona, Cominco, American Copper and Nickel, Kennecott, and Hemlo.

The 1980s heralded the first successful modern exploration and production at Haile. Piedmont Land and Exploration Company (later Piedmont Mining Company) explored Haile and surrounding properties from 1981 to 1985. Piedmont drilled 67 core holes and 1,215 reverse circulation holes on the property and greatly expanded the footprint of the Haile deposits. Piedmont mined the Haile deposits from 1985 to 1992 and produced 85,000 ounces of gold from open pit heap leach operations in oxide and transitional ores. New areas mined by Piedmont included the Gault Pit (next to Blauvelt), the 601 pits (by the US 601 highway), and the Champion Pit. Piedmont expanded the Chase Hill and Red Hill pits and combined the Haile-Bumalo zone into one pit. Piedmont also discovered the large Snake deposit sulfide gold resource and mined its small oxide cap. Piedmont extracted gold ores from a mineralized trend 1.6 km long, from east to west. Historical gold production at Haile is estimated at 360,000 ounces (Speer and Madry, 1993, Maddry and Kilbey, 1995).

In June 1991, Amax signed an agreement to evaluate Haile to determine if it should enter into a joint venture. During the evaluation period, core drilling stepped north of the Haile-Bumalo area and discovered the new sulfide resource at the Mill zone under the old 1940s mill. Amax and Piedmont entered into a joint venture agreement and established the Haile Mining Company (HMC) in May 1992.

From 1992 to 1994, HMC completed a program of exploration and development drilling, property evaluation, Mineral Resource estimation, and technical report preparation. During this period, the large Ledbetter resource zone was discovered under a mine haul road. At the end of the HMC program in 1994, the gold reserve was stated as 780,000 ounces of gold contained within 7.9 million tonnes at an average gold grade of 3.05 g/t. A qualified person has not done sufficient work to classify the historical estimate as Mineral Resources or Mineral Reserves. HGM is not treating the historical estimate as Mineral Reserves. Because of unfavorable economic conditions at the time, Amax did not proceed with mining, and began a reclamation program to mitigate acid rock drainage (ARD) conditions at the site.

Kinross acquired Amax in 1998, assumed Amax's portion of the Haile joint venture, and later purchased Piedmont's interest. Because Haile was a low priority compared to larger and more profitable projects, Kinross decided not to reopen the mine and continued the reclamation and closure program. Reclamation and closure proceeded through to 2015 when Haile operations commenced again under Romarco Minerals Inc.

Romarco acquired Haile from Kinross in October 2007 and began a confirmation drilling program in late 2007. Romarco completed the confirmation drill program in early 2008 and began infill and exploration drilling focused around the Ledbetter resource. Drilling accelerated in early 2009 with a major reverse circulation infill drilling program that continued through 2012. Condemnation drilling by Romarco for mine facilities commenced in September 2009. Drilling east of the Snake deposit discovered the high-grade Horseshoe deposit in 2010 and required the planned tails storage facility to be relocated 3 to 4 km northwest of the mine. Geotechnical drilling was initiated in September 2009 for pit slope designs. The final hole at Ledbetter discovered a deeper northwest extension in 2010 that was named Mustang. Drilling between the Red Hill and Horseshoe areas had identified large zones of lower grade material that led to the late 2011 discovery of the deep Palomino prospect. Due to low gold prices and mine permitting, Haile exploration drilling was suspended during 2013 and 2014.

Romarco submitted a feasibility study for Haile in February 2011. Drillhole data available as of November 17, 2011, were used in the March 2012 Mineral Resource estimate. Romarco completed a large portion of detailed engineering and permitting for the project in 2011 and 2012. In November 2014, an updated feasibility study was completed after receiving the necessary permits. In April 2015, construction of the project began by Romarco and mining commenced in the Mill Zone pit.

OceanaGold Corporation acquired Romarco Minerals Inc. in October 2015 and became owner and operator of Haile. Project construction during 2015 and 2016 included a new Carbon-In-Leach (CIL)-flotation process plant, power upgrades, a lined PAG overburden storage area, and a tails storage facility. The first gold pour at the new process plant was in January 2017.

7 Geological Setting and Mineralization

7.1 Regional Geology

Gold endowment in the southern Appalachian piedmont is predominantly from the *Carolina Slate Belt* (CSB), also known as the *Carolina Terrane* (Hibbard et al., 2010). The 700 km long belt is characterized by a strong northeast structural grain (stratigraphy, faults, foliation, fold axes) extending from Alabama to Virginia that is up to 140 km wide in North Carolina. Volcanic arcs formed adjacent to the African continent and were accreted to the North American craton during the Late Proterozoic to Silurian (Hibbard et al., 2010).


The CSB is a northeast-trending, late Proterozoic to early Cambrian belt of felsic volcanic flows and pyroclastic rocks admixed with fine-grained epiclastic and turbiditic sediments. Volcanic rocks of the belt are both fragmental tuffs and cohesive lavas that generally define a bimodal suite of calc-alkaline to felsic rocks based on SiO₂ content and Ti/Al ratios (Feiss, 1982). Sedimentary rocks were deposited under calm, subaqueous anoxic slopes conditions as evidenced by laminated, laterally extensive siltstones. Volcanic and sedimentary facies are interfingered in the Haile region, and are cut by post-metamorphic mafic dikes.

The CSB has a prominent flexure in central South Carolina near Haile. Structural trends southwest of this area are east–northeasterly, whereas trends northeast of the flexure is mostly northeasterly (Hibbard et al., 2002). The CSB was intruded by dominantly granite plutons approximately 595 to 520 Ma and by post-metamorphic Carboniferous granite plutons approximately 300 Ma (Fullagar and Butler, 1979). Hydrothermal activity prior to Alleghanian regional metamorphism is indicated by folded and recrystallized quartz veins and by pressure shadows with fringes of chlorite and quartz on pyrite. Four tectonothermal periods are recorded in the Carolina Terrane (Hibbard et al., 2002), including:

- Late Neoproterozoic to Early Cambrian Virgilina events (617 to 544 Ma): folding, foliation and faulting with granite plutonism.
- Late Ordovician–Silurian Taconian events (457 to 425 Ma): upright folding with a penetrative axial planar cleavage accompanied by greenschist facies metamorphism.
- Devonian events of the Gold Hill–Silver Hill dextral shear zone (393 to 381 Ma) that juxtaposes the Carolina and Charlotte Terranes.
- Late Paleozoic Alleghanian events (333 to 286 Ma): ductile mylonitic shear zones (e.g. Hyco, Modoc shears) (Hibbard et al., 1998) with orogenic quartz veins, greenschist facies metamorphism and granite plutonism. This event is strongly superimposed on the rocks at Haile.

Gold mineralization at Haile (approximately 549 Ma, Mobley et al., 2014) occurred during suturing of the Carolina and Charlotte arcs coincident with emplacement of the Longtown and Little Mountain stitching plutons (Barker et al., 1998) (Figure 7-1). The Alleghanian orogeny formed the Appalachian Mountains with the emplacement of granite plutons and mafic dikes approximately 250 million years after gold mineralization at Haile (Hibbard et al., 2002, Hatcher et al., 2007). Importantly, the Alleghanian Orogeny superimposed a pervasive regional structural fabric on all pre-Alleghanian rocks. Greenschist facies metamorphism converted micas and clay minerals to chlorite and introduced carbonate and pyrite. Northwest-trending magnetic diabase dikes were intruded about 100 million years later during the Triassic period. Erosion and weathering with saprolite and strong sericite formation up to 40 m deep occurred in a sub-tropical, humid paleo-environment. A southeastward-

thickening apron of clayey sands with basal quartz-rich gravels was deposited in the Cretaceous period. Continental uplift and Atlantic Ocean regression have caused continued erosion and incision of the region by dominantly southeast-flowing drainage systems.

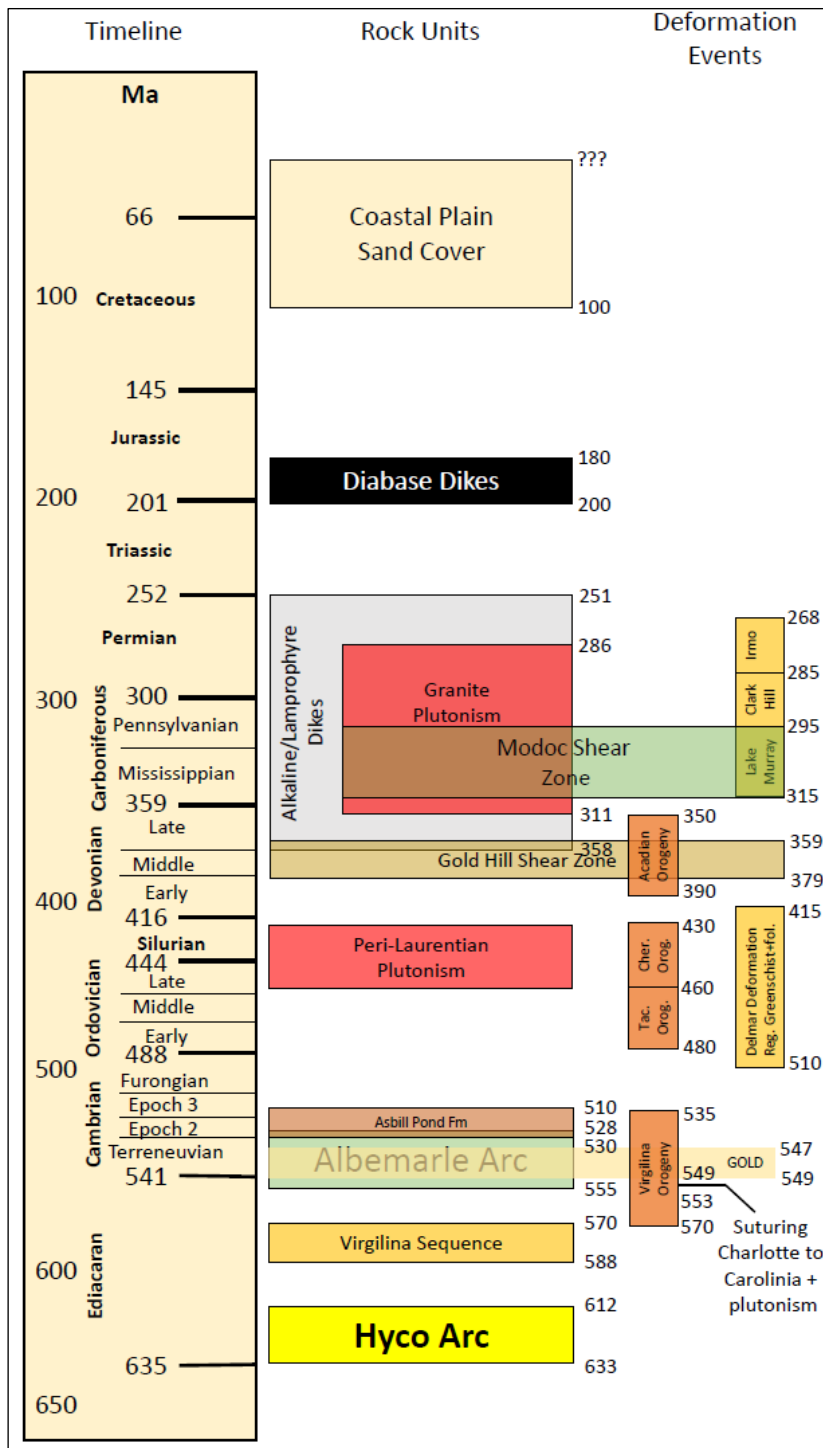

Source: OceanaGold

Figure 7-1: Time Distribution of Major Geological Events in the Carolinas

Volcaniclastic sedimentation and slope sedimentation are characteristic of convergent plate margins in marine forearcs and back arcs. The forearc region between the volcanic arc and the down-going subducting crustal slab, above which lies the trench, can be up to 300 km wide and can form a large forearc basin (Fisher and Schmincke, 1994). This tectonic setting is interpreted during formation of Haile host rocks in the Carolina Terrane. The volcaniclastic component depends on intensity and proximity of volcanic activity and the volume of debris that enters the sedimentary environment. Sediments in the fore arc basin are largely turbidite-dominated, and clastics are epiclastic volcanic and reworked pyroclastics and hyaloclastites. Pyroclastics as lapilli tuffs and ash flow tuffs dominated during episodes of aerial volcanism, whereas epiclastic deposition dominated between volcanic episodes. This overlap of volcanic and sedimentary rocks produces frequent facies changes and rheological contrasts in the Haile region.

Stratigraphic nomenclature for Carolina Terrane units has not been standardized between North and South Carolina. Generally, the Uwharrie and Tillery Formations (the latter being the lowermost formation in the Albemarle Group) in North Carolina are equivalent to the Persimmon Fork and Richtex Formations, respectively, in South Carolina. The Persimmon Fork and Richtex Formations are respectively about 3,000 m and 5,000 m thick (Whitney et al., 1978, Secor and Snoke, 1986). Variability in composition, grain size, and proximity to hydrothermal centers during subaqueous lithification produced highly variable alteration geochemistry and textures. Cohesive dacite lavas that experienced alkali loss, silica addition, quenching and variable cooling rates produced mottled textures that can be mistaken for volcaniclastic rocks.

The largest gold deposits in the southeastern US are in the north-central portion of South Carolina. They are oriented SW-NE and occur at or near the contact between metamorphosed volcanic and sedimentary rocks of Neoproterozoic to Early Cambrian age. Gold is present in quartz veins and as fine-grained disseminations in sedimentary and volcanic rocks with silicified, argillic, and propylitic alteration zones. The largest gold deposits in South Carolina are the Haile (4.2 Moz resource), Ridgeway (1.44 Moz resource) and Brewer (0.26 Moz resource) deposits (Foley and Ayuso, 2012) as shown in Table 7-1. Haile is the largest and is currently the only active gold mine in the region. The inactive Brewer and Ridgeway mines are respectively located 12 km northeast and 50 km southwest of Haile. Haile and Brewer are hosted in sedimentary and volcanic rocks of the upper Persimmon Fork Formation. Ridgeway is hosted in sheared metasediments along the Persimmon Fork- Richtex contact. Gold in sediments is often stratiform and occurs along lithotectonic boundaries between interfingering volcanic and sedimentary rocks of the Persimmon Fork Formation. Haile is classified as a low sulfidation, sediment-hosted, disseminated, epithermal gold deposit with proximal quartz-sericite-pyrite alteration and distal carbonate-chlorite alteration (Robert et al., 2007). Ridgeway is geologically similar to Haile in that it is dominantly sediment-hosted with mineralized volcanic rocks. East-west to ENE structural controls and local folding characterize the Haile and Ridgeway deposits. Brewer is a high sulfidation pyrite-enargite-chalcophyrite-topaz-rich, volcanic-hosted, breccia pipe overprinted by advanced argillic alteration (pyrophyllite-andalusite).

Table 7-1: Geological Summary of Major Gold Deposits of SE USA

Deposit	Type	Host Rocks	Alteration	Resource (Moz Au)	Au Age (Ma)
Haile	Sediment-hosted epithermal	Persimmon Fork metasediments	quartz-pyrite-sericite	4.20	549
Ridgeway	Sediment-hosted epithermal	Persimmon Fork metasediments	quartz-pyrite-sericite	1.44	553
Brewer	High sulfidation	Persimmon Fork metavolcanics	pyrite-enargite-chalcopyrite	0.26	550
Barite Hill	VMS	Persimmon Fork metasediments	quartz-barite-sericite	0.06	566

Source: OceanaGold & Foley and Ayuso, 2012

7.2 Local Geology

Haile geological history includes several major events, as listed below from oldest to youngest. Regional and local geologic maps are presented in Figure 7-2 and Figure 7-3. A schematic stratigraphic column is presented in Figure 7-4. A map of drillholes and two geologic cross sections are presented in Figure 7-5 and Figure 7-6.

Late Pre-Cambrian to Early Cambrian (580 to 530 Ma)

- Carolina Terrane formed as part of a subduction zone-oceanic island arc complex
- Persimmon Fork Formation deposited with metavolcanic and metasedimentary rocks - foliated laminated siltstone unit is the primary host rock for Haile mineralization
- Gold mineralization at Haile dated at ~549 Ma (Mobley, et al., 2014)
- Transition from volcanism to basinal sedimentation ~548 Ma (Persimmon Fork-Richtex boundary)
- Richtex Formation deposited (mudstones and siltstones) conformably on the Persimmon Fork

Carboniferous (320 to 290 Ma)

- ENE structural fabric developed during NW-SE compression and emplaced granite plutons and lamprophyre dikes within 5 km of Haile

Triassic - Early Jurassic (250 to 200 Ma)

- Diabase dikes intrude the Carolina Terrane as magnetic NW-SE-trending anomalies

Cretaceous to Present (100 Ma)

- Coastal Plain clayey sands deposited over all units, thickens southeastward

7.2.1 Lithology

The following rock units are described in chronostratigraphic order from oldest to youngest. Haile stratigraphy is described from mapping and core drilling over a thickness of about 1 km.

Neoproterozoic Rocks

Volcanic and interbedded epiclastic rocks are assigned to the approximately 3 km thick Persimmon Fork Formation that formed about 555 to 551 Ma (Hibbard et al., 2002). Richtex Formation siltstones conformably overlie the Persimmon Fork Formation approximately 0.5 km southeast of the Haile district. The Persimmon Fork-Richtex boundary marks the ~550 Ma change from volcanic-dominated

arc terrane to basinal sedimentary facies. Persimmon Fork and Richtex units are pervasively metamorphosed to lower greenschist facies with chlorite, carbonate, and pyrite. Neoproterozoic orthoclase-rich pink granites, such as the Longtown granite near Ridgeway, do not outcrop at Haile; the nearest equivalent outcrop is 10 km north of Haile.

Persimmon Fork Formation

The Neoproterozoic Persimmon Fork Formation at Haile consists of laminated siltstone with minor sandstone and conglomerate overlain and interfingering with lapilli and ash flow tuffs. Grey laminated, pyritic siltstones are the dominant host rocks the middle and lower portions of the mine stratigraphy. Siltstones dominantly strike N40°E to N75°E and dip 30-60° NW in north, west and central mine areas and dip 60-80°SE along the southern flank of the Haile district. Clastic rocks coarsen westward as sandstones around the Champion deposit. Sedimentary units are intruded by dacite, rhyodacite and rhyolite dikes and sills that range in thickness from 1 to 150 meters. Contacts are often gradational, and all units are foliated and sheared. Mylonites are frequently observed within 5-10 meters of lithologic contacts. Dacite is the most common volcanic rock at Haile with blocky, massive textures that contrast with the platy, foliated, more pyritic (1-2%) metasediments. Light grey dacite has porphyritic textures with 1 to 2 mm long euhedral plagioclase phenocrysts (3 to 10%) in an aphanitic groundmass with <1% pyrite. U-Pb ages from zircons in dacite yielded crystallization ages of 553 ± 2 Ma (Ayuso et al., 2005). The 550 Ma Haile gold system has been preserved from erosion because it is largely capped by resistant dacite flows and by rotation into its current sub-vertical position. Dacite occurs in three main areas:

- Along the southeast edge of the Haile system where dacite constrains mineralization at Horseshoe, Palomino and Red Hill;
- As a 10 to 60 m thick ENE-trending, 30-40° NW-dipping sill that cuts and underplates orebodies at Red Hill, Haile and Snake;
- Overlying and capping ore zones along the north edge of the district at Mill Zone and Ledbetter.

Dacite is conformably overlain and interbedded with pale grey, pyrite-poor lapilli and ash flow tuffs with subangular siltstone clasts in a fine-grained tuffaceous matrix with chloritized pumice fragments. Tuffaceous rocks mostly occur in north-central areas of the Haile district at Ledbetter and Snake. They have irregular, hackly joints in contrast to the harder, well-jointed dacites. Quartz feldspar porphyry (QFP) dikes with stockwork quartz-pyrite veins are locally mineralized at Ledbetter, Horseshoe, Snake and Palomino. QFP dikes may be an important component of the hydrothermal system and cause local upgrading.

Richtex Formation

The Richtex Formation conformably overlies the Persimmon Fork Formation along the southeast edge of Haile. The Richtex consists of ENE-striking, 40 to 60° SE-dipping, thin-bedded siltstone and mudstone with sandstone. The lower portion of the Richtex Formation contains mafic tuff and amygdaloidal basalt flows near Ridgeway (Secor and Wagener, 1968). Thickness near Haile is unknown but is >3 km thick near Ridgeway. The Richtex Formation is unconformably overlain by Cretaceous Coastal Plain Sands southeast of Haile.

Lamprophyre Dikes

Lamprophyre dikes intrude rocks of the Persimmon Fork and Richtex Formations. Lamprophyres are dark green and fine-grained with spherulitic textures. These dark green dikes contain biotite, hornblende and plagioclase with chlorite and calcite. The near-vertical dikes are strike N-S and E-W and range in thickness from 1 cm to 2 m. Lamprophyre volume at Haile is estimated at about 1%. Lamprophyres are not foliated or pyritic and were likely emplaced during waning stages of the Alleghanian Orogeny. $^{40}\text{Ar}/^{39}\text{Ar}$ dates in biotite yielded Pennsylvanian ages at approximately 311 Ma, coincident with the Dutchman Creek Gabbro (Fullagar and Butler, 1979).

Granites

The northeast-elongated Liberty Hill and Pageland plutons are exposed 8 km west and 5 km north of the Haile mine. These fresh, medium-grained granites have less than 5% biotite + hornblende and are weakly foliated. The Liberty Hill granite (30 x 20 km) is dated at 293 ± 15 Ma. The Pageland granite (25 x 10 km) is dated at 296 ± 5 Ma (Fullagar and Butler, 1979). Granite has not been observed in drillholes at Haile. Metamorphic aureoles around the plutons are <0.5 km wide and do not impact rocks at Haile.

Diabase Dikes


Diabase dikes are dark gray, dense, medium-grained, ophitic and magnetic. These dikes conspicuously cut all other units except the Coastal Plain Sands. Dominant minerals are plagioclase and pyroxene with minor biotite, olivine, chlorite and calcite. The diabase dikes often have chilled margins that are sometimes faulted with apparent dextral displacement. The dikes strike N20°W to N30°W with near-vertical dips and range in thickness from 1 to 30 m. Diabase dikes at Haile occur as both discrete dikes and as swarms (at Mill Zone and Horseshoe) tens of meters wide with a spacing of 300 to 400 meters. Diabase dikes have horsetail, anastomosing and sigmoidal geometries. The dikes weather to dark brown, earthy colors. The Triassic diabase dikes postdate gold mineralization and range in age from 222 to 220 Ma (Dooley and Smith, 1982). They account for about 5% by volume of rocks at Haile and often truncate ore zones.

Saprolite

Most of South Carolina is covered by saprolite. Saprolite is a thick, structureless, unconsolidated, kaolin-rich, red orange to white residuum derived from intense acidic bedrock weathering in sub-tropical climates. Saprolite thickness ranges from 10 to 40 m at Haile and is thickest in Fe-Mg-rich metavolcanic rocks and along faults. The base of saprolite is irregular and grades downward into partially weathered bedrock. Saprolite is rarely mineralized at Haile.


Coastal Plain Sand

The Cretaceous Middendorf Formation (Nystrom et al., 1991) is a southeastward-thickening apron of unconsolidated sand. Its northwest limit conceals much of the Haile property. The sands postdate gold mineralization and is the youngest unit in the region. The sands are up to 30 m thick at Haile and hundreds of meters thick south of Haile. The basal portion contains 10 to 60 cm thick layers of red brown ferricrete and quartz pebbles in a sandy matrix. The middle unit is white to red sand with a kaolinite matrix with frequent cross bedding. The upper unit is a clean tan to white quartz sand.

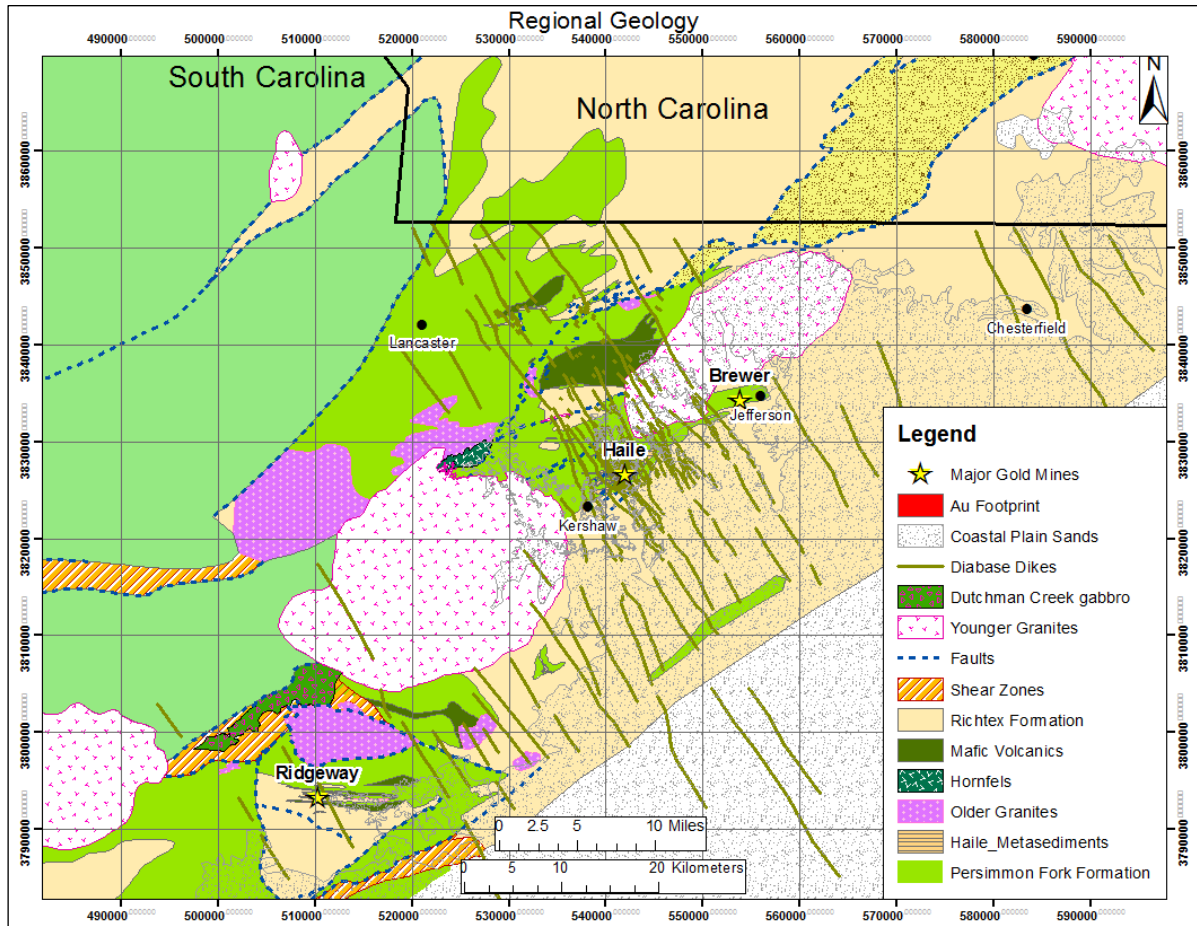


Source: OceanaGold

Figure 7-2: District Geology of North-Central South Carolina (UTM NAD83 Z17N)

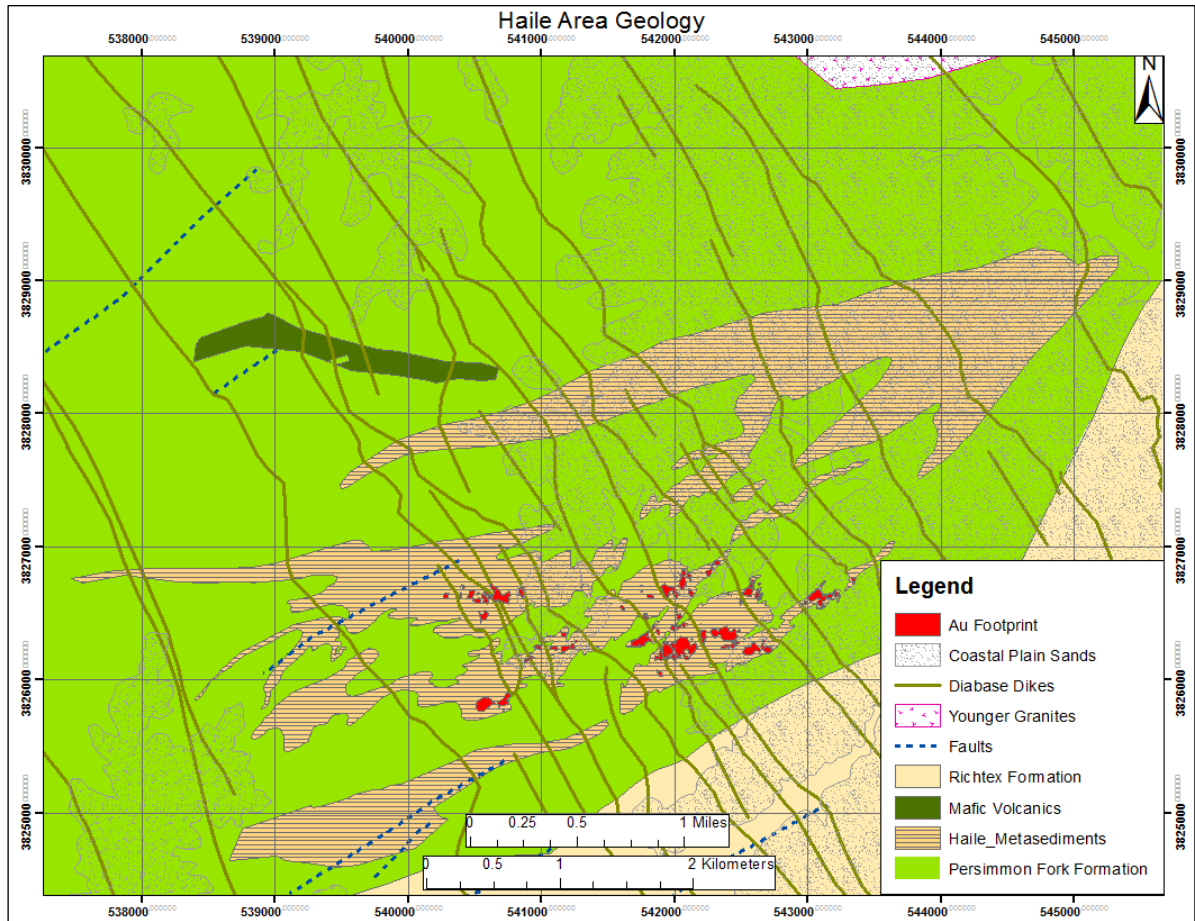


Source: OceanaGold

Figure 7-3: Geologic Map of the Haile Area with Gold Zones (UTM NAD83 Z17N)

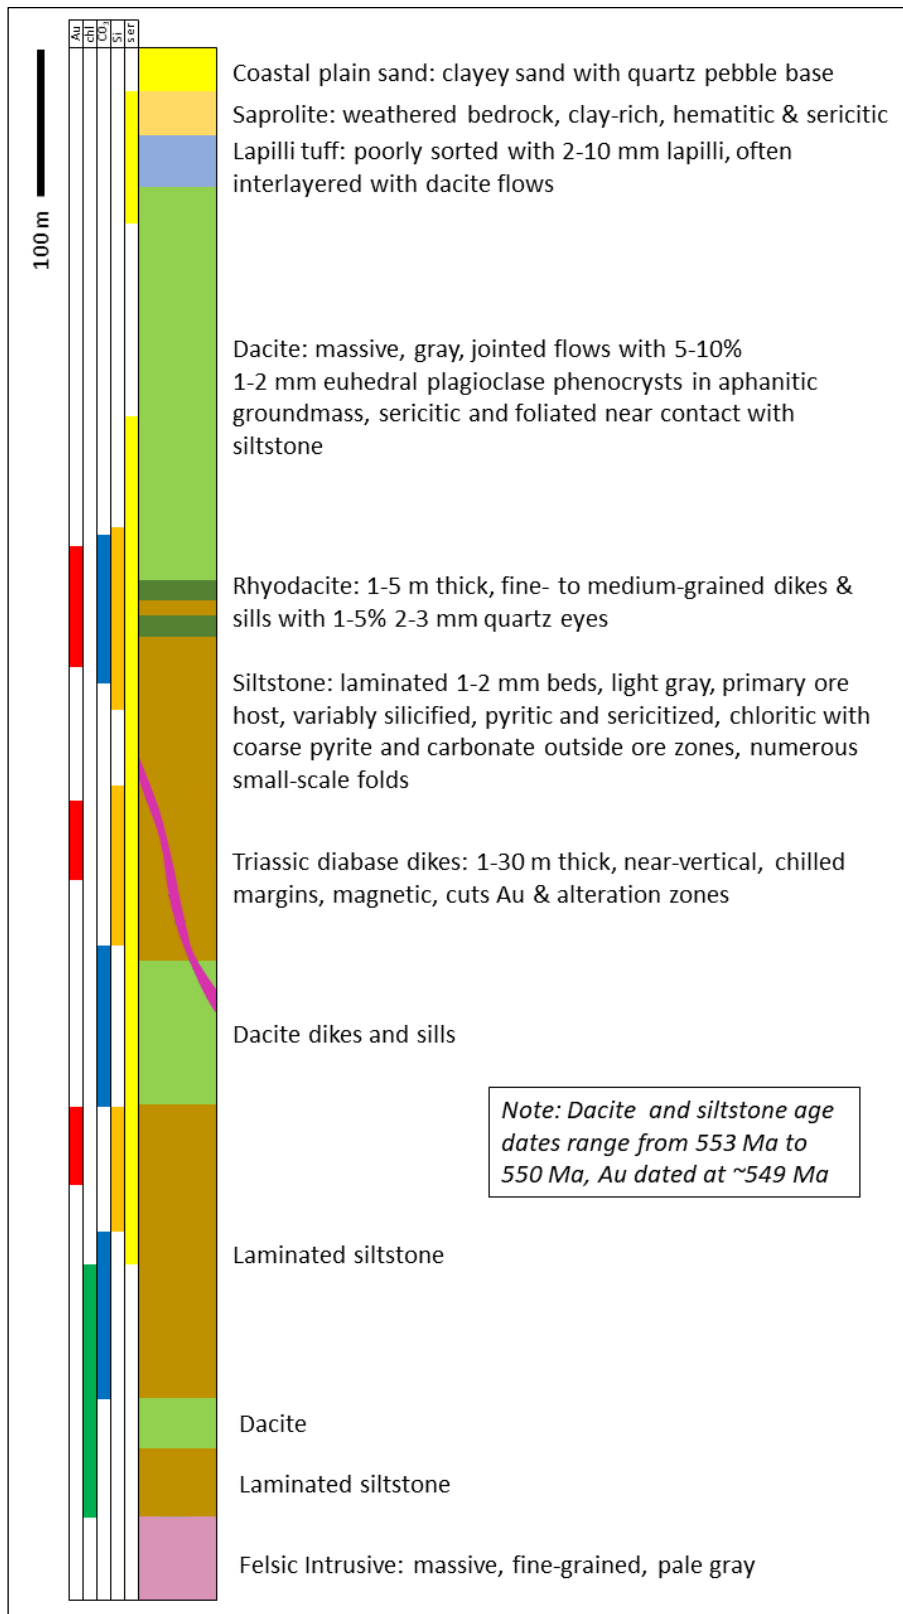


Source: OceanaGold

Figure 7-4: Haile Stratigraphic Column

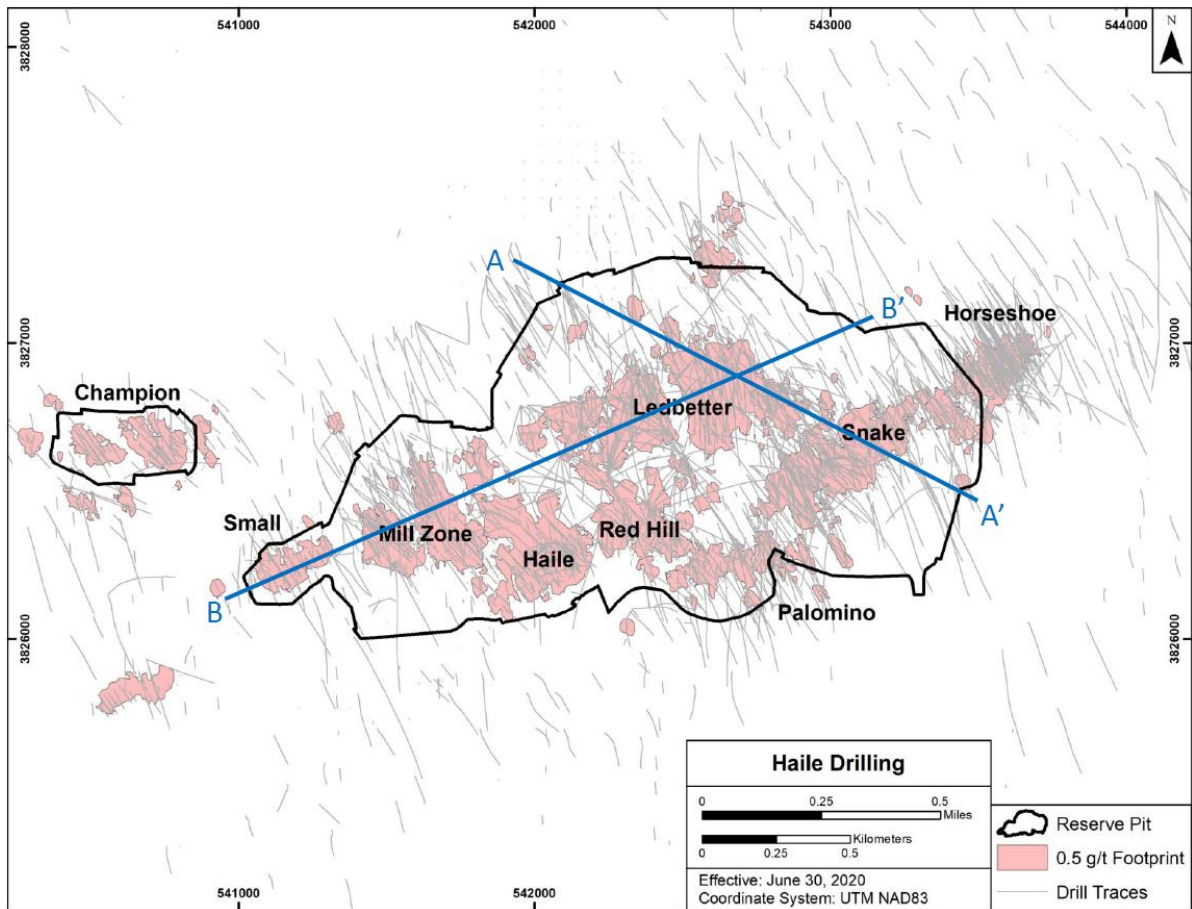

Source: OceanaGold

Figure 7-5: Plan View of Drillholes used for Resource Estimation, Gold Mineralization, and EOY 2019 Reserve Pit Limit (Sections A-A' and B-B' are Presented in Figure 7-6)

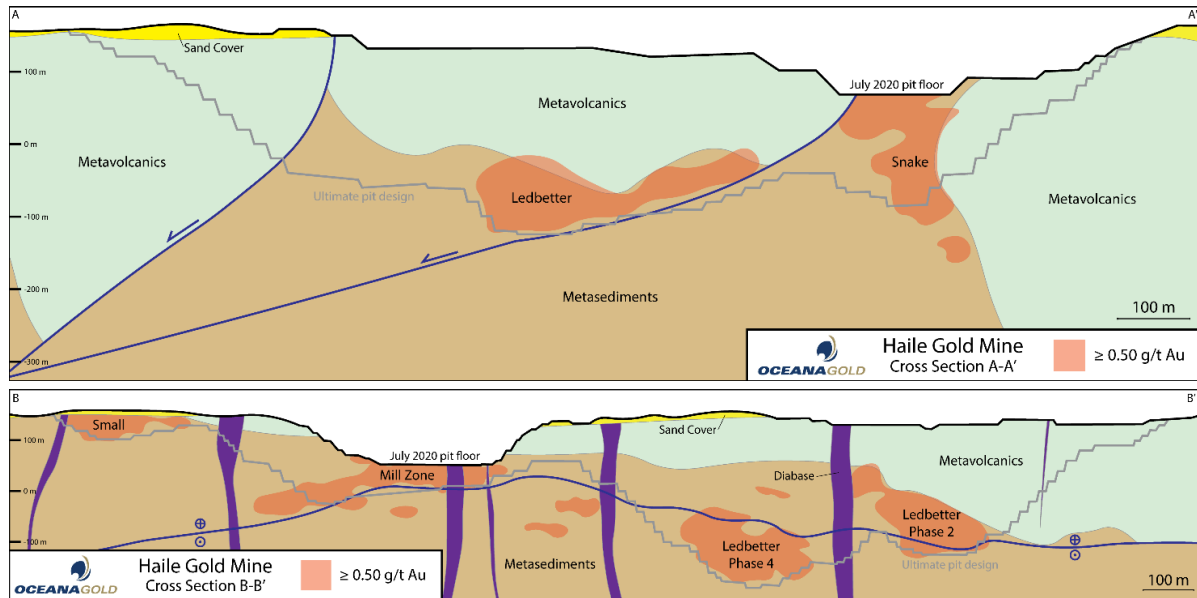

Source: OceanaGold

Figure 7-6: Cross-sections A-A' (NE-looking) and B-B' (NW-looking) with Geology, Gold Mineralization, and Pit Design

7.2.2 Structure

The structural history of Haile is complex and is affected by four orogenic episodes, as summarized in Section 7.1 and depicted in Figure 7-1.

Four deformation/geological events are observed at Haile; the D₁ and D₂ events provide the dominant geometric constraints on the Haile ore deposits.

- **D₁ syn-mineral hydrothermal replacement** of sedimentary rocks by silica and pyrite with Au, Ag, As and Mo precipitation along ENE faults and foliation; rocks were likely in a nearly flat position and were intruded by dacite flows and capped by pyroclastic rocks.
- **D₂ regional Alleghanian metamorphism and deformation** (folding, shearing, pervasive foliation, quartz veins) and greenschist facies metamorphism (chlorite, carbonate, coarse pyrite); this is the dominant event that overprints the Haile region. Pervasive foliation strikes east-northeast and dips 40-60° northwest. Foliation intensity increases along sedimentary-volcanic contacts and is strongly developed in laminated siltstones where gold mineralization is hosted. Rocks were folded into an asymmetric anticlinorium with a steep southeast limb and moderate northwest limb.
- **D₃ minor brittle reactivation** of foliation along NW-dipping normal faults; displaces some ore zones.
- **D₄ diabase dike intrusion** and minor dextral faults down step district from west to east (Figure 7-6).

Figure 7-7 highlights the intense ductile and brittle strain fabrics that overprint and deform ore zones at Haile. The top photo shows pressure solution cleavage S1 imposed on folded S0 bedding flanked by a shear zone of completely transposed bedding. The lower photo shows axial planar cleavage S1 in folded and bedded S0 siltstone with folded pyrite lenses. At ore deposit scale, the pyrite lenses are similar to irregular ore zone shapes. Compositional layering sub-parallel to foliation is generally transposed bedding and represents a S1 or S2 fabrics (Hayward, 1992). S1 foliation is formed by both pressure solution parallel to axial planes of folds and ductile shear strain.

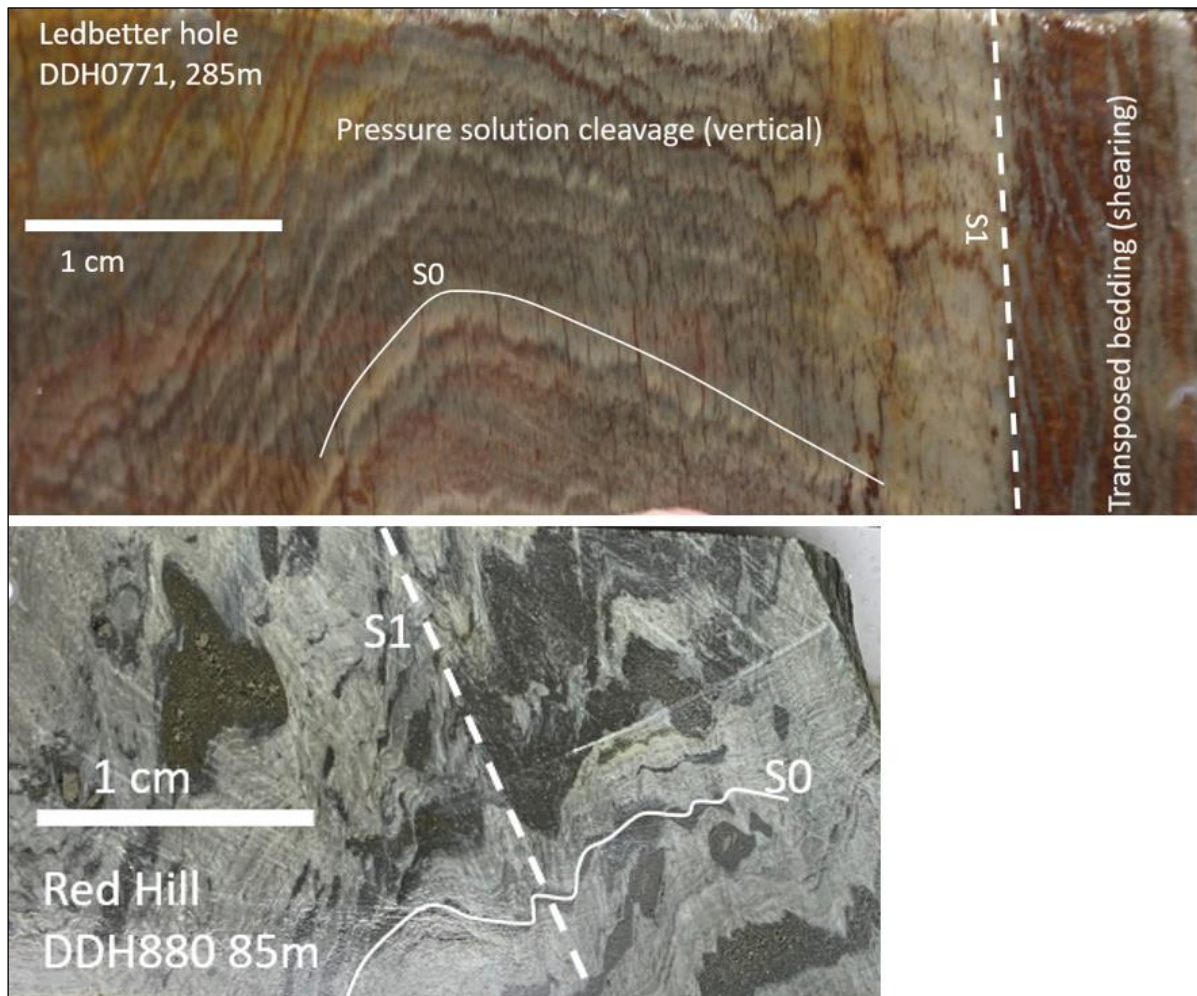


Figure 7-7: High Strain Fabrics in Core Samples

Many contacts between volcanic and sedimentary rocks have undergone grain size reduction and thus represent high strain zones recording ductile slip. Greenschist facies metamorphism produced significant volume loss due to dehydration reactions at temperatures of 250 to 300°C and developed pressure solution cleavage. Metamorphism converted micas and feldspars to chlorite and clays.

The Haile gold deposits are exposed within a metasediment (Ms) window flanked and overlain by metavolcanic rocks (Mv). Eastward tilting and erosion have exposed an oblique section with older rocks exposed in the west near the Champion deposit. The ENE-trending window is about 4 km long by 0.5 to 1 km wide (Figure 7-3). Sedimentary rocks are folded within an ENE-trending anticlinorium

with a steep SE limb and a moderate NW limb. The Mv/Ms contact is conformable with bedding. High strain fabrics overprint all Mv and Ms units in the mine area. The ENE-striking Mv/Ms contact dips 60-80°SE along the southeast margin of the district and constrains gold mineralization at Red Hill East, Palomino, Deep Snake and Horseshoe. The Mv/Ms contact dips 30-50°NW in north-central portions of district and caps gold mineralization at Ledbetter, Upper Snake, Mill Zone, and Red Hill West.

The district is dissected by several ENE-striking, 30 to 60° NW-dipping dip- and oblique-slip normal faults that appear to both focus gold mineralization and displace mineralized zones. The eastern portions of Ledbetter are interpreted to represent the fault-displaced and sheared upper part of the Snake orebody (Figure 7-6). The Mill Zone orebody is faulted into two segments with about 100 m of normal displacement and is likely a normal displaced portion of the Haile deposit. Brittle deformation is characterized by anastomosing shear zones with discrete but thin slip planes, commonly filled with ribbon quartz or gouge. Fold axes observed in drilling and mapping are mostly occur in the southeast portion of the district in the Red Hill, Palomino and Snake deposits. Portions of the Ledbetter deposit contain chaotic folds with variable orientations. Fold axes strike N40° E to N70° E and plunge gently east.

Quartz ($\pm$ pyrite + calcite + ankerite) veins are locally common at Haile, notably in the Mill Zone, Haile, Red Hill and Horseshoe deposits. Near-vertical quartz veins typically strike N-S to N15°E, are 1 to 60 cm thick, and are rarely mineralized. Crustiform textures indicative of boiling are only observed in high-grade portions of the Horseshoe and Ledbetter deposits. Two phases of quartz veins are recognized at Haile. The earlier phase is pale gray with finely disseminated pyrite, has diffuse contacts, and is very fine-grained. In rare mineralized examples, pyrite adjoins or is interlocked with visible gold up to 0.2 mm in size at Horseshoe. The more common quartz vein type consists of massive, cross-cutting, white bull quartz veins that are barren of gold.

7.2.3 Mineralization and Alteration

Haile gold mineralization occurs as en echelon clusters of moderately to steeply dipping ore lenses within a 4 km x 1 km area. Nine named gold deposits are recognized at Haile. From west to east, these deposits include Champion, Small, Mill Zone, Haile, Ledbetter, Red Hill, Palomino, Snake and Horseshoe that often show 'pearls on a string' alignment (Figure 7-5). Ledbetter is by far the largest orebody (approximately 1M oz) and includes the shallow Chase and deep Mustang deposits. Orebody geometry, depth, size, grade, mineralogy, and alteration are variable. Orebody geometry is partly controlled by orientation of volcanic-sediment contacts and location of barren dacite sills. Ore lenses are typically 50 to 300 m long, 20 to 100 m wide, and 5 to 30 m thick. Ore zones are separated by barren siltstone, dacite sills and diabase dikes. The Mv/Ms contact and gold mineralization gradually deepen from west to east across the Haile district (Figure 7-6). The Mv/Ms contact at Champion has been partly removed by erosion in the west portion of the district and is over 500 m deep at the Horseshoe deposit, 4 km east of Champion. Depth and position of the contact are complicated by faulting and folding. Drilling in southeast areas around Palomino has encountered gold mineralization up to 1 km deep.

Gold mineralization at Haile is mostly hosted by laminated siltstone in the Upper Persimmon Fork Formation and is capped by less permeable coherent dacite. Mineralization is typically within 100 m of the dacite-siltstone contacts. Gold mineralization is disseminated in silicified and fine-grained, pyritic siltstone with local K-feldspar and molybdenite. Small mineralized zones at Ledbetter, Red Hill and Snake are hosted in dacite along fault zones within 15 m of the Mv/Ms contact. Gold grades in

mineralized dacite are typically weaker than in the underlying siltstone and sericite alteration is stronger in the dacite. Hydrothermal brecciation is common in portions of the Ledbetter, Horseshoe, Small and Champion deposits where milled, silicified siltstone clasts occur in a fine-grained quartz-pyrite matrix intruded by fingers of quartz feldspar porphyry with quartz stockwork veinlets.

Mineral zonation grades outward from quartz-pyrite $\pm$ K-feldspar + gold (QS) $\rightarrow$ quartz-sericite-pyrite $\pm$ gold (QSP) $\rightarrow$ sericite + pyrite $\pm$ pyrrhotite $\rightarrow$ chlorite-calcite $\pm$ epidote (propylitic). QS and QSP mineralized zones are tens of meters thick. Sericite envelopes range in thickness from tens to hundreds of meters and are controlled by protolith, permeability, and weathering. Within the mineralized zones, quartz is dominant (60% to 80%), pyrite is moderate (1% to 10%), and sericite is variable at 5% to 40%. Semi-massive pyrite zones are locally observed over thicknesses of 0.5 to 5 m, especially in the Mill Zone, Red Hill and Haile pits.

Two silicification events are observed in the mineralized zones. Early massive silicification is finely disseminated to diffuse with less than 1% pyrite. This pyrite-poor silicification correlates roughly with the 0.1 g/t Au shell. Phase two silicification is manifested as matrix fill in tectonic and hydrothermal breccias with 1% to 5% pyrite and is associated with grades more than 0.5 g/t Au. High-grade gold zones more than 3 g/t are characterized by intense silicification and more than 1% fine-grained disseminated pyrite. Pyrite grain size is typically less than 20 microns in ore zones. Pre-ore silica-pyrite zones are frequently stretched, boudined and sheared (Figure 7-7). A second phase of barren, coarse, cubic, undeformed pyrite overprints the fine-grained pyrite that formed during regional greenschist metamorphism. Pyrite cubes in chloritic metamorphosed rocks are 0.5 to 1 mm in size but can be as large as 1 to 2 cm. Pyrrhotite occurs in 5 to 25 m thick halos around and on the edges of ore zones. Its ductile nature produces length: width ratios more than 5:1 in foliated rocks. Pyrrhotite formation is interpreted to be coeval with early, fine-grained pyrite precipitation.

Supergene sericite-kaolinite alteration forms large bleached, cream to white halos around the ore zones with little to no pyrite that was removed during intense acidic leaching. Strong supergene alteration caps and flanks most of the district. Strong sericite alteration is rarely observed deeper than 40 to 50 m. Numerous shallow sericite-kaolinite bodies were mined historically for paint filler.

Propylitic alteration is characterized by increased chlorite (25% to 50%) and a mottled texture with blebs of 1 to 5 mm calcite/ankerite aggregates (2 to 10%) and stockwork. Late calcite $\pm$ quartz veining is often focused along fault zones and along shear zones within strongly deformed rocks. Sigmoidal pods of strained quartz are often observed. Oxidation at Haile extends to depths of 20 to 60 m and is deepest along faults and in volcanic rocks. Hematite and goethite are strongest near surface in the saprolite and decrease at depth as weak joint stains.

Gold spatially correlates with silver, arsenic, molybdenum, and tellurium. Base metals are rare at Haile. Thin section petrography and scanning electron microscopy show that the gold occurs as native gold, gold-pyrite and gold-pyrite-pyrrhotite clusters in fine-grained silicified zones. Smeared molybdenite occurs primarily on foliation surfaces and as fine-grained aggregates in silicified zones. Molybdenite at Haile has been dated by Re-Os isotopes at 553.8 ± 9 Ma (Stein et al., 1997), which is coeval with the zircon crystallization age of 553 ± 2 Ma reported by Ayuso et al. (2005). This age correlation indicates that molybdenite mineralization was concurrent with Persimmon Fork volcanism. Seven Re-Os molybdenite ages from Haile (Mobley et al., 2014) yielded ages ranging from 529 to 564 Ma. Four of these samples produced an average age date of 548.7 ± 2 Ma (Mobley et al., 2014).

8 Deposit Type

Hundreds of gold deposits in the southeast USA are located along a 700 km long SW-NE trend that extends from Alabama to Virginia (McCauley and Butler, 1966, Butler and Secor, 1991). Most of these deposits are small prospects worked and explored along narrow quartz veins. The larger gold deposits are located at or near the contact between volcanic and sedimentary rocks, including the Haile, Brewer, Barite Hill and Ridgeway mines. Brewer is unique in the region and is classified as a high-sulfidation epithermal gold system with volcanic and breccia-hosted gold accompanied by quartz, pyrite, topaz, enargite and chalcopyrite. Gold mineralization at Barite Hill contains the assemblage of pyrite-chalcopyrite-galena-sphalerite and is characteristic of a submarine, high-sulfidation volcanogenic massive sulfide deposit. Haile and Ridgeway are similar in that sediment-hosted gold mineralization is hosted by silicified, sheared and foliated siltstone.

8.1 Haile Genetic Model

The origin of the Carolina slate belt deposits is one of the more controversial types of gold deposits. Genetic models include:

- Worthington and Kiff (1970) concluded that a genetic link must exist between ore genesis and volcanism in the Carolina Terrane due to their volcanic host rocks.
- Spence et al. (1980) found a genetic link between gold mineralization hosted within siliceous and pyritic zones and intense alumina alteration which produced kaolinite and sericite-rich zones stratigraphically above mineralized zones and interpreted these as analogous to features observed in modern hot springs based on geochemical signatures, stratiform nature, stratigraphic position, and geochronology.
- Feiss et al. (1993) built on the model of Spence et al. (1980) by proposing that hot spring-type mineralization must have occurred under extension in a back-arc setting based on oxygen isotope data, which they interpreted to mark a shift from a subaerial to submarine environment. Feiss et al. classified Haile as a syngenetic hot spring system formed as the volcano-sedimentary pile accumulated with subsequent metamorphic overprints.
- Maddry and Speer (1993) proposed an exhalative model for mineralization at Haile whereby gold deposition resulted from hydrothermal fluids venting to the seafloor to produce stratabound ore bodies in marine volcanoclastic rocks. They interpreted intense alumina alteration noted by Spence et al. (1980) to be the effects of saprolitic weathering in warm, humid climates.
- Strong ductile deformation and structural dismemberment, mineral paragenesis, and mineral textures suggest ore deposition within shear zones or fold axes and that the fluid source was from metamorphic devolatilization reactions and pressure solutions related to Precambrian collisional events (e.g., Tomkinson, 1988; Hayward, 1992). Hayward (1992) emphasized the importance of folds in controlling the location of ore formation in anticlinal fold hinges. Hayward also noted that alteration zones at Haile are generally discordant to bedding and commonly display symmetrical patterns around ore bodies.
- Tomkinson (1988) proposed that Haile was an orogenic deposit based on textural and structural connections between gold mineralization and shear zones.

- Bierlein & Crowe (2000) discussed evidence for epigenetic (i.e. orogenic) vs. syngenetic gold mineralization for CSB gold deposits and concluded the evidence strongly favored syngenetic mineralization with local gold remobilization.
- Hardy (1989) and Worthington (1993) interpreted the features observed by Hayward (1992) and Tomkinson (1988) as evidence for the remobilization of pre-existing mineralized horizons, causing gold enrichment along structurally controlled pathways during deformation which postdated the primary phase of mineralization at Haile. Hardy also concluded that fluids deposited silica, K-feldspar, pyrite, and gold in breccia zones.
- Gillon et al. (1995) proposed a model at Ridgeway that invoked early gold mineralization and remobilization during Neoproterozoic deformation.
- O'Brien et al. (1998) proposed that the gold deposits were formed during arc-related volcanic activity in a hydrothermal system.
- Foley et al. (2001) observed multiple generations of pyrite in Haile ores and concluded that disseminated pyrite and gold mineralization were contemporaneous with host volcanic rocks and volcanoclastic sediments.

Pressure shadows around pyrite grains, stretched pyrite and pyrrhotite grains, and flattened hydrothermal breccia clasts indicate that gold mineralization is largely pre-tectonic. Mineralized zones were subsequently foliated and sheared during the Alleghanian Orogeny approximately 250 million years after gold mineralization. Deformation was accompanied by regional greenschist facies metamorphism. Similar timing for gold mineralization and peak magmatism in the Haile and Ridgeway areas indicates that the hydrothermal systems that produced these deposits were driven by magmatism and were not the product of collision, orogeny, and/or a related metamorphic event. Haile is interpreted as a low sulfidation, disseminated, sediment-hosted, epithermal gold system based on tectonic setting, structural control of shear zone-hosted mineralization, low sulfide contents, host rock lithology, and geochemistry.

8.2 Haile Geological Model

The Haile geological model was constructed using Maptek's Vulcan and Seequent's Leapfrog software. The model box is approximately 4 km EW by 2 km NS by 800 m deep. Geologic controls for Haile ore bodies are well understood and are documented by mapping and drilling in 3,295 drillholes including 1,255 core holes for 394,771 m (57% m) and 2,040 holes for 294,216 m (43% m). Mineralization is relatively continuous for reliable grade models constrained by geological controls (sand, dikes, volcanic-sediment contacts). The Haile geological models are updated twice per year.

The model consists of 3D solids for the following five geological units, from youngest to oldest: Coastal Plain Sands, saprolite, diabase dikes, metasedimentary rocks, and metavolcanic rocks. Surfaces that represent oblique-normal faults, the base of oxidation, and the base of clay have also been modeled. Consistency of the geologic model has been improved by relogging of several hundred core holes and incorporation of pXRF and other geochemical data.

9 Exploration

9.1 Pre-Romarco

Modern exploration, development, and mining activity on the Haile property began with mapping in 1970 (Worthington and Kiff, 1970). Between 1973 and 1977, Cyprus Exploration Company (Cyprus) conducted an extensive exploration program consisting of surface geophysical surveys, trenching, geologic mapping, auger drilling, core drilling, air-track drilling, and metallurgical testing. Cyprus calculated the Haile resources at 186,000 oz (5,785 kg) of gold with an average grade of 2.13 g/t. Resources reported in this section do not conform to the standards of NI 43-101 and are included only as part of the historic record.

Between 1981 and 1985, Piedmont explored the historic Haile Mine and surrounding properties with core and reverse circulation drilling, surface geophysics, soil sampling, trenching, and rock-chip sampling. Piedmont's total drilling footage was 69,647 m, much of which was for mine development. Piedmont mined several deposits on the Haile property from 1985 to 1992, producing about 86,000 oz (2,675 kg) of gold.

In 1991, Amax performed an extensive exploration program on the Haile property under an exploration option with Piedmont. In 1992, Amax and Piedmont formed HMC as a joint venture, and from 1992 to 1994 HMC (the operating company) completed a program of exploration/development drilling using core and reverse circulation drilling, mineral resource estimation, and technical report preparation. The Ledbetter deposit was discovered, and the Mill and Snake areas were expanded.

Kinross acquired Amax in 1998, assumed Amax's portion of the HMC joint venture, and later purchased Piedmont's interest. Kinross performed no exploration activities on the property and limited their operations to a highly successful reclamation program from 1998 to 2007.

9.2 Romarco

Romarco completed the Haile property acquisition in October 2007. By February 2008 Romarco had confirmed the quality of historical drilling and assay data and turned their effort to exploration and resource expansion drilling. During its ownership, Romarco expanded the resource and reserve of the property by five-fold. This report documents the results of the drill program achieved to date with Romarco assay data available through November 17, 2011 (i.e. data cut-off for previous IMC15 resource estimate), and subsequently by OceanaGold, as described below.

9.3 OceanaGold Exploration

OceanaGold purchased the Haile property from Romarco in October 2015 and continued the drilling programs designed to expand resources and reserves at Haile. Mine development drilling is ongoing.

9.3.1 Geologic Mapping and Surface Sampling

Numerous workers have performed geologic mapping and surface sampling in and around the Haile Mine area. Mapping is challenged by poor bedrock exposure due to extensive saprolitic weathering, Coastal Plain Sand cover, and dense vegetation. Outcrop is estimated at only 1% to 2% in the Haile area. High-quality mapping is generally restricted to excavations related to mining. The USGS published a geologic map for the Kershaw quadrangle in 1980 (Bell, 1980). More detailed mapping

was conducted at Haile by Spence, Kiff, and Maye, who constructed a detailed geologic map for the mine site in 1975. Subsequent detailed geologic mapping was done by Taylor in 1985 and Cochrane in 1986. Ph. D. dissertations by Tomkinson (1985) and by Hayward (1988) included detailed geologic mapping in open pits. Geologic mapping at the Mill Zone pit resumed with mining in 2016 by OceanaGold geologists.

Historical mapping has been scanned and loaded into the Vulcan software for structural interpretation, exploration planning, and geologic modeling. The use of the structural dataset in conjunction with the drilling dataset has provided the foundation for a 3D digital geologic model. This model continues to be used successfully to expand the resources and reserves at the Haile property. Surface samples have been compiled into an Access database and evaluated by OceanaGold. Over 5,000 samples have been compiled based on location, sample type (rock chip, saprolite, soil, stream sediment), rock type, alteration and assay. QA/QC data are generally lacking for these samples and most were assayed only for gold.

9.3.2 Geophysics

Numerous geophysical surveys have been conducted at Haile since the 1970s. The following geophysical methods have been applied at Haile:

- Gravity
- Airborne Magnetism
- Airborne Electromagnetics
- Ground-based Induced Polarization
- Ground-based Electrical Resistivity
- Self-Potential

Numerous IP/Resistivity surveys have been conducted at Haile, including surveys by Piedmont in 1975 and 1989, by Romarco in 2015 at Champion, Mill Zone, Ledbetter, and Horseshoe, and by OceanaGold in 2016 adjacent to Haile. Geophysical surveys conducted by Piedmont in the late 1980s include ground magnetism and dipole-dipole IP/resistivity methods that led to discovery of the Snake deposit (Larson and Worthington, 1989). The ground magnetic data were acquired in a patchwork fashion and were not corrected for diurnal changes. The dipole-dipole IP/resistivity data were reprocessed by OceanaGold in 2016 (Weis, 2016).

Regional gravity survey and aeromagnetic data have been downloaded from the South Carolina data repository (Daniels, 2005). These were supplemented by more detailed gravity stations in 2009 and 2010 by Romarco along roads in the Haile area and as transects over Haile deposits.

Airborne EM and magnetic surveys were flown by Aeroquest for Romarco in 2010 over the Haile-Brewer area on 50 m and 100 m spaced flight lines with a bearing of 150°-330°. The magnetic data can map the diabase dikes and granite plutons but do not differentiate the older units. Proprietary 3D inversion modeling was conducted by OceanaGold in 2016 to depths of 1,500 m using airborne magnetic and EM data.

10 Drilling

During 2016, the Romarco Minerals drilling database was translated to OceanaGold's standard Acquire database platform. Where available, original source assay and survey data were used for the Acquire translation and database validation. There was a further internal database review in late 2018/early 2019. No material errors were identified.

10.1 Type and Extent

Drilling at the Haile property commenced in the 1970s and has continued intermittently to the present by several companies. The database used for this resource estimate was extracted from the Acquire database on 14 May 2020. It contains 3,295 drillholes including 1,255 core holes for 394,771 m (57% m) and 2,040 reverse-circulation (RC) holes for 294,216 m (43% m). Some of the historical drilling (i.e. shallow exploration auger or air-track holes) was judged insufficiently reliable and was excluded from the resource model. RC and core drilling by Romarco continued from 2008 to 2012 and then resumed in 2015 after a two-year hiatus due to permitting and lower gold prices. Drilling at Haile since early 2015, has almost entirely been as core drilling. Drill campaigns by company and year are summarized in Table 10-1.

Table 10-1: Haile Drilling Campaigns by Year, Owner and Lab

Start Hole ID	End Hole ID	Hole Type	Start Yr.	End Yr.	Owner	Lab
DDH0001	DDH0031	core	1975	1977	Cyprus	CMS, Cyprus, Union
DDH0032	DDH0098	core	1985	1990	Piedmont	Piedmont, NE
DDH0099	DDH0288	core	1991		AMAX	Geochemical
DDH0289	DDH0341	core	2008	Aug 2015	Romarco	Bondar Clegg
DDH0342	DDH0431	core	2008	2009	Romarco	Inspectorate
DDH0432	DDH511	core	2009	Sep-11	Romarco	Alaska
						Kershaw Mineral Lab (KML)
DDH512	DDH596	core	Oct-11	Jun-17	OceanaGold	KML
DDH0597	DDH1006	core	Jul-17	ongoing	OceanaGold	ALS
NHD0001	NHD0037	core	1985	1988	Nicor	Cone Geochemical
NRH0001	NRH0054	RC	1987	1988	Nicor	Cone Geochemical
RC0001	RC0031	RC	1985	1986	Piedmont	Union
RC0032	RC0183	RC	1986	1987	Piedmont	NE Geochemical
RC0184	RC1230	RC	1987	1990	Piedmont	Bondar Clegg, NE
RC1231	RC1303	RC	1990	1992	Piedmont	Geochemical
RC1304	RC1501	RC	1992	1994	AMAX	Bondar Clegg
RC1502	RC1527	RC	2008	2009	Romarco	Bondar Clegg
RC1528	RC2083	RC	Jan-10	Jan 2011	Romarco	Inspectorate
RC2084	RC2122	RC	Jan-11	Sep-11	Romarco	Alaska
						Acme, Chemex, KML
RC2123	RC2105	RC	Oct-11	Jun-15	Romarco	KML
RCT0001	RCT0157	RC/core	Apr-10	Jan-11	Romarco	Alaska
RCT0158	RCT0178	RC/core	Jan-11	Sep-11	Romarco	Acme
RCT0179	RCT0211	RC/core	Oct-11	Dec-12	Romarco	KML
WW0600	WW0673	RC	1975	1990	Piedmont	NE Geochemical

Source: OceanaGold

10.2 Sample Collection

Both Reverse Circulation (RC) and Diamond Drilling (DDH) have been used for the resource estimates at Haile. This section describes the sampling procedures applied to both data collection techniques. Historical drilling prior to 2007 accounts for approximately 28% of the data. The sample procedures applied to the historic drilling (i.e. drilling prior to Romarco Minerals Inc.) at Haile are not well documented. Having said this, approximately four years of mining has tested the veracity of the resource estimates which are based on this data. No material flaws have been identified.

The techniques described in this section reflect the procedures applied by Romarco and OceanaGold during the period 2007 to July 2020. John Jory, Director of Exploration for OceanaGold since August 2016, is the competent person for this section. He has reviewed the sample preparation, analysis, and security utilized by HGM and finds the procedures to be proper for determination of Mineral Resources and Ore Reserves.

Reverse Circulation (RC) Drilling

RC drills are equipped with a cyclone and a rotary splitter. Most RC drilling at Haile was under wet conditions. Water injection was typically 0.25 to 0.31 L/sec (4 to 5 gpm) above the water table and decreased to 0.06 L/sec (1 gpm) when groundwater was encountered.

Sample sizes were between 3 to 7 kg (20 and 30 lbs) with a minimum requirement of 3 kg (15 lbs). The standard size reflected a 15 to 20% split of the total drilled volume. Drill intervals were generally 1.5 m (5 ft) intervals.

For each 1.5 m (5 ft) interval, a sample container was placed on top of the splitter table to catch the flow from the sample splitter. Labeled, sample bags measuring 500 mm by 600 mm (20" by 24") were placed in 20 L (five to seven-gallon) plastic buckets. Multiple 6 mm (quarter inch) holes were predrilled in the plastic buckets to reduce the suction of a full sample bag and allow limited water drainage. The top of the sample bag was folded securely over the edge of the bucket. This was the sample container that was placed under the splitter to catch the sample discharge. Flocculent was added to each sample bag as it was placed on the splitter table to aid in precipitating fine material from the sample. As one sample container filled, another sample bag was prepared in advance and staged near the splitter table. On the driller's signal, the sample containers were switched instantaneously at the break between 1.5 m (5 ft) drill intervals.

Sampling during advancement of each twenty-foot (6.1 m) rod was a continuous process. Sample timing was metered by the count of the driller, as determined by drill speed and sample return rate. After each rod break, a new rod was attached, and the borehole was thoroughly flushed. The driller would raise the bit slightly off bottom and blow the borehole clean before beginning the next interval. Once the sample return was clean, the bit was lowered, and drilling began on the next twenty-foot rod. Then, the driller counted the time it took for the discharge water to turn from clear to muddy, which approximated the return rate of samples to the surface. Markings on the drilling rig feeder cable denoted five-foot intervals. When the feeder cable indicated the completion of the 1.5 m (5 ft) sample interval, the driller counted the measured return rate to allow the last sample material to reach the surface.

The rod break depth was determined by the drilling rig set-up and varied with every drillhole. The rod break generally occurred within a 1.5 m (5 ft) sample interval. The sample collected over a rod break would be removed from beneath the sample splitter during borehole flushing. Following the addition of a new rod and subsequent flushing, the sample container was replaced, and drilling continued. During the rod break, the sampler would clean the splitter, check the splitter plates, measure the pH and temperature of discharge water, and keep current with logging. For rod breaks occurring at shift changes, the crew was mindful of the incomplete sample and communicated its location to the next crew. Rod additions, timing, and bit changes were recorded in the drilling progress log. Filled sample bags were typically kept at the drilling rig during each shift. The samples were stored on the ground or in the bed of a pickup truck to begin water drainage. At the end of each shift, the samples were transported to the sample storage area for initial drying.

During each drilling interval, a metal mesh-screened strainer (rice/pasta strainer) was placed on the splitter table beneath the waste stream to obtain a representative chip sample for geologic logging. The lithologic sample was collected from the waste discharge material to avoid biasing the assay sample partition. A small portion of the sample was placed in, plastic chip trays for geologic logging. Chip trays were labeled with the drillhole number and 5 ft (1.5 m) depth intervals in permanent marker. Each chip tray had twenty compartments and therefore represented 100 ft (31 m) of drilling. Chip tray compartments typically measure about 3 cm x 2 cm x 2 cm deep.

Sample bags were collected at the end of each shift and transferred to the Haile sample storage area for initial drying.

Diamond Drilling

Diamond core drilling is by wireline methods and generally utilizes HQ and NQ size core with 63.5 mm and 48.3 mm diameters, respectively. Drill rods are ten feet (3.1 m) long. Core is transferred from the core barrels into plastic core boxes at the drill rig by the driller.

Each core box can hold up to ten feet (3.1 m) of cored stored in five rows each two feet (0.6 m) long. Core is gently broken by hammer as required to completely fill the boxes and marked on core as a mechanical break. Hole numbers and drill depths are marked on the outside of the core boxes and interval marker blocks are labeled and placed in the core box. Boxed whole core is covered with plastic lids and is transported to the core shed for logging and sampling by OceanaGold personnel.

Sample Recovery

No primary RC sample weights were recorded for RC drilling so RC recoveries cannot be directly calculated. However, 34,000 rotary split RC sub-samples were weighed by Romarco. Splitter ratio settings ranged from 8% to 17% and on the basis of backcalculating the range of likely total sample weights, RC recoveries appear to have been largely acceptable. As a precautionary measure, factors have been applied to gold grades where RC recoveries are estimated to be low on the basis of sub-sample mass and sampled at depths >200 m. These factors will remain until verified and/or replaced by diamond samples. Sensitivity analysis shows the impact on the resource estimates to be low (a few per cent globally). Given this mitigation, the residual risk is considered to be low.

Core recoveries average 97% and are rarely less than 90%. There is no observed grade relationship between core recovery and grade. Core recovery in saprolite ranges from 10% to 50%. Minimal ore has been identified in saprolite.

10.3 Collar Locations and Downhole Surveys

Drillhole numbers are assigned and maintained by company geologists via an Excel tracking spreadsheet that records location, depth, azimuth, dip, start and end dates. Historical drillhole collar surveys by Piedmont and Cyprus were surveyed by theodolite and recorded on paper. Drill set ups in the field were by traditional Brunton compass methods to establish azimuths within 2° accuracy. Since February 2019, the Reflex Aziliner tool has been used for drillhole set ups within 0.3° accuracy.

Haile drillhole collars from 2007 to October 2017 were surveyed by Romarco and OceanaGold surveyors using digital GPS methods. Survey equipment included a SPS985 Rover receiver and a TSC3 SCS900 data receiver. Surveys utilized an on-site base station with sub cm accuracy. Since October 2017, collar surveys have been collected by the geologist overseeing drilling using a Juniper Geode GPS Receiver with accuracy to 2 cm.

Collar surveys are named by hole number, downloaded as .csv files and saved on a network drive. Collar coordinates are verified against planned coordinates by the geologist overseeing the drilling, and then imported into the acQuire database. Drillhole collars are marked with 10 cm PVC pipe and a metal tag. After verification of collar coordinates, drill sites are rehabilitated within 60 days as mandated by the operating permit.

Historical drillholes prior to Romarco in 2007 were not surveyed for downhole deviation. Since 2007, all angle holes have been surveyed using the Reflex Sprint-IQ and EZ-Gyro survey tools. The tools are stored in a case at the Haile OceanaGold office and are calibrated at the Reflex office in Tucson, Arizona once a year. Multishot surveys are recorded down hole for azimuth and dip every 6.1 m (20 feet). Survey data are downloaded and verified using Imdex HUB-IQ software by the geologist overseeing the drilling. Upon verification, the data are imported into the acQuire database.

Original paper or printed survey records are located in the OceanaGold exploration office and are filed by hole number with other relevant drill data. Survey data are also stored digitally in the acQuire database. As part of a company-wide metrification process, OceanaGold transformed all surface and drillhole data from the South Carolina NAD27 coordinate system to the UTM NAD83 zone 17N system in November 2016. Coordinate transfer was verified by geologists and engineers and no issues were identified. Coordinate transformation was supported and utilized by SRK personnel during the Horseshoe underground evaluation.

10.4 Significant Results and Interpretation

Haile has a large percentage (28% of drill meters) of historical holes drilled before 2007 for which sampling methods have not been well documented. Drilling since that time is summarized in this report. For the historical drilling, collar coordinates were written on paper and therefore some field note errors may have occurred during surveys or copying into databases. Historical holes were also not surveyed for downhole deviation and their location in 3D space cannot be verified. QA/QC records are sparse for the historical drillholes and QA/QC methodology was not documented.

As discussed previously, in 2016, during the translation of the Romarco Minerals drilling database to OceanaGold's standard AcQuire database platform, where available, original source assay and survey data were used for the AcQuire translation and database validation. There was a further internal database review in late 2018 / early 2019. No material errors were identified and OceanaGold believe that the database is sufficient for the purposes of resource estimation.

The database used for this technical report includes 4,301 holes in the Haile district. Drillhole data are securely stored in OceanaGold's acQuire database. Drillhole collar locations, downhole surveys, geological logs, geotechnical logs and assays have been verified and used to build 3D geological models and in grade interpolations. Geologic interpretation is based on structure, lithology and alteration as logged in the drillholes.

Significant mineralization has been recorded in drillholes at nine named gold deposits at Haile within a 3.5 km by 1 km area since drilling commenced in the 1970s. Hole depths used for resource estimates typically range from 120 to 500 m and are dependent on depth of mineralization. Drillhole spacing typically ranges from 30 to 60 m. Resource drilling at Haile has predominantly been conducted by core holes angled to the southeast at dips of -45° to -75° , roughly perpendicular to regional foliation and bedding. Intersection angles between drillholes and mineralized zones are typically in the range of 40° to 70° . Significant drillhole intercepts therefore range from 70% to 100% of true mineralized widths. Many holes have been angled to the north, northwest and west to infill drill gaps where collar access is restricted by infrastructure (leach pads, pits, haul roads, lakes, wetlands). Sample interval lengths are typically 1.5 m (5 feet) and increase to 3.0 m in potentially barren rocks in relatively homogenous rock units. Variable sample interval lengths are selected by the geologists based on core logging to reflect changes in rock type, alteration, mineralogy and structure.

11 Sample Preparation, Analysis and Security

11.1 Sample Preparation for Analysis

Reverse Circulation Drilling

RC drilling has not been conducted at Haile since 2011.

The reverse circulation drilling at Haile typically used 16 cm drill bits. Sample intervals were predominately 1.5 m. The RC rigs were equipped with a cyclone and a rotary splitter. Most RC sampling at Haile was under wet conditions. Water injection was typically 15 to 19 L/min above the water table and decreases to 4 L/min when groundwater is encountered. Wet samples were bagged, drained and allowed to settle (aided by flocculent) before being transported to a storage facility for initial drying. Sample sizes were generally between 9 and 14 kg dry mass, representing a 11% to 17% split of the total sample mass.

The reverse circulation (RC) sample bags were transferred by company personnel to the Haile sample handling facility where they are prepared for shipment to a lab. RC samples were prepared at either the Kershaw Mineral Lab (KML) in Kershaw, South Carolina or the AHK Geochem (AHK) preparation facility in Spartanburg, South Carolina.

Lithological chip samples are retained in chip trays, labelled with the drillhole number and depth intervals in permanent marker.

Diamond Drilling

Diamond core drilling is by wireline methods and generally utilizes HQ and NQ size core 6.35 cm and 4.8 cm core. Core is transferred from the core barrels to plastic core boxes at the drill rig by the driller. Core orientation is not utilized other than for specific geotechnical programs. Core is broken as required to completely fill the boxes. Drill intervals are marked on the core boxes and interval marker blocks are labelled and placed in the core box. Whole core is transported to the sample preparation area by company personnel

RC Samples

RC drilling has not been used at Haile since 2011.

The reverse circulation (RC) sample bags from the truck were transferred to the Haile sample handling facility where they are prepared for shipment to a lab. RC samples were prepared at either the Kershaw Mineral Lab (KML) in Kershaw, South Carolina or the AHK Geochem (AHK) preparation facility in Spartanburg, South Carolina.

Samples follow one of two paths:

- Some samples are weighed, and sample number tags added to the bags. The samples are poured through a Jones splitter to reduce the size to roughly 2.7 kg (6 lbs) for shipment to the sample lab. Coarse rejects are kept in their original sample bags and stored on site on pallets.
- Alternatively, samples are staged at Haile and placed in containers for direct shipment to KML or AHK.

Core Samples

At the core logging facility, the core is cleaned, measured, and photographed. Geotechnical and geologic logging are completed on the whole core. All logging and sampling handling are conducted by OceanaGold personnel. Data collecting during core logging include structure, rock type, alteration, mineralogy, Rock Quality Designation (RQD), core recovery, hardness and joint condition. Alteration is logged as relative intensity and includes weak, moderate and strong categories. Mineralogy is visually estimated to the nearest 0.1%. Standardized templates are used for all logging with drop down menus. Geologists routinely review core together and compare notes to ensure accuracy and consistency. Density samples are collected every 10 m (33 ft) and use the water immersion method to measure specific gravity. Competent core at Haile does not require plastic or wax coatings for density measurements. Paper logs are entered into an Excel spreadsheet and then imported in the acQuire database by the admin assistant. Logs are periodically checked by the geologists for accuracy and completeness. Tablet-based geology logging in Excel was initiated in 2017 and enables logs to be directly uploaded into acQuire.

Logging is conducted in the Imperial system using feet due to the 10-ft drill rods. Data are converted to metric units after being imported into the acQuire database. The logging geologist assigns the sample intervals and sample numbers prior to core sawing. Sample ID tags are placed in the core boxes. Sample lengths are typically 5 feet (1.5 m) and can range in length from 1 ft (0.3 m) to 10 ft (3.1 m). Geologic sample breaks may be selected by the geologists based on contacts or structural boundaries. 'No sample' intervals are marked by orange flagging tape in surficial fill or rubble zones and in massive barren diabase dikes exceeding 50 feet (15 m) in thickness.

Core is sawed in half along the core axis using circular masonry blades and then placed into sample bags labelled with the sample ID. Paper ID tags are also placed into the bags. Saprolite zones are manually cut with a putty knife. The saw or knife are cleaned between each sample. A brick or barren rock sample is sawed between intervals to minimize cross-contamination. The cooling water for the saw is not recycled and is discharged into a permitted pond.

Core samples are delivered to the sample preparation facilities. Core is prepared primarily at the company-owned Kershaw Mineral Lab (KML) facility in Kershaw, South Carolina, and secondarily at the AHK preparation facility in Spartanburg, South Carolina.

11.1.1 Off-Site Sample Preparation

AHK, Spartanburg, South Carolina (ISO/IEC 17025 accredited)

Once the samples arrive at AHK in Spartanburg, South Carolina the following procedures were applied:

- Sample Preparation
- Inventory and log samples into the laboratory LIMS tracking system
- Print worksheets and envelope labels
- Dry samples at 65°C (150°F)
- Jaw crush samples to 80% passing 2 mm
- Clean the crusher between samples with barren rock and compressed air
- Split sample with a riffle splitter to prepare the sample for pulverizing
- Pulverize a 250 g sample to 90% passing 150-mesh (0.106 mm)

- Clean the pulverizer between samples with sand and compressed air
- Ship about 125 g of sample pulp for assay
- Coarse rejects are returned to Haile for storage
- The 125 g reserve pulps are stored at the AHK facility in Spartanburg with a seal. They represent an independent chain of custody sample library.

Sample pulps were shipped to the AHK Laboratory in Fairbanks, Alaska for analysis.

Kershaw Mineral Laboratory (KML), Kershaw, South Carolina (ISO/IEC 17025 accredited)

Once the samples arrived at KML, the following procedures are applied:

- Sample Preparation
- Inventory and log samples into the laboratory LIMS tracking system
- Print worksheets and envelope labels
- Dry samples at 93°F (200°F)
- Jaw crush samples to 70% passing 10-mesh (2 mm)
- Clean the crusher between samples with barren rock and compressed air
- Split sample with a riffle splitter to prepare the sample for pulverizing
- Pulverize a 450 g sample (± 50 g) to 85% passing 140-mesh (0.106 mm)
- Clean the pulverizer between samples with sand and compressed air
- Approximately 225 g of pulp sample is sent for fire assay
- Coarse rejects and reserve pulps are returned to Haile for storage.

Sample pulps from KML were shipped to the AHK Laboratory in Fairbanks, Alaska for analysis.

11.2 Sample Analysis

The procedures applied at AHK in Fairbanks, Alaska for assay were as follows:

- Inventory the samples and create worksheets
- Insert Quality Control samples of two duplicates, one certified standard, and one blank in each batch of 40 samples.
- Fire assay a 30 g aliquot for gold with 4-acid digestions and Atomic Absorption finish.
- Analyze 0.50 g samples for Multi-Element by inductively coupled plasma mass spectrometry (ICP-MS).
- Review the internal QC results and check as required.
- Review and sign off on final values including the internal check assays.
- Issue the final report and certificate of assay.
- Deliver the certificate to the client.

AHK is ISO/IEC 17025 accredited for all facilities that handle Haile samples.

ALS Chemex is ISO 9001 certified and ISO/IEC 17025 accredited. Coarse rejects and returned samples are stored at Haile under the control of company personnel. During off-shift hours, a Deputy Sheriff is on site providing security for the site and sample storage facility.

The procedures currently applied at KML for assay are as follows:

- Inventory the samples and create worksheets.
- Insert Quality Control samples of one duplicate, one certified standard, and one blank in each batch of 24 samples.
- Fire assay 30 g of pulp sample for gold, with Atomic Absorption finish.
- If the gold assay result from step 3 is greater than or equal to 3 g/t Au, an additional 30 g of pulp sample is fire assayed for gold using gravimetric finish, and 0.5 g of pulp sample is analyzed for silver using a 4-acid digestion with Atomic Absorption finish.
- Multi-Element ICP analysis is performed as requested.
- Carbon and sulfur determinations are performed as requested.
- Review the internal QC results and perform check assays as required.
- Review and sign off on final values including the internal check assays.
- Issue the final report and certificate of assay.
- Deliver the certificate to the client.

KML is ISO/IEC 17025:2005 accredited for gold and silver assays through the Standards Council of Canada.

The procedures currently applied at KML for assays are as follows:

- Inventory the samples and create worksheets.
- Insert Quality Control samples of one duplicate, one certified standard, and one blank in each batch of 24 samples.
- Fire assay 30 g of pulp sample for gold, with Atomic Absorption finish.
- If the gold assay result from step 3 is greater than or equal to 3 g/t Au, an additional 30 g of pulp sample is fire assayed for gold using gravimetric finish, and 0.5 g of pulp sample is analyzed for silver using a 4-acid digestion with Atomic Absorption finish.
- Multi-Element ICP analysis is performed as requested.
- Carbon and sulfur determinations are performed as requested.
- Review the internal QC results and perform check assays as required.
- Review and sign off on final values including the internal check assays.
- Issue the final report and certificate of assay.
- Deliver the certificate to the client.

11.3 Check Assays

Early in the Romarco drill program, samples were sent to the Inspectorate Lab in Reno, Nevada for preparation and assay. Inspectorate is an ISO 9001 certified laboratory. Check assays were sent to ALS-Chemex in Reno, Nevada. Sample analysis procedures at ALS are as follows:

- Inventory the samples and create worksheets.
- Insert Quality Control samples of one duplicate, one certified standard, and one blank in each batch of 20 samples.
- Fire assay 30 g of pulp sample for gold, with Atomic Absorption finish.
- If the gold assay result from step 3 is greater than or equal to 3 g/t Au, an additional 30 g of pulp sample is fire assayed for gold using gravimetric finish, and 0.5 g of pulp sample is analyzed for silver using a 4-acid digestion with Atomic Absorption finish.
- Multi-Element ICP analysis is performed as requested.

- Carbon and sulfur determinations are performed as requested.
- Review the internal QC results and perform check assays as required.
- Review and sign off on final values including the internal check assays.
- Issue the final report and certificate of assay.
- Deliver the certificate to the client.

11.4 Quality Assurance/Quality Control Procedures

11.4.1 Standards

Certified standards are routinely inserted at a rate of one in twenty samples (5%) per industry guidelines. Standards used by Romarco and OceanaGold are purchased from and certified by Rocklabs and include six standards of various grades. Five are oxide standards and one is sulfidic.

11.4.2 Blanks

Blanks are routinely inserted at a rate of one in twenty samples (5%). Blanks used by Romarco and OceanaGold include commercially available marble, sand, quartz pebble.

11.4.3 Duplicates

No duplicate samples were collected or analyzed.

11.4.4 Actions and Results

QA/QC data and graphs are generated from the acQuire database. Standards and blanks greater than 20% of the expected value are re-assayed for failed batches (20 samples). Reruns have been acceptable, and those values were imported into the acQuire database.

Security Measures

RC coarse rejects and returned samples are stored and secured at Haile where they are under the control of OceanaGold personnel. Pulps are stored in converted turkey barns at Haile with the coarse rejects. RC chip trays are stored in the exploration office. Boxed core is palletized and stored in a sand lot on the south side of the mine property. Pallets are covered by tarps and aluminum tags with hole IDs are attached to each pallet.

11.5 Opinion on Adequacy (Security, Sample Preparation, Analysis)

Haile has a large percentage (28% of drill meters) of historical holes drilled before 2007 for which sampling methods have not been well documented. There is no evidence of material problems with the pre-2007 drilling, sampling and analyses. Furthermore, over four years of mining has tested the veracity of the resource estimates which are based on this data. No material flaws have been identified.

Drilling, sampling and analyses since 2007 are summarized in this section.

Sample collection, preparation and analysis are according to industry standards. All labs used by Romarco and OceanaGold are certified to ISO-9001 standard or 17025 accredited for gold and silver through the Standards Council of Canada. The primary external lab used for check assays at ALS Reno is both ISO-9001 certified and 17025 accredited.

Core, pulp and RC sample storage are considered secure based on the opinion of John Jory, Director of Exploration, Haile gold mine. Sample transport is by company personnel between secure facilities and by approved couriers to external labs. No significant risks have been identified for sample contamination or sample exchange. No samples have been reported as missing during transport or as tampered with upon receipt at the lab.

All Haile drillhole data (assays, logs, surveys) are stored in the secure acQuire database, which is managed by the senior database specialist in New Zealand. Assay data can only be imported by the database specialist. The database specialist has no direct reporting relationships to the Haile geologists or to the Director of Exploration. The acQuire database is an industry certified database. Database changes are tracked and verified. Strict data importing and verification protocols must be followed to avoid, for example, overlapping or missing intervals, mismatched hole depths in different fields, duplicate hole IDs or sample numbers, and invalid logging codes.

In the opinion of the qualified person, the sample security, sample preparation and analyses are adequate for the purposes of resource estimation.

12 Data Verification

Haile has a large percentage (28% of drill meters) of historical holes drilled before 2007 for which sampling and analytical methods have not been well documented. There is no evidence of material problems with the pre-2007 drilling, sampling and analyses. Furthermore, over four years of mining has tested the veracity of the resource estimates which are based on this data. No material flaws have been identified.

During 2016, the Romarco Minerals drilling database was translated to OceanaGold's standard Acquire database platform. Where available, original source assay and survey data were used for the Acquire translation and database validation. There was a further internal database review in late 2018 / early 2019. No material errors were identified.

Verification of drilling, sampling and analyses is discussed as Pre-Romarco, Romarco and OceanaGold data groups in the sections below.

12.1 Data Validation of Pre-Romarco Holes

Data validation was conducted by OGC Exploration geologists in 2019 for pre-Romarco (pre-2008) RC and core holes. Haile has been drilled by multiple companies since 1975 (Table 10-1 in section 10.1). A total of 1,775 holes representing 54% of the resource database were validated using AuBest values stored in the acQuire database. This includes drillholes RC0001-1501 (n=1403), DDH0001-0288 (n=288), NDH0001-0037 and NRH0001-0054 (n=84) drilled between 1975 and 1994. Key projects were to compile, sort, file and record source data using original logs and assay certificates from dozens of binders and hard copy files for each drillhole. Differences between assays, depths, dips, azimuths, downhole surveys and collar coordinates were recorded and evaluated in spreadsheets. All paper files and logs are securely stored in OceanaGold's exploration office at Haile.

No major or systematic errors were identified and there is no material impact to reserves or resources based on validation of pre-2008 drillhole data (Jory, 2019). Legacy drillhole data from 1975 to 1994 stored in acQuire are regarded as reliable and accurate. Romarco and OGC data are also reliable and accurate. Minor data corrections were made for some legacy gold assays, collar coordinates, hole depths and interval depths. Data validation showed that 0.77% of DDH holes and 5.4% of RC holes required corrections based on differences >0.007 ppm Au between acQuire AuBest values and assay certificates or assay sheets. Many of the RC holes had negligible errors <1% of the acQuire assay vs. original assay. Most of the suspect holes are from the early Cyprus and Piedmont drill campaigns. AMAX holes are of high confidence and include certified assays by Bondar Clegg with fire and gravimetric assays.

As a precautionary measure, diamond core drilling targeted within reserve pit designs has been completed in areas with large numbers of legacy (pre-Romarco) RC holes, including Snake, Red Hill and Haile. The Mill Zone, Ledbetter, Horseshoe and Small pits are largely drilled with core holes and have no RC grade bias risk.

12.2 Verification of Romarco and OceanaGold Data

21,498 standards are recorded in the OceanaGold Acquire database. There are an additional 16,514 blanks. The number of standards submitted by year (Table 12-1) varies and largely reflects the drilling activity in that year. The performance of these standards revealed no material problems with laboratory performance. QA/QC inserts decreased in 2018, 2019 and 2020 proportional to decreased drill meters; blanks and standards are inserted at industry normal frequencies of 1 in 20 samples.

Table 12-1: Number of Standards Inserted by Year

Year	No. of Standards
2008	242
2009	2,640
2010	4,981
2011	7,318
2012	2,653
2013	475
2014	52
2015	233
2016	926
2017	907
2018	459
2019	457
2020 YTD	155
Total	21,498

12.3 Romarco Data Verification

In addition to the checks done by OceanaGold during database translation and the 2018/2019 review, the following checks have been made by IMC for drilling completed by Romarco (2008 to 2014).

- A comparison of certificates of assay from the laboratory versus the Romarco computerized data base to check the reliability of data entry
- Statistical analysis of the standards reference materials that were inserted by Romarco for analysis by the assay lab
- Statistical analysis of the blank samples that were inserted by Romarco for analysis by the assay lab
- Statistical analysis of the check samples that were submitted by Romarco to a third-party laboratory

The qualified person has reviewed the checks and believes that the data are of acceptable quality for the purposes of resource estimation. In 2016, OceanaGold undertook a program of database verification for drilling at the Horseshoe Underground deposit:

- Assay Verification – 5% check of assay values
- Collar Verification – 100% check of collar locations
- Downhole Survey Verification – 100% check on downhole surveys
- Standard and Blank QA/QC
- KML vs. ALS Horseshoe assay comparison


The review identified no material flaws. The Horseshoe data is considered of acceptable quality for the purposes of resource estimation. The KML vs. ALS check assay comparison study for Horseshoe

concluded that “statistical variance from these studies for AuAA vs. AuFA comparisons (n=512) between KML and ALS Tucson indicate that the KML lab is 5% to 10% low, or conversely that the ALS lab is 5% to 10% high. KML adjusted their AA dilution process in late October to achieve better fit with expected values”. The KML assay data were validated and used in the resource model.

12.4 Horseshoe Data Verification 2016

Horseshoe drillhole data were validated by OceanaGold in late 2016. Validation included assays, collar locations, and downhole surveys in the acQuire database for Romarco and OceanaGold drillholes. This includes a 5% check of assay values and a 100% check of collar coordinates and downhole surveys. An analysis of standards and blanks from the 2015 to 2016 Horseshoe drilling program was also conducted. All Horseshoe drilling was core using OceanaGold LF90 drills and company drillers. Sample preparation and assays were conducted by OceanaGold’s Kershaw Mineral Lab (KML) at Haile. Check assays on sample pulps were performed by ALS in Tucson, AZ. No significant errors were identified by the study.

Standards and blanks greater than 20% of the expected value were scrutinized and were re-assayed in some cases. Of the 1,699 controls submitted for FA-atomic absorption (AA) during the Horseshoe drilling campaign, 39 standards and blanks (2.3%) are outside acceptable limits. Most failed controls were in unmineralized zones. Validated blanks were used for assays up to 0.080 g/t. Box and whiskers plots for standards and blanks were generated and evaluated as shown in Figure 12-1. Batches with failed standards in mineralized zones were re-assayed at KML and passed the second time.

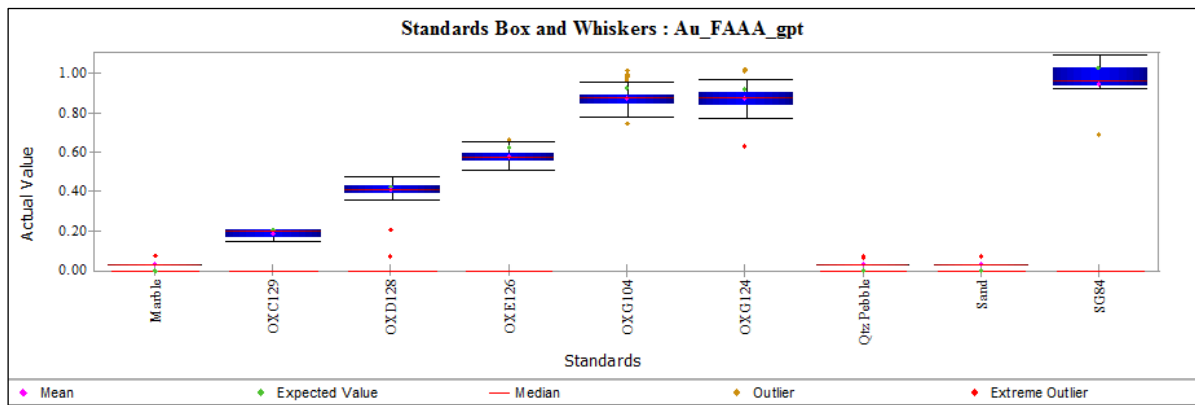


Source: OceanaGold

Figure 12-1: Box and Whiskers Plots for Horseshoe 2016 Standards and Blanks

A check assay program was conducted for the Horseshoe drilling at ALS Tucson, AZ. Conclusions were:

- KML is 10% lower for AuAA values than ALS for 259 Horseshoe sample pairs in the 0.5 to 3 g/t range ($R^2=0.73$).
- KML is 5% lower for AuFA values than ALS for 253 Horseshoe samples pairs in the 0 to 53 g/t range ($R^2=0.90$) shown in Figure 12-2 Assays >100 g/t Au (n=18) show poor correlation when comparing KML to ALS results, likely due to the presence of coarse gold and difficulty in achieving assay precision.

Statistical variance from these studies for AuAA vs. AuFA comparisons (n=512) between KML and ALS Tucson indicate that the KML lab is 5% to 10% low, or conversely that the ALS lab is 5% to 10% high (Figure 12-2). KML adjusted their AA dilution process in October 2016 to achieve better fit with expected values. There were no changes to fire assay procedures at KML. It is suggested that gold assay upgrades of 5% can be applied for internal planning, but that no upgrade be used for external reporting.

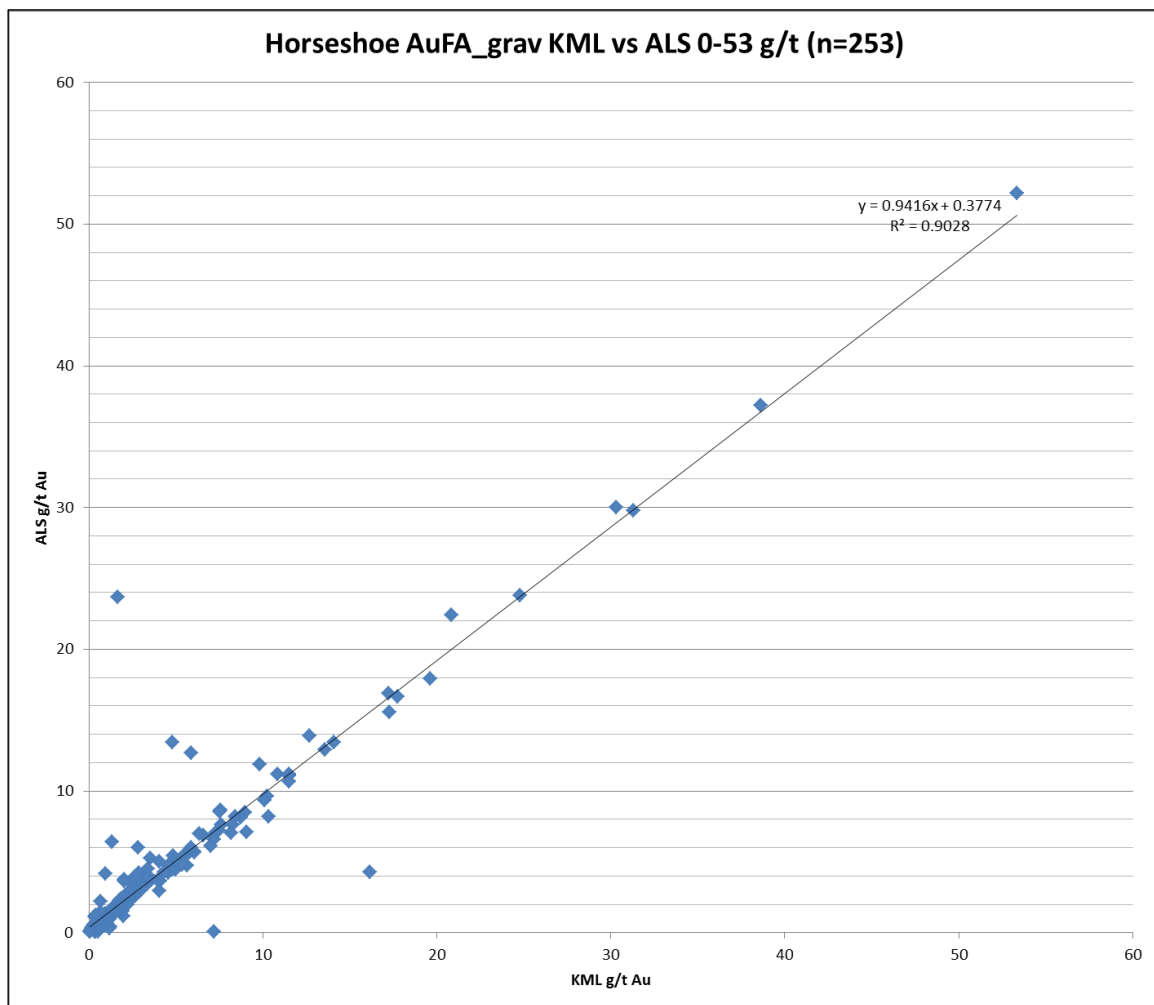

Source: OceanaGold

Figure 12-2: Horseshoe AuFA_grav KML vs. ALS 0-53 g/t (n=253)


This section focuses on verification of the drilling, sampling, and assaying completed for the data included in the Horseshoe block model completed by OceanaGold Exploration on November 20, 2016.

12.5 Haile QA/QC ALS July 2017-July 2020

During the period July 2017-July 2020, exploration and resource definition samples were submitted to ALS laboratories. Samples were prepared at the Tucson, AZ lab and certified assays were done in Reno, NV. Analyses for Au were by Fire Assay, and any assay returning over 3.0 g/t Au was re-assayed with a gravimetric finish. Analyses have been reported (and are stored) in g/t in the acQuire database. All historic data is converted to g/t for resource and reserve purposes.


12.5.1 July 2017- July 2020 CRM Performance

ALS Reno laboratory accuracy was monitored by insertion of commercially Certified Reference Materials (CRMs) into the sample stream. CRMs were inserted at a rate of one per forty samples (10%) and alternated with blank insertions at one per forty samples (10%). Hence, alternating blanks and CRMs were inserted at a rate of one in 20 (5%) per industry guidelines. A total of 19 different CRMs sourced from Rocklabs were submitted in sample batches for a total of 1,457 CRM analyses during the three-year period. Thirteen of the 19 CRMs had more than 30 insertions into the sample stream. CRMs include oxide, sulfide, and high silica standards. Figure 12-3 shows CRM values plotted against the expected values. Purple triangles show the averaged results for a CRM, while greyed boxes show the number of submissions for each CRM. Figure 12-4 shows a zoomed in view of the most commonly inserted CRMs. No obvious bias was observed within the CRM expected versus actual data. Relative standard deviation of all CRMs was very good at 2 to 4% of expected values. Results confirm excellent precision and accuracy of assays provided by ALS Reno for Haile resource calculations that are within industry guidelines. Results from blanks showed no contamination of samples used for resource calculations.

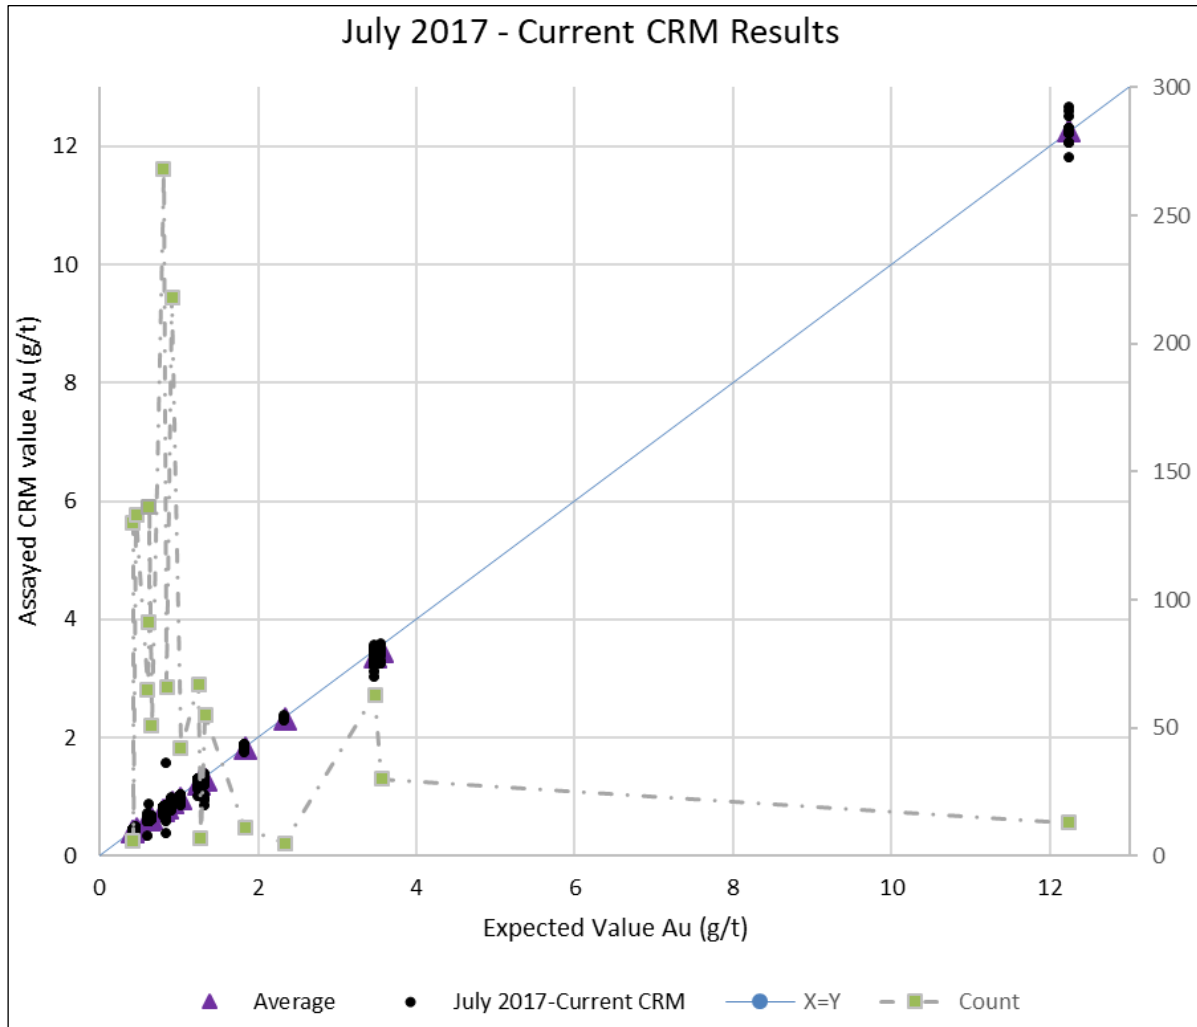

Source: OceanaGold


Figure 12-3: July 2017-Current CRM Analyses versus Expected Value (n=1,457)

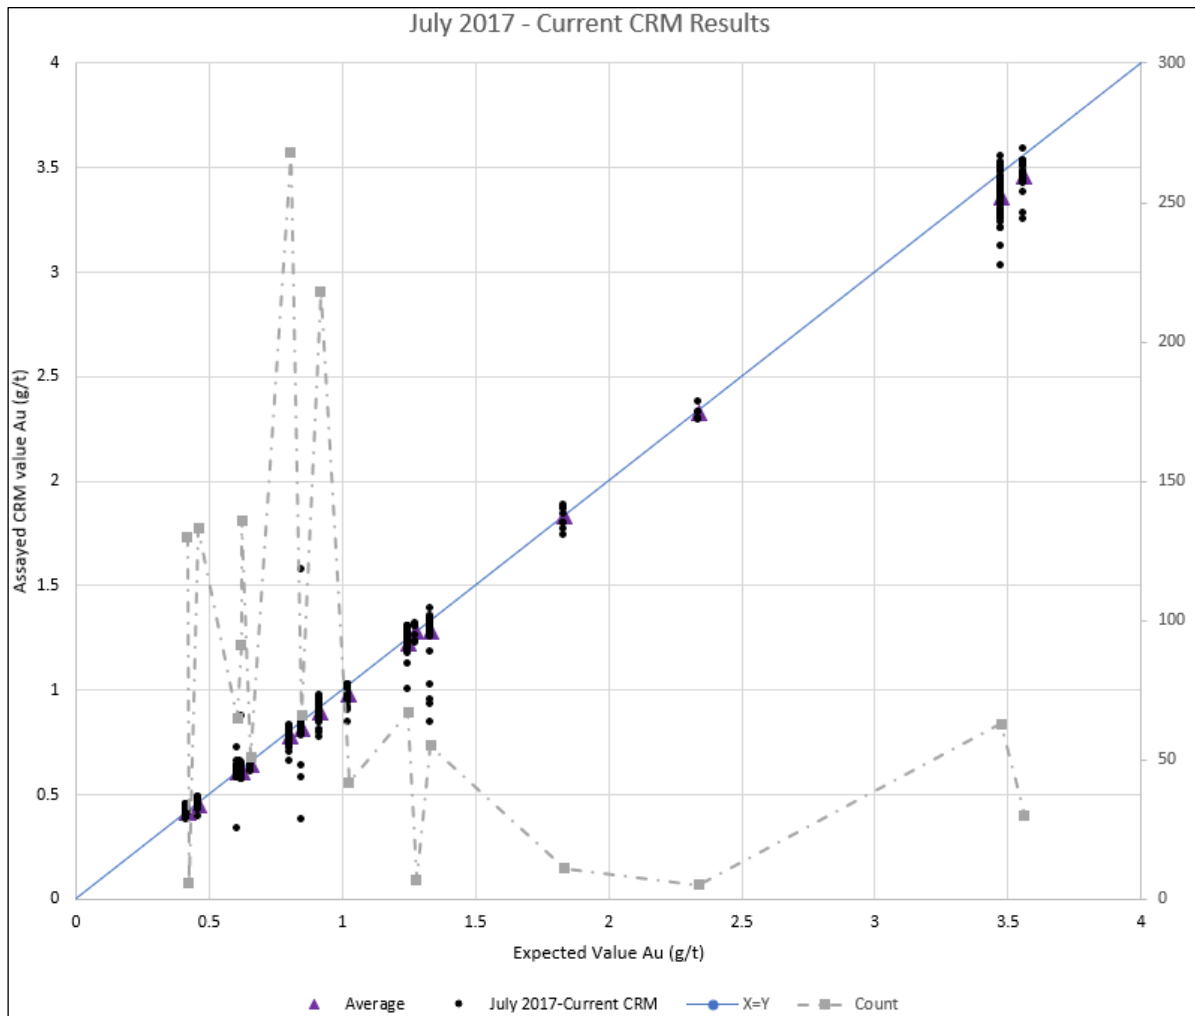

Source: OceanaGold


Figure 12-4: July 2017-Current CRM Analyses versus Expected Value <4 g/t (n=1,444)

Standard control charts were plotted for commonly used CRMs. Examples of oxide (OxF125, OxF124), sulfide (SG84), and high silica (HiSilK2) CRMs are shown in Figure 12-5 through Figure 12-8. No obvious trends in the process mean are apparent in the longer run CRM results, and there are only minor variations in precision. If a CRM returned a value greater than two standard deviations of the expected value, then all intervals within the failed batch and the nearest passing CRM or Blank were successfully rerun and uploaded into the database.

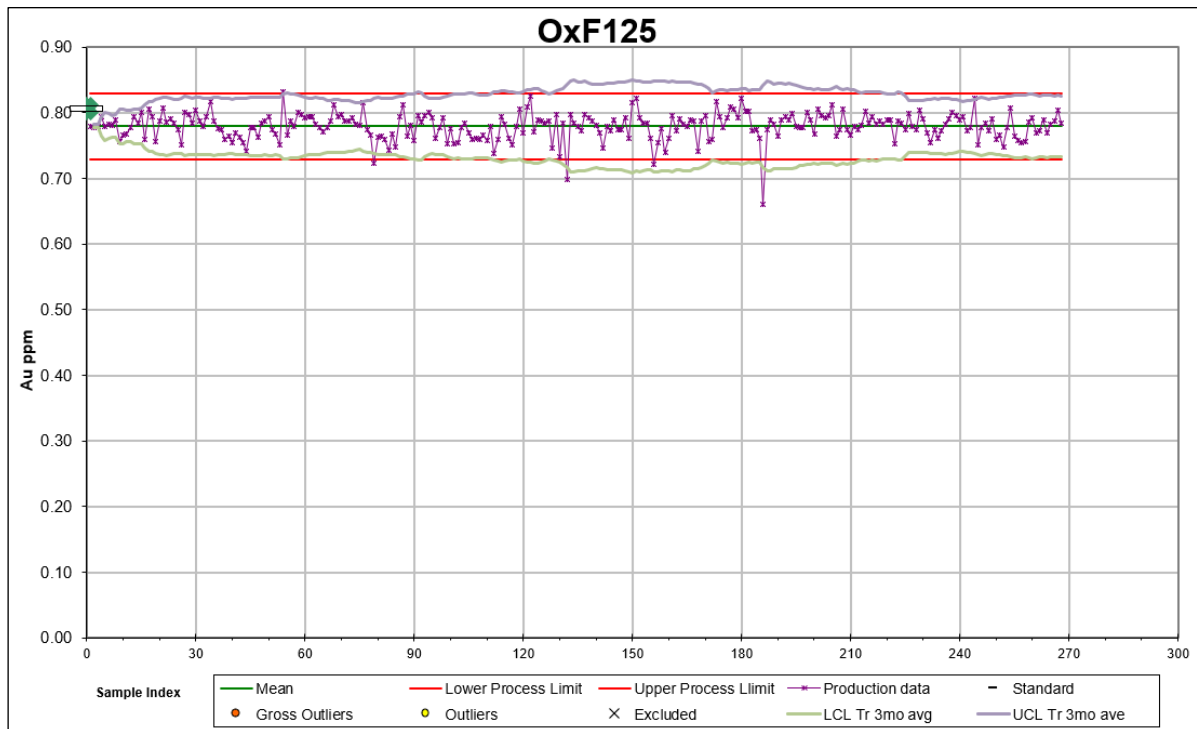


Source: OceanaGold

Figure 12-5: July 2017-Current, Control Chart, OxF125 (n=268)

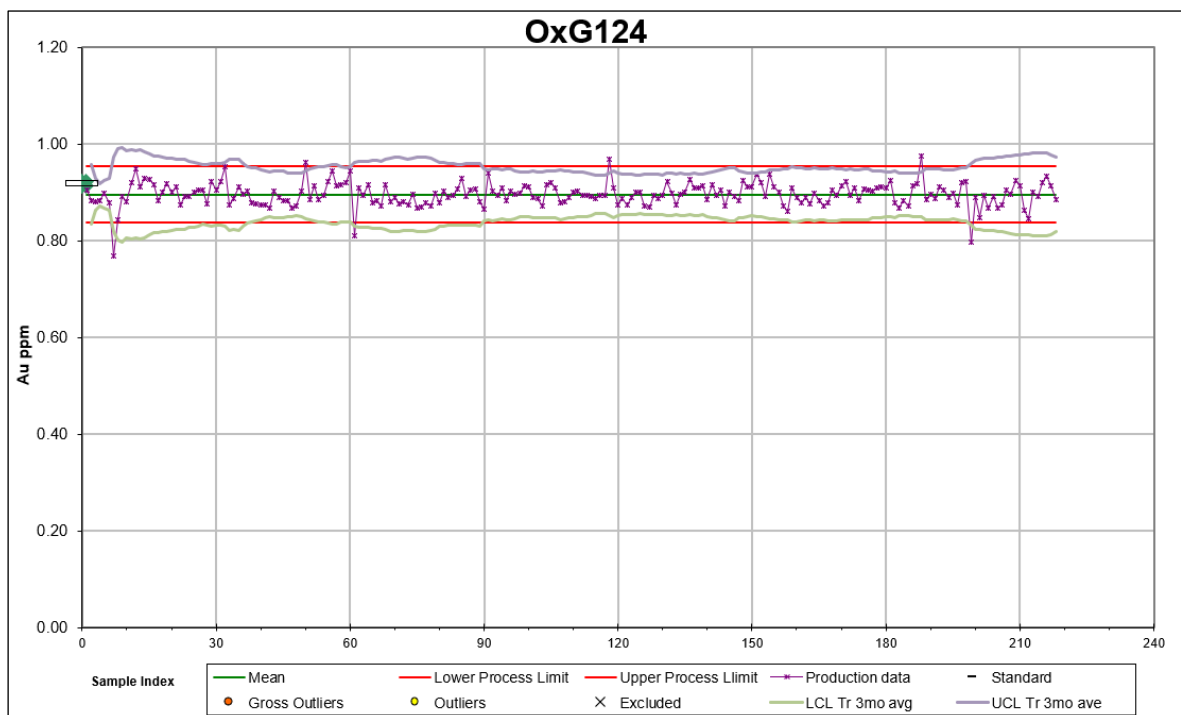


Source: OceanaGold

Figure 12-6: July 2017-Current, Control Chart, OxG124 (n=218)

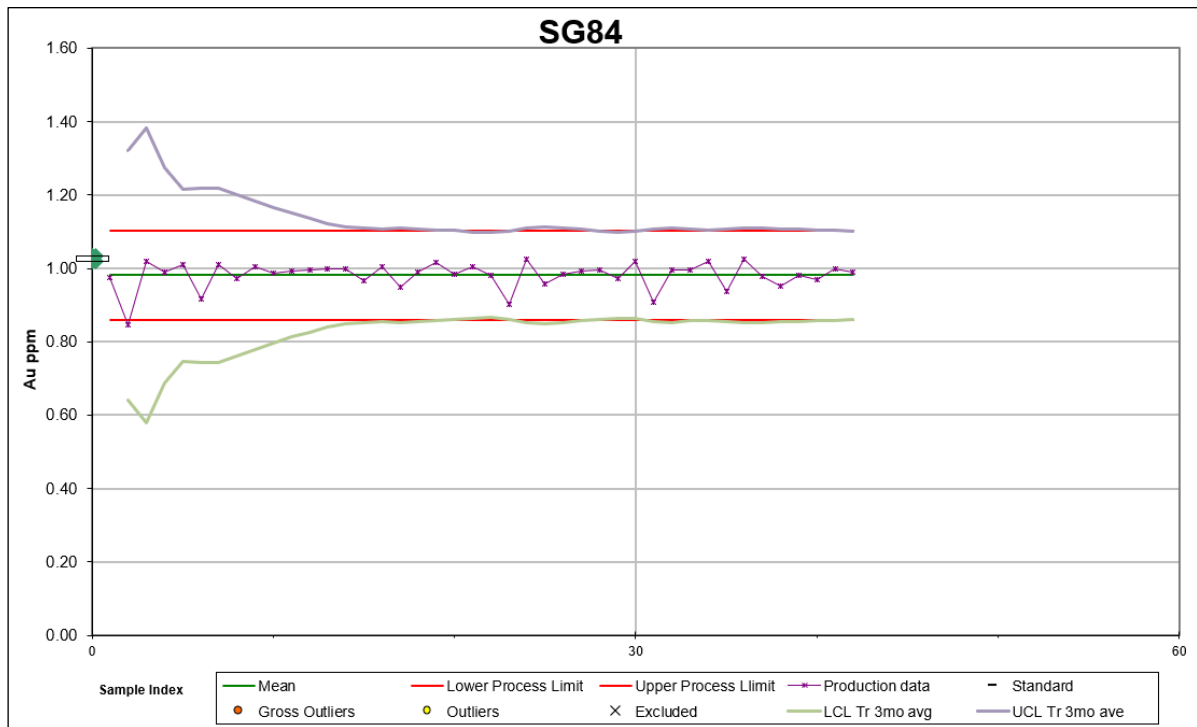

Source: OceanaGold

Figure 12-7: July 2017-Current, Control Chart, SG84 (n=42)

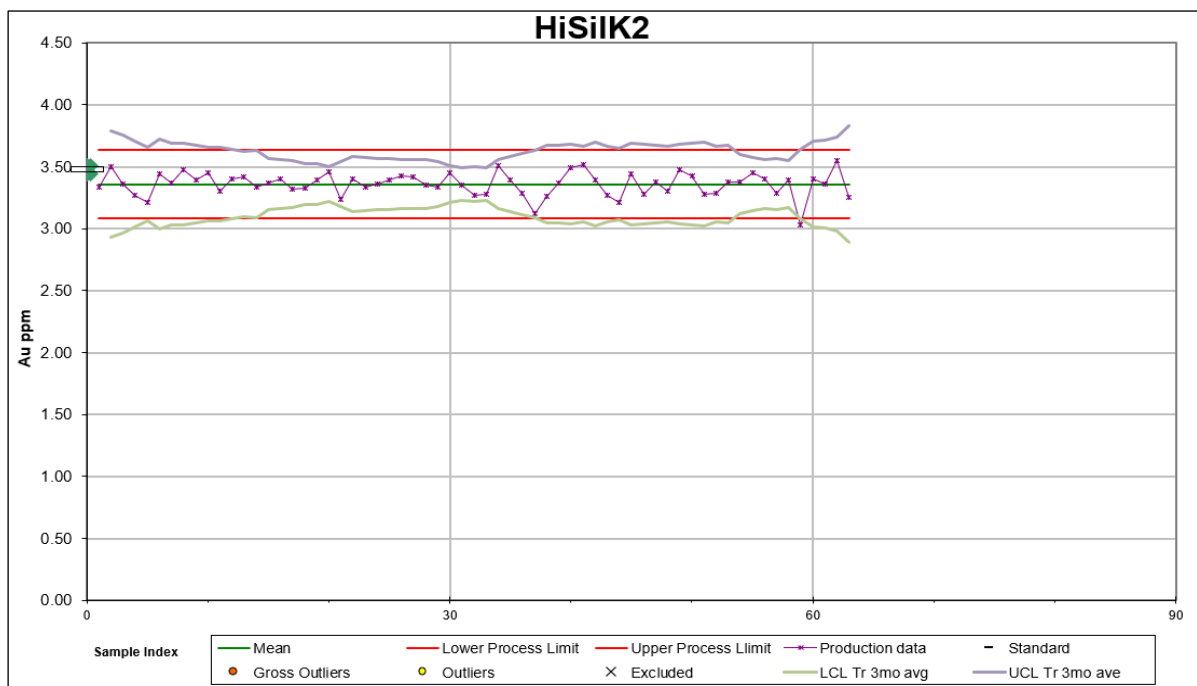


Source: OceanaGold

Figure 12-8: July 2017-Current, Control Chart, HiSilK2 (n=63)

12.5.2 Contamination Monitoring

Contamination is monitored by insertion of blank materials. From July 2017-July 2020 a total of 1,363 blank samples of four different materials were inserted: Marble, Sand, Gravel, and Quartz Pebble. Results from the ALS Reno laboratory are shown in Figure 12-9. Two minor non-compliances were observed in the reporting period. Lab detection limit (LDL) is 0.005 ppm Au and control limit used is 10 times the LDL (i.e. 0.050 ppm Au). If a blank returned a value greater than two standard deviations of the expected value, then all intervals between the failed Blank and the nearest passing Blank or CRM were rerun. Overall, there is no indication of contamination during sample preparation.

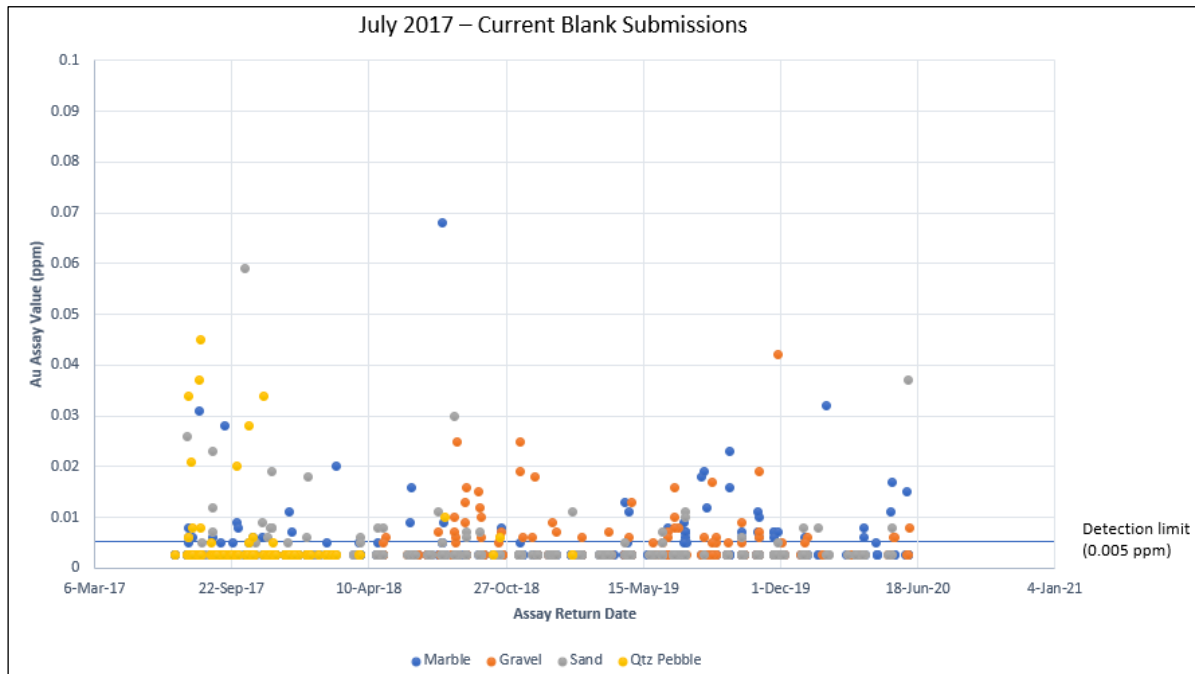

Source: OceanaGold

Figure 12-9: July 2017-Current Blank Insertions (n=1,363)

The qualified person has reviewed the July 2017 to current data and believes it to be of acceptable quality for the purposes of resource estimation.

12.9.2 Statement of Data Adequacy

The qualified person believes that the data reviewed above, including drilling prior to 2007 and subsequent drilling by Romarco and OceanaGold, is adequate for the purposes of resource estimation.

13 Mineral Processing and Metallurgical Testing

Sample preparation and characterization, grinding studies, gravity concentration tests, whole ore leach tests, flotation tests and leaching of flotation tailings and flotation concentrate tests were completed to determine the metallurgical response of the ore.

Samples of ore were collected by HGM for metallurgical testing. A series of metallurgical testing programs have been completed by independent commercial metallurgical laboratories. The test work indicated that the ore will respond to flotation and direct agitated cyanide leaching technology to extract gold. The results of the test programs are available in the following reports:

- Phillips Enterprises, LLC (Phillips) 17 September 2008, Progress Report #2 Process and Metallurgical Testing on Haile Gold Mine Ore Project No. 082003
- Pocock Industrial Inc. (Pocock) Salt Lake City, Utah, May 2009, Flocculant Screening, Gravity Sedimentation, Pulp Rheology, Vacuum Filtration and Pressure Filtration Studies Conducted for Romarco Minerals Haile Gold Project
- Resource Development Inc. (RDi), Wheat Ridge, Colorado, September 16, 2009, Romarco Minerals, Inc. Haile Gold Project, Metallurgical Report
- Metso Minerals Industries Inc. (Metso), York, Pennsylvania, December 7, 2009, Test Plant Report No. 20000134-135
- Resource Development Inc. (RDi), Wheat Ridge, Colorado, March 31, 2010, Romarco Minerals, Inc. Work Index Data for Haile Composite Sample
- Resource Development Inc. (RDi), Wheat Ridge, Colorado, March 31, 2010, Romarco Minerals, Inc. Metallurgical Testing of Ledbetter Extension Samples
- Resource Development Inc. (RDi), Wheat Ridge, Colorado, May 27, 2010, Romarco Minerals, Inc. Flash Flotation, Cyanide Destruction & Leaching of Concentrate and Tailing for Haile Composites
- Resource Development Inc. (RDi), Wheat Ridge, Colorado, September 27, 2010, Romarco Minerals, Inc. Optimization of Leaching of Flotation Concentrate
- Resource Development Inc. (RDi), Wheat Ridge, Colorado, August 2010, Metallurgical Testing of Horseshoe Zone Samples
- Metso Minerals Industries, Inc. (Metso), York, Pennsylvania, February 2011, Stirred Media Detritor and Jar Mill Grindability Test on Bulk Flotation Concentrate T11-04
- KML Metallurgical Services, (KML), Kershaw, South Carolina, December 27, 2012, HGM Years 1 – 3 Silver Characterization Project Test Report
- Resource Development Inc. (RDi), Wheat Ridge, Colorado, June 6, 2011, Production of Flotation Concentrate and Confirmation Testing of Flowsheet
- G&T Metallurgical Services Ltd (G&T), Kamloops, Canada November 24, 2011, Flotation & Cyanidation Testing on Samples from the Horseshoe Deposit, Haile Gold Mine KM3076;
- Gekko Global Cyanide Detox Group (Gekko), Ballarat, Australia, July 18, 2016, OceanaGold Haile Gold Mine Cyanide Detox Test Work DTXSC021
- ALS Metallurgy Kamloops, BC, Canada, December 2016, Comminution Testing on Samples from the Haile Gold Mine KM 5180
- ALS Metallurgy Kamloops, BC, Canada, Comminution and Thickening Testing for Haile Gold Mine KM 5293

The metallurgical test results were used to develop process design criteria and the flow sheet for processing the ore in both the existing and for the upgraded plant.

The following sections contain some information in short tons (st) and others in metric tonnes (t).

13.1 Testing and Procedures

13.1.1 Comminution

Comminution test work on mineralized samples was performed by RDi (using Phillips Enterprises, LLC) and by ALS Kamloops.

Bond ball mill (BM) work indices were determined by RDi for various Haile samples. Bond impact and abrasion tests were also completed. The BM work index results for selected composites from this work are presented in Table 13-1.

Table 13-1: Bond Ball Mill Work Indices (Wi) for Haile Samples

Composite Number	Area	BM Wi @ 100-mesh (kWh/st)
1	Mill Zone	8.42
2	Mill Zone	8.07
3	Mill Zone	7.95
4	Mill Zone	8.03
5	Mill Zone	7.88
6	Haile	8.55
7	Haile	9.78
8	Ledbetter	7.49
26	Snake	10.34
27	Snake	10.39
31	Snake	5.13

Source: OceanaGold

Further testing, including Bond rod mill (RM) index testing as completed on Mill Zone, Haile, Ledbetter and Red Hill ore zone samples. The Bond ball mill work index for each composite was also determined at both 100- and 200-mesh for these samples.

The results for selected composites from this work are presented in Table 13-2.

Table 13-2: Bond Rod and Ball Mill Work Indices for Haile Composite

Composite Number	Sample Description	RM Wi (kWh/st)	BM Wi @ 100-mesh (kWh/st)	BM Wi @ 200-mesh (kWh/st)
2	Mill Zone-Average Grade	11.08	8.21	7.78
6	Mill Zone-High Grade	11.30	8.21	8.17
8	Haile-Average Grade	12.49	9.47	8.92
20	Ledbetter-Average Grade	12.18	8.95	8.42
24	Ledbetter-High Grade	12.56	9.47	9.03
34	Red Hill-Average Grade	-	8.73	9.47
54	Red Hill- Low Grade	-	8.83	9.50

Source: OceanaGold

RDi also performed comminution tests on samples from the Ledbetter Extension zone. The Bond rod and ball mill indices and an abrasion index for an ore composite (83) was determined. The results of this work are presented in Table 13-3.

Table 13-3: Rod and Ball Mill Work Indices for Ledbetter Extension Samples

Abrasion Index	Value (kWh/st)
Rod Mill Work Index	12.71
Ball Mill Work Index at 100-mesh	10.21
Ball Mill Work Index at 200-mesh	9.81

Source: OceanaGold

RDi also performed comminution studies on samples from Horseshoe. The Bond rod, ball mill and abrasion indices for four different composites were determined. The samples were relatively abrasive and moderately hard. The results are presented in Table 13-4.

Table 13-4: Rod & Ball Mill Work and Abrasion Indices for Horseshoe Samples

Composite Number	Sample Description (Hole ID / intercepts / lithology)	RM Wi (kWh/st)	BM Wi @ 200-mesh (kWh/st)	Abrasion Index
83	RCT-03 / 1412 to 1460 ft / Silicified Metasediment	-	12.29	0.2167
84	RCT-04 / 1460 to 1510 ft / Silicified Metasediment	-	11.29	0.2691
85	RCT-04 / 1510 to 1585 ft / Silicified Breccia	14.93	12.95	0.3786
86	RCT-04 / 1585 to 1655 ft / Silicified Breccia	13.56	13.77	0.8330

Source: OceanaGold

ALS performed comminution tests on samples from Horseshoe and Ledbetter. The SMC and Bond ball mill indices for composites were determined. The results of this work are presented in Table 13-5.

Table 13-5: ALS Comminution Tests on Horseshoe Samples

Composite Number	A x b	SCSE (kWh/st)	BM Wi @ 200-mesh (kWh/st)
Horseshoe 1	28.9	11.4	13.5
Horseshoe 2	29.9	11.3	13.6
Horseshoe 3	30.7	11.2	9.3
Horseshoe 4	29.4	11.6	10.9
Horseshoe 5	28.0	11.6	14.4
Horseshoe 6	27.1	12.4	10.6
Ledbetter 1	27.3	12.0	11.6
Ledbetter 2	25.6	12.2	13.5
Ledbetter 3	27.8	11.9	11.8
Ledbetter 4	30.8	11.3	8.9

Source: OceanaGold


ALS performed JK Drop Weight and Bond ball mill index tests on samples from mineralized material exposed in Mill Zone Pit. The results of this work are presented in Table 13-6.

Table 13-6: ALS Comminution Tests on Mill Zone Pit Samples

Composite Number	A x b	SCSE (kWh/st)	BM Wi @ 200-mesh (kWh/st)
1a	93.6	7.15	9.4
1b			9.1
2a	52.8	8.85	6.8
2b			6.6

Source: OceanaGold

The comminution circuit design developed for the expansion project incorporated the additional competency test work and power modelling for the overall circuit was developed with the assistance of external consultants. A series of plant grinding circuit surveys were completed in 2017 and 2018 to validate the predictions of the modelling work. The survey data indicated the Haile SAG specific energy requirement was significantly lower than that predicted from the SMC test results on all surveys. Additional modelling work developed a Haile site specific model for SAG specific energy as a function of the drop weight index (DWI) from the SMC test and Bond ball mill work index. The results of the modelled against actual measured SAG specific energy are shown in Figure 13-1.

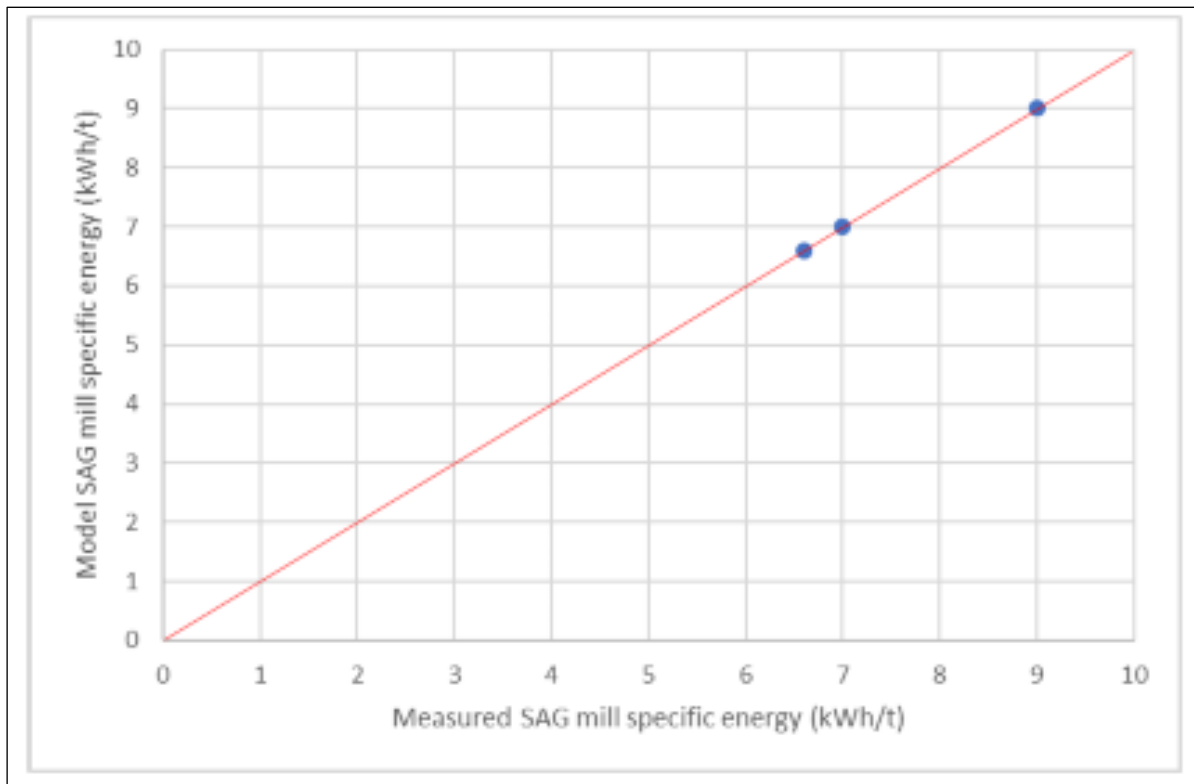

Source: OceanaGold

Figure 13-1 Modelled vs Measured SAG Specific Energy Values

Updated throughput modelling, using the site-specific model, indicated an increase in throughput averaging 70 tph higher than the original work. Based on the outcome of the power modelling work, the confidence of achieving 3.5 to 4.0 Mtpa throughput rates for the majority of the ore sources was sufficient to proceed with the installation of the pebble crushing circuit but not to proceed with the detailed design of the secondary crushing circuit.

ALS performed SMC, Bond rod mill and Bond ball mill index tests on a further 17 composite samples taken from the Ledbetter, Snake, Haile and Red Hill pits from infill drilling in 2018. These allowed additional variability analysis on expected ore competency across these pits based on the power modelling work that represented mill feed from 2019 to 2024. The results of the program are summarized in Table 13-7 and indicate similar values to the previous programs.

Table 13-7: ALS Comminution test results for 2018 Infill Sample Program

Sample ID (DDH/Deposit)	A x b	SCSE (kWh/tonne)	BM Wi @ 200-Mesh (kWh/tonne)
672A Ledbetter	25.4	12.6	11.0
693A Snake	39.8	10.1	8.6
698A Snake West	27.9	11.8	11.3
726A Snake West	24.8	10.6	10.9
726B Snake West	28.9	11.7	8.9
746A Snake	40.5	10.0	9.8
746B Snake	31.0	11.3	11.6
746C Snake	36.2	10.5	10.0
752A Ledbetter	28.3	11.9	9.9
752B Ledbetter	33.0	10.9	10.2
773A Ledbetter	28.9	11.8	10.1
802A Haile	31.7	11.2	8.8
802C Haile	35.7	10.5	10.1
802C Haile	31.1	11.2	9.4
802D Haile	38.4	10.1	9.1
803A Red Hill	31.8	11.2	10.5
806A Red Hill	46.6	9.4	7.5

Source: OceanaGold

13.1.2 Flotation and Cyanidation

The Philips test work described in the September 2008 report was performed on composite ore samples of average grade material from the Haile and Mill Zone pit areas.

The testing was conducted to substantiate metal recoveries from sulfide flotation and cyanide leaching of flotation tailings and investigate oxidation methods for enhancing gold extraction from sulfide concentrate. Additional work was executed on tailings samples to assess thickening and filtration response, neutralization requirements, and provide material for environmental and tailing disposal engineering studies by others.

The work confirmed the sulfides carry the majority of the metal values in Haile deposits and this allows their concentration into a smaller fraction for processing. Previous operations at the site recognized this and sulfide concentration was practiced. However, the sulfides do not easily release the metal values and limited extraction was experienced by simple cyanidation.

The sulfides contained in the ore composites tested by Phillips showed the same characteristics.

Flotation tests on the Haile composite indicated 66% of the gold was separated into a concentrate that represented 6.7% of the flotation feed mass. Tests on the Mill Zone composite indicated 89% of the gold was separated into a flotation concentrate that represented 13.6% of the feed. The Mill Zone composite test had a finer flotation feed particle size distribution and extended residence time which may explain the difference in recovery.

Leach tests on flotation tail indicated 82% (stage) extraction for gold for both composites. Leach tests on a blend of Haile and Mill Zone flotation concentrate revealed gold extraction of only 67% of the gold with the as-floated particle size. Applying a test procedure entailing a regrind in cyanide solution to 80% passing 15µm, followed by an agitated cyanidation step, raised extraction to 80%.

The subsequent phase of work from 2009 was carried out by RDi on samples from the five areas within the Haile Gold mineralized zone; Mill Zone, Haile, Red Hill, Ledbetter and Snake. These discrete areas

were provisionally derived from initial distinct open pits, but later design work and optimization may make the designation merely a legacy naming convention.

The methodology of compositing samples was to prepare composites from each hole's intervals based on their assays as follows:

- Less than 0.5 g/t Au was considered waste;
- Less than 1 g/t but greater than 0.5 g/t Au were combined as low-grade composites;
- Between 1 g/t Au and 4 g/t Au were combined as average grade; and
- Over 4 g/t Au were combined as high-grade.

Almost all the samples assayed over 0.3% sulfur and sulfide sulfur accounted for over 95% of the total sulfur.

RD i performed gravity concentration testing using a laboratory centrifugal concentrator with cleaner gravity concentration using a shaking Gemini table. The results indicate that the cleaner stage recovered about 20% of the feed gold but into a concentrate with a mass pull of 1 to 2% of the feed, assaying 11 to 75 g/t Au. The concentrate grade was too low grade to treat separately and there appears to be no coarse gold in the deposit, thus a gravity circuit was not considered to be applicable.

RD i performed whole-ore cyanide leach tests to examine the effect of ore grind size and leach time on gold recovery. The test work indicated that direct leaching gold extraction from the samples was generally poor and variable, ranging from 40 to 79%.

Most of the gold that leached was in the initial six hours of leach time and extraction generally increased with increasing fineness of grind. The refractoriness of the gold is partially due to size dependence but predominantly due to gold association with sulfides. A summary of the test work is presented in Table 13-8.

Table 13-8: RD i Whole-Ore Leach Test Results

Composite Number	Grind Size (P ₈₀ , mesh)	% Gold Extraction, Leach Time			NaCN Consumption at 48 hr. (lbs/st)
		6 hr.	24 hr.	48 hr.	
Mill Zone Average	100	57.0	65.0	64.7	0.50
Mill Zone Average	200	64.7	65.7	65.9	0.42
Mill Zone Average	325	68.0	69.2	68.4	0.84
Haile Average	200	67.5	71.3	71.5	0.52
Haile Average	325	69.0	73.7	75.3	0.96
Ledbetter Average	200	72.2	75.60	75.8	0.24
Ledbetter Average	325	70.4	80.3	79.1	1.40

Source: OceanaGold

RD i performed flotation test work to investigate the recovery of gold and silver to a sulfide mineral concentrate. The tests indicated that a reagent suite of potassium amyl xanthate (PAX), AERO 404 (or equivalent), and methyl isobutyl carbinol (MIBC) frother, along with a laboratory flotation time of 6-minutes and a grind size of 200-mesh or finer will result in the highest gold recovery values.

A summary of the RD i flotation test work is presented in Table 13-9 and Table 13-10.

Table 13-9: Flotation Test Results – Averages by Grind

Sample Description	Primary Grind (P ₈₀ , mesh)	Flotation Concentrate 6-minute Flotation Time Recovery %			Concentrate Grade (oz/st)	
		% wt	Au	Ag	Au	Ag
Mill Zone Average	100	18.2	92.7	50.9	0.516	0.341
Mill Zone Average	200	14.2	91.7	58.7	0.630	0.679
Mill Zone Average	325	12.6	90.8	61.6	0.779	0.846
Red Hill Average	200	16.8	82.6	75.2	0.493	1.420
Red Hill Average	325	15.6	82.3	73.1	0.557	1.053
Ledbetter Average	200	10.3	91.8	57.7	1.234	0.749
Ledbetter Average	325	10.5	88.6	42.8	1.301	0.674
Haile Average	200	12.8	86.7	59.9	0.519	0.752
Haile Average	325	11.3	86.4	65.6	0.618	0.834
Snake Average	200	15.4	90.2	50.4	0.665	0.475
Snake Average	325	15.0	91.6	49.0	0.636	0.446

Source: OceanaGold

Table 13-10: Flotation Test Results Average by Grade and Grind

Sample Description	Primary Grind (P ₈₀ , mesh)	Flotation Concentrate 6-minute Flotation Time Recovery %			Concentrate Grade (oz/st)	
		% wt	Au	Ag	Au	Ag
Mill Zone Average-Grade	200	13.5	93.4	77.1	0.674	1.012
Mill Zone Average-Grade	325	12.9	90.7	70.8	0.697	0.992
Mill Zone High-Grade	200	13.3	92.1	83.5	1.374	1.274
Mill Zone High-Grade	325	12.7	94.8	60.4	1.461	1.015
Red Hill Average-Grade	200	16.6	76.6	83.1	0.338	1.409
Red Hill Average-Grade	325	15.2	82.1	77.8	0.347	0.662
Red Hill High-Grade	200	20.0	93.9	94.3	1.569	3.228
Red Hill High-Grade	325	18.2	93.2	80.5	1.496	2.633
Ledbetter Average-Grade	200	12.2	90.7	68.9	0.703	0.624
Ledbetter Average-Grade	325	14.1	89.5	44.2	0.563	0.271
Ledbetter High-Grade	200	8.0	95.7	57.5	3.071	1.534
Ledbetter High-Grade	325	7.9	87.5	53.3	2.033	1.175
Haile Average-Grade	200	12.2	84.9	65.1	0.365	0.726
Haile Average-Grade	325	11.2	86.5	64.0	0.402	0.682
Haile High-Grade	200	14.8	91.8	86.0	1.595	1.858
Haile High-Grade	325	12.5	87.6	67.3	1.423	1.371
Snake Average-Grade	200	16.4	96.1	53.5	0.472	0.432
Snake Average-Grade	325	17.1	89.1	38.4	0.382	0.350
Snake High-Grade	200	19.0	96.2	69.9	1.575	0.962
Snake High-Grade	325	17.1	95.3	65.6	1.560	0.688

Source: OceanaGold

RDi performed flotation tailing cyanide leach tests to investigate the extraction of gold from the flotation tailing. The test results indicate that gold can be extracted from the flotation tails. A summary of the test work is presented in Table 13-11.

Table 13-11: Flotation Tailing Leach Test Results Average by Grade and Grind

Sample Description	Primary Grind (P ₈₀ , mesh)	Gold Extraction Leach Time – 24 hr. (%)	NaCN Consumption (lbs/st)	Lime Addition Ca(OH) ₂ (lbs/st)
Mill Zone Average-Grade	200	52.9	0.14	3.08
Mill Zone Average-Grade	325	63.0	0.50	3.08
Mill Zone High-Grade	200	71.7	0.16	3.08
Mill Zone High-Grade	325	71.9	0.44	3.08
Red Hill Average-Grade	200	68.5	0.74	13.19
Red Hill Average-Grade	325	67.5	1.22	12.83
Red Hill High-Grade	200	74.1	2.56	15.76
Red Hill High-Grade	325	81.1	1.40	15.30
Ledbetter Average-Grade	200	68.6	0.44	6.35
Ledbetter Average-Grade	325	70.7	0.24	5.65
Ledbetter High-Grade	200	72.0	0.20	n.r.-
Ledbetter High-Grade	325	76.5	0.16	n.r.
Haile Average-Grade	200	62.7	0.16	13.68
Haile Average-Grade	325	62.2	0.26	13.70
Haile High-Grade	200	75.6	0.22	6.71
Haile High-Grade	325	77.1	0.18	6.31
Snake Average-Grade	200	62.38	0.02	8.53
Snake Average-Grade	325	66.34	0.16	8.45
Snake High-Grade	200	70.00	0.20	6.39
Snake High-Grade	325	70.90	0.24	6.29

Source: OceanaGold

Larger scale flotation test results achieved 91% gold recovery into a concentrate representing 8.8% weight of the flotation feed in 13.5 minutes of flotation time. Subsequent leach tests of flotation tail gave results that indicated 50% gold extraction in 16-hours of leaching.

Regrind test work on concentrate samples generated was performed by Metso Minerals Industries, Inc. (Metso) to predict specific energy requirements for concentrate regrind.

RD i performed flotation test work on 23 drill core composite samples from the Ledbetter Extension zone. The methodology for compositing samples by grade was the same as used earlier.

Gold recovery by flotation averaged 86% for the 100-mesh grind samples, averaged 87% for the 150-mesh grind samples, and ranged from 81% to 95% but averaged 89% for the 200-mesh grind samples.

The flotation tailing samples were leached for 24 hours at 40% solids and gold extractions averaged 66% for 100-mesh grind samples, from 52% to 85% and averaged 68% for 150-mesh grind samples, and from 44% to 87% and averaged 69% for 200-mesh grind samples.

In 2010, RD i performed additional metallurgical testing on duplicate ore samples from the earlier testing. Additional composite samples were made to evaluate carbon loading, cyanide destruction, flash flotation, conventional flotation time, and leaching of concentrate and tailing samples.

A procedure was developed and used to evaluate “flash flotation”. Flash flotation was shown to recover 62 to 66% of the gold in two minutes of flotation time. Conventional flotation improves the total flotation

gold recovery to about 80% and leaching of flotation tailing extracts 76 to 80% of the gold from the flotation tailing sample.

Fifteen samples were selected for the generation of flotation concentrate in one cubic foot flotation cell tests. The fifteen samples were low, average and high grade from different ore zones (Red Hill, Snake, Ledbetter, and Mill Zone).

Five samples were selected for the generation of flotation concentrate in small-scale laboratory flotation cell tests. The five samples were identified as average grade material from the different ore zones.

The flotation tests were followed by leaching tests conducted on the flotation concentrates and flotation tailings. The results of these tests are presented in Table 13-12.

Table 13-12: Test Results for Flotation and Leaching

Test No.	Zone	Grade	Comp. No.	Flotation			Conc. Leaching			Tails Leaching			Total Recovery Au (%)
				Head Grade Au (oz/st)		Au Recovery (%)	Head Grade Au (oz/st)		Au Extraction (%)	Head Grade Au (oz/st)		Au Extraction (%)	
				Assay	Calc		Assay	Calc		Assay	Calc		
1/2	RH	L	49	0.027	0.033	91.5	0.172	0.140	62.7	0.003	0.005	83.8	64.5
7/8	H	L	47	0.010	0.011	64.7	0.093	0.190	82.6	0.004	0.006	85.9	83.8
17/18	S	L	51	0.015	0.015	84.0	0.230	0.245	79.8	0.003	0.003	66.0	77.6
19/20	L	L	43	0.021	0.020	86.7	0.248	0.207	71.9	0.003	0.005	61.3	70.5
25/26	MZ	L	H290	0.024	0.035	95.4	0.152	0.190	77.4	0.002	0.004	72.5	77.2
15/16	RH	A	34	0.080	0.095	92.0	0.589	0.513	83.3	0.009	0.010	67.2	82.0
11/12	H	A	8	0.085	0.064	85.5	0.455	0.467	74.8	0.010	0.012	60.3	72.7
9/10	S	A	39	0.056	0.052	89.6	0.735	0.583	64.2	0.006	0.006	77.7	65.8
3/4	L	A	23	0.059	0.073	89.6	1.009	0.752	80.4	0.008	0.013	71.8	79.5
13/14	MZ	A	2	0.057	0.059	92.6	0.423	0.382	69.3	0.005	0.006	69.2	69.3
C34	RH	A	-	0.073	0.072	86.0	-	0.370	80.0	0.012	0.012	80.2	80.0
C28	H	A	-	0.086	0.085	68.1	-	0.580	59.7	0.030	0.029	79.6	66.0
C31	S	A	-	0.051	0.056	93.7	-	0.166	58.5	0.005	0.005	45.1	57.7
C61	L	A	-	0.048	0.047	86.1	-	0.341	80.7	0.007	0.008	81.4	80.4
C5	MZ	A	-	0.073	0.078	92.2	-	0.292	69.5	0.008	0.008	67.0	69.3
27	RH	H	35	-	0.429	94.1	2.601	2.094	73.6	0.030	0.038	77.5	73.8
28	H	H	9	0.180	0.194	90.5	1.394	1.321	88.5	0.021	0.024	64.5	86.2
5/6	S	H	53	0.304	0.312	95.2	2.365	1.875	75.2	0.017	0.020	68.3	74.9
23/24	L	H	71	0.240	0.274	94.7	2.622	2.222	74.0	0.015	0.034	81.5	74.4
21/22	MZ	H	12/3	0.168	0.199	96.0	1.563	1.155	79.7	0.009	0.020	73.3	79.4

Source: OceanaGold

The overall extraction, sorted by sampled zones, is presented in Table 13-13.

Table 13-13: Gold Recovery by Ore Zone and Ore Grade

Ore Zone	Au Extraction – Combined %			Average Au Extraction (%)
	Low Grade	Average Grade	High Grade	
Red Hill	64.5	82.0	80.0	75.1
Haile	83.8	72.7	66.0	77.2
Snake	77.6	65.6	57.5	68.9
Ledbetter	70.5	79.5	80.8	76.3
Mill Zone	77.2	69.3	69.3	73.0
Average	74.7	72.3	77.8	74.3

Source: OceanaGold

RDİ performed additional leach tests on flotation concentrates to ascertain if better results could be obtained.

The results of performing leach tests on larger concentrate samples (i.e., twice the size used in previous tests) demonstrated a significant improvement in gold and silver extraction. Concentrate samples were ground to a size distribution of 80% passing 15 to 18 microns. The slurry was then pre-aerated for four hours and lead nitrate was added for the final three hours of pre-aeration and then leached for 48 hours with carbon present. A summary of the larger scale leach test results is presented in Table 13-14.

Table 13-14: CIL Test Results for Fine Ground Flotation Concentrate

Test No.	Pit	Grade	Composite Number	Grind Size (P ₈₀ , µm)	48 hr. Leach Time % Extraction		NaCN Consumption (lbs/st)
					Au	Ag	
37	Red Hill	L	49	17	80.9	71.1	2.00
36	Haile	L	47	14	77.2	49.5	4.99
38	Snake	L	51	16	81.0	94.4	10.83
35	Ledbetter	L	43	16	88.3	91.9	5.09
21	Mill Zone	L	Hole 290	-	79.8	91.0	5.59
26	Mill Zone	L	Hole 290	-	85.0	82.3	4.75
33	Red Hill	A	34	16	85.8	77.2	4.60
31	Haile	A	28	18	95.6	97.4	4.36
22	Haile	A	8	-	81.6	93.2	3.62
32	Snake	A	31	18	58.8	18.2	4.26
24	Snake	A	39	-	84.7	96.4	5.25
40	Ledbetter Ext	A	61	14	89.8	98.3	1.96
27	Mill Zone	A	2	16	81.5	96.2	4.77
28	Mill Zone	A	5	17	79.2	50.0	4.72
41	Ledbetter Ext	A	73	16	83.7	93.4	3.30
23	Ledbetter	A	23	-	88.3	79.9	4.72
34	Red Hill	H	35	16	92.6	95.9	3.66
29	Haile	H	9	20	93.7	97.7	3.46
39	Snake	H	53	16	83.4	97.4	5.03
30	Mill Zone	H	12/3	19	88.7	95.9	4.00
25	Ledbetter Ext	H	71	-	94.9	95.6	12.3

Source: OceanaGold

KML was commissioned to perform additional flotation and leach tests on 29 composites from Mill Zone and Snake areas. The samples selected were chosen to represent the initial three-years of the operation's mine schedule anticipated at the time.

Each composite was subjected to bulk flotation. The flotation concentrate was reground to a P₈₀ of approximately 13 microns and leached for 48 hours. The flotation tailing was also leached for 48 hours. The overall gold recoveries ranged from 71.6% to 91% and overall silver recoveries ranged from 32.9% to 81.9%. A summary of the results is presented in Table 13-15.

Table 13-15: Tests Results for Composites from Mill Zone and Snake areas

Composite	Au Head Grade (oz/st)	Au Recovery (%)	Ag Head Grade (oz/st)	Ag Recovery (%)
1	0.224	90.6	0.07	75.8
2	0.028	74.7	0.05	74.2
3	0.127	89.8	0.06	73.1
4	0.101	82.6	0.05	73.8
5	0.128	88.6	0.06	81.4
6	0.037	71.6	0.04	68.4
7	0.320	90.7	0.08	77.7
8	0.071	83.7	0.06	77.5
9	0.077	87.9	0.13	81.1
10	0.142	88.7	0.17	81.9
12	0.038	77.5	0.05	64.5
13	0.064	81.3	0.06	78.5
14	0.047	84.0	0.11	80.6
15	0.079	85.1	0.11	75.0
16	0.114	82.6	0.15	75.3
17	0.056	82.9	0.06	78.7
18	0.054	76.0	0.09	75.5
19	0.061	77.7	0.03	70.7
20	0.036	75.8	0.04	76.7
21	0.065	76.6	0.08	71.8
22	0.148	87.5	0.12	71.6
23	0.245	91.0	0.10	74.4
24	0.055	86.5	0.03	52.8
25	0.029	87.6	0.02	43.6
26	0.013	76.3	0.02	62.3
27	0.010	80.8	0.01	58.0
28	0.016	76.8	0.02	35.5
29	0.027	80.9	0.01	32.9
30	0.107	88.8	0.04	46.0

Source: OceanaGold

RDi undertook additional test work on the composite samples from the Horseshoe Zone to determine the response to the process flowsheet selected. Visible gold was reported in some core intercepts used for Horseshoe test work. Test work included comminution (described above) and flotation and leaching of concentrate and flotation tailing.

The flotation process utilizing a simple reagent suite (PAX, AP404 and MIBC) developed for the deposit in earlier studies recovered 85% to 90% of the gold into the concentrate for most of the composites. Cyanide leaching consistently extracted about 70% of the gold in the flotation tailings. The composite concentrate samples were reground and subjected to a preparation step and a carbon in leach (CIL) test, which showed gold and silver extractions of over 90% for most composites. Lower recoveries were achieved for the low-grade composite 83.

A summary of the test results is presented in Table 13-16.

Table 13-16: Test Results for Horseshoe Samples

Composite Number	Assay Head Au (g/t)	Primary Grind Size (P ₈₀ , mesh)	Flotation Recovery (%)		Tailing Leach (%) Extraction		Concentrate Leach Extraction (%)		Overall Extraction (%)	
			Au	Ag	Au	Ag	Au	Ag	Au	Ag
83	1.8	100	86.5	63.0	70.2	3.7	69.3	64.9	69.4	42.3
83		150	89.0	57.1	70.4	9.6			69.4	41.2
83		200	87.6	54.1	73.9	5.5			69.9	37.6
84	9.1	100	88.4	74.4	69.4	5.3	96.2	94.6	93.1	71.7
84		150	90.2	77.3	71.3	22.0			93.8	78.1
84		200	90.1	77.7	71.0	7.1			93.7	75.1
85	10.4	100	83.3	70.7	66.5	39.4	96.0	91.9	91.1	76.5
85		150	89.2	81.4	71.7	19.1			93.4	78.4
85		200	87.4	80.7	76.3	37.5			93.5	81.4
86	12.1	100	86.4	74.5	67.2	8.9	94.9	92.1	91.1	70.9
86		150	85.8	73.8	72.5	45.8			91.7	80.0
86		200	90.4	75.2	76.6	40.7			93.1	79.4
87	10.6	100	69.7	57.7	59.5	53.4	95.2	95.0	84.4	77.4
87		150	77.8	64.8	66.1	54.1			88.7	80.6
87		200	75.9	69.0	70.8	54.1			89.3	82.3

Source: OceanaGold

In late 2011, G&T Metallurgical Services was selected to perform the metallurgical test program on additional Horseshoe samples. The metallurgical test program involved testing of twelve variability samples to evaluate recoveries by flotation and cyanidation of concentrate and flotation tails.

The Horseshoe samples responded very well to the Haile flowsheet. A summary of the test results compiled by HGM personnel is provided in Table 13-17.

Table 13-17: Test Results for Horseshoe Samples

Composite Number	Gold Head Grade (oz/st)	Flotation P ₈₀ (µm)	Kinetic Flotation Recovery (%)	Bulk Flotation Recovery (%)	Regrind P ₈₀ (µm)	Concentrate Leach Extraction (%)	Tailings Leach Extraction (%)	Overall Gold Recovery (%)
1	0.199	81	93.9	86.5	15	90.4	81.1	89.2
2	0.339	70	92.5	90.7	13	99.5	67.3	96.6
3	0.043	78	96.5	94.0	14	86.1	87.6	89.8
4	0.060	73	93.3	97.0	16	98.5	74.1	86.1
5	0.076	81	90.2	83.4	10	94.9	85.5	94.4
6	0.168	84	88.4	86.0	11	93.0	90.2	94.9
7	0.082	82	85.2	88.0	15	94.9	75.6	93.8
8	0.094	66	89.0	84.4	12	98.6	83.3	92.6
9	0.057	69	86.2	89.2	11	97.1	81.7	96.0
10	0.121	75	75.1	77.6	15	90.3	82.1	90.6
11	0.349	88	86.2	87.5	14	97.4	88.4	95.8
12	0.129	77	85.3	83.6	10	97.4	84.2	96.1

Source: OceanaGold

Laboratory testing on ore composite samples demonstrated that the mineralization was readily amenable to flotation and cyanide leaching process treatment. A conventional flotation and cyanide leaching flow sheet can be used as the basis of process design. The relative low variability of flotation test work indicates that the mineralized zones are relatively similar in terms of mineral composition, and flotation and cyanide leaching response.

The samples tested responded favorably at a moderately fine feed size range of 80% passing 200-mesh (74 microns). Therefore, a primary grind size of 80% passing 200-mesh was recommended for process circuit design development. Operational experience and mineralogy may allow this criterion to be relaxed reducing comminution requirements and increasing plant capacity.

The flotation testing indicated that gold can be recovered in a flotation concentrate that will also contain the majority of the silver in the ore. The tailing from the flotation circuit can then be processed by cyanide leaching to recover gold onto activated carbon.


The test work indicated that the circuit should include regrinding of the flotation concentrate before slurry pre-aeration, and a leach time of 24 hours. A regrind circuit product size of 80% passing 15 microns is an appropriate target for regrind circuit design. Operational experience may allow this criterion to be relaxed reducing comminution requirements and increasing plant capacity.

Leaching of the flotation concentrate can extract 82% to 91% of the gold and 80% to 96% of the silver. Leaching of the flotation tailing can extract 45% to 86% of the gold in the flotation tailings. It appears that overall gold recovery will be in the range of 65% to 92% dependent primarily on head grade to the mill and less dependent on from which zone the ore is mined.

The unit operations that determine the amount of gold extraction are flotation, flotation concentrate regrind and leaching, and flotation tailing leaching.

The data developed in the test programs has been used to establish a relationship between overall gold recovery and head grade as shown in the graph in Figure 13-2. The algorithm for the “best-fit” line that describes the head grade to recovery relationship can be used to estimate gold recovery from a predicted mill head grade for example, at a mill head grade of 2.3 g/t, the recovery equation graph predicts a gold recovery of 84.2%.

The results of grade and recovery data analysis are shown in Figure 13-2.

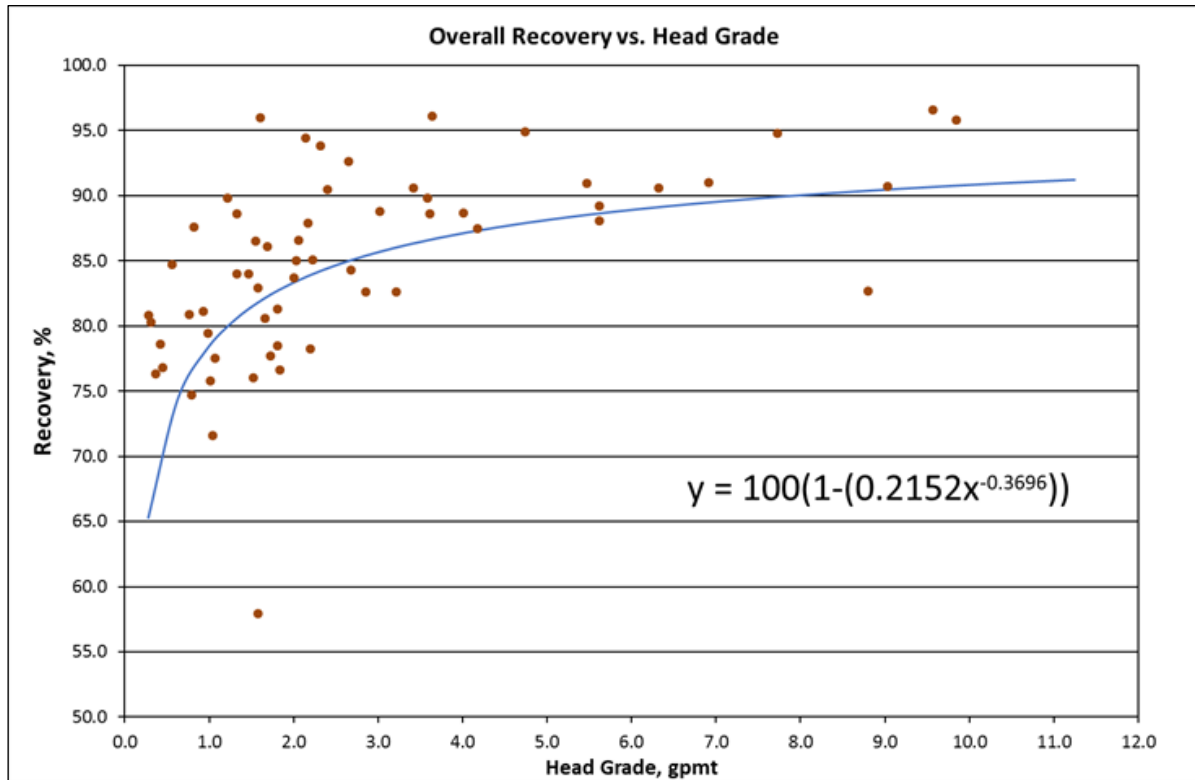

Source: OceanaGold

Figure 13-2: Overall Percent Recovery vs. Head Grade

Overall, the results from Horseshoe tests were in-line with or exceeded the recovery model.

The cyanide destruction test results indicated that the sulfur dioxide (SO₂)/air cyanide destruction process destroys weak acid dissociable (WAD) cyanide very effectively, as well as free cyanide. Operations to date have achieved target levels of cyanide removal from the TSF and reagent usage is being optimized to further reduce costs.

13.1.3 Sample Representativeness

Samples were collected from a range of locations across the main area of the resources that is planned to be fed to the processing plant over the LoM.

The minimal variability of test work indicates that the different mineralized zones are relatively similar in terms of ore grindability, chemical and mineral compositions, and flotation and cyanide leaching response. Given the uniform geological setting and mineralization, this is not surprising.

It is evident from the comminution testing that ore competency is increased in the deeper resources (e.g., Horseshoe underground). This is typified by the trend of increased Bond Ball Milling Work indices for samples sourced from lower levels.

13.2 Recovery Estimate Assumptions

The recovery estimate previously was based on the interpretation of test work results from a range of samples and test work campaigns and shown in Figure 13-2 as a function of gold grade. This was based on the original flowsheet incorporating sulfide flotation and open circuit regrind of concentrate in the SMD circuit to a target P80 of 13 μm .

Operating experience since plant commissioning has been below target due to the inability of the original regrind circuit to achieve the planned 13 μm grind size and, with the staged increase in mill throughput, the concentrate feed rate to the regrind section continued to increase above the original design further exacerbating the issue. The completion of the replacement of the regrind circuit in 2019 with a two stage Towermill/Isamill circuit operating in closed circuit has achieved the targeted regrinding product size. In addition, a number of plant modifications have been implemented to address mechanical issues in the CIL circuit leading to short circuiting and issues with carbon management related to interstage screen cleaning schedules.


With the plant ramping up tonnage ahead of plan in 2019, mill feed has been supplemented with oxide material from stockpiles in the feed blend. While the flotation concentrates and tailings are leached allowing the oxide material to be blended, there has been a detrimental impact on flotation performance impacting the recovery of sulfide to the regrind circuit and subsequent gold loss to leach tailings. Since June 2020, the mill feed strategy has been altered to campaign the oxide feed on its own direct to CIL to minimize the impact on sulfide processing.

Additional flowsheet development has been ongoing throughout 2019/20 with changes to process control, CIL circuit operation and concentrate pretreatment. The overall effect has been to achieve gold recoveries in excess of that predicted by the FS when feeding the plant predominantly fresh sulfide ore. The performance of the plant from June to August 2020 is shown in Figure 13-3 with daily reconciled data and the recovery predicted by the feasibility relationship resulting in a 2.5% increase on this model.

With the current level of blending of old oxide material mined during the pre-production period a more conservative recovery relationship was developed in 2019 reflecting plant operation data prior to improvements in regrind classification performance and ore-aeration. This relationship was used in preparation of the 2020 budget until the end of 2022 to reflect the expected ramp up to the long-term feasibility-based relationship.

For the purposes of the current life of mine plan the first 18 months to the end of 2021 has utilized this more conservative model to allow time to complete implementation of current projects complete ramp up to the 4.0 Mtpa rate.

Based on the metallurgical development projects completed and planned in the process plant and performance on fresh sulfide feed, the recovery model used post-2022 has adopted the 2.5% increase above the original feasibility relationship. By the end of 2021 it is expected the older rehandle oxide material will have been processed and the majority of rehandled material will be fresh sulfide feed. A recovery discount to the long-term model of 5% has been applied to rehandled feed after 2022 in the production model.

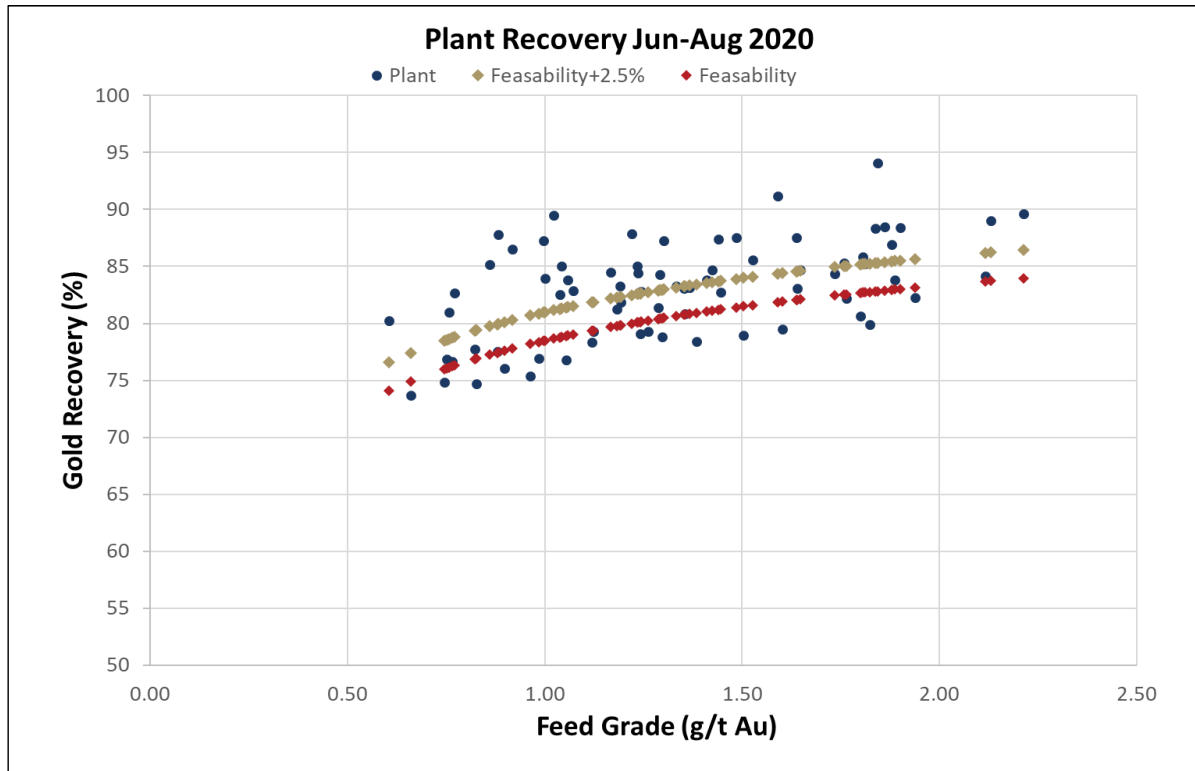

Source: OceanaGold

Figure 13-3: Plant Gold Recovery Performance Jun-Aug 2020

Silver recovery is estimated based on work completed at the KML laboratory on an additional 30 composites in 2012, representing the first three years of the mine plan looking at the performance of silver recovery. This program looked at composites over a wide range of silver to gold ratios from 0.25:1 to 2.23:1 and generated a recovery model based on silver recovery to the flotation concentrate and subsequent leach extraction from the reground concentrate and flotation tailings. This has been used for predicting overall silver recovery and metal production for byproduct credit calculations and to confirm sufficient capacity exists in the refinery stripping and electrowinning circuits for total gold and silver values. Silver recovery averages 81% of life of mine in the current models. Silver revenue accounts for approximately 1.3% of overall total sales and as such the the impact of changes to the silver recovery have a marginal impact on overall economic outcomes.

The product from Haile is gold containing moderate amounts of silver. The doré bars are 95% pure with minimal or no deleterious elements.

14 Mineral Resource Estimate

This section describes the Mineral Resource estimation methodology and summarizes the key assumptions adopted by OceanaGold. In the opinion of OceanaGold, the Mineral Resource estimate reported herein is a reasonable representation of the global Mineral Resources at Haile. The Mineral Resources and a classification of resources were prepared in accordance with the Canadian Institute of Mining, Metallurgy and Petroleum (CIM) Standards on Mineral Resources and Reserves: Definitions and Guidelines, May 10, 2014 (CIM, 2014). Mineral Resources are reported in accordance with NI 43-101. Mineral Resources are not Mineral Reserves and do not have demonstrated economic viability. There is no certainty that all or any part of the Mineral Resource will be converted into Mineral Reserve.

The Mineral Resource estimates were prepared under the supervision of Mr. Jonathan Moore, BSc (Hons) Geology, DipGrad Physics, member and Chartered Professional of the Australasian Institute of Mining and Metallurgy. Mr Moore is OceanaGold Chief Geologist, a Qualified Person as this term is defined pursuant to NI 43-101 for Mineral Resources. The effective date of the resource statement is June 30, 2020.

Separate block models were generated for the open pit and then underground areas given the differing mining selectivity and cut-off grade assumptions.

The open pit resource model is “HA0520OLM” built under the supervision of J. Moore. The geologic model was provided by the OceanaGold Haile Exploration department. Implicit gold grade shell generation, grade estimation and block model construction were completed within Vulcan software. Resource pit shells were generated using Whittle software.

The Horseshoe underground model is “HA0420UG_R” and was built under the supervision of J. Moore. The implicit gold grade shell was generated in Leapfrog software whilst grade estimation and block model construction were completed in Vulcan software.

The Palomino underground model is “HP0420URR” and was built under the supervision of J. Moore. The implicit gold grade shell was generated in Leapfrog software whilst grade estimation and block model construction were completed in Vulcan software.

14.1 Open Pit Mineral Resources Estimate

Grade estimation was completed with Vulcan software, using Multiple Indicator Kriging (MIK) based on 2.5 m bench composites to produce E-Type gold estimates into a 10 m E x 10 m N x 5 m RI model blocks.

Gold estimation was constrained within implicitly modelled grade shells, approximating a 0.065 g/t gold indicator. Metasediment/metavolcanic contacts were not used as hard boundary constraints for gold estimation. Modeled post-mineralization dikes were assigned zero grade.

MIK is well suited to estimating positively skewed grade distributions. Top caps of 50 g/t Au were used to temper mean grades above the top-class indicator threshold and are supported by reconciliation against production data.

Ordinary kriging (OK) was used for silver, sulfur and carbon estimates.

- Extraction of drillhole data from acQuire database

- Data validation, exclusion of drillholes from early drilling campaigns of unknown quality
- Composite drillholes to 2.5 m for Au, total carbon, total sulfur and silver
- Update grade shell in Vulcan using Implicit modelling tool
- Flag drillholes for lithology, domain area and grade shell
- Code model with lithological wireframes, domain area and grade shell
- Run MIK estimation for Au
- Set block grades to zero for blocks coded as post-mineralization dike
- Run OK estimation for Ag (with simulated values), total carbon % and total sulfur %
- Deplete resource with historical open pit and underground workings
- Assign model densities
- Classify model

14.1.1 Drillhole Database

During 2016, the Romarco Minerals drilling database was translated to OceanaGold's standard Acquire database platform. Where available, original source assay and survey data were used for the Acquire translation and database validation. There was a further internal database review in late 2018/early 2019. No material errors were identified.

Historical drilling (i.e., prior to 2007) accounts for approximately 28% of the data. The sample procedures applied to the historical drilling (i.e., drilling prior to Romarco Minerals Inc.) at Haile were not well documented. Having said this, approximately four years of mining at Haile has tested the veracity of the resource estimates which are based on this data. No material flaws have been identified.

Drillhole data available in April 2020, up to and including DDH0996, was included in the HA0520OLM estimate (Table 14-1). 1,700 historical drillholes were excluded on the basis of unknown quality.

The assay coverage for gold covers all core and RC drilling. However, the collection of carbon, sulfur and silver assay data has largely been retrospective and is significantly sparser than for gold. Sulfur and carbon data are primarily used for the prediction of waste classification types. Sulfur grades are also used for mill feed sulfur estimates. Silver grades are provided for metallurgical considerations (carbon stripping and electro-winning) as well as for revenue estimation, albeit silver is a minor contribution relative to total revenue

Table 14-1: Sample Numbers for Gold, Sulfur and Carbon

	Au	S	C	Ag
Count	376,522	63,238	31,400	14,418

Source: OceanaGold

14.1.2 Geologic Model Concepts

A detailed 3D lithological model, including weathering, has been constructed. This model, which has evolved over time, has been used to assign variable densities to the block model (Table 14-5). Faults have also been modelled. However, other than post-mineralization dikes, and post-mineralization erosion/deposition, there are few geological features that define mineralization boundaries at the economic cut-off grade.

14.1.3 Lithology

Lithologic codes used at Haile capture many geologic attributes including the primary rock type, presence of brecciation, silicification, lamination and numerous variations on the general rock unit. For the purpose of block modelling and building a resource model, these 150+ codes were reduced to a summary set of codes.

The majority of mineralization is hosted within the metasediments and the lithological units are as follows:

- S - sand
- Sap - saprolite
- MV - metavolcanics
- DB - intrusive dikes
- Fill - back-fill from historical mining
- MI - laminated metasediments
- Ms - silicified metasediments
- Breccia - brecciated rocks

14.1.4 Silicification

The progression of 'silicification' increases from 0 (non-existent) to 3 (main component) and is logged visually by site geologists. The minor silicification (1) population has an average grade of about 0.5 g/t. The average grade of moderately silicified (2) rocks is 1.0 g/t and the very silicified (3) average grade increases to approximately 2.0 g/t. The gold to silicification relationship is strong.

14.1.5 Pyrite


Multiple morphologies of pyrite have been identified at Haile, ranging from fine to coarse cubic pyrite. Based on logging, it has been established that the fine-grained pyrite is commonly associated with mineralization.

14.1.6 Grade Domain Construction

Although both silicification and pyrite occurrence are qualitatively associated with gold mineralization, their relationships are not used for quantitative gold domain definition. Implicit modelling in Vulcan software was used to create a grade shell at a 0.065 g/t gold threshold. The grade threshold selection was optimized, using sensitivity estimate comparisons against production data.

The grade shell was then sub-divided into two domains based upon gold distribution and orientation, albeit the differences were not large between the two domains.

The mineralized zones within domain 1 (blue in Figure 14-1), approximate a dip direction of -40 to 330, while in domain 2 (green), they approximate a dip direction of -30 to 335.

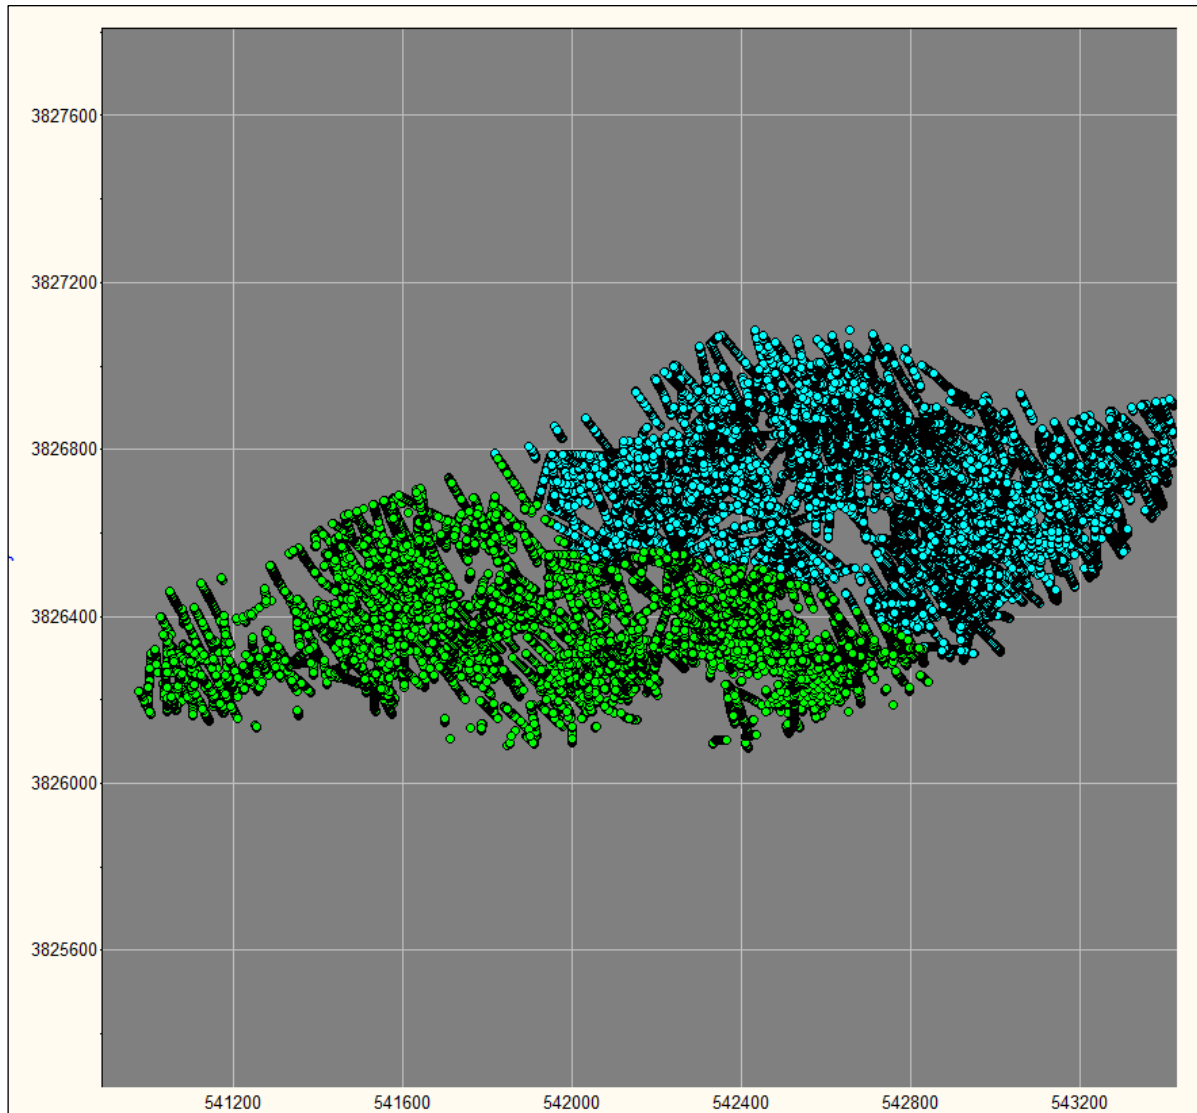

Source: OceanaGold

Figure 14-1: Estimation Domains

14.1.7 Compositing

2.5 m bench composites for carbon, gold and sulfur were calculated for estimation. Due to the paucity and uneven distribution of data, carbon and sulfur were estimated directly from the sample grades which were collected intermittently down the hole, typically only one sample per 6.1 m of drilling.

14.1.8 Assay Cap Values

Multiple Indicator Kriging (non-linear estimation) has been used for gold estimation which is better suited to positively skewed grade distributions than linear estimation methods. 2.5 m composited gold grades were top capped to 50 g/t Au based on reconciliation to production data. This lowered the mean grade of the top indicator class.

14.1.9 Multiple Indicator Gold Class Thresholds and Means

Gold Indicator thresholds were set at cumulative frequencies of 10th, 20th, 30th, 40th, 50th, 60th, 70th, 80th, 85th, 90th, 95th, 97.5th and 99th. Table 14-2 summarizes the indicator threshold grades and class means used for gold estimation.

Table 14-2: Indicator Gold Class Thresholds and Means

Cumulative Frequency	Domain 1		Domain 2	
	Threshold	Mean	Threshold	Mean
10	0.05	0.03	0.03	0.02
20	0.07	0.06	0.06	0.05
30	0.10	0.09	0.09	0.07
40	0.13	0.12	0.13	0.11
50	0.18	0.16	0.19	0.16
60	0.25	0.21	0.28	0.23
70	0.37	0.30	0.43	0.35
75	0.46	0.41	0.55	0.48
80	0.59	0.52	0.71	0.62
85	0.79	0.68	0.97	0.82
90	1.17	0.96	1.48	1.18
95	2.07	1.55	2.71	1.89
98	3.05	2.51	4.16	3.32
99	6.00	4.14	9.20	5.64
Max	50.00	11.34	50.00	12.90

Source: OceanaGold

14.1.10 Variogram Analysis and Modeling

Variograms were estimated for gold for each indicator threshold. Variograms for carbon and sulfur were estimated globally.

14.1.11 Block Model

The HA0520OLM resource block model was constructed in Vulcan and the parameters below in Table 14-3 are based on a Parent block size of 10 m x 10 m x 5 m in x, y, z respectively and is not sub-blocked or rotated.

Table 14-3: HA0520OLM Block Model Dimensions

Variable	East	North	RL
Minimum	539,810	3,825,575	-800
Maximum	544,510	3,827,725	200
Block Size (Parent)	10	10	5
No. of Blocks (Parent)	470	215	200

Source: OceanaGold

14.1.12 Estimation Methodology Gold, Sulfur and Carbon

Gold estimation was completed using Multiple Indicator Kriging, while carbon and sulfur were estimated using ordinary kriging. Carbon and sulfur values are used for classification of waste material.

For gold estimation, two domains were used:

- Domain 1 (Mill Zone, Haile/Red Hill, Champion)
- Domain 2 (Snake, Ledbetter)

Each domain area was estimated in three passes, with each subsequent search ellipse larger than the previous. Each of the main two open pit domain areas has unique search parameters based upon indicator variogram models for 14 different Au cut-offs. Table 14-4 shows the block search parameters.

Table 14-4: HGM16 Block Search Parameters

Domain	Area	Search Orientation			Search Radius				Sample Thresholds		
		Bearing	Plunge	Dip	Pass	Major Semi		Minor	Min	Max Max/Hole	
1	Mill Zone, Champion, Red Hill/Haile	335	-30	0	1	30	30	10	4	16	3
1	Mill Zone, Champion, Red Hill/Haile	335	-30	0	2	60	60	15	4	16	3
1	Mill Zone, Champion, Red Hill/Haile	335	-30	0	3	90	90	20	1	12	3
2	Snake, Ledbetter	330	-40	0	1	30	30	10	4	16	3
2	Snake, Ledbetter	330	-40	0	2	60	60	15	4	16	3
2	Snake, Ledbetter	330	-40	0	3	90	90	20	1	12	3

Source: OceanaGold

14.1.13 Estimation Methodology Silver

Silver estimates have not been completed for the underground.


For the open pit, silver grade estimates are provided for metallurgical considerations (carbon stripping and electro-winning) as well as for revenue estimation, albeit silver contributes only about 1.5% of total revenue and so is not particularly material. Silver content is not used as a gold-equivalent input for cut-off calculation nor to guide mine design decisions.

The sample support basis for the open pit silver estimates is approximately 10% of that for gold (54,100 x 3 m composites for gold versus 5,551 x 3 m composites for silver). While the paucity of data reduces the local accuracy of silver estimates, it does not preclude providing silver estimates for revenue modelling given that silver is mined as a by-product and not used for ore delineation.

The selection of samples for silver assaying was undertaken retrospectively, based upon previously assayed gold grades. Sample selection for silver assaying tended to favor more strongly gold-mineralized intervals, leaving less intensely mineralized intervals, on the flanks of the mineralization under-represented. In order to mitigate the impacts of the selection bias, bivariate simulation was implemented (using the “simulate missing data” program in GS3 proprietary software). This non-spatial simulation assigned silver grades to locations with gold assays, but no silver assays, based upon relationships between silver and gold in the assay database. Figure 14-2 shows gold-ranked silver and gold percentile means to highlight the underlying silver gold relationship. The silver gold relationship changes with gold grade; lower gold grades show a significantly higher silver gold ratio. Overall, the assayed population showed a rank spearman correlation coefficient of 0.47, reflecting a moderate correlation between silver and gold. This relationship was captured in the simulation process.

From the original 5,551 assayed samples with a mean silver grade of 2.36 g/t, a combined population of 54,100 assayed and simulated values (i.e. simulated silver values based on gold assay grades) with a mean silver grade of 1.84 g/t resulted. The result confirmed that a selection bias was present and provided justification for the downward silver grade adjustment via simulation.

A 95th percentile top cap value of 9.9 g/t Ag was applied to both domains, the 95th percentile was selected to err on the side of conservatism.

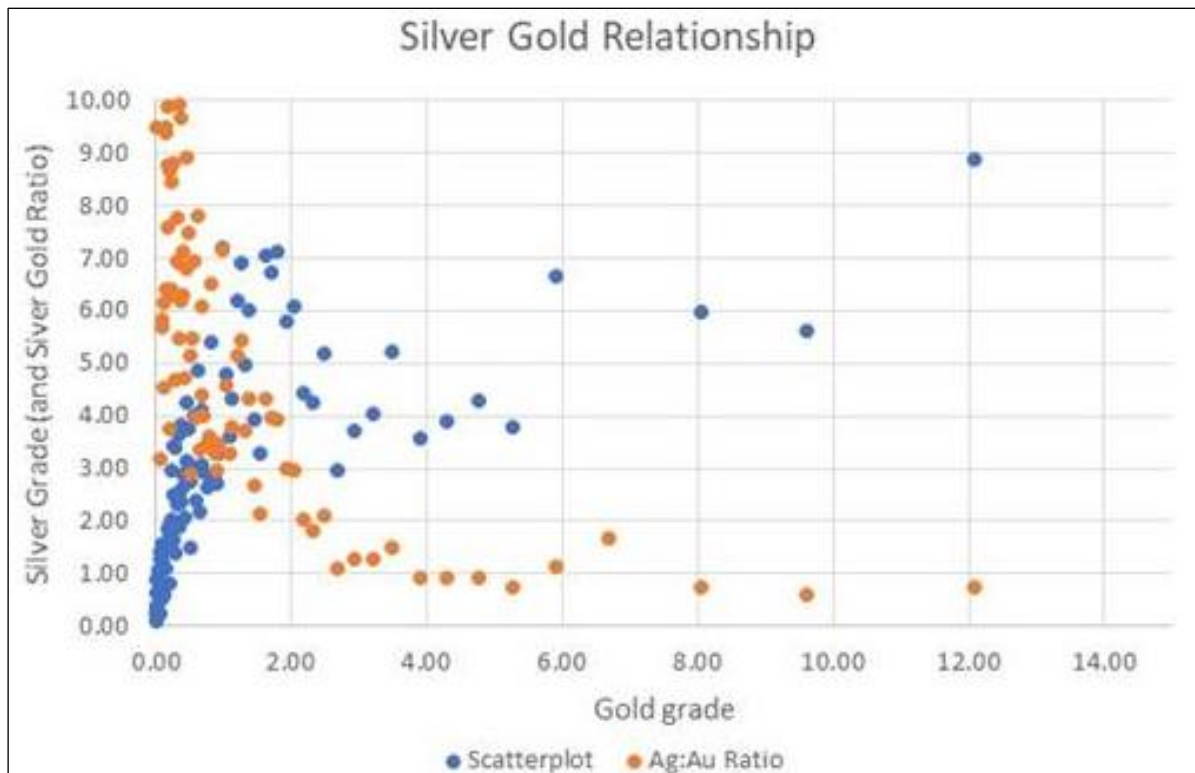

Source: OceanaGold

Figure 14-2: Silver Gold Relationship for Gold Ranked Percentile Averaged Grades

The domaining and search orientations as used for gold, were used for silver. Given the low number of original silver assays, ordinary kriging (not MIK) was used.

For mining to-date, the resource-estimated silver gold ratio is 1.15. Processing plant metallurgical accounting estimates a silver gold ratio of 1.04. The resources estimate is within acceptable limits (11%).

The silver estimation methodology described above is considered to be appropriate for the purposes of silver byproduct estimation.

14.1.14 SG

In situ density determinations have been carried out at regular intervals on drill core. The immersion/displacement method involved weighing the sample both in air and in water. Average measurements were used for each lithology. SG values were assigned to model blocks based on geological coding rather than estimated as a continuous variable (Table 14-5). Over 44,000 density measurements have been collected from core samples.

Table 14-5: HA0520OLM SG Assignment

SG Assignment Criteria								Criteria for Ore vs. Waste			
								Ore = Inside Gold Shell			
								Waste = Outside Summary Shell			
SG Assignment Criteria for HA0619OLM Model											
Sand	Saprolite	Dike	Meta Volcanics		Meta Sediments				Pag Fill	Tails	Heap
2.06	2.18	2.88	Oxidized	Fresh	Ore		Waste		1.89	2.14	1.7
			2.52	2.7	Oxidized	Fresh	Oxidized	Fresh			
					2.57	2.78	2.49	2.76			

Source: OceanaGold

14.1.15 Resource Classification


Resource classification was assigned by Vulcan script according to the search criteria for each domain and estimation pass tabulated in Table 14-4. That is, search distance and minimum sample numbers (limited to maximum sample numbers per hole with pass 1 = Measured, pass 2 = Indicated, pass 3 = Inferred).

14.1.16 Model Validation

Numerous methods have been used to validate the HA0520OLM resource model.

- Cross-sectional checks on composite file and block model coding from lithological wireframes, domain area and grade shell
- Visual checks of estimated block grade on sections, plan and in 3D to ensure good correlation with composite data
- Swath plots comparing the gold estimates with the underlying composite grades
- Detailed comparisons to previous model at global and local scales
- Review of the methodology and validation of the scripts used


The swath plots in Figure 14-3 and Figure 14-4 compare 2.5 m bench composite grades to the estimated block grades for gold, carbon, sulfur and silver respectively.

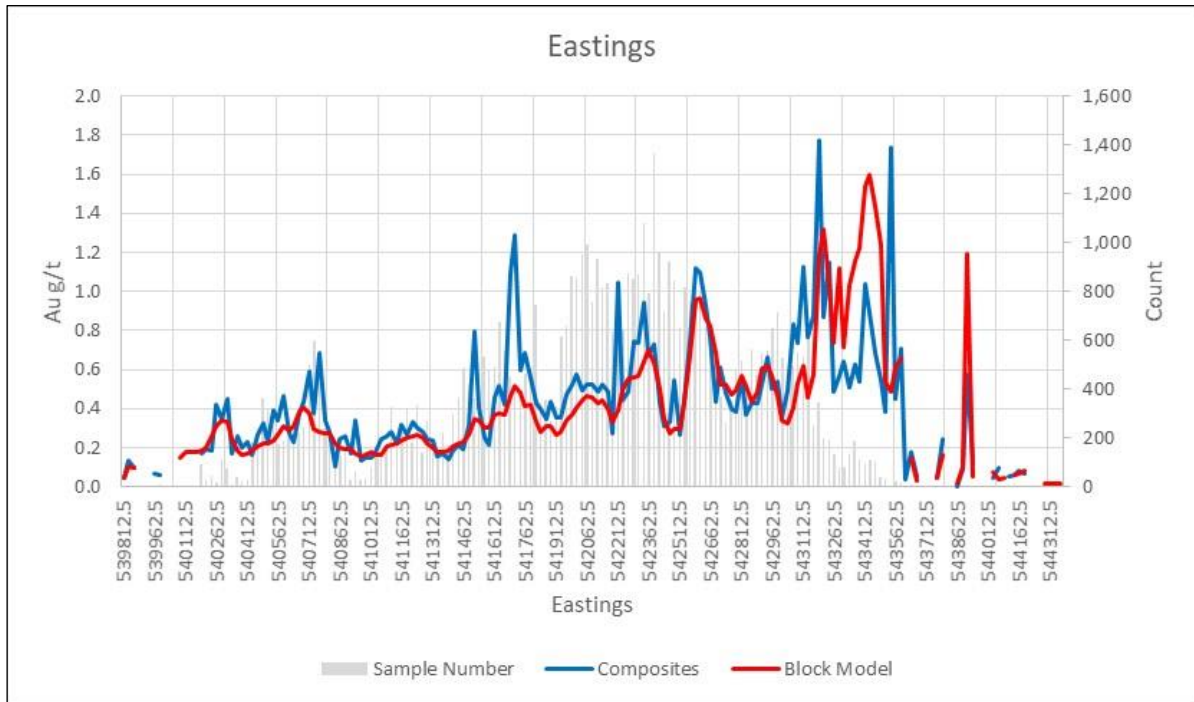

Source: OceanaGold


Figure 14-3: Swath Plot with Mean Composite Gold Grade vs HA0520OLM Block Values

Carbon and sulfur were estimated from raw drillhole data because of the lack of data relative to the gold and silver data sets. Swath plots for carbon, sulfur, and silver are shown in Figure 14-4 through Figure 14-6.

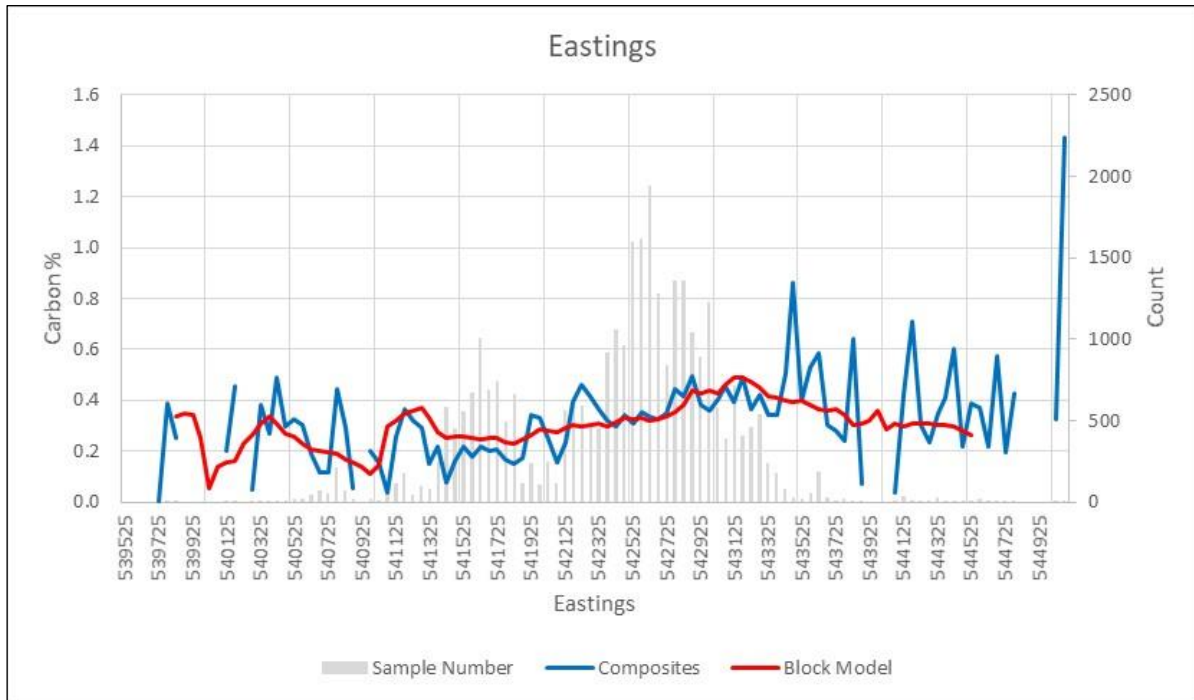


Source: OceanaGold

Figure 14-4: Swath Plot with Mean Composite Carbon Grade vs HA0520OLM Block Values

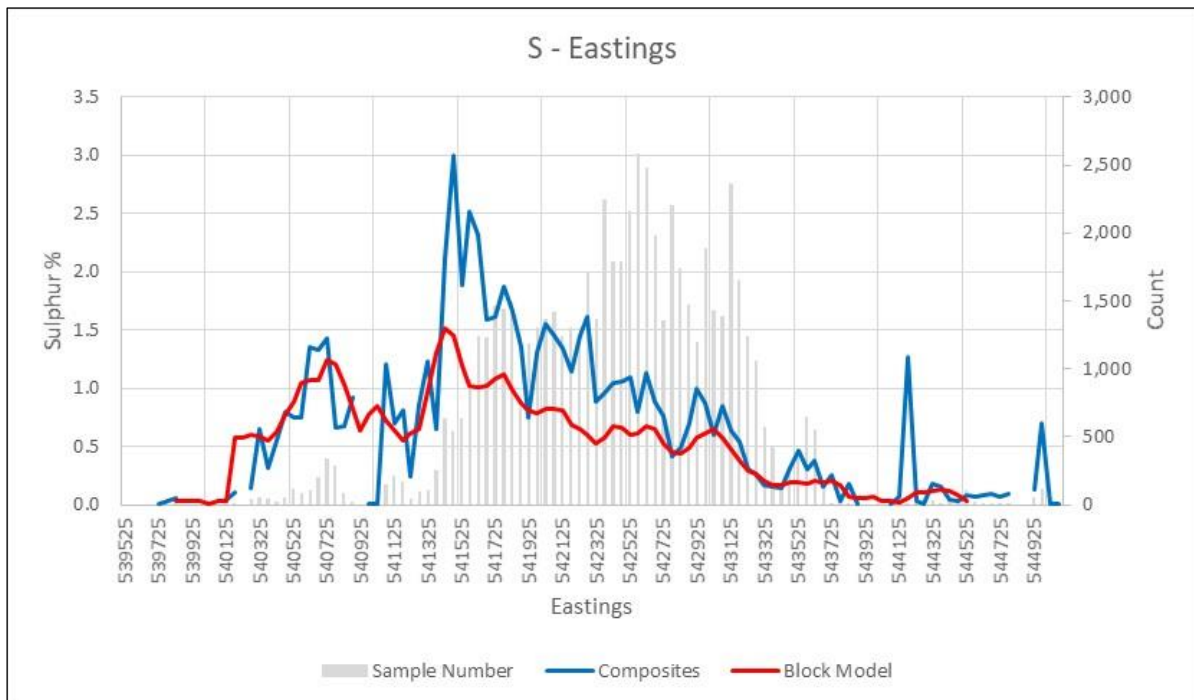

Source: OceanaGold

Figure 14-5: Swath Plot with Mean Composite Sulfur Grade vs HA0520OLM Block Values

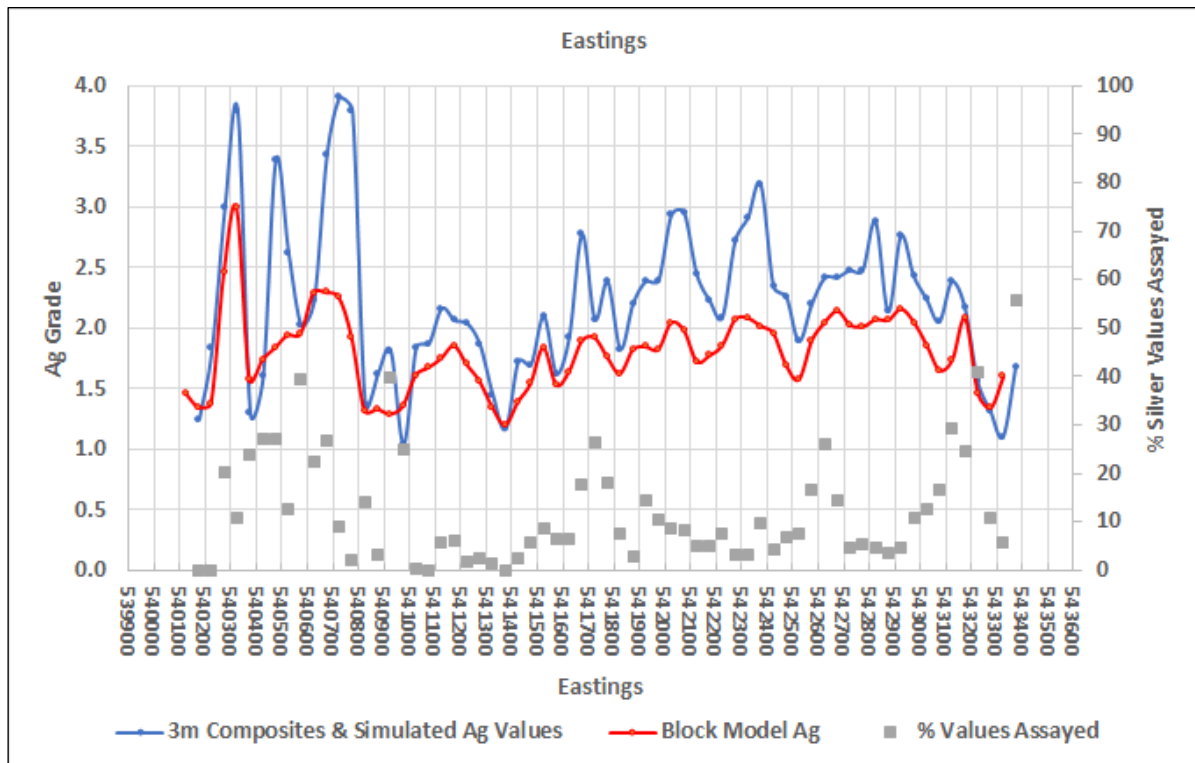

Source: OceanaGold

Figure 14-6: Swath Plot with Mean Composite Silver Grade vs HA0520OLM Block Values

As a gold estimation methodology check, an independent large panel recoverable resource estimate using MIK was constructed and compared to HA0520OLM on a stage-by-stage and easting swath basis. The estimate did not require constraint by an implicitly derived grade shell for gold estimation, so provided a useful parallel estimate via alternative modelling assumptions. Globally, the two estimates are within 2% of each other in terms of tonnes, grade and contained gold. There were some local differences, most pronounced in Haile Pit and Red Hill Pit areas where the distribution of mineralization is locally more complex.

14.1.17 Resource Model Reconciliation

Table 14-6 summarizes the resource model reconciliations for 2018, 2019 and 2020 to-date (30 June). The reconciliation is expressed as a ratio of resource model/mine x mine/mill. This is equivalent to resource model/mill, where 1.0 reflects parity.

Based upon resource model to mine to mill reconciliation data for 2018, 2019 and 2020 to-date (30 June), the resource estimates are within 2% for tonnage, grade and contained gold and reflect acceptable long-term model prediction. On this basis, the long-term predictions based upon the open pit resource estimates are believed to be acceptable for medium to long term mine planning purposes.

Table 14-6: Resource Model Reconciliation

Period	Tonnes	Grade	Gold
2018	0.90	1.13	1.02
2019	0.96	0.99	0.96
H1 2020	1.22	0.92	1.13
Total	0.99	1.02	1.01

Source: OceanaGold

14.1.18 Mineral Resource Statement

Table 14-7 summarizes the resulting open pit resources. A US\$1,700/oz shell was used with a cut-off of 0.45 g/t.

Table 14-7: Open Pit Total Mineral Resources as of 30 June 2020

Class	Tonnes (Mt)	Au Grade (g/t)	Contained Au (Moz)	Ag Grade (g/t)	Contained Ag (Moz)
Measured	3.2	1.35	0.14	2.61	0.27
Indicated	52.3	1.53	2.57	2.40	4.04
Measured & Indicated	56	1.52	2.71	2.41	4.30
Inferred	7.6	1.0	0.2	1.32	0.32

Source: OceanaGold

- Cut-off grade 0.45 g/t Au based on a gold price of US\$1,700/oz.
- Open pit resource is reported within a US\$1,700/oz optimized shell.
- Mineral Resources include Mineral Reserves and are reported on an in-situ basis.
- There is no certainty that Mineral Resources that are not Mineral Reserves will be converted to Mineral Reserves.
- All figures are rounded to reflect the relative accuracy and confidence of the estimates and totals may not add correctly.
- The open pit Mineral Resources were estimated under the supervision of Jonathan Moore, MAusIMM CP(Geo), a Qualified Person.

The reader is cautioned that Inferred Mineral Resources are considered too speculative geologically to have economic considerations applied to them that would enable them to be categorized as Mineral Reserves. There is no certainty that the Inferred Mineral Resources will be realized or that they will convert to Mineral Reserves.

14.2 Underground Mineral Resource Estimate

14.2.1 Horseshoe

The Horseshoe resource estimation is based on the current drillhole database, interpreted lithologies, geologic controls and current topographic data. The resource estimation is supported by drilling and sampling current to April 22, 2020.

Gold estimation was constrained within implicitly modelled grade shells, approximating a 1 g/t gold indicator. The 1 g/t Au threshold was selected to be sufficiently below the reserve reporting cut-off grade of 1.44 g/t Au to minimize conditional bias. Model blocks with centroids outside the 1 g/t shell were coded as unclassified and not reported (i.e. assigned zero grade).

Modeled post-mineralization dikes were assigned zero grade. Metasediment/metavolcanic contacts were not used to constrain gold estimation.

Gold grades were estimated with Vulcan™ modelling software into 10 m E x 10 m N x 10 m RI blocks (sub-blocked to 5mE x 5mN x 5mRI) using Ordinary Kriging with 3 m composites.

Densities based upon core analyses were assigned by rock type.

The Mineral Resources reported for the Horseshoe deposit are classified as Indicated and Inferred Mineral Resources, based primarily on drillhole spacing since all other supporting data is of good quality.

Horseshoe General Geology and Geologic Model

The Horseshoe deposit is the highest grade and easternmost known gold deposit in the Haile district. Mineralization extends over a vertical distance of 350 m, however, the deposit footprint is only about 200 m x 120 m. The top of the deposit is about 120 m below surface. The deposit is one of several siltstone-hosted deposits located near the steeply SE-dipping contact with metamorphosed volcanic rocks of the upper Persimmon Fork Formation. Horseshoe is a Neoproterozoic gold deposit characterized by strong silicification, 1-5% pyrite, and a halo of 0.5-1% pyrrhotite. The rocks have been deformed by high strain, isoclinal folding and shearing with a pervasive foliation striking 060°E and dipping 40-60°NW. All units are cut by post mineralization diabase dikes striking 330° with near-vertical dips. OceanaGold has constructed a geologic model which includes the siltstone, volcanics, diabase dikes, saprolite and sand. Siltstone is significantly mineralized. These five rock types constitute the lithologies coded in the block model. This has resulted in a detailed, 3D geologic model created by Leapfrog®.

This has resulted in a detailed, 3D geologic model created with Leapfrog® software.

Horseshoe Geologic Model and Controls on Gold Mineralization

Mineralization is concentrated in two main zones based on vertical position which form a “horseshoe” geometry over a vertical distance of 350 m. Both zones strike NE adjacent to the siltstone-dacite contact, however, the upper zone dips about 40°NW and the bulk geometry of the lower zone is near-vertical. The upper zone NW-dipping high-grade lenses of mineralization are focused along bedding-parallel foliation with intense silicification. The Horseshoe fault (NE strike, 40°NW dip) juxtaposes the hanging wall of upper Horseshoe against barren dacite with a sill-like geometry. This geometry extends southwestward into the nearby Snake pit. The steeply dipping Lower Zone is adjacent to the sub-vertical contact with barren dacite. Compared to the upper zone, gold grades are lower, silicification is less intense, and pyrite contents are lower. Extents of economic mineralization in lower Horseshoe have not been fully delineated by drilling.

Horseshoe Density

Model densities are based on domain averages, as shown in Table 14-8. The model densities were assigned through a combination of lithology, oxidation, alteration, and an ore/waste threshold. The SG was assigned for each lithology type. In-situ density determinations have been carried out at regular intervals on drill core samples. The method involved weighing the sample both in air and in water. The measurements were then averaged for each lithology.

Table 14-8: Densities Assigned in the Block Model

SG Assignment Criteria								Criteria for Ore vs. Waste			
								Ore = Inside Gold Shell			
								Waste = Outside Summary Shell			
SG Assignment Criteria for HA0619OLM Model											
Sand	Saprolite	Dike	Meta Volcanics		Meta Sediments				Pag Fill	Tails	Heap
2.06	2.18	2.88	Oxidized	Fresh	Ore		Waste		1.89	2.14	1.7
			2.52	2.7	Oxidized	Fresh	Oxidized	Fresh			
					2.57	2.78	2.49	2.76			

Source: OceanaGold

Horseshoe Sample Database

Previous owners drilled the majority of the holes over the entire area of mineralization between 1981 and 2015. OceanaGold have continued with focused diamond core drilling at Horseshoe since 2015. 90 drillholes for 31,873m were used within the Horseshoe resource area. Of these 74 drillholes intersected the 1 g/t grade shell, the remainder were outside the volume.

Horseshoe Compositing and Top Capping

Compositing was completed in Vulcan software to 3-m downhole lengths with no breaks at lithologic contacts. The 3 m length was chosen to reflect the low degree of mining selectivity and the absence of any visual features that coincide with the 1 g/t cu-off. It also reduced noise in the data which was resulting in irregular implicit shell geometries and smoothed assay values across two 1.5 samples.

Table 14-9 summarizes the statistics of 3 m composites within the 1 g/t Au indicator shell. Sample localities without gold assays were assigned 0.0 grades unless belonging to drillholes with pending assays results.


Table 14-9 Basic Statistics for 3 m Composites Within 1 g/t Au Indicator Shell

	Sample Stats
	Au
Count	1,194
Min	0.005
Max	149
Mean	4.63
CV	2.13

Source: OceanaGold

Statistical analysis of the original drillhole sample data has resulted in a capping value of 100 g/t for the composites used in the estimation. The results of the cumulative distribution plot are presented in Figure 14-7.

Compositing was completed in Vulcan software to 3-m downhole lengths with no breaks at lithologic contacts. The 3 m length was chosen to reflect the low degree of mining selectivity and the absence of any visual features that coincide with the 1 g/t cu-off. It also reduced noise in the data which was resulting in irregular implicit shell geometries and smoothed assay values across two 1.5 samples.

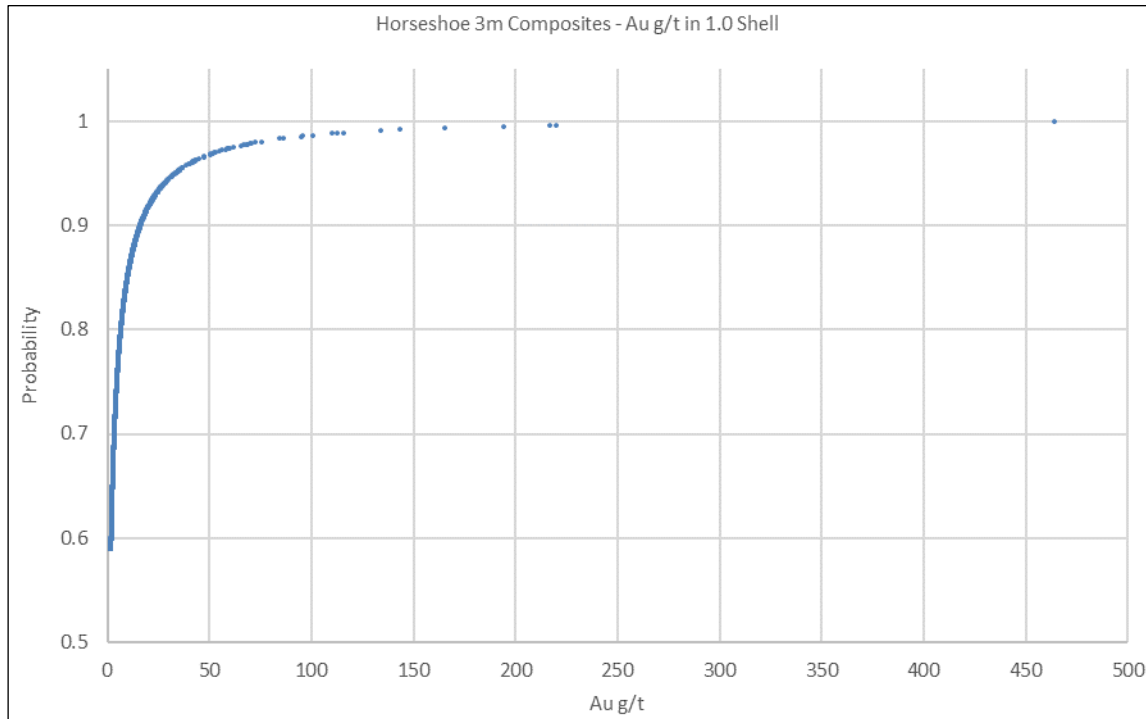

Source: OceanaGold

Figure 14-7: Log Normal Cumulative Distribution Plot of Gold Assays Above 2 g/t

Horseshoe Block Model

In July 2019, an 030-rotated local grid was created for Horseshoe. This rotated grid facilitated Mine Design due to alignment of the primary 060° mineralization direction with the long axis. Details of the rotation, and block model limits of the OceanaGold resource model are listed below. The block model coordinates are referenced to a rotation about the UTM NAD83 coordinate system and are based on a compromise between the average drillhole spacing, a typical underground stope selective mining unit and the variability of the mineralization.

The HUG local grid is based on a 30° clockwise rotation around 3,824,000 m N and 541,000 m E, with a 1,000 m adjustment to elevations as shown in Table 14-10. Elevations were increased by 1000 meters relative to sea level to remove negative values. The origin, limits and block sizes are listed in Table 14-11.

Table 14-10: HUG Grid Transformation Details

	Haile Surface Grid			Horseshoe UG Local Grid		
	Easting	Northing	RL	Easting	Northing	RL
Origin	541,000	3,824,000	0	0	0	1,000
Point 1	543,431	3,826,789	0	3,500	1,200	1,000
Point 2	542,732	3,825,000	0	2,000	0	1,000

Source: OceanaGold

Table 14-11: Block Model Dimensions and Origin

Variable	X	Y	Z
Minimum	3,300	900	620
Maximum	3,920	1,600	1,200
Block Size (Parent)	10	10	10
Sub-block size	5	5	5
No. of Blocks (Parent)	62	70	58

Source: OceanaGold

Horseshoe Estimation

Gold estimation was constrained within implicitly modelled grade shells, which were implemented as hard boundaries. The shells were generated in Leapfrog® software at a 1 g/t Au threshold guided by interpreted trend planes of mineralization. The trend planes were developed by digitizing section profiles of gold continuity which were then triangulated into 3D planes of gold continuity. The upper zone of mineralization utilized two trend planes which essentially represent the hanging wall and footwall of mineralization. The lower zone utilized two additional trend planes.

As described above, the gold mineralization is hosted in two domains each with a unique orientation. For each zone, the trend planes used to guide the grade shells construction were translated outward to capture all model blocks enclosed by the grades shell. These translated planes were then used to guide a dynamic search orientation utilized in the ordinary kriging gold grade estimation.

The grade estimations utilize a two-pass sample search strategy with each pass searching longer distances than the previous. The search distances and variogram parameters are listed in Table 14-12 and Table 14-13, respectively. For all estimations, the following criteria were used:

- Dynamic search orientation essentially parallel to the plane of gold continuity for each zone
- Minimum of two composites and maximum of twelve composites to estimate grade
- Sample length weighting to account for any short composites located at the ends of drillholes
- Composites from a minimum of two drillholes
- Composites from a minimum of two octants

Table 14-12: Au Grade Estimation Search Distances

Estimation Domain	Estimation Pass	Search Range (m) (X, Y, Z)
Upper	1	60,20,10
	2	300,100,50
Lower	1	60,60,60
	2	210,210,210

Source: OceanaGold

Table 14-13: Ordinary Kriging Parameters


Estimation Domain	Variogram Structure	Nugget	Sill Differential	Rotations (Vulcan, X, Y, Z)	Ranges (m) (X, Y, Z)
Upper	1 st Spherical	0.3	0.3	20°, 0°, 75°	15,12,9
	2 nd Exponential		0.7	20°, 0°, 75°	65,30,15
Lower	1 st Spherical	0.3	0.42	Isotropic	12,12,12
	2 nd Exponential		0.32		105,105,105

Source: OceanaGold

Horseshoe Model Validation

Several techniques were used to evaluate the validity of the block model. All new drilling and lithological mapping data were visually validated. QA/QC was performed on drilling data as per database procedures, and visual validation of lithological logging was performed on new drillholes. A visual review of all generated wireframes, including implicitly modelled mineralization wireframes, was performed, to compare with previous versions and to drillhole lithological logging. The methodology used for the resource modelling was reviewed, to ensure industry standard processes and assumptions were used. A review of all macros used in the estimation process was performed, to ensure all appropriate files were used, and correct naming conventions were followed. Model estimation parameters were reviewed to evaluate the performance of the model with respect to supporting data. This included the number of composites used, number of drillholes used, average distance to samples used, and the number of blocks estimated in each pass. Comparisons were made to the previous 2019 resource model (HUG19), in terms of grade, tonnages and contained metal.


Figure 14-8 compares estimates and reveals very little change.

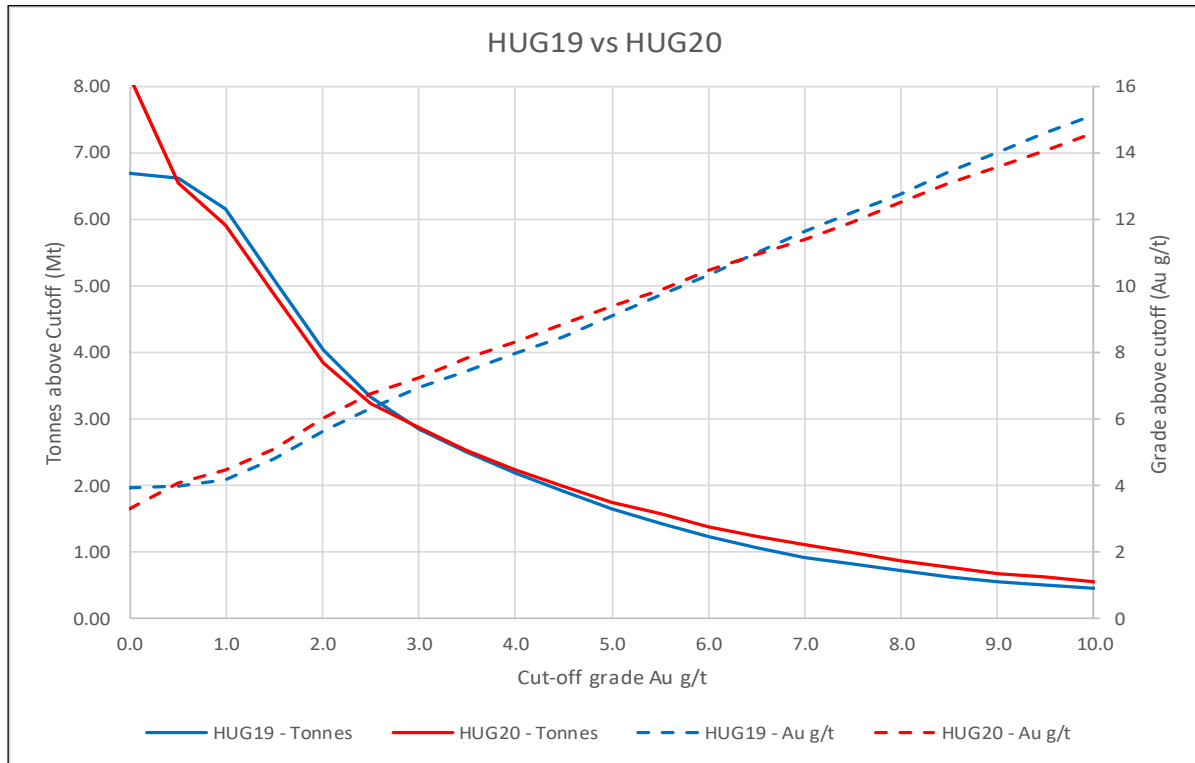

Source: OceanaGold

Figure 14-8: Global Grade Tonnage Comparison between 2019 and 2020 Models


Swath plots were used to compare the estimation with underlying composite grades for each domain. Figure 14-9 shows an acceptable correlation between the composites and the block estimation grade for the Upper Domain. The deterioration at 3650 m E is related to the relatively low number of composites at that Easting.

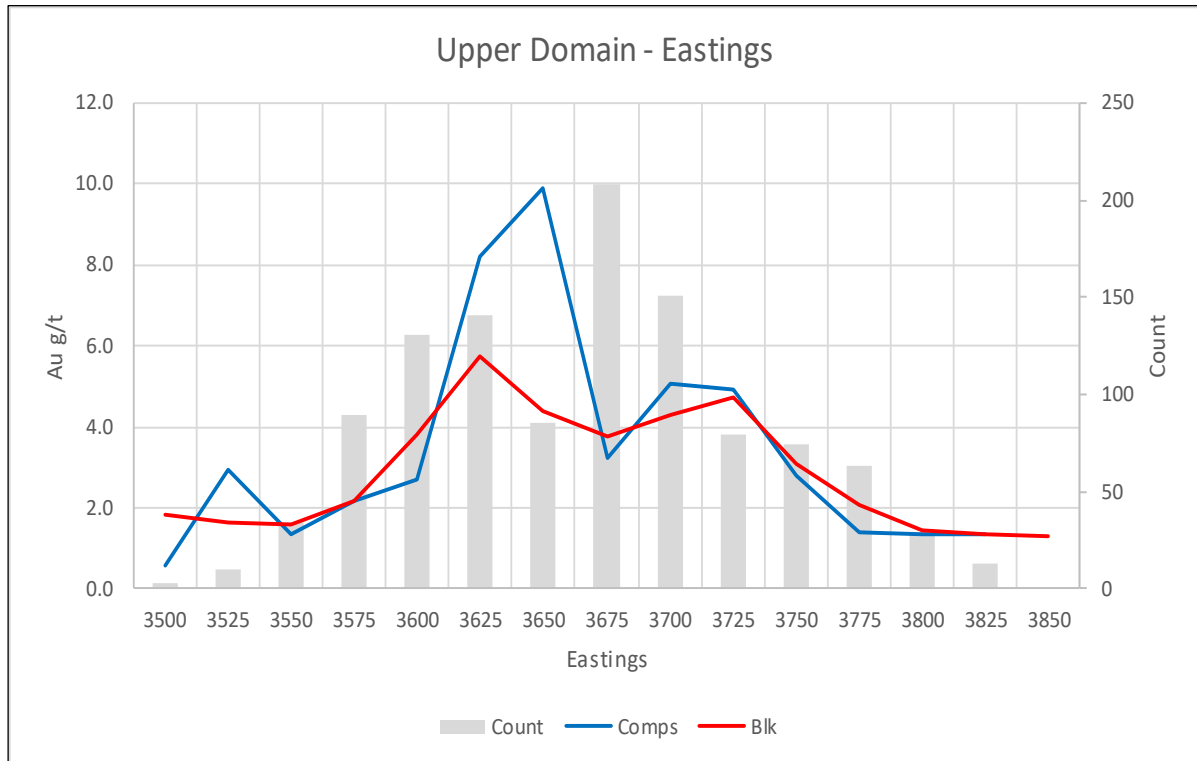

Source: OceanaGold

Figure 14-9: Upper Domain Easting Swath Plot


Figure 14-10 shows the Lower Domain and shows an acceptable correlation between the composites and the block estimation grades. The last validation involved a visual validation of the final block model to both domain limits and composite grade comparison.

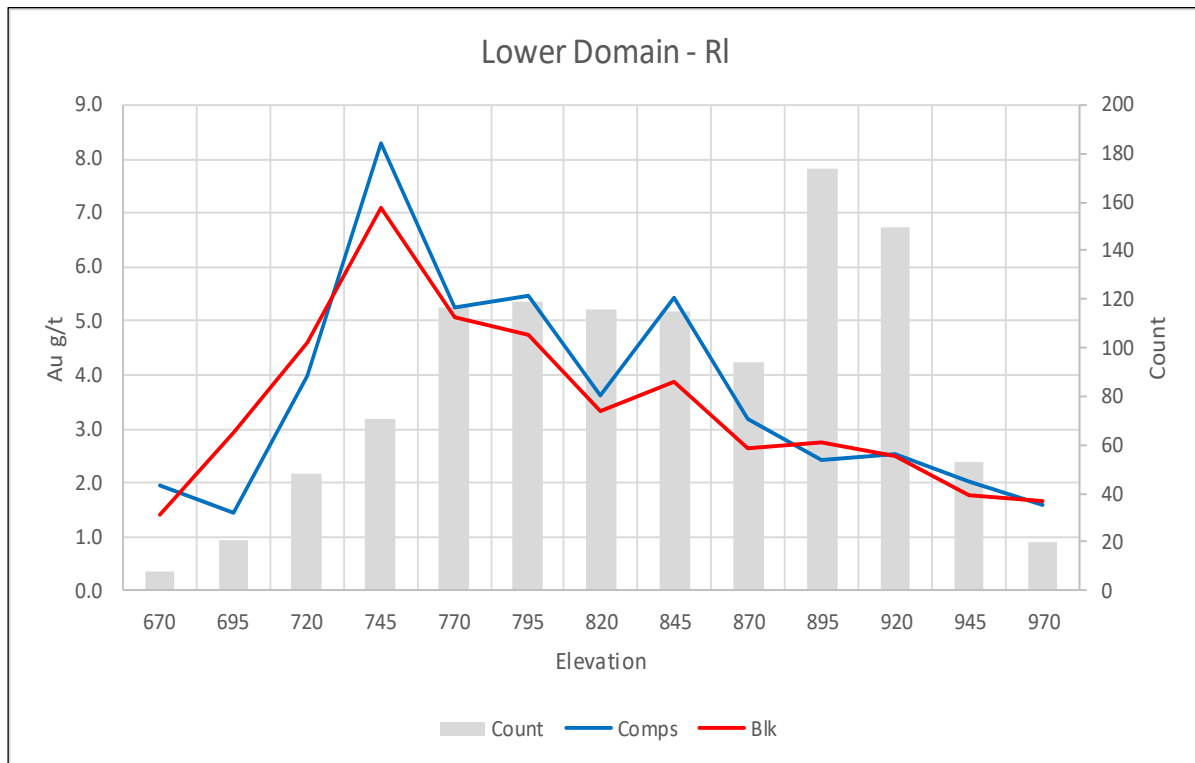

Source: OceanaGold

Figure 14-10: Lower Domain RI Swath Plot

Figure 14-11 and Figure 14-12 show representative cross sections of the gold estimation results.

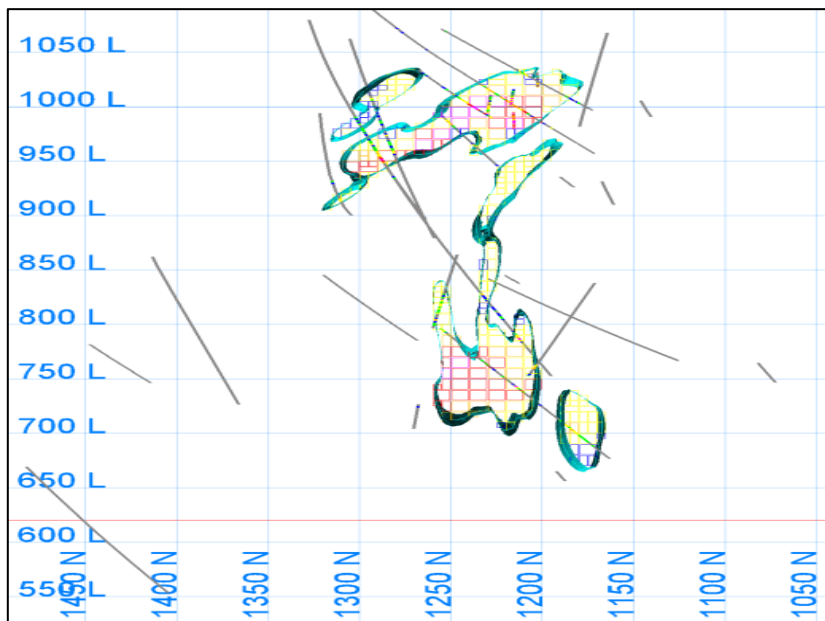

Source: OceanaGold


Figure 14-11: Representative Cross Section with Estimated Au Grades (Viewing E90°)

Based on the results of the various model validations, the OK estimate was chosen as the final Mineral Resource estimation. All resource reporting tables are based on this estimation.

Horseshoe Resource Classification


Mineral Resources are classified as Indicated and Inferred in accordance with CIM guidelines. There are no Measured Resources. Classification of the Mineral Resources reflects the relative confidence of the grade estimates and the continuity of the mineralization. This classification is based primarily on the sample spacing and geological complexity. No single factor controls the Mineral Resource classification, rather each factor influences the end result.

A wireframe solid was constructed around the areas where the majority of the blocks were estimated in the first pass of the estimation, Figure 14-12. These wireframe solids were used to assign the Indicated Mineral Resource classification. All blocks outside of the Indicated wireframes were classified as Inferred Mineral Resources. No resource was estimated outside of the 1.0 g/t implicit grade shell. Figure 14-13 shows a representative cross section of the final resource classification.

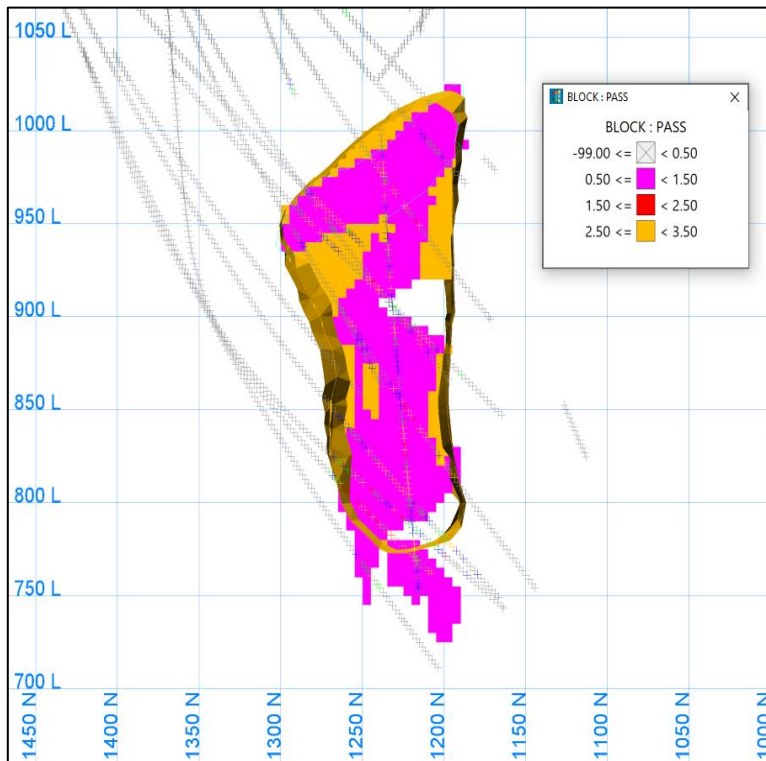

Source: OceanaGold

Figure 14-12: Representative Cross Section Showing Indicated Wireframe around Pass 1 Estimated Blocks (Viewing N90°E)

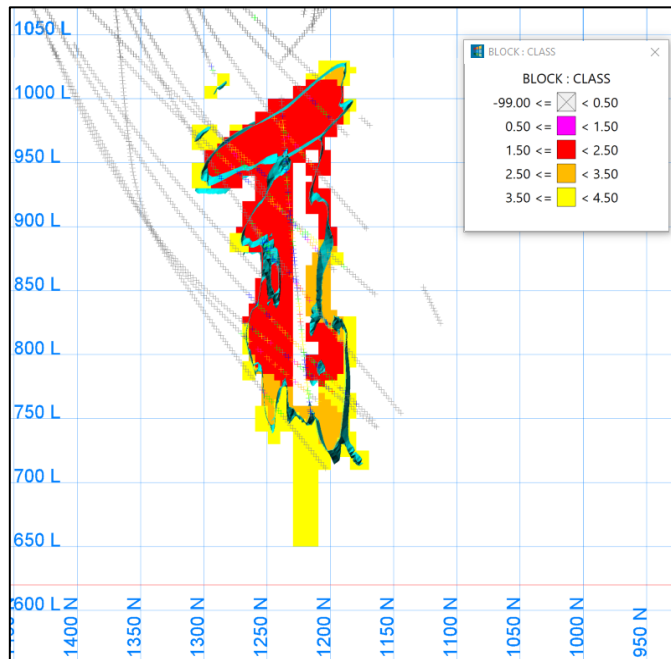

Source: OceanaGold

Figure 14-13: Representative Cross Section Showing Resource Classification (Viewing N90°E)

Horseshoe Mineral Resource Statement

The Horseshoe Mineral Resource statement is based on the OK model as presented in Table 14-14. A CoG of 1.26 g/t Au has been applied without constraint within any conceptual design. The CoG assumes underground mining methods and is based on a mining cost of US\$45/t, milling cost of US\$9.69/t, administration cost of US\$3.2/t, a gold price of US\$1,700/oz, and a gold recovery of 88%.

Table 14-14: Horseshoe Underground Mineral Resource Statement as of June 30, 2020

Class	Tonnes (Mt)	Au Grade (g/t)	Contained Au (Moz)
Measured	0.0	0.00	0.00
Indicated	3.3	4.95	0.53
Measured & Indicated	3.3	4.95	0.53
Inferred	2.1	4.4	0.3

Source: OceanaGold

- Cut-off grade 1.26 g/t Au based on a gold price of US\$1,700/oz.
- Spatially constrained by a 1 g/t Au indicator shell.
- Mineral Resources include Mineral Reserves and are reported on an in-situ basis.
- There is no certainty that Mineral Resources that are not Mineral Reserves will be converted to Mineral Reserves.
- All figures are rounded to reflect the relative accuracy and confidence of the estimates and totals may not add correctly.
- The underground Mineral Resources were estimated under the supervision of Jonathan Moore, MAusIMM CP(Geo), a Qualified Person.


Horseshoe Mineral Resource Sensitivity

The Indicated Mineral Resources shown in Table 14-15 are presented at a range of CoGs, subdivided. Graphical representations of the grade and tonnage sensitivities of the Indicated resources are presented in Figure 14-14. Resources are not confined within any conceptual stope design.

Table 14-15: Mineral Resource Sensitivity

Cut-off	Indicated		
	Au (g/t)	Tonnes (Mt)	Au (koz)
1	4.68	3.58	538
1.26	4.95	3.32	529
1.5	5.28	3.04	516
1.75	5.69	2.73	500
2	6.08	2.48	484

Source: OceanaGold

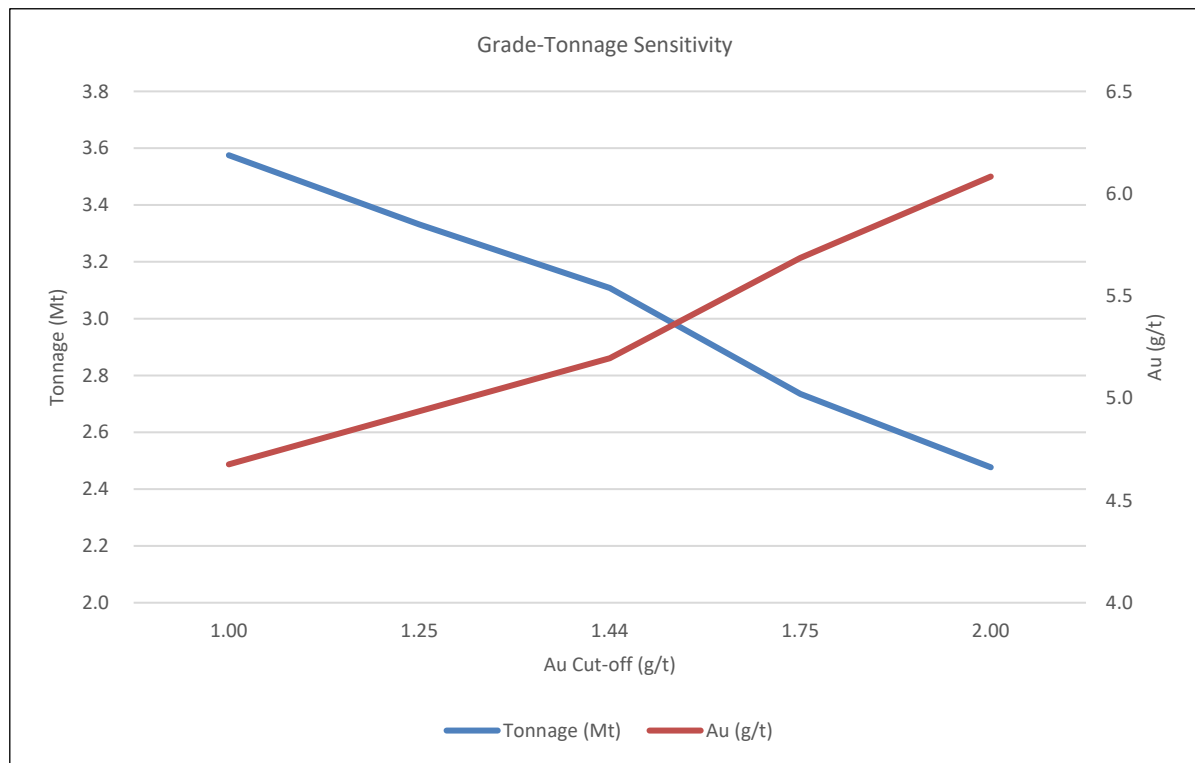

Source: OceanaGold

Figure 14-14 Sensitivity of Indicated Resource Tonnes and Grade to Cut-off

14.2.2 Palomino Resource Estimate

The Palomino deposit is located approximately 1 km southwest of the Horseshoe deposit, and 400 m below surface. Palomino is a medium grade (2-6 g/t Au) underground gold deposit, located at 300 m to 500 m below surface. The deposit dimensions are approximately 300 m long by 50-100 m thick by 100-150 m wide. Lozenge-shaped mineralized zones strike ENE, dip northwest and plunge gently northeast. Diamond drillhole spacing ranges from 40 to 70 metres. The style of mineralization is similar to the Horseshoe deposit. Fine-grained gold is hosted in pyritic and silicified siltstone and intrusives along a steeply SE-dipping, ENE-striking contact with barren dacite flows. Mineralization is truncated by several NNW-striking, sub-vertical, 1-25 meter-thick diabase dikes. The Palomino resource estimation is based on the current drillhole database, interpreted lithologies, geologic controls and current topographic data. The resource estimation is supported by drilling and sampling current to November 11, 2019.

Gold estimation was constrained within implicitly modelled grade shells using Leapfrog® software, approximating a 1.0 g/t gold indicator. 28 drillholes provide 396 x 3m composites for estimation within the indicator shell. The maximum grade was 31 g/t Au and the coefficient of variation is 1.28. Top capping was not applied.

Ordinary kriging was used with the following criteria:

- The 1 g/t Au indicator shell was implemented as a hard boundary
- Dynamic search orientation essentially parallel to the plane of gold continuity
- Minimum of four composites and maximum of twelve composites to estimate grade
- Sample length weighting to account for any short composites located at the ends of drillholes
- Composites from a minimum of four drillhole
- Composites from a minimum of two octants

Gold grades were estimated into 5 m E x 5 m N x 5 m RI with Vulcan™ modelling software using Ordinary Kriging on 3 m composites. Sub-blocking was not used.

Metasediment/metavolcanic contacts were not used to constrain gold estimation. Post-mineralization dykes were assigned zero grade.

Densities based upon core analyses were assigned by rock type.

Validation included visual cross-sectional and 3D checks of modelled vs sample grades, script reviews and global model vs sample grade comparison (3.24 g/t vs 3.31 g/t respectively).

The results of the validations support a robust estimation.

The Palomino Mineral Resource statement is presented in Table 14-16. The reported resource is constrained within a conceptual stope design based on a gold price of US\$1,700/oz, approximating a 1.37 g/t cut-off. All unclassified material within the conceptual design was assigned zero grade for the purposes of reporting.

The Mineral Resources reported for the Palomino deposit are classified as Inferred Mineral Resources, based primarily on drillhole spacing and geological understanding. All blocks outside of the Inferred wireframes remain unclassified.

The Palomino Mineral Resource statement is based on the Ordinary Kriging (OK) model. resource is constrained within a conceptual stope design using a CoG of 1.37 g/t Au. which assumes underground mining methods and is based on a mining cost of US\$45/t, milling cost of US\$9.69/t, administration cost of US\$3.2/t, based on a gold price of US\$1,700/oz, and a gold recovery of 85%.

Table 14-16: Palomino Underground Mineral Resource Statement as of June 30, 2020

Class	Tonnes (Mt)	Au Grade (g/t)	Contained Au (Moz)
Measured	0.0	0.0	0.0
Indicated	0.0	0.0	0.0
Measured & Indicated	0.0	0.0	0.0
Inferred	6.9	2.7	0.6

Source: OceanaGold

- Cut-off grade 1.37 g/t Au based on a gold price of US\$1,700/oz.
- Mineral Resources are reported on an in-situ basis.
- There is no certainty that Mineral Resources that are not Mineral Reserves will be converted to Mineral Reserves.
- All figures are rounded to reflect the relative accuracy and confidence of the estimates and totals may not add correctly.
- The underground Mineral Resources were estimated under the supervision of Jonathan Moore, MAusIMM CP(Geo), a Qualified Person.

14.3 Open Pit and Underground Combined Mineral Resource Statement

Table 14-17 presents the combined open pit and underground resource statement for Haile.

Table 14-17: Haile Combined Open Pit and Underground Resource Statement June 30, 2020

Type	Class	Tonnes (Mt)	Au Grade (g/t)	Contained Au (Moz)	Ag Grade (g/t)	Contained Ag (Moz)
Open Pit	Measured	3.2	1.35	0.14	2.61	0.27
	Indicated	52.3	1.53	2.57	2.40	4.04
	Measured & Indicated	55.5	1.52	2.71	2.41	4.30
	Inferred	7.6	1.0	0.2	1.32	0.32
Underground	Measured	0.0	0.00	0.00		
	Indicated	3.3	4.95	0.53		
	Measured & Indicated	3.3	4.95	0.53		
	Inferred	9.0	3.1	0.9		
Combined	Measured	3.2	1.35	0.14	2.61	0.27
	Indicated	55.6	1.73	3.10	2.40	4.04
	Measured & Indicated	58.8	1.71	3.24	2.41	4.30
	Inferred	17	2.1	1.1	1.32	0.32

Source: OceanaGold

- Cut-off grades for the open pit, Horseshoe underground and Palomino underground are 0.45 g/t, 1.26 g/t and 1.37 g/t Au respectively, based on a gold price of US\$1,700/oz.
- Open pit resource is reported within a US\$1,700/oz optimized shell. Palomino is constrained within a conceptual stope design and Horseshoe underground is spatially constrained within the 1 g/t Indicator shell.
- Mineral Resources include Mineral Reserves and are reported on an in-situ basis.
- There is no certainty that Mineral Resources that are not Mineral Reserves will be converted to Mineral Reserves.
- All figures are rounded to reflect the relative accuracy and confidence of the estimates and totals may not add correctly.
- The underground Mineral Resources were estimated under the supervision of Jonathan Moore, MAusIMM CP(Geo), a Qualified Person.

The reader is cautioned that Inferred Mineral Resources are considered too speculative geologically to have economic considerations applied to them that would enable them to be categorized as Mineral Reserves. There is no certainty that the Inferred Mineral Resources will be realized or that they will convert to Mineral Reserves.

14.4 Relevant Factors

At this time, there are no unique situations in relation to environmental, socio-economic or other relevant conditions that would put the Haile Mineral Resource at a higher level of risk than any other

developing resource within the United States, or that would materially affect the Mineral Resource estimates.

15 Mineral Reserve Estimate

Separate Mineral Reserve estimates were generated for the open pit and underground mines. A combined Mineral Reserve statement is provided in Section 15.3. The open pit and underground mining areas are located entirely on land owned by HGM. There are no royalties.

The open pit work was completed using the site coordinate system, UTM NAD83. The underground work was completed in a local grid which is based on a 30° clockwise rotation around 3,824,000 mN and 541,000 mE, with a 1,000 m adjustment to elevations. Due to this translation, elevations and coordinates in open pit and underground figures are different. Table 15-1 shows the transformation details.

Table 15-1: Haile Underground Coordinate Transformation Details

	Haile Surface Grid			Horseshoe UG Local Grid		
	Easting	Northing	RL	Easting	Northing	RL
Origin	541,000	3,824,000	0	0	0	1,000
Point 1	543,431	3,826,789	0	3,500	1,200	1,000
Point 2	542,732	3,825,000	0	2,000	0	1,000

Source: OceanaGold

15.1 Open Pit Mineral Reserve Estimate

Open pit LoM plans and resulting open pit Mineral Reserves are determined based on a gold price of US\$1,500/oz Au. Reserves stated in this report are dated effective as of June 30, 2020.

The ore material is converted from Mineral Resource to Mineral Reserve based primarily on positive cash flow pit optimization results, pit design and geological classification of Measured and Indicated resources. The in-situ value is derived from the estimated grade and certain modifying factors.

The open pit reserve consists of several pit areas. Material is truck hauled from the pits to an existing crusher/processing facility. Waste material is categorized, and truck hauled to the appropriate waste rock stockpile location.

15.1.1 Introduction

The geological model was used without modification, as the block size in the model matched the SMU size of 10 m x 10 m x 5 m. This block size is currently considered appropriate for the loading units operating at Haile.

The open pit Ore Reserves are reported within a pit design based on open pit optimization results (Lerch-Grossman algorithm). The optimization included Measured, Indicated and Inferred Mineral Resource categories with a gold price of US\$1,500/oz Au. Subsequent to pit optimization, inferred material (approximately 10% by volume) within the reserve pit was treated as waste and given a zero-gold grade. Whittle optimization parameters were derived by OceanaGold and are shown in Table 15-2.

The overall pit slopes (inter-ramp angle slopes) used for the design are based on operational level geotechnical studies and range from 32° to 45°. This includes a 5° allowance for ramps and geotechnical catch benches.

Table 15-2: Pit Optimization Parameters

Parameter	Unit	Value
Base Mining Cost	US\$/t	1.41
Incremental Mining Cost	US\$/t / 5 m bench	0.01
PAG Rehabilitation Cost	US\$/t PAG waste	0.95
Processing Cost	US\$/t ore	11.00
G&A Cost	US\$/t ore	3.20
Ore Rehandle Cost	US\$/t ore	0.70
TSF Expansion	US \$/t ore	2.44
Gold Recovery	%	$(1-(0.2152 \cdot \text{au grade}^{-0.3696}))+0.025$
Mill Throughput	Mtpa	4.0
Gold Price	US\$/oz	1,500
Gold Refining & Selling Cost	US\$/oz	3.00
Calculated Au Cutoff Grade	US \$/t	0.45
Royalties	%	0.0
Discount Rate	%	5.0

Source: OceanaGold

A 3D mine design, based on the selected Whittle pit, was completed using Vulcan software and is the basis for the open pit reserves.

15.1.2 Conversion Assumptions, Parameters and Methods

The conversion of Mineral Resource to Mineral Reserve entails the evaluation of modifying factors that should be considered in stating a Mineral Reserve. Table 15-3 shows a reserve checklist and associated commentary on the risk factors involved for the Haile Open Pit Reserve statement.

Table 15-3: Haile Open Pit Reserve Checklist

Unit	Data Evaluated	Data Not Evaluated	Not Applicable	Notes
Mining				
Mining Width	X			Average 300 to 400 m
Open Pit and/or Underground	X			Open pit and underground
Density and Bulk handling	X			Density and swell considered
Dilution	X			SMU 10 m x 10 m x 5 m
Mine Recovery	X			Full mine recovery assumed
Waste Rock	X			NAG/PAG waste dumps
Grade Control	X			Operating mine – blast chips
Processing	X			
Representative Sample	X			Previous feasibility study and operating mine
Product Recoveries	X			Feasibility study - operating
Hardness (Grindability)	X			Feasibility study - operating
Bulk Density	X			Feasibility study - operating
Deleterious Elements	X			Feasibility study - operating
Process Selection	X			Feasibility study - operating
Geotechnical/Hydrological	X			
Slope Stability (Open Pit)	X			Majority FoS greater than 1.3. Small foliation/orientation risk in localized areas.
Water Balance	X			Full site water balance
Area Hydrology	X			Hydrology considered
Seismic Risk	X			Low
Environmental				
Baseline Studies	X			Operating Mine
Tailing Management	X			Operating Mine

Unit	Data Evaluated	Data Not Evaluated	Not Applicable	Notes
Waste Rock Management	X			Operating Mine – NAG/PAG plan
ARD Issues	X			Lined waste facilities
Closure and Reclamation Plan		X		
Permitting Schedule	X			Ongoing – reasonable expectation of success
Location and Infrastructure				
Climate	X			High rainfall events
Supply Logistics	X			Operating Mine
Power Source(S)	X			Operating Mine
Existing Infrastructure	X			Operating Mine
Labor Supply and Skill Level	X			Operating Mine – Training ongoing
Marketing Elements or Factors				
Product Specification and Demand	X			Gold Market
Off-site Treatment Terms and Costs	X			Favorable refining conditions
Transportation Costs	X			Low
Legal Elements or Factors		X		
Security of Tenure	X			Operating Mine
Ownership Rights and Interests	X			Operating Mine
Environmental Liability	X			ARD potential
Political Risk (e.g., land claims, sovereign risk)	X			Low political risk - USA
Negotiated Fiscal Regime		X		
General Costs and Revenue Elements or Factors				
General and Administrative Costs	X			Operating Mine
Commodity Price Forecasts	X			US\$1,500/oz Au
Foreign Exchange Forecasts			X	
Inflation	X			Small
Royalty Commitments	X			No royalty
Taxes	X			Operating Mine
Corporative Investment Criteria		X		
Social Issues				
Sustainable Development Strategy	X			Environmental Impact Statement (EIS)
Impact Assessment and Mitigation	X			EIS
Negotiated Cost/Benefit Agreement	X			EIS
Cultural and Social Influences	X			EIS

Source: SRK, 2020

15.1.3 Reserve Estimate

Mineral Reserves were classified using the 2014 CIM Definition standards. Measured Mineral Resources were converted to Proven Mineral Reserves, and Indicated Mineral Resources were converted to Probable Mineral Reserves by applying the appropriate modifying factors, as described herein, to potential mining pit shapes created during the mine design process.

The open pit mine design process results in open pit mining reserves of 49.4 Mt with an average grade of 1.57 g/t. The Mineral Reserve statement, as of June 30, 2020 for the Haile Open Pit is presented in Table 15-4.

Table 15-4: Haile Open Pit Mineral Reserves Estimate as of June 30, 2020

Category	Tonnes (Mt)	Au (g/t)	Ag (g/t)	Au Contained (Moz)	Ag Contained (Moz)
Proven	3.01	1.37	2.54	0.13	0.25
Probable*	46.4	1.58	2.35	2.36	3.50
Proven + Probable	49.4	1.57	2.36	2.49	3.75

* Includes 722kt of stockpile material grading 1.23g/t Au and 1.78g/t Ag

Source: SRK

- Reserves are based on a US\$1,500/oz Au gold price.
- Open pit reserves are stated using a 0.45 g/t cut-off and assume full mine recovery.
- Metallurgical recoveries are based on a recovery curve $(1 - (0.2152 \cdot \text{Au grade}^{-0.3696})) + 0.025$ that equate to an overall recovery of 82%.
- Reserves are converted from resources through the process of pit optimization, pit design, production schedule and supported by a positive cash flow model.
- Reserves are inclusive of Mineral Resources. All figures are rounded to reflect the relative accuracy of the estimates. Totals may not sum due to rounding.
- 5% dilution at zero grade and 98% mining recovery was applied for 2020 and 2021 mine schedule. Remaining years open pit reserves are not diluted further to dilution inherent to the resource model and assume selective mining unit of 10 m x 10 m x 5 m.
- The open pit Mineral Reserves were estimated by Fernando Rodrigues, BS Mining, MBA, MMSAQP #01405, MAusIMM #304726 of SRK, a Qualified Person.


Relevant Factors

SRK knows of no existing environmental, permitting, legal, socio-economic, marketing, political, or other factors that might materially affect the Mineral Reserve estimate.

15.2 Underground Mineral Reserve Estimate

15.2.1 Introduction

Mineral Resources extend below and outside of the existing open pit mine. A portion of these Mineral Resources will not be mined by the ultimate pit shell that is described in this feasibility study and therefore have been evaluated for potential underground mining. The Mineral Resource area evaluated for underground mining is referred to as “Horseshoe”. Horseshoe is located to the northeast of the Snake Pit, as shown in Figure 15-1. Note that the underground reserve does not consider the Palomino underground resource at this time.

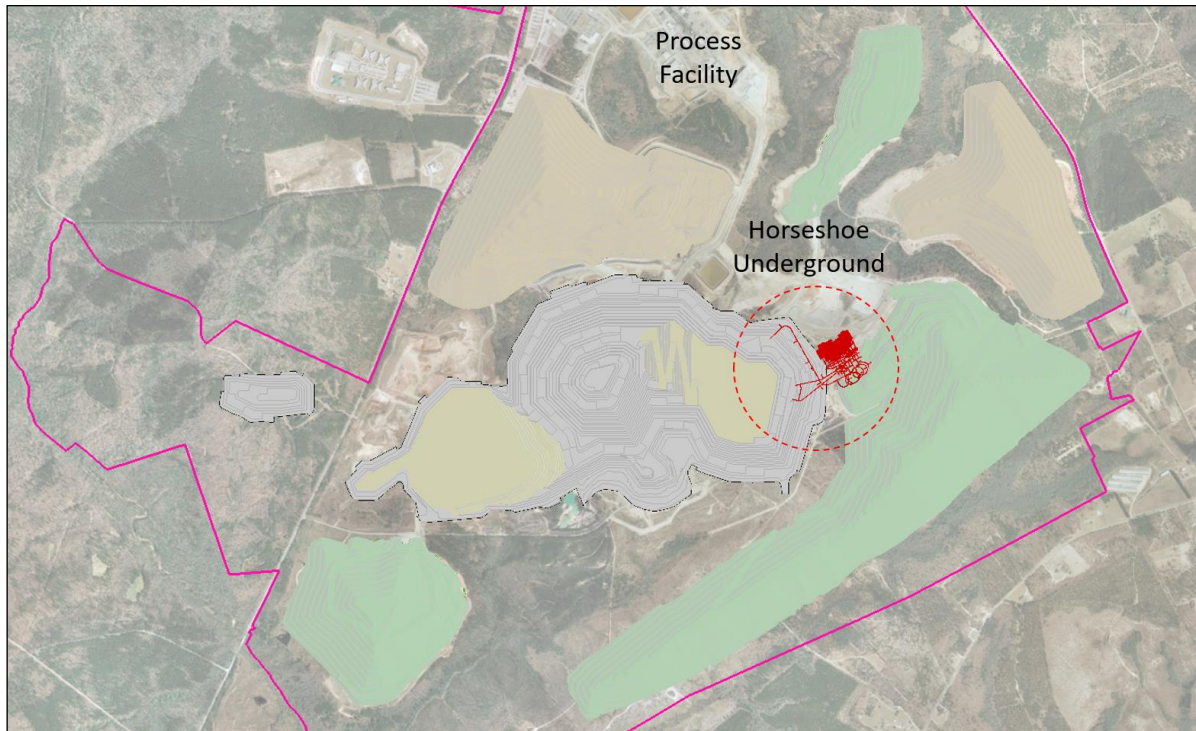

Source: OceanaGold


Figure 15-1: General Site Layout and Location of the UG Reserve Area

15.2.2 Conversion Assumptions, Parameters and Methods

Measured and Indicated Mineral Resources were converted to Proven and Probable Mineral Reserves by applying the appropriate modifying factors, as described herein, to potential mining block shapes created during the mine design process.

Based on the orientation, depth, and geotechnical characteristics of the mineralization, a transverse sublevel open stoping method (longhole) with ramp access is used. The stopes will be 20 m wide and stope length will vary based on mineralization grade and geotechnical considerations. A spacing of 25 m between levels is used. Cemented rock fill (CRF) will be used to backfill the stopes. There will be an opportunity for some non-cemented waste rock to be used in select stopes based on the mining sequence. The CRF will have sufficient strength to allow for mining adjacent to backfilled stopes.

The deposit has been divided into three production areas as shown in Figure 15-2. Using the local grid, the uppermost block extends from approximately the 930 m elevation to 1,030 m elevation and includes four stoping levels that will be mined bottom up. The mid-block extends from approximately the 850 m elevation to the 930 m elevation and includes three stoping levels that will be mined bottom up. The uppermost level in this block includes mining out of the sill. The lowest block extends from approximately the 780 m elevation to the 930 m elevation. It includes three stoping levels that are also mined bottom up. The uppermost level in this block also includes mining out of the sill. A lower extraction has been used for sill levels.

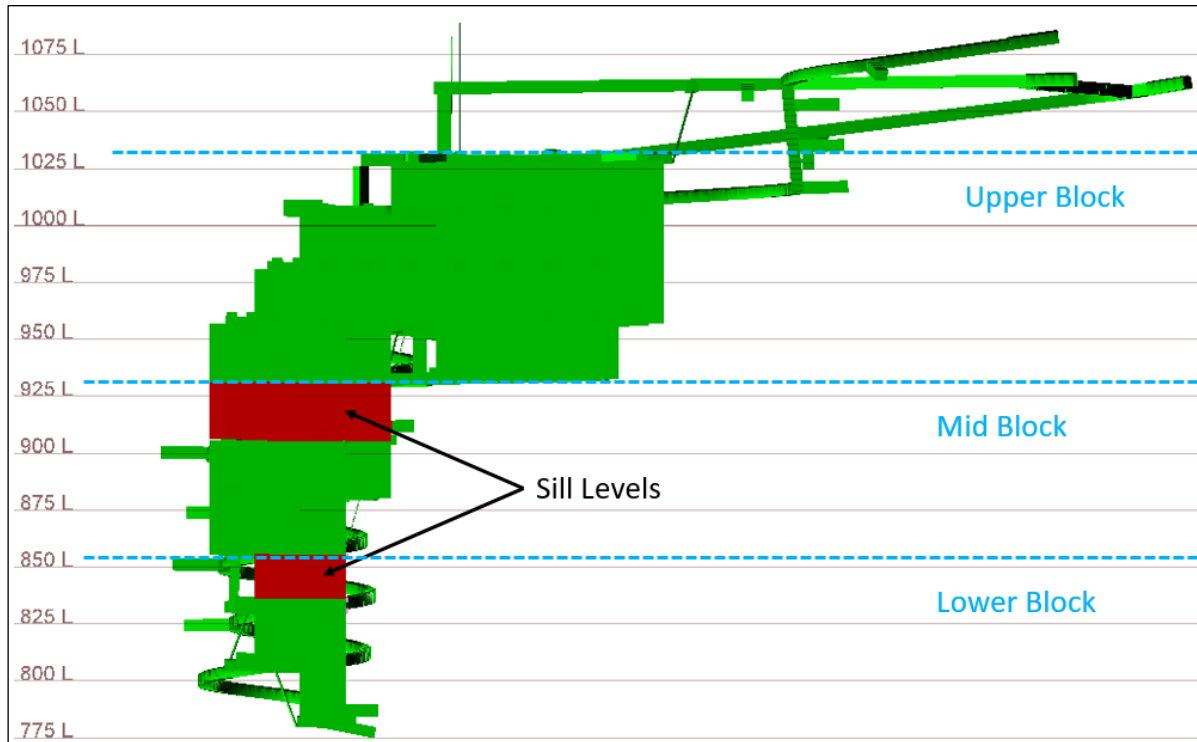

Source: SRK

Figure 15-2: UG Design Sill Levels (local grid)

A detailed design was completed including re-mucks, passing bays, etc.

All Mineral Reserve tonnages are expressed as "dry" tonnes (i.e., no moisture) and are based on the density values stored in the block model. Inferred Mineral Resources are not included in the mine plan. Mining dilution and recovery have been applied to the reserves using the methodologies described in the following sections.

Dilution

The mining dilution estimate is based on the equivalent linear overbreak/slough methodology (ELOS; Clark, 1997). ELOS is an empirical design method that is used to estimate the amount of overbreak/slough that will occur in an underground opening based on rock quality and the hydraulic radius of the opening.

Dilution estimates were applied differently for primary and secondary stopes as follows:

- For a typical primary stope, the sources of dilution are in the floor (CRF backfill) and in the front endwall of the stope (CRF backfill). Dilution from the sidewalls and the back endwall is not included, as this material is typically ore and is already accounted for within the volumes of adjacent secondary stopes.
- For a typical secondary stope, the sources of dilution are in the floor (CRF backfill), in the front endwall of the stope (CRF backfill), and in the sidewalls of the stope (CRF backfill).

- For the sill pillar primary and secondary stopes, an additional source of dilution is applied from the crown (CRF backfill). To account for more difficult expected mining conditions in the sill stopes, an additional dilution allowance has been included.

ELOS assumptions are shown in Table 15-5.

Table 15-5: Dilution ELOS Assumptions

Type	ELOS Value (m)
Sidewalls (backfill)	0.40
Endwall (backfill)	0.15
Floor (backfill)	0.10
Crown (backfill)	0.50

Source: OceanaGold

The rock sidewall/endwall dilution material will contain low-grade mineralization. However, a conservative approach was adopted by applying zero grade to all rock dilution. Zero grade was applied to CRF backfill dilution.

The ELOS and additional dilution factor for the sill stopes results in the dilution factors shown in Table 15-6. These factors were conservatively applied uniformly across each stope type.

Table 15-6: Mine Design Dilution Factors

Stope Type	Dilution Applied (at Zero Grade)
Primary Stopes	2%
Secondary Stopes	6%
Sill Pillar Primary Stopes	6%
Sill Pillar Secondary Stopes	10%

Source: OceanaGold

For all horizontal development, dilution of 10% was applied at zero grade.

Recovery

A stope recovery factor of 94% was used. For sill levels, a 75% recovery factor was used to account for material left in situ in the sill. The following items were used to calculate this factor:

- Material loss into backfill (floor) of 0.15 m
- Material loss to side and endwalls (under blast) of 0.15 m
- Material loss from leaving wing-shaped pillars in stope crowns (for stope stability and to enable tight-filling of stopes)
- Material loss to mucking along the sides and in blind corners of the stopes
- Additional loss factor due to rockfalls, misdirected loads, and other geotechnical reasons

A development recovery factor of 100% was used for all horizontal development. Recoveries of the temporary sill levels have been reduced by 25%, to reflect room and pillar mining of the sill pillars.

15.2.3 Reserve Estimate

Mineral Reserves were classified using the 2014 CIM Definition standards. Indicated Mineral Resources were converted to Probable Mineral Reserves by applying the appropriate modifying factors, as described herein, to potential mining shapes created during the mine design process.

The underground mine design process resulted in underground mining reserves of 3.4 Mt (diluted) with an average grade of 3.78 g/t Au. The Mineral Reserve statement, as of June 30, 2020, for the Haile Horseshoe Underground is presented in Table 15-7.

Table 15-7: Haile Horseshoe Underground Reserves Estimate as of June 30, 2020

Category	Tonnes (Mt)	Au (g/t)	Ag (g/t)	Au Contained (Moz)	Ag Contained (Moz)
Proven	-	-	-	-	-
Probable	3.42	3.78	-	0.42	-
Proven + Probable	3.42	3.78	-	0.42	-

Source: SRK

- Reserves are based on a gold price of US\$ 1,500/oz. Metallurgical recoveries are based on a recovery $(1 - (0.2152 \cdot \text{Au grade}^{-0.3696})) + 0.025$ that equates to an overall recovery of 88%.
- Underground reserves are stated using a 1.44 g/t Au cut-off. The reserve estimate is based on a mine design using an elevated cut-off grade of 1.67 Au g/t, with adjacent lower grade stopes included in the design. Incremental material is included in the reserves based on an incremental stope cut-off grade of 1.29 g/t Au and an incremental development cut-off grade of 0.38 g/t Au.
- Mining recovery ranges from 94% to 100% depending on activity type. Sill levels use a 75% recovery. Mining dilution is applied using zero grade. The dilution ranges from 2% to 10% depending on activity type.
- Reserves are inclusive of Mineral Resources. All figures are rounded to reflect the relative accuracy of the estimates. Totals may not sum due to rounding.
- Mineral Reserves have been stated on the basis of a mine design, mine plan, and cash-flow model.
- The Mineral Reserves were estimated by Joanna Poeck, BEng Mining, SME-RM, MMSAQP #01387QP of SRK, a Qualified Person.

Relevant Factors

SRK knows of no existing environmental, permitting, legal, socio-economic, marketing, political, or other factors which could materially affect the underground Mineral Reserve estimate.

15.3 Open Pit and Underground Combined Reserves Statement

Table 15-8 presents the combined open pit and underground Mineral Reserves statement for Haile.

Table 15-8: Reserve Statement for OceanaGold's Haile Gold Mine as of June 30, 2020

Type	Category	Tonnes (Mt)	Au Grade (g/t)	Au Grade (g/t)	Au Contained (Moz)	Ag Contained (Moz)
OP	Proven	3.01	1.37	2.54	0.13	0.25
	Probable*	46.4	1.58	2.35	2.36	3.50
	<i>Proven + Probable</i>	49.4	1.57	2.36	2.49	3.75
UG	Proven		-	-		-
	Probable	3.42	3.78	-	0.42	-
	<i>Proven + Probable</i>	3.42	3.78	-	0.42	-
OP + UG	Proven	3.01	1.37	2.54	0.13	0.25
	Probable	49.8	1.73	2.19	2.77	3.50
	Proven + Probable	52.8	1.71	2.21	2.91	3.75

*Includes 722kt of stockpile material grading 1.23g/t Au and 1.78g/t Ag

Source: SRK

- Mineral Reserves are based on a gold price of US\$ 1,500/oz. Metallurgical recoveries are based on a recovery curve $(1 - (0.2152 \cdot \text{Au grade}^{-0.3696})) + 0.025$ that equates to an overall recovery of 82% for the open pit material and 88% for the underground material.
- Open pit Mineral Reserves are stated using a 0.45 g/t Au cut-off and assume full mine recovery. 5% dilution at zero grade and 98% mining recovery was applied for 2020 and 2021 mine schedule. Remaining years open pit reserves are not diluted further to dilution inherent to the resource model and assume selective mining unit of 10 m x 10 m x 5 m.
- Open pit reserves are converted from resources through the process of pit optimization, pit design, production schedule and supported by a positive cash flow model.
- Underground reserves are stated using a 1.44 g/t Au cut-off. The reserve estimate is based on a mine design using an elevated cut-off grade of 1.67 Au g/t, with adjacent lower grade stopes included in the design. Incremental material is included in the reserves based on an incremental stope cut-off grade of 1.29 g/t Au and an incremental development cut-off grade of 0.38 g/t Au. Mining recovery ranges from 94% to 100% depending on activity type. Sill levels use a 75% recovery. Mining dilution is applied using zero grade. The dilution ranges from 2% to 10% depending on activity type.
- Mineral Reserves are inclusive of Mineral Resources. All figures are rounded to reflect the relative accuracy of the estimates. Totals may not sum due to rounding.
- Mineral Reserves have been stated on the basis of a mine design, mine plan, and cash-flow model.
- The open pit Mineral Reserves were estimated by Fernando Rodrigues, BS Mining, MBA, MMSAQP #01405, MAusIMM #304726 of SRK, a Qualified Person. The underground Mineral Reserves were estimated by Joanna Poeck, BEng Mining, SME-RM, MMSAQP #01387QP of SRK, a Qualified Person.


16 Mining Methods

Both open pit and underground mining methods will be used at Haile. As such, the following sections describe the open pit and underground mining methods separately. A combined open pit and underground production schedule is provided in Section 16.3.

16.1 Open Pit Mining Methods

SRK worked in conjunction with OceanaGold staff in the mine planning of the Haile open pit operations. OceanaGold was responsible for mine fleet capital and operating cost estimation while SRK was responsible for pit optimization, pit design, phase design, haulage and production scheduling. The mine plans are valid from June 30, 2020 and are based on a surveyed topographical surface of the same date. The optimized mine plan is intended to maximize potential reserves from open pit operations while integrating the Horseshoe underground mine into the Haile LoM plan and reserve.

The primary pit names referenced in the sections to follow are based on historical naming conventions when many of the smaller gold pits did not merge into the large Haile open pit described in this report. As such, phases have been named to replicate the historical pit areas. Figure 16-1 illustrates the pit area names.

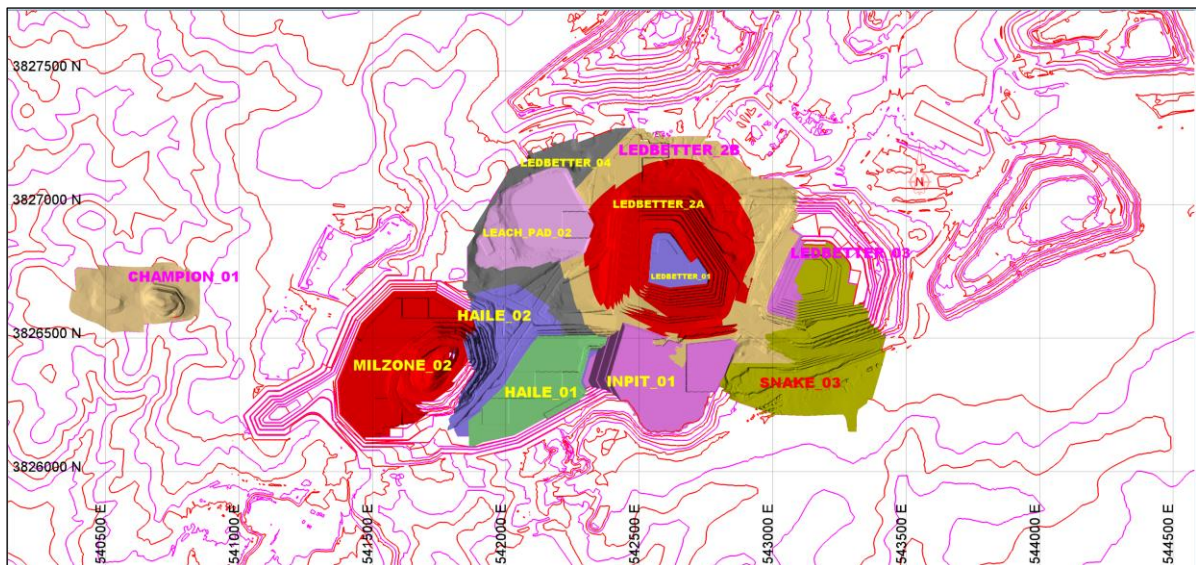

Source: SRK

Figure 16-1: Haile Open Pit Naming Convention

16.1.1 Current or Proposed Mining Methods

Haile is currently being mined using conventional open pit methods and OceanaGold plans to continue with current mining methods.

The material encountered at Haile is a combination of soft (Costal Plains Sands [CPS] and saprolite) and hard (metavolcanics and metasediments) rock units.

CPS is loosely consolidated sand which can be mined without the need for drilling and blasting. Mineralization is not present in CPS thus drilling for the purposes of ore control and waste classification is not necessary.

Saprolite is mined without blasting where possible. Saprolite is sampled for waste classification to meet the requirements in Haile's Overburden Management Plan (OMP).

Drilling and blasting are required in all hard rock. Drilling and blasting are performed on 10 m benches. Multiple bit sizes (115 mm, 171 mm, 200 mm) are used depending on material type and application. Blast hole depth is 10 m plus subdrill; subdrill ranges from 1.4 m to 1.9 m.

The number of samples taken per blasthole is material-type dependent. Blastholes in waste are typically sampled twice on 5m intervals (top half and bottom half). Blastholes in ore are typically sampled three times at 3.3 m sample intervals.

Flitch height is variable. Waste is typically mined on a 10 m flitch. Ore is mined on either 3.3 m or 5 m flitches.

Ore is usually mined with hydraulic excavators, while the majority of waste is mined with hydraulic shovels. Front-end loaders may be used in either application in back-up capacity. The haul truck fleet is a mix of 175 t, 140 t and 90 t payload units.

16.1.2 Parameters Relevant to Mine or Pit Designs and Plans

Geotechnical

The Interramp Slope Angle (ISA) recommendations presented in Table 16-1 through Table 16-5 are based on a slope stability study performed by Call & Nicholas, Inc. for Haile Gold Mine. The design criteria for the ISA recommendations are a minimum Factor of Safety (FOS) of 1.20 for overall slopes, an 80% catch bench width reliability for 10-meter high single benches, or a 90% catch bench width reliability for 20 m high double benches. Catch bench scale structural evaluations were performed using CNI's probabilistic bench-scale analytical method (backbreak) while the FOS for overall slopes were based on two-dimensional and three-dimensional limit equilibrium analyses. The ISA recommendations are the highest achievable angles that meet all design criteria.

Data used for this study included the following:

- 3D geology block model based on drilling and pit mapping (developed by HGM)
- 3D geotechnical rock type (GTRCK) block model developed by CNI
- RQD Data from 632 drillholes
- 3D RQD block model developed by CNI
- Structure data from 52 cells mapped within the Mill Zone pit between the 70 and 125 mine levels
- Structure data from 11 televiewer drillholes
- Structure data from eight oriented core holes
- A total of 20 small scale direct shear test performed on four different rock types
- 22 disc tension test performed on two different rock types
- 20 uniaxial compression tests performed on three different rock types
- 2017 pit slope study performed by BGC Engineering Inc. (BGC)

- An interpreted 3D phreatic surface (weathered Water Levels_EOM_Feb2018_linear.dxf) for the project area by HGM

The GTRCK block model consists of twelve geomechanical groups, based on geology, RQD, and material properties:

- Coastal Plain Sands (CPS)
- Sericite
- Saprolite (SAP)
- Metasediments
 - $RQD \leq 30\%$
 - $30\% < RQD \leq 60\%$
 - $60\% < RQD$
- Metavolcanics
 - $RQD \leq 30\%$
 - $30\% < RQD \leq 60\%$
 - $60\% < RQD$
- Diabase dikes
 - $RQD \leq 30\%$
 - $30\% < RQD \leq 60\%$
 - $60\% < RQD$

Material properties used in this analysis were either derived from a combination of laboratory testing, statistical regression, and RQD data, or were previously reported during earlier studies. Without additional laboratory testing available for the CPS and saprolite units, CNI used strength properties reported in the *Haile Gold Mine Optimization Study – Open Pit Slope Designs* report by BGC Engineering Inc. from July 2017. The material properties for the sericite unit (actually, a low plasticity silt), were derived from small scale direct shear test.

Linear rock mass properties were calculated for the metasediment, metavolcanic, and diabase rock types based on three RQD ranges: $RQD \leq 30\%$, $30\% < RQD \leq 60\%$, and $60\% < RQD$. The $RQD \leq 30\%$ unit roughly correlates to the “Weathered” category from earlier studies, while the $30\% < RQD \leq 60\%$ unit represents a transition zone between the “Weathered” and the higher RQD ($60\% <$) “Fresh” material from the previous studies.

The shear strength of a rock mass is weakest along discontinuities. The orientation of discontinuities therefore defines the critical direction of shear strength anisotropy. At Haile, this direction is parallel to foliation and to a lesser extent, parallel to cross joint orientations. Anisotropic rock mass strengths were used for both the metasediment and metavolcanic rock types in the slope stability analysis. The rock mass properties are presented in Table 16-6.

The main geologic structures identified in the project area are:

- Regional northwest-dipping foliation, best developed in the metasedimentary rocks
- Southeast and southwest-dipping joints
- Sub-vertical or steeply dipping joints parallel to the north-northwest-striking diabase dikes
- Regional faults dipping northwest

For the probabilistic backbreak analysis, the property was separated into four geologic domains based on rock strength and structural orientation data. Due to spatial variations in the structure data, the Mill Zone Pit was separated from the other pits. These two spatial domains were each divided into two additional domains based on rock type. Within each of the four geologic domains, twelve design sectors were defined based on wall orientations and locations of ramps. All design sectors in each domain were evaluated for both single and double catch bench performance to identify the optimal bench design parameters that meet the reliability criteria. The backbreak analysis is based on the use of controlled blasting. If controlled blasting is not possible, the ISA design parameters may need to be adjusted.

Two-dimensional limit-equilibrium analyses were performed on 14 critical sections by CNI, six in the Mill Zone pit, four in the Ledbetter pit, three in the Snake pit, and one in the Red Hill pit (sample section shown in Figure 16-2). Rocscience's Slide® limit equilibrium software (LEQ) was utilized to calculate the lowest overall slip surface FOS for each analysis section. CNI also used SVSlope® 3D, a 3D limit equilibrium stability software, to analyze the northwest corner of the Ledbetter Pit (Figure 16-3 and Figure 16-4).

Depressurization of the pit slopes was conservatively estimated by constructing a phreatic surface 10 meters horizontally behind the pit slope face from the pit bottom up to the elevation of the regional phreatic surface. In some areas where the regional water level is high and significant slope heights of saprolite and CPS exist, additional depressurization is needed. The ISA recommendations require depressurizing the saprolite and CPS portions of the pits to 25 m horizontally behind the pit slope for all areas where the saprolite slope height is 50 m or less. Depressurization requirements increase to 40 m behind the pit slopes for saprolite slope heights greater than 50 m and less than 110 m. If any future design options expose saprolite slope heights in excess of 110 m, additional depressurization will be required. Assuming all depressurization is achieved, all sections analyzed meet or exceed the minimum design criteria of $FOS \geq 1.2$.

CNI recommends the following future work as HGM continues to optimize their mine plans:

- Perform overall stability analysis on future mine plans to verify changes in slope geometry, geology, and wall orientations still meet design criteria.
- Additional cell mapping to expand the rock fabric database – this data is required to optimize the bench designs and to determine if areas that do not meet the design reliabilities are caused by structural conditions or by non-optimal blasting and excavation practices.
- Continued geologic mapping is required to identify major fault structures that could impact the Haile Gold Mine design. A geologic model of the major fault structures should be continually updated for the project area. Modifications to the design may be required if adverse fault structures are identified.
- Additional laboratory testing is recommended to further refine the material properties used in stability analyses. A focus should be placed on triaxial compression testing in the diabase, metasediments, and metavolcanics.
- Continued geotechnical drilling is recommended to continue design optimizations. When possible oriented core or televiewer logging data should also be collected.
- Continue auditing constructed benches to determine if the design is being achieved satisfactorily – Lidar scans or aerial drone surveys of the excavated benches can be used to provide the data needed to perform the audit.

- A 3D model of foliation orientations should be developed. The orientation of the foliation will dictate the achievable bench face angle in some areas. A good understanding of the foliation will enable mine planners to minimize the impact of unfavorable orientations.

Table 16-1: ISA Recommendations for Near Surface Materials

Material Type	ISA (°)	Height (m)	BFA (°)	CBW (m)	Maximum Slope Height (m)	Comment
CPS and “Sericite”	30	5	50	4.5	15	
Saprolite - 1	35	5	63	4.6	50	Requires depressurization a minimum of 25 m behind face
Saprolite - 2	32	5	63	5.5	110	Requires depressurization a minimum of 40 m behind face

Source: Call & Nicholas Inc., 2018

Table 16-2. Mill Zone ISA Recommendations for Metasediments and Diabase Dikes

Range of Wall DDR (°)	Metasediments / Diabase Dikes - Bench Design							
	ISA (°)	Height (m)	BFA (°)	CBW (m)	ISA (°)	Height (m)	BFA (°)	CBW (m)
355 - 025	42	10	78	9	20 m Bench Heights not Recommended			
025 - 055	48	10	78	6.9	50	20	78	12.5
055 - 085	48	10	78	6.9	50	20	78	12.5
085 - 115	48	10	78	6.9	50	20	78	12.5
115 - 145	46	10	78	7.5	48*	20	78	13.8
145 - 175	45	10	78	7.9	48*	20	78	13.8
175 - 205	46	10	78	7.5	50	20	78	12.5
205 - 235	48	10	78	6.9	50	20	78	12.5
235 - 265	47	10	78	7.2	50	20	78	12.5
265 - 295	48	10	78	6.9	50	20	78	12.5
295 - 325	40	10	78	9.8	20 m Bench Heights not Recommended			
325 - 355	37	10	78	11.1	20 m Bench Heights not Recommended			

* ISA design controlled by overall slope stability

Source: Call & Nicholas Inc., 2018

Table 16-3: Mill Zone ISA Recommendations for Metavolcanics

Range of Wall DDR (°)	Metavolcanics - Bench Design							
	ISA (°)	Height (m)	BFA (°)	CBW (m)	ISA (°)	Height (m)	BFA (°)	CBW (m)
355 - 025	43	10	78	8.6	20 m Bench Heights not Recommended			
025 - 055	48	10	78	6.9	50	20	78	12.5
055 - 085	48	10	78	6.9	50	20	78	12.5
085 - 115	48	10	78	6.9	50	20	78	12.5
115 - 145	47	10	78	7.2	48*	20	78	13.8
145 - 175	46	10	78	7.5	48*	20	78	13.8
175 - 205	46	10	78	7.5	50	20	78	12.5
205 - 235	48	10	78	6.9	50	20	78	12.5
235 - 265	47	10	78	7.2	50	20	78	12.5
265 - 295	48	10	78	6.9	50	20	78	12.5
295 - 325	40	10	78	9.8	20 m Bench Heights not Recommended			
325 - 355	38	10	78	10.7	20 m Bench Heights not Recommended			

* ISA design controlled by overall slope stability

Source: Call & Nicholas Inc., 2018

Table 16-4: ISA Recommendations for Metasediments and Diabase Dikes – Snake, Haile, Red Hill, and Ledbetter Pits

Range of Wall DDR (°)	Metasediments / Diabase Dikes - Bench Design							
	ISA (°)	Height (m)	BFA (°)	CBW (m)	ISA (°)	Height (m)	BFA (°)	CBW (m)
345 - 015	44	10	78	8.2	20 m Bench Heights not Recommended			
015 - 045	47	10	78	7.2	50	20	78	12.5
045 - 075	47	10	78	7.2	50	20	78	12.5
075 - 105	47	10	78	7.2	50	20	78	12.5
105 - 135	47	10	78	7.2	50	20	78	12.5
135 - 165	47	10	78	7.2	48	20	78	13.8
165 - 195	47	10	78	7.2	50	20	78	12.5
195 - 225	47	10	78	7.2	50	20	78	12.5
225 - 255	47	10	78	7.2	50	20	78	12.5
255 - 285	46	10	78	7.5	50	20	78	12.5
285 - 315	42	10	78	9	20 m Bench Heights not Recommended			
315 - 345	37	10	78	11.1	20 m Bench Heights not Recommended			

Source: Call & Nicholas Inc., 2018

Table 16-5: ISA Recommendations for Metavolcanics – Snake, Haile, Red Hill, and Ledbetter Pits


Range of Wall DDR (°)	Metavolcanics - Bench Design							
	ISA (°)	Height (m)	BFA (°)	CBW (m)	ISA (°)	Height (m)	BFA (°)	CBW (m)
345 - 015	45	10	78	7.9	20 m Bench Heights not Recommended			
015 - 045	47	10	78	7.2	50	20	78	12.5
045 - 075	47	10	78	7.2	50	20	78	12.5
075 - 105	47	10	78	7.2	50	20	78	12.5
105 - 135	47	10	78	7.2	50	20	78	12.5
135 - 165	47	10	78	7.2	48	20	78	13.8
165 - 195	47	10	78	7.2	50	20	78	12.5
195 - 225	47	10	78	7.2	50	20	78	12.5
225 - 255	47	10	78	7.2	50	20	78	12.5
255 - 285	46	10	78	7.5	50	20	78	12.5
285 - 315	42	10	78	9	20 m Bench Heights not Recommended			
315 - 345	37	10	78	11.1	20 m Bench Heights not Recommended			

Source: Call & Nicholas Inc., 2018

Table 16-6: Summary of Rock Mass Properties


Rock Type	Strength Type	Density (kN/m ³)	Cohesion (kPa)	Phi (°)
Meta Sediments	10% RQD	28.0	309.6	25.4
	40% RQD		667.4	27.8
	70% RQD		1448.6	31.3
	Foliation Anisotropy		197.2	21.5
	Cross Joint Anisotropy		382.0	22.4
Meta Volcanics	10% RQD	25.8	360.6	29
	40% RQD		779.1	31.2
	70% RQD		1692.7	34.5
	Foliation Anisotropy		227.5	25.4
	Cross Joint Anisotropy		443.3	25.9
Diabase Dike	10% RQD	25.9	424.7	28.3
	40% RQD		913.6	31.3
	70% RQD		1980.9	35.8
CPS	Rock-mass	19.0	2.0	30
Saprolite	Rock-mass	22.0	20.0	32

Source: Call & Nicholas Inc., 2018

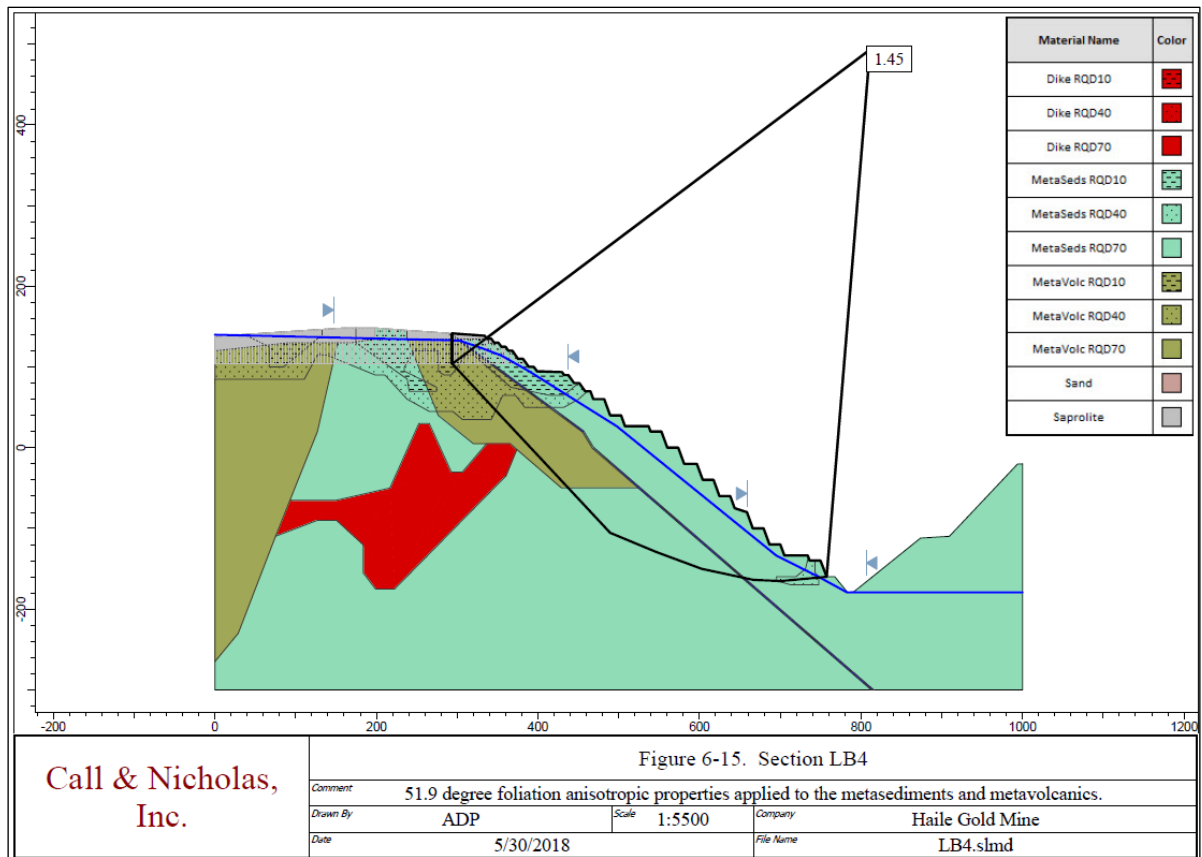


Source: Call & Nicholas Inc., 2018

Figure 16-2: Example Overall Analysis: Cross-Section LB4 for the Southeast Wall of the Ledbetter Pit

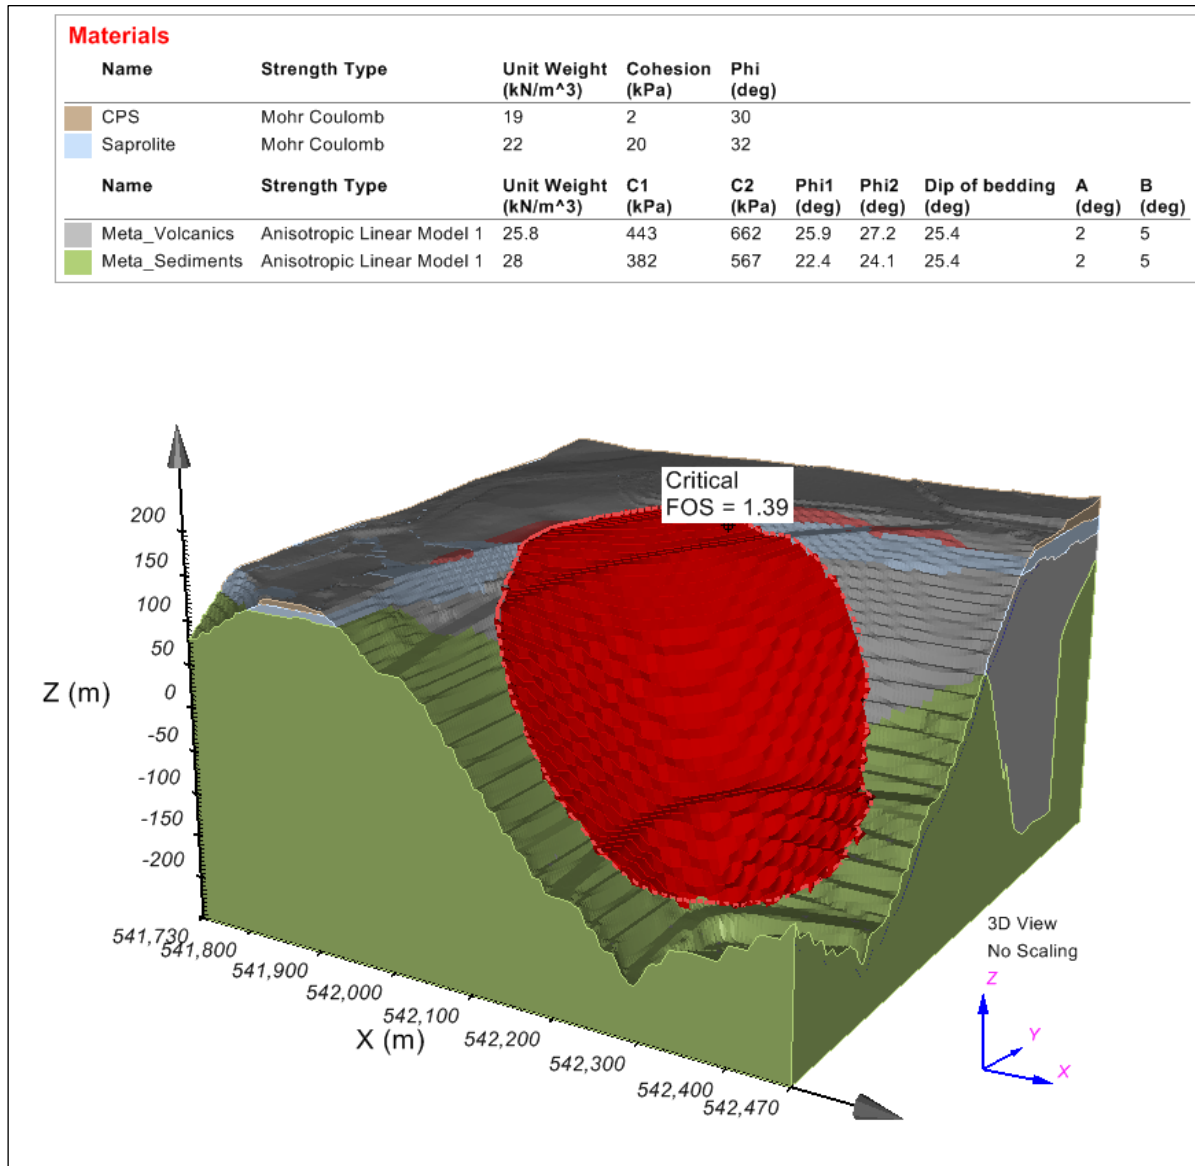

Source: Call & Nicholas Inc., 2018

Figure 16-3: Example of 3D Overall Analysis: Northwest Corner of the Ledbetter Pit

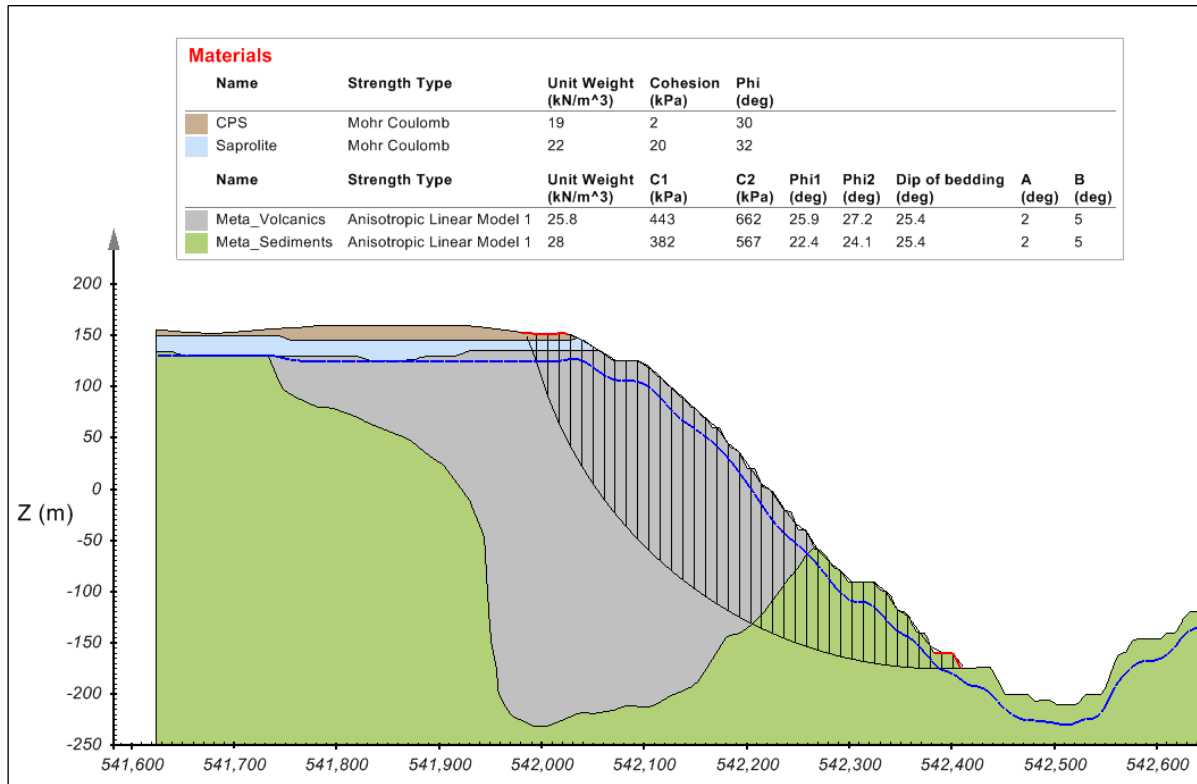

Source: Call & Nicholas Inc., 2018

Figure 16-4: Section View Through Critical Mass of 3D Overall Analysis of Northwest Corner of the Ledbetter Pit


Hydrogeological

Dewatering and depressurization of highwalls is on-going. Ground water levels continue to decrease, and the drawdown trend appears to be reaching steady state in active mining areas. There are currently eleven dewatering wells in service at Haile. Additional wells are planned to facilitate efficient and safe mining in accordance with the mine plan.

16.1.3 Optimization

The sub-blocked geological model was regularized to a 10 m x 10 m x 5 m block model. This block size is considered appropriate for the loading units currently operating at Haile. No further ore losses or ore dilution were applied at the optimization stage.

The open pit Ore Reserves are reported within a pit design based on open pit optimization results shown in Figure 16-5 and Table 16-7. The optimization included Measured, Indicated and Inferred Mineral Resource categories with a gold price of US\$1,500/oz Au. The optimization results without using inferred material are very similar (within 2%) and therefore was considered immaterial. Starting topography for optimization work was June 30, 2020.

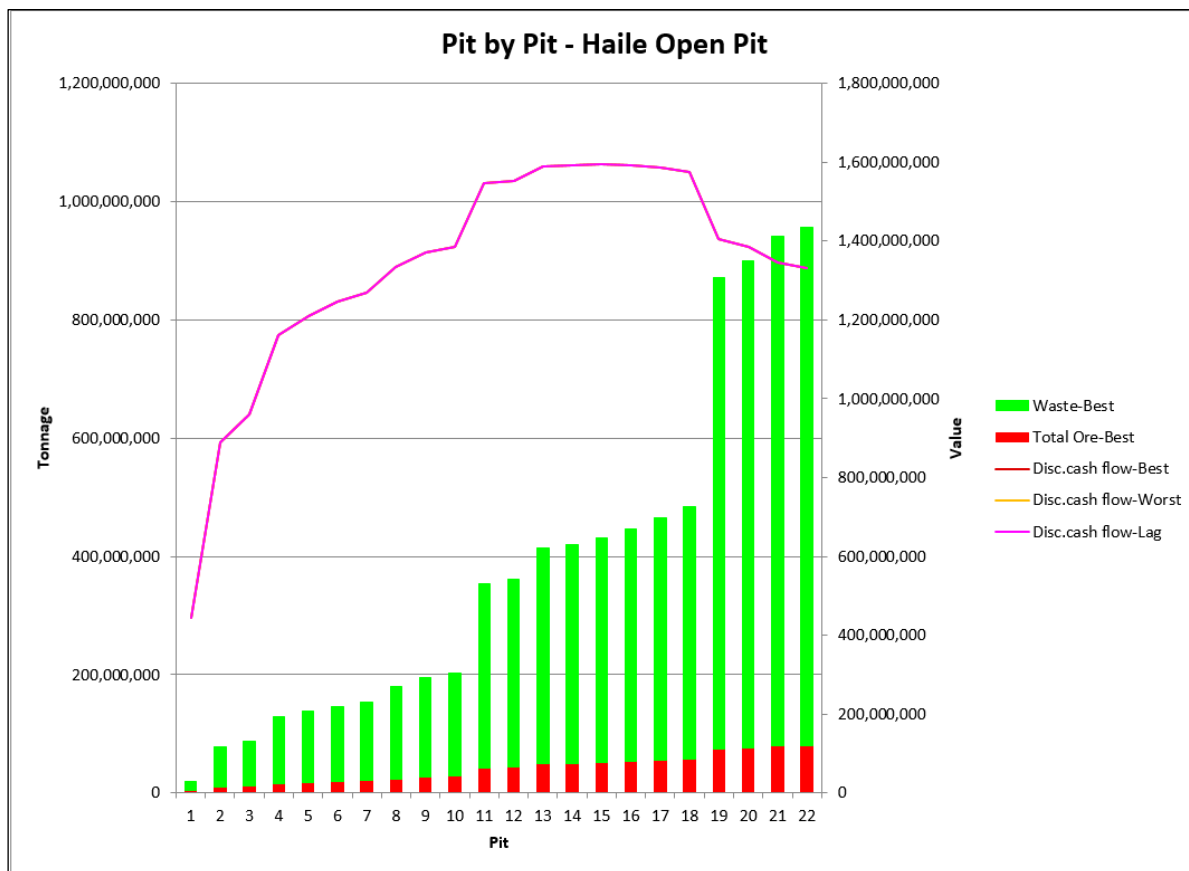

Source: SRK

Figure 16-5: Pit Optimization Tonnes by Revenue Factor

Table 16-7: Optimization Results for Selected Shell on \$75 Gold Price Increments

Pit	Rev Factor	Au Sell Price	SR	Total Tonnes	Ore Tonnes	Waste Tonnes	Inf Ox Tonnes	Inf Fresh Tonnes	Au Recov Toz	Au Cont Toz	Au g/t	MCOST Unit Cost \$/t Moved	PCOST Unit Cost \$/t ROM	SELL COST Unit Cost \$/t Oz	Ore Inc Tonnes	Waste Inc Tonnes	Inc SR	Inc Au Cont Toz	Avg Cash Cost	Avg Met Recov	Mine Life Yrs
1	0.30	\$450	3.22	18,808,446	4,454,486	14,353,960	1,090	143,355	374,358	421,245	2.94	\$2.22	\$16.64	\$3.00	4,454,486	14,353,960	3.2	374,358	\$312	89%	1.1
2	0.35	\$525	6.33	77,570,190	10,581,178	66,989,012	2,180	397,219	823,499	931,259	2.74	\$2.17	\$16.64	\$3.00	6,126,692	52,635,052	8.6	510,013	\$421	88%	2.6
3	0.40	\$600	6.31	87,758,813	12,003,997	75,754,816	2,180	510,974	902,309	1,022,469	2.65	\$2.18	\$16.64	\$3.00	1,422,819	8,765,804	6.2	91,211	\$436	88%	3.0
4	0.45	\$675	6.83	128,982,476	16,479,609	112,502,867	7,825	621,057	1,147,408	1,305,763	2.46	\$2.18	\$16.64	\$3.00	4,475,612	36,748,050	8.2	283,293	\$487	88%	4.1
5	0.50	\$750	6.79	139,107,391	17,867,028	121,240,363	15,625	690,848	1,209,325	1,378,686	2.40	\$2.18	\$16.64	\$3.00	1,387,419	8,737,496	6.3	72,924	\$500	88%	4.5
6	0.55	\$825	6.51	146,809,294	19,537,227	127,272,067	55,611	760,171	1,264,616	1,445,567	2.30	\$2.19	\$16.64	\$3.00	1,670,199	6,031,704	3.6	66,881	\$514	87%	4.9
7	0.60	\$900	6.48	153,644,281	20,529,380	133,114,901	82,369	838,618	1,300,733	1,488,966	2.26	\$2.19	\$16.64	\$3.00	992,153	5,842,835	5.9	43,399	\$524	87%	5.1
8	0.65	\$975	6.62	180,140,065	23,632,019	156,508,047	108,034	1,017,619	1,419,587	1,629,965	2.15	\$2.21	\$16.64	\$3.00	3,102,639	23,393,145	7.5	140,999	\$561	87%	5.9
9	0.70	\$1,050	6.35	195,503,377	26,591,767	168,911,610	125,567	1,705,027	1,501,869	1,730,756	2.02	\$2.22	\$16.64	\$3.00	2,959,748	12,403,563	4.2	100,791	\$587	87%	6.6
10	0.75	\$1,125	6.23	202,938,623	28,080,008	174,858,616	200,793	2,059,862	1,540,111	1,778,157	1.97	\$2.23	\$16.64	\$3.00	1,488,241	5,947,006	4.0	47,401	\$600	87%	7.0
11	0.80	\$1,200	7.34	353,736,178	42,398,428	311,337,749	243,603	3,635,472	2,059,134	2,394,390	1.76	\$2.35	\$16.64	\$3.00	14,318,420	136,479,134	9.5	616,233	\$749	86%	10.6
12	0.85	\$1,275	7.26	360,622,229	43,682,518	316,939,710	258,673	3,750,748	2,088,920	2,431,849	1.73	\$2.35	\$16.64	\$3.00	1,284,090	5,601,961	4.4	37,460	\$756	86%	10.9
13	0.90	\$1,350	7.41	413,767,687	49,213,546	364,554,140	276,873	4,501,698	2,259,167	2,637,181	1.67	\$2.35	\$16.64	\$3.00	5,531,028	47,614,430	8.6	205,332	\$796	86%	12.3
14	0.95	\$1,425	7.37	420,375,393	50,213,987	370,161,407	327,448	4,745,018	2,282,153	2,665,888	1.65	\$2.35	\$16.64	\$3.00	1,000,440	5,607,266	5.6	28,707	\$802	86%	12.6
15	1.00	\$1,500	7.40	432,293,114	51,478,609	380,814,505	333,288	5,045,258	2,316,784	2,708,137	1.64	\$2.35	\$16.64	\$3.00	1,264,622	10,653,098	8.4	42,249	\$812	86%	12.9
16	1.05	\$1,575	7.41	445,863,848	52,989,033	392,874,815	340,218	5,399,268	2,355,479	2,755,615	1.62	\$2.36	\$16.64	\$3.00	1,510,424	12,060,310	8.0	47,478	\$824	85%	13.2
17	1.10	\$1,650	7.51	464,501,182	54,588,838	409,912,345	347,538	5,675,578	2,398,960	2,808,614	1.60	\$2.36	\$16.64	\$3.00	1,599,805	17,037,529	10.6	52,998	\$838	85%	13.6
18	1.15	\$1,725	7.52	484,537,364	56,879,572	427,657,792	360,868	6,396,868	2,451,179	2,873,470	1.57	\$2.37	\$16.64	\$3.00	2,290,735	17,745,447	7.7	64,856	\$857	85%	14.2
19	1.20	\$1,800	10.71	871,290,715	74,387,491	796,903,224	361,958	12,966,678	3,158,788	3,704,732	1.55	\$2.39	\$16.64	\$3.00	17,507,919	369,245,432	21.1	831,263	\$1,055	85%	18.6
20	1.25	\$1,875	10.79	898,973,595	76,241,016	822,732,579	373,248	13,872,748	3,210,781	3,768,130	1.54	\$2.39	\$16.64	\$3.00	1,853,525	25,829,355	13.9	63,398	\$1,069	85%	19.1
21	1.30	\$1,950	10.80	940,622,232	79,698,721	860,923,511	397,593	15,080,138	3,292,020	3,868,727	1.51	\$2.40	\$16.64	\$3.00	3,457,705	38,190,932	11.0	100,597	\$1,091	85%	19.9
22	1.35	\$2,025	10.85	957,156,470	80,757,386	876,399,084	397,593	15,575,608	3,319,161	3,902,049	1.50	\$2.40	\$16.64	\$3.00	1,058,665	15,475,573	14.6	33,322	\$1,099	85%	20.2

Yellow-Revenue Factor 1
Blue – Pit selected for design
Source: SRK 2020

Whittle optimization parameters are summarized in Table 16-8.

Table 16-8: Pit Optimization Parameters

Parameter	Unit	Value
Base Mining Cost	US\$/t	1.41
Incremental Mining Cost	US\$/t / 5 m bench	0.01
PAG Rehabilitation Cost	US\$/t PAG waste	0.95
Processing Cost	US\$/t ore	11.00
G&A Cost	US\$/t ore	3.20
Ore Rehandle Cost	US\$/t ore	0.70
TSF Expansion	US \$/t ore	2.44
Gold Recovery	%	$(1-(0.2152 \cdot \text{au grade}^{-0.3696})) + 0.025$
Mill Throughput	Mtpa	4.0
Gold Price	US\$/oz	1,500
Gold Refining & Selling Cost	US\$/oz	3.00
Calculated Au Cutoff Grade	US \$/t	0.45
Royalties	%	0.0
Discount Rate	%	5.0

Source: SRK

The base mining cost was applied to all blocks and an incremental cost was added to blocks below the elevation where the haulage ramp exits the pit. The incremental cost was not added to blocks above the pit exit. As the Whittle optimization was completed prior to the pit design, pit exit elevations were taken from previous pit design work.

Rehabilitation costs have been added to potentially acid generating (PAG) blocks that will not be processed as this material will require permanent storage within the lined JPAG facility. The cost associated with permanent storage of processed blocks within the Tailing Storage Facility (TSF) is included in the processing cost. The determination of whether a block is processed and, by extension rehabilitation cost, is made by Whittle during optimization.

16.1.4 Mine Design

Mine Block Model

SRK was supplied with the OceanaGold Resource block model. For mine planning purposes, the model was modified to include:

- Geotechnical variables for berm width, batter angle and bench height
- Ore and waste classifications based on different gold prices and Measured, Indicated and Inferred material
- Haul routes for red/yellow waste, green waste, ore and saprolite
- Cycle times and distances for red/yellow waste, green waste, ore and saprolite
- NAG/PAG determination
- Production period flagging


The NAG/PAG determinations govern the routing of waste material to either a lined PAG waste dump facility or an unlined NAG dump.

Pit Design

SRK used the Whittle pits as a guide for practical phase design. The major design parameters used are as follows:

- Ramp grade = 10%
- Full ramp width = 32 m (3x operating width for 730E)
- Single ramp width = 20 m for up to 60 m vertical or six benches
- Minimum mining width = 40 m but targets between 150 m to 300 m
- Flat switchbacks
- Bench heights, berm widths and bench face angles in accordance with current site-specific design criteria

Figure 16-6 illustrates the final open pit design and associated ramp system. Ramp locations targeted saddle points between the various pit bottoms with ramps also acting as catch benches for geotechnical purposes. Each bench has at least one ramp for scheduling purposes.

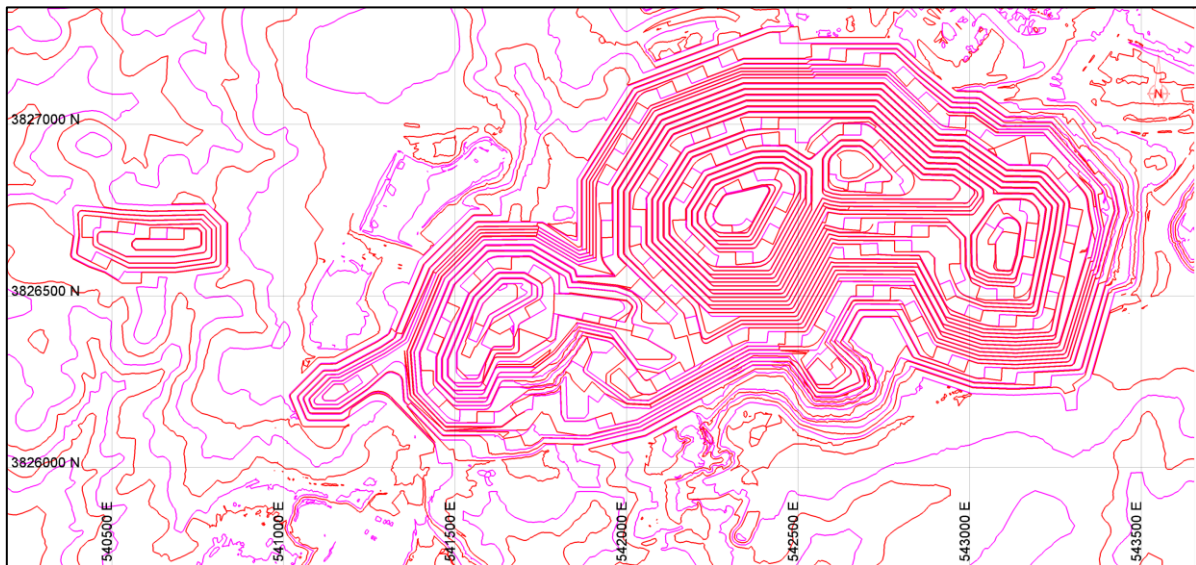

Source: OceanaGold, 2020

Figure 16-6: LoM Pit Design

Grade Tonnage

While the current reserve pit balances reserve size with mine life, there is the potential to modify the operating parameters to increase and decrease grade according to operational parameters encountered during operations (i.e., a grade binning approach to increase the gold grade is possible by increasing the mining rate and stockpiling lower grade material.)


Table 16-9 details the grade tonnage and incremental tonnage at various cut-offs within the pit design. The CoG used for reserves is 0.45 g/t.

Table 16-9: Grade Tonnage Curve within the Pit Design (not diluted)

Cut-off	Au g/t	Mt	Contained Au Mtoz
0.10	0.90	100.1	2.90
0.20	1.06	82.9	2.82
0.30	1.26	65.9	2.67
0.40	1.48	53.2	2.53
0.50	1.68	44.5	2.41
0.60	1.87	38.3	2.31
0.70	2.04	33.6	2.20
0.80	2.20	29.9	2.12
0.90	2.35	26.9	2.03
1.00	2.50	24.4	1.96
1.10	2.64	22.2	1.89
1.20	2.77	20.4	1.82
1.30	2.91	18.7	1.75
1.40	3.04	17.2	1.68
1.50	3.16	16.0	1.63
1.60	3.28	14.9	1.57
1.70	3.40	13.9	1.52
1.80	3.52	12.9	1.46
1.90	3.65	12.0	1.41

Source: SRK

Figure 16-7 shows the grade tonnage curve graphically above a 0.1 g/t lower limit.

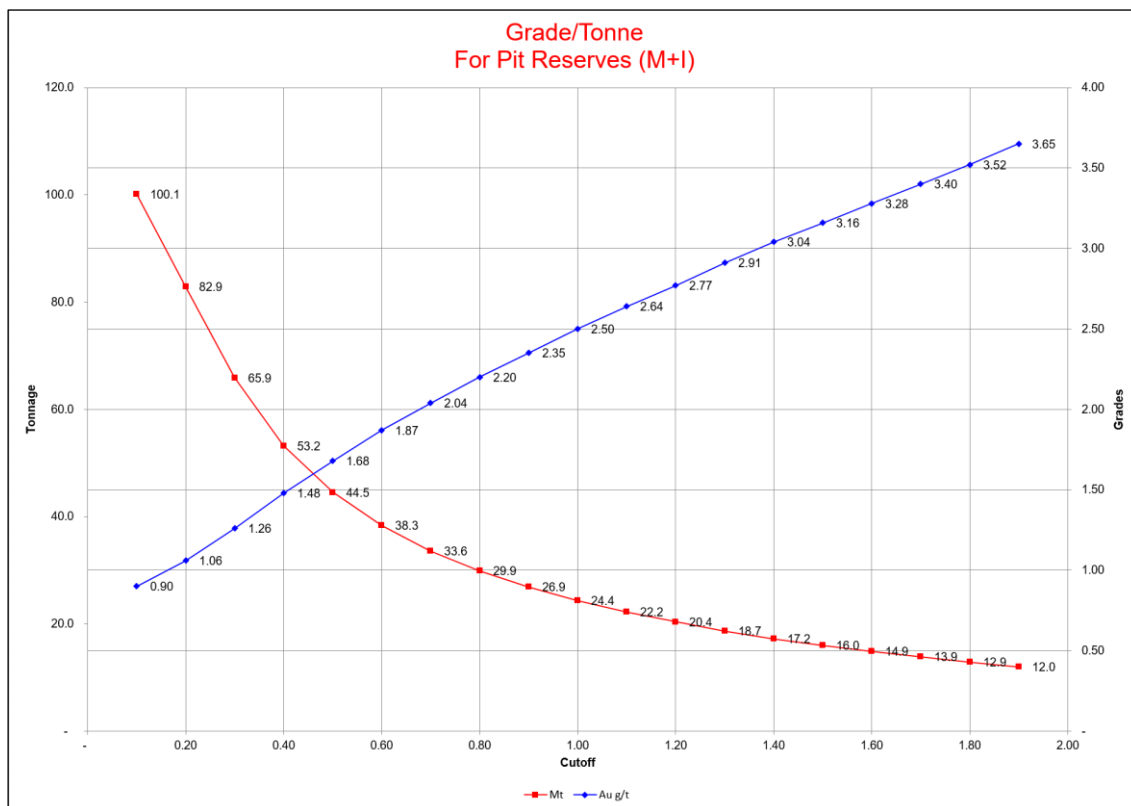

Source: SRK

Figure 16-7: Grade Tonnage Curve within Reserve Pit (Measured and Indicated Material)

16.1.5 Overburden/Geochemical

Overburden mined at Haile consists of oxide and sulfide material. Oxidation generally extends 20 to 40 m deep with no sulfide minerals. Unweathered rock below the base of oxidation contains sulfides with potential to generate sulfuric acid when exposed to air and water. The most common sulfide mineral at Haile is pyrite, FeS_2 , typically at levels of 0.1 to 2%. Minor pyrrhotite and molybdenite are also observed in drillholes and pit exposures. Schafer (2015) performed an extensive geochemical characterization program of existing and future mine development rocks to identify, manage and mitigate geochemical risks at Haile as part of the open pit plan. The characterization program included static testing of 4,911 samples as well as kinetic testing of nine samples of overburden and one tailings sample. The current development rock management plan employs three categories based on combinations of the total sulfur content (S_T) and net neutralization potential (NNP). The NNP is a measure of overall acid generation potential calculated as the difference between the neutralization potential (NP) and AP. The categories of potentially acid generating (PAG) development rock are:

- Red PAG – Strongly acid generating:
 - $\text{NNP} < -31.25 \text{ kg CaCO}_3/\text{t}$
- Yellow PAG – Moderately acid generating:
 - $S_T > 0.2 \%$ or NNP between 0 and $-31.25 \text{ kg CaCO}_3/\text{t}$
- Green – Not acid generating, oxidized rock:
 - $S_T < 0.2 \%$ and $\text{NNP} > 0 \text{ kg CaCO}_3/\text{t}$

The geochemical categories, and their associated management approaches, of development rock and saprolite within 15 m (50 ft) of the bedrock contact are summarized in Table 16-10. This is identical to categories in the underground plan described in section 16.2.4.

Kinetic testing of “Red” and “Yellow” material confirmed the applicability of the development rock classification scheme based on results of static tests, which included:

- Test work over 140 weeks on Red PAG samples developed low pH values (1.6 to 2.2) and released sulfate corresponding to one-third to one-half of the pyritic sulfur originally contained in the sample.
- Yellow PAG samples also had acidic pH values, though generally higher than Red PAG. High concentrations of metals were also released from these samples. Cumulative sulfate leached was much lower than for Red PAG samples owing to the lower levels of pyritic sulfur.
- Green overburden samples maintained near neutral pH and also maintained low to non-detectable sulfate levels.

Table 16-10: Current Open Pit and Adopted UG Overburden Classification at Haile

Operational Testing Criterion	Overburden Abundance	Characteristics	Proposed Management
Red PAG - Strongly Acid Generating Overburden			
Found in Metasediment Unit. For Metasediment, NNP < -31.25 kg/t as CaCO ₃	About 38% of Metasediment unit	When oxidized, contact water will have low pH (< 3.0) and very high metals, sulfate and acidity (>5,000 mg/L)	Stored in geomembrane encapsulated PAG cell, placed in lifts, compacted and Saprolite-lined outside perimeter to reduce oxygen supply
Yellow PAG - Moderately Acid Generating Overburden			
Found in Metasediment and Metavolcanic Bedrock Units and Saprolite. For bedrock, Total S > 0.2% or NNP <0 and NNP> -31.25 kg/t as CaCO ₃ . For Saprolite within 50 feet of bedrock contact, Total S > 0.2% and NNP> -31.25 kg/t as CaCO ₃	About 22% of Metasediment unit, 6% of Metavolcanic unit, and 5% Saprolite	If allowed to oxidize, contact water will have low pH (3.0 to 4.0) and low to moderate metals (mostly Fe & Al)	Managed as above then may be placed in lifts as subaqueous pit backfill (2 lbs/t lime added as needed and 5-ft saprolite cover)
Green Overburden - Not Acid Generating			
Found in Metasediment and Metavolcanic Bedrock Units, Saprolite and Coastal Plain Sands. For Bedrock, Total S < 0.2% and NNP > 0 kg/t as CaCO ₃ . For Saprolite within 50 feet of bedrock contact, Total S < 0.2%. All Saprolite more than 50 feet above bedrock and all Coastal Plain Sand is Green Overburden.	40% Metasediment Unit, 94% Metavolcanics, 95% Saprolite and all Coastal Plain Sand	Contact water may have moderately acidic to alkaline pH (4.0 to 8.0), sulfate low (<1,000 mg/L) and metals non-detectable.	Placed in unlined overburden piles. Runoff will not require treatment assuming it meets storm water requirements as expected

Source: Schafer, 2015

Overburden type calculated from blasthole sulfur and carbon assays and informs the placement of materials as follows:


- All Red PAG is sent to the East or West OSAs. These are lined facilities, with the East OSA already in use. Material will be placed in lifts and compacted by haulage fleet traffic. At the completion of each lift, the face will be covered with saprolite prior to dozing to reclaimed slope angles. For closure, the top of these facilities will be covered with saprolite, followed by an HDPE geomembrane liner and then a layer of growth media. The growth media will be seeded to establish vegetation.
- Yellow PAG can be stored in the East or West OSAs, or below a prescribed water table within pits. Yellow material in-pit will be mixed with lime before placement in the pit void. Material will be placed in lifts and compacted by haulage fleet traffic. At the completion of each lift, the face will be covered with green waste prior to dozing to reclaimed slope angles. For closure, the

top surface of these facilities will be covered with green waste. Yellow PAG is able to be utilized in-pit for road construction.

- Green material will be stored in unlined facilities or backfilled into the pits. Material placed on unlined facilities will be placed in lifts and compacted by haulage fleet traffic. At the completion of each lift, the face will be dozed to reclaimed angles. The reclaimed slopes will be seeded to establish vegetation.
- The historic heap leach material that will be mined in the pit will be placed on either the East or West OSA.

Over the life of the mine, various initiatives will be pursued to increase the accuracy of definition of waste types and reduce overall production of waste with PAG classifications. Areas of investigation will include confirmation sampling techniques, grade control and excavation practices in waste areas, alternatives to the LECO testing currently employed and opportunities, based on analysis and test work, for reclassification of some areas of Yellow PAG waste to Green.

The overburden storage is discussed in more detail in Section 18.2, with the final year site plan shown in Figure 16-8.

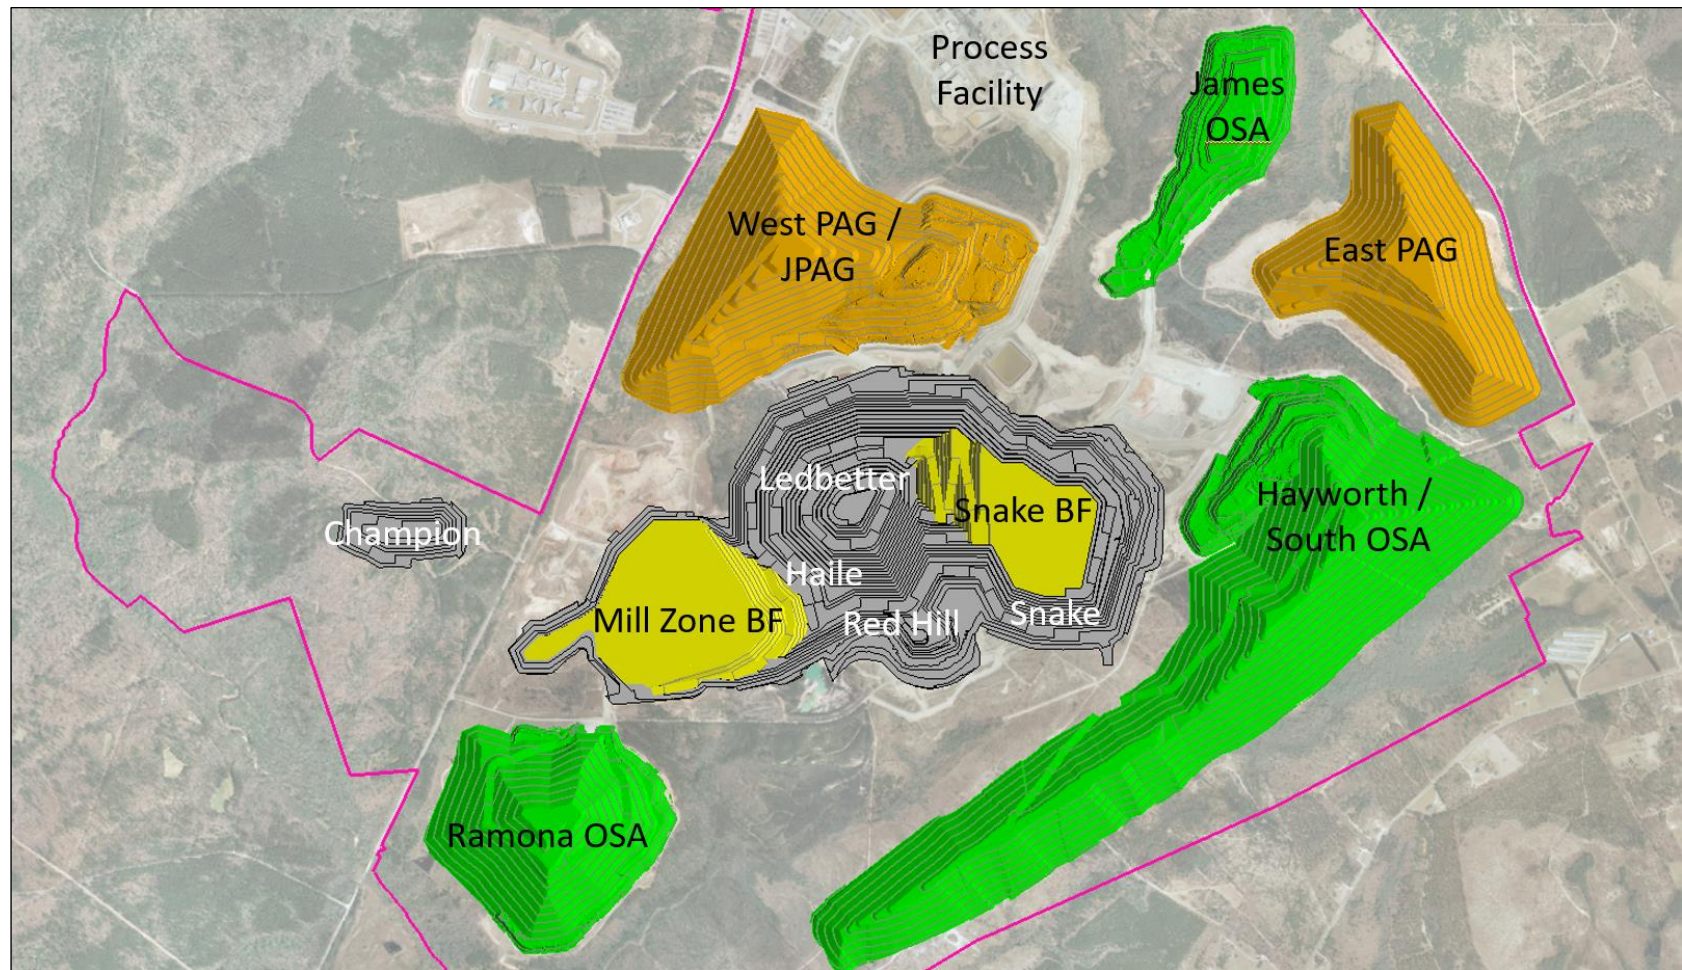

Yellow inside pits is backfill material.
Source: OceanaGold

Figure 16-8: Final Pit Design and Ultimate Overburden Storage Site Plan

16.1.6 Mine Production Schedule

Cut-Off Grade

OceanaGold have used a mine breakeven CoG for the determination of ore and waste. The base assumptions for the calculation are detailed in Table 16-11. The actual CoG grade applied to Measured and Indicated Resources was rounded to 0.45 g/t Au.

Table 16-11: Cut-off Grade Calculation

Description	Units	CoG
Assumptions		
Gold Price	US\$/oz	1,500
Smelting & Refining	US\$/oz	3.00
Au Grade	g/t	0.45
Au Recovery	%	82.5
Operating Costs		
Smelting & Refining	US\$/t ore	0.0324
Mining*	US\$/t mined	1.41
G&A	US\$/t ore	3.20
Tailings	US\$/t ore	2.44
Processing	US\$/t ore	11.00
Subtotal	US\$/t	18.09
CoG - Head Grade	g/t	0.45

*Variable cost based on pit depth. Base mining cost used for cut-off grade calculation.
Source: OceanaGold

Dilution and Mining Recovery

Reserves are based on the Haile resource block model that was regularized using a 10 m x 10 m x 5 m block dimension.

Phase Design Inventory

The first 18 months of material was taken from the short-term site plan. This totals to 5.4 Mt at a grade of 1.91 Au g/t and 2.03 g/t Ag. The following section describes the material quantities starting January 1, 2022.

The ultimate pit design has been broken into 12 mine phases for sequenced extraction in the SRK production schedule. The design parameters for each phase are the same as those used for the final pit design including assumed ramp widths. Phase designs were constructed by splitting up the final pit into smaller and more manageable pieces, while still ensuring each bench within each phase has ramp access. The phases have been developed by balancing mining constraints with the optimum extraction sequence suggested by pit optimization results presented previously.

The phases and direction of extraction allow for multiple benches on multiple elevations with a sump always available for pit dewatering. This means that during periods of heavy rainfall, perched benches will be available for extraction.

Once the phases have been designed, solid triangulations are created for each phase as they cut into topography from previous phases. These solid phases are then shelled (cut) on a 5 m lift height that corresponds to one block model block. These shells form a bench within each phase and represent the basic unit that is scheduled for the life-of-mine (LoM) production plan.

Table 16-12 details the phase inventory that formed the basis of the SRK production schedule.

Table 16-12: Phase Inventory (1/1/2022 to End of Mine Life)*

Phases	Ore (Measured + Indicated)			Waste Inferred (Inferred)			Waste	
	Tonnes (kt)	Au g/t	Contained Au (koz)	Tonnes (kt)	Au g/t	Contained Au (koz)	Tonnes (kt)	SR
CP_01	1,258	0.81	33	125	0.70	3	4,353	3.6
HL_01	1,320	1.33	56	14	0.76	0	4,290	3.3
HL_02	4,121	1.03	137	534	0.75	13	16,084	4.0
IP_02	36	0.85	1	-	-	-	8,032	224.1
LB_01	431	2.91	40	1	2.08	0	937	2.2
LB_02A	2,799	2.48	224	141	2.34	11	31,659	11.4
LB_02B	2,797	2.27	204	381	1.49	18	57,103	20.6
LB_03	5,649	2.03	368	201	1.20	8	21,837	3.9
LB_04	15,941	1.24	634	2,564	0.74	61	138,523	8.9
LP_02	7	0.48	0	-	-	-	2,278	337.9
MZ_02	3,473	1.76	196	457	1.78	26	20,764	6.1
SP_03	4,618	1.39	207	299	0.81	8	41,344	9.0
Grand Total	42,449	1.54	2,100	4,717	0.97	148	347,205	8.3

Source: SRK, 2020

*Approximately 5.4 Mt of Ore and 60 Mt of Waste is planned from July/1/2020 to December 31, 2020. The site has generated a separate mine plan for the first 18 months. Totals do not include current and planned stockpiles.

Production Schedule Targets

The SRK production schedule was based on June 30, 2020 pit topography and comprised of 2.5 years of monthly periods, with the remaining LoM schedule completed quarterly. SRK used the IBM ILOG CPLEX Optimizer (CPLEX) linear solver to meet the minimum and maximum tolerances detailed in Bench sinking rates maxed at 10 benches per phase per year.

Production Schedule Results

The results of the SRK production schedule are detailed in Table 16-13. A more detailed breakdown of the production schedule is found in Table 16-14. Note that stockpile material is not included in this summary and therefore numbers here do not match the reserve table and economic models (which do include stockpile material).

Table 16-13: Open Pit Production Summary

Year	Ore (kt)	Au Grade (g/t)	Ag Grade (g/t)	Waste (kt)
2020	1,638	2.15	2.04	19,282
2021	3,769	1.81	2.02	40,553
2022	4,207	1.65	2.28	40,258
2023	4,210	1.31	2.36	40,357
2024	4,200	1.94	2.58	40,299
2025	3,133	1.56	2.55	40,719
2026	4,203	2.29	2.50	40,478
2027	4,797	1.50	2.42	40,497
2028	4,200	1.14	2.11	40,284
2029	4,371	0.93	2.35	40,427
2030	4,588	1.32	2.50	20,067
2031	4,176	1.65	2.62	3,658
2032	539	3.00	3.04	161
2033	-	-	-	-
Total	48,031	1.58	2.39	407,040

Points of note on the schedule:

- The 2020 and 2021 plan targets approximate current production and site budget targets for the period.
- Stripping was brought forward from 2020 to 2025 to keep ounce production above 200 koz/yr.
- Grade reduces after 2026 as the Haile and Red Hill phases are mined and Ledbetter ore is accessed.
- Grade spikes in 2026 as high-grade ore in Ledbetter is exposed.


Figure 16-9 illustrates the annual production schedule for ore, waste and Inferred tonnes.

Figure 16-10 breaks down the Red/Yellow waste, Green waste, Saprolite and Ore tonnes for the LoM. The Green waste is common early in the mine life but as the Ledbetter pit is exposed the amount of Red/Yellow waste increases.

Table 16-14: Mine (UG + OP) and Mill Production Schedule


Description	Description	2020	2021	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032	2033	LoM Total
UG Ore	RoM (kt)	-	-	15	661	751	742	738	510	-	-	-	-	-	-	3,416
	RoM Au (g/t)	-	-	5.03	3.99	4.07	4.53	3.26	2.70	-	-	-	-	-	-	3.78
	RoM Ag (g/t)	-	-	0.90	0.90	0.90	0.90	0.90	0.90	-	-	-	-	-	-	0.90
OP Ore > 1.2 g/t	RoM (kt)	-	-	1,939	1,440	2,282	1,245	2,768	2,200	999	672	1,690	2,095	407	-	17,736
	RoM Au (g/t)	-	-	2.71	2.45	2.96	2.78	3.08	2.36	2.58	2.42	2.30	2.52	3.71	-	2.68
	RoM Ag (g/t)	-	-	2.53	2.57	2.98	2.54	2.81	2.70	2.23	2.36	2.73	2.91	3.06	-	2.71
OP Ore > 0.7 to 1.2 g/t	RoM (kt)	-	-	1,131	1,228	935	973	846	1,468	1,293	1,155	1,566	1,173	86	-	11,855
	RoM Au (g/t)	-	-	0.92	0.91	0.92	0.92	0.93	0.93	0.89	0.89	0.92	0.92	0.94	-	0.92
	RoM Ag (g/t)	-	-	2.17	2.43	2.13	2.62	2.04	2.31	2.17	2.43	2.55	2.37	2.78	-	2.34
	EOP Stock (kt)	-	652	-	-	34	73	231	603	-	-	-	-	-	-	-
	EOP Stock AU (g/t)	-	0.71	-	-	0.96	0.94	0.94	0.93	-	-	-	-	-	-	-
	EOP Stock Ag (g/t)	-	2.18	-	-	2.11	1.93	2.16	2.21	-	-	-	-	-	-	-
OP Ore > 0.45 to 0.7 g/t	RoM (kt)	-	-	1,137	1,543	983	915	588	1,129	1,908	2,544	1,333	908	46	-	13,033
	RoM Au (g/t)	-	-	0.56	0.56	0.56	0.56	0.56	0.57	0.56	0.55	0.56	0.58	0.55	-	0.56
	RoM Ag (g/t)	-	-	0.76	0.75	0.75	0.75	0.74	0.76	0.76	0.76	0.76	0.76	0.76	-	0.75
	EOP Stock (kt)	-	249	1,123	1,994	2,900	2,736	3,324	4,453	5,245	5,616	6,204	6,380	2,908	-	-
	EOP Stock AU (g/t)	-	0.30	0.50	0.53	0.54	0.54	0.55	0.55	0.55	0.55	0.55	0.56	0.56	-	-
	EOP Stock Ag (g/t)	-	2.30	1.98	2.04	2.05	2.08	2.02	2.01	2.00	2.03	2.05	2.05	2.05	-	-
Total OP Ore	RoM (kt)	1,638	3,769	4,207	4,210	4,200	3,133	4,203	4,797	4,200	4,371	4,588	4,176	539	-	48,031
	RoM Au (g/t)	2.15	1.81	1.65	1.31	1.94	1.56	2.29	1.50	1.14	0.93	1.32	1.65	3.00	-	1.58
	RoM Ag (g/t)	2.04	2.02	1.96	1.87	2.27	2.04	2.36	2.12	1.54	1.44	2.10	2.29	2.82	-	2.01
	EOP Stock (kt)	N/A	901	1,123	1,994	2,934	2,809	3,750	5,056	5,245	5,616	6,204	6,380	2,908	-	-
	RoM Au (g/t)	N/A	0.59	0.50	0.53	0.54	0.55	0.70	0.60	0.55	0.55	0.55	0.56	0.56	-	-
	RoM Ag (g/t)	N/A	2.22	1.98	2.04	2.05	2.08	2.05	2.04	2.00	2.03	2.05	2.05	2.05	-	-
UG Mill Feed	Ore Feed (kt)	-	-	15	661	751	742	738	510	-	-	-	-	-	-	3,416
	Ore Feed Au (g/t)	-	-	5.03	3.99	4.07	4.53	3.26	2.70	-	-	-	-	-	-	3.78
	Ore Feed Ag (g/t)	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
OP Mill Feed	Ore Feed (kt)	1,844	4,000	3,985	3,339	3,260	3,258	3,262	3,490	4,011	4,000	4,000	4,000	4,011	2,908	49,369
	Ore Feed Au (g/t)	1.93	1.91	1.73	1.51	2.34	1.51	2.63	1.95	1.23	0.96	1.44	1.70	0.88	0.56	1.57
	Ore Feed Ag (g/t)	2.00	1.80	2.35	2.43	2.72	2.51	2.66	2.57	2.16	2.34	2.55	2.63	2.18	2.05	2.36
Total Mill Feed	TOTAL Feed (kt)	1,844	4,000	4,000	4,000	4,011	4,000	4,000	4,000	4,011	4,000	4,000	4,000	4,011	2,908	52,785
	TOTAL Feed Au (g/t)	1.93	1.91	1.75	1.92	2.66	2.07	2.74	2.04	1.23	0.96	1.44	1.70	0.88	0.56	1.71
	TOTAL Feed Ag (g/t)	2.00	1.80	2.34	2.03	2.21	2.04	2.17	2.24	2.16	2.34	2.55	2.63	2.18	2.05	2.21
	Total Feed Contained Au (koz)	114	246	224	247	343	266	353	263	158	123	185	218	114	52	2,907
	Total Feed Contained Ag (koz)	119	231	301	261	285	263	279	288	279	302	328	338	282	192	3,746

Source SRK 2020
*SRK generated the long range mine plan from 2022 to the end of the mine life. The site generated the monthly mine plan until the end of 2021. EOP = End of Period

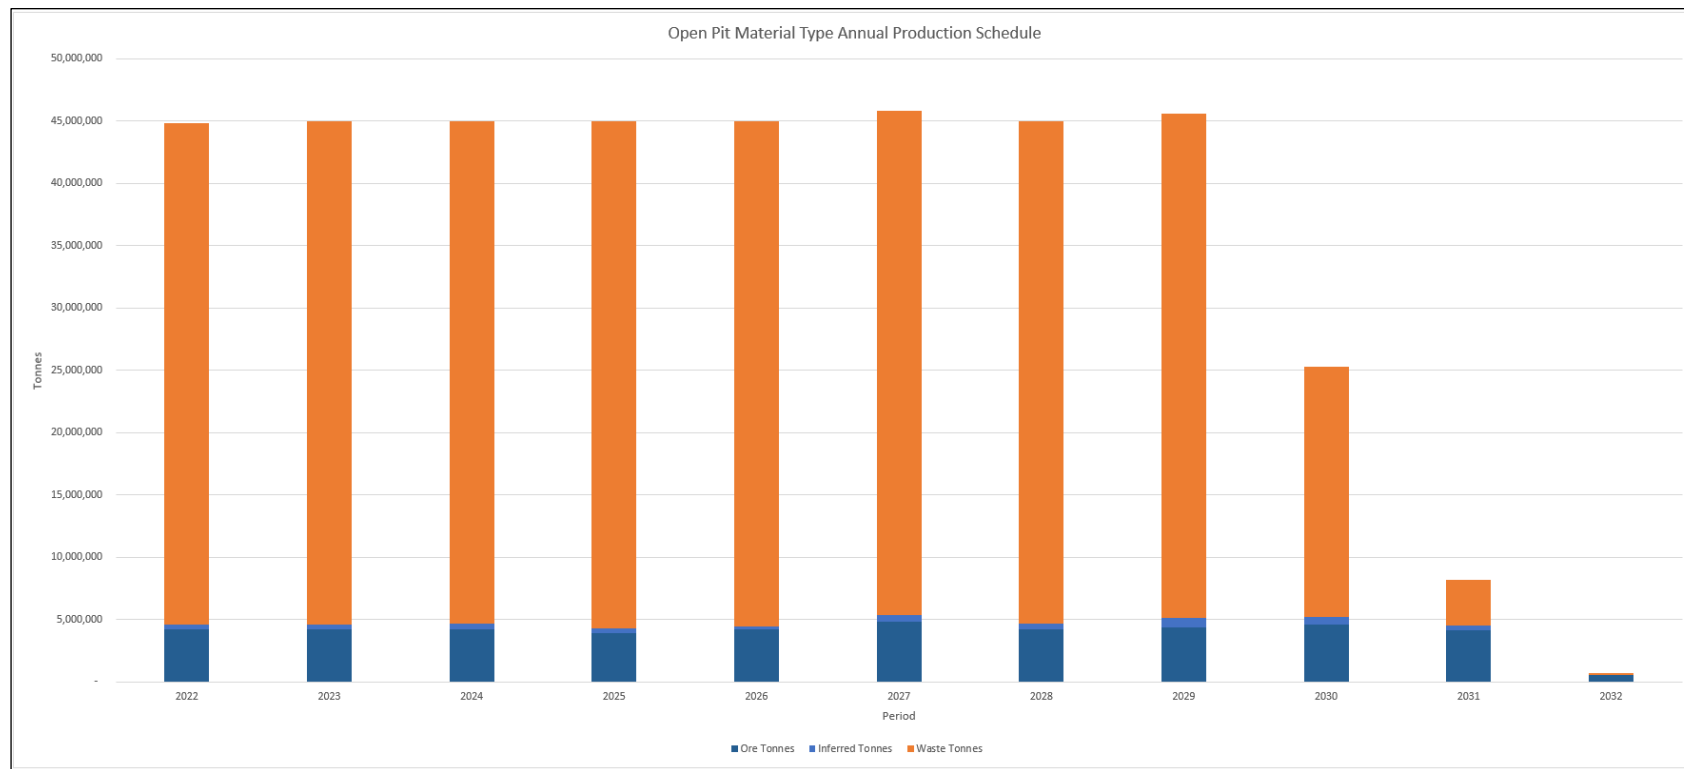

Source: SRK, 2020

Figure 16-9: Annual Production Schedule

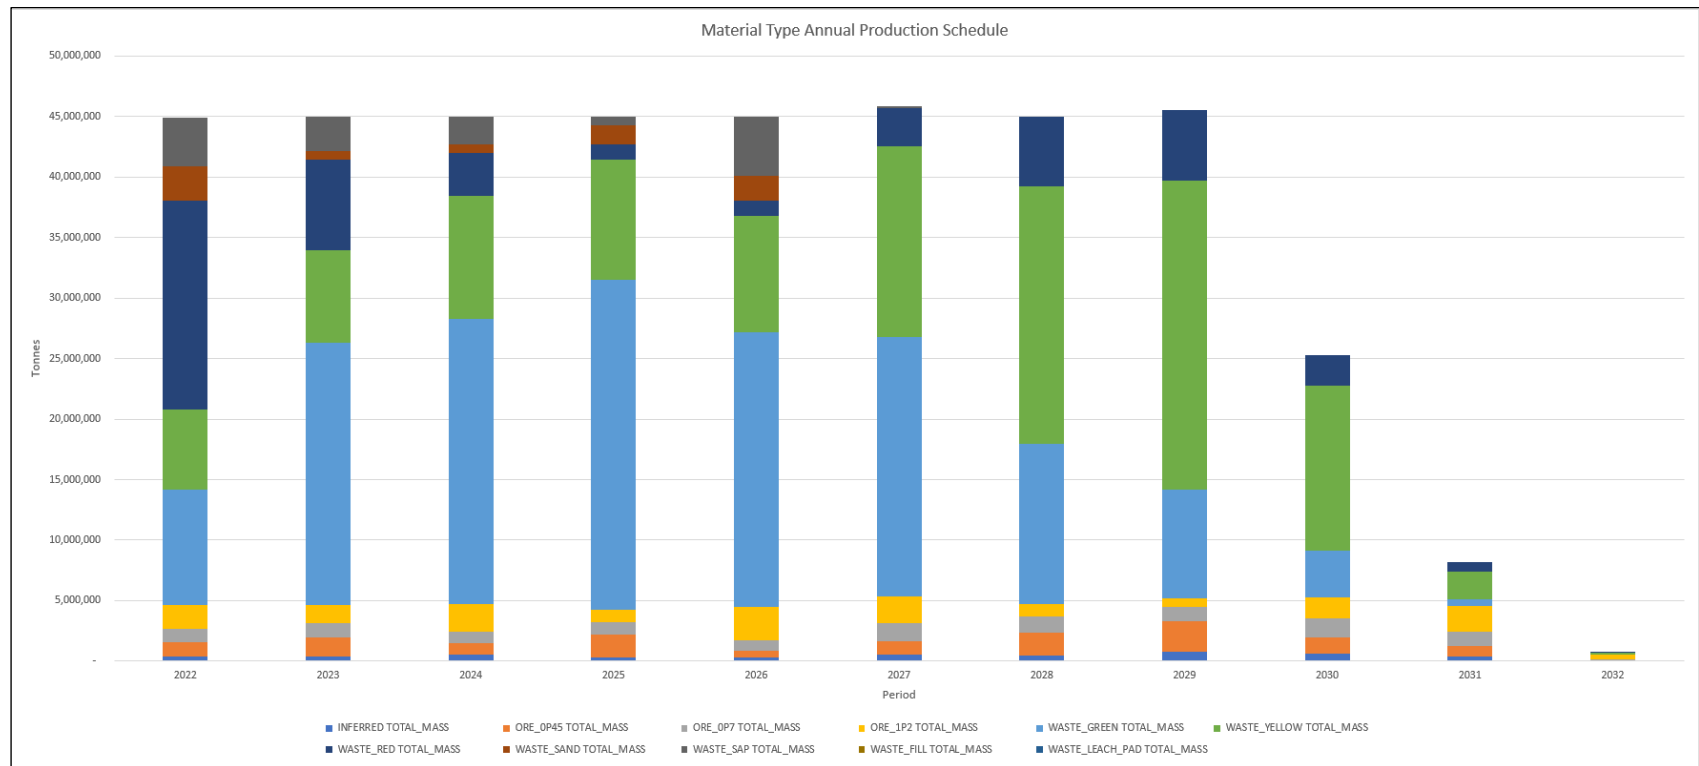

Source: SRK, 2020

Figure 16-10: Material Type Annual Schedule

Bench Sinking Rate

Table 16-15 shows the benches mined from each pit/phase on an annual basis. Sinking rates are reasonable in each year.

Table 16-15: LoM Yearly Bench Sinking Rates

Phase ID	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032
CP_01	1.0	-	1.7	2.8	-	-	-	-	-	-	-
HL_01	4.0	1.0	-	-	-	-	-	-	-	-	-
HL_02	2.0	7.7	1.9	0.4	-	-	-	-	-	-	-
IP_01	4.0	2.0	1.0	1.0	-	-	-	-	-	-	-
LB_01	4.0	-	-	-	-	-	-	-	-	-	-
LB_02A	4.6	9.2	2.8	-	-	-	-	-	-	-	-
LB_02B	1.0	1.9	1.7	2.5	2.7	-	-	-	-	-	-
LB_03	-	-	1.0	2.4	1.6	1.5	-	-	-	-	-
LB_04	-	-	-	0.3	1.8	1.4	1.2	1.7	1.7	1.5	1.8
LP_02	3.0	-	-	-	-	-	-	-	-	-	-
MZ_02	9.9	4.1	-	-	-	-	-	-	-	-	-
SP_03	-	-	-	2.4	2.9	2.6	1.0	0.9	4.0	-	-

Source SRK 2020

Haulage Cycle Times

Haulage is based on material from each phase going to either the green stockpiles or red/yellow stockpile or crusher location. Because there are multiple ramps within the pit, the haulage profile within the pit to an exit point was controlled by a pit ramp haulage route. The in-pit haulage time is then added to the cycle time defined by haul road strings to the waste dumps or crusher from the pit exit. The cycle time and distance are stored in the block model and the haul cycles are matched with a routing block code in the block model. For example, waste blocks are assigned the waste cycle time based on the distance of the block to the waste dump. Strings to dumps are based on centroid locations. In the years where bulk fill is required for the tailings dam construction, the waste haul routes were extended to account for the additional haul times that will deliver waste rock at the required rate. Individual locations were not specified, but the nature of the tailings dam design means elevation changes will be minimal.

Haulage times reported in the block model are instantaneous times and do not have any efficiency corrections (other than speed around corners) delays, spot times or dump times. These corrections are made in the OceanaGold truck fleet estimation spreadsheet that uses the cycle times reported as the basis for the estimate.

The rimpull curve estimated speeds used in the cycle time estimation are detailed in Table 16-16.

Table 16-16: Rimpull Curve Representing Truck Speeds by Gradient

175-t Truck	Gradient (%)	Speed Uphill (km/h)	Speed Downhill (km/h)
Loaded	0-2	25.0	25.0
	2-4	25.0	25.0
	4-6	18.0	25.0
	6-7.5	14.0	25.0
	7.5-9	11.0	25.0
	9+	10.0	25.0
Empty	0-2	25.0	25.0
	2-4	25.0	25.0
	4-6	25.0	25.0
	6-7.5	23.0	25.0
	7.5-9	21.0	25.0
	9+	19.0	25.0

Source: SRK, 2020

*Due to the rain amount, SRK capped maximum speeds at truck haul roads to 25 km/hr. During some periods of the year, higher speeds may be achieved.

Table 16-17 shows the calculated haulage cycle times (truck only cycle time) and one-way distances by destination.

Table 16-17: Annual Truck Cycle Times and Distances

Type	Value	20 22	20 23	20 24	20 25	20 26	20 27	20 28	20 29	20 30	20 31	20 32	20 33
Ore (Pit to Crusher)	Cycle Time (min)	21. 63	21. 98	22. 17	22. 21	24. 73	24	22. 18	24. 89	29. 85	34. 47	37. 68	
	One Way Dist (m)	3,6 04	3,6 33	3,4 95	3,6 38	3,6 64	3,6 18	3,4 86	3,7 87	4,3 50	4,8 86	5,2 64	
Ore (Pit to Stockpile)	Cycle Time (min)	21. 63	21. 98	22. 17	22. 21	24. 73	24	22. 18	24. 89	29. 85	34. 47	37. 68	
	One Way Dist (m)	3,6 04	3,6 33	3,4 95	3,6 38	3,6 64	3,6 18	3,4 86	3,7 87	4,3 50	4,8 86	5,2 64	
Ore (Stockpile to Crusher)	Cycle Time (min)			3.3 6	3.3 6	3.3 6	3.3 6	3.3 6	3.3 6	3.3 6	3.3 6	3.3 6	3. 36
	One Way Dist (m)			88 6	88 6	88 6	88 6	88 6	88 6	88 6	88 6	88 6	88 6
Inferred (Pit to Stockpile)	Cycle Time (min)	21. 63	21. 98	22. 17	22. 21	24. 73	24	22. 18	24. 89	29. 85	34. 47	37. 68	
	One Way Dist (m)	3,6 04	3,6 33	3,4 95	3,6 38	3,6 64	3,6 18	3,4 86	3,7 87	4,3 50	4,8 86	5,2 64	
Waste Green to TSF	Cycle Time (min)	25. 02	25. 99	26. 91	32. 61	26. 93	31. 55	32. 76					
	One Way Dist (m)	4,8 18	4,9 70	5,1 35	5,8 83	5,1 18	5,6 49	5,7 96					
Waste Green to Dumps (Expit)	Cycle Time (min)	17. 39	19. 29	19. 55	24. 52	19. 15	22. 01	25. 58	29. 09	34. 63	39. 31		
	One Way Dist (m)	2,9 06	2,8 30	3,0 48	3,3 95	2,7 31	3,1 97	3,6 62	4,0 84	4,7 17	5,2 74		
Waste Green to Dumps (Inpit)	Cycle Time (min)		6.5 3	6.9 3	14. 8	25. 02	20. 63	21. 42	10. 06	11. 59	16. 55	20. 35	
	One Way Dist (m)		1,1 87	1,2 26	2,3 27	3,8 52	3,3 31	3,0 89	1,6 57	1,7 45	2,3 51	2,8 08	
Waste Red + Yellow to Dumps (Expit)	Cycle Time (min)	17. 82	19. 39	18. 47	22. 63	17. 37	17. 96	19. 43	27. 91	30. 12	35. 35	39. 57	
	One Way Dist (m)	2,8 19	2,9 10	2,7 46	3,2 61	2,6 30	2,6 50	2,7 88	3,7 09	4,3 14	4,9 15	5,4 58	

16.1.7 Mining Fleet and Requirements

The open pit loading and hauling equipment fleet consists of hydraulic excavators (Komatsu PC3000 and PC4000 models) and rigid frame haul trucks (CAT 777, CAT 785 and Komatsu 730). Blasthole drilling and wall control drilling is performed with a fleet of Sandvik DR410i and Epiroc D65 drills. Typical ancillary equipment, including track dozers, wheel dozers, motor graders and water trucks support the mining operation.

Table 16-18 shows the estimation of the scheduled hours per year after deducting for weather delays. Table 16-19 shows the assumed mechanical availabilities and use of availabilities for the loading and hauling equipment to estimate the potential operating hours per year.

Table 16-18: Estimation of Scheduled Hours per Year for a Typical Year

Maximum Days Per Year	365
Weather Days/year	24
Operating Days/year	341
Scheduled hours/shift	12
Shifts/day	2
Scheduled hours/year	8,184

Source: OceanaGold

Table 16-19: Factors in Estimation of Potential Operating Hours for a Typical Year

	140 t Truck	175 t Truck	Excavators
Mechanical Availability	0.85	0.89	0.89
Use of Availability	0.84	0.84	0.85
Operating Hours per Year	6,254	6,549	6,626

Source: OceanaGold

Waste is drilled with either 171 mm or 200 mm diameter holes and ore is drilled with 171 mm diameter holes. Productivity rates vary depending on drill type and rock type, but the average LoM drilling productivity is approximately 26.5 m/hr across the drill fleet.

Five to seven passes of the primary digging units will be used to load the matching trucks. Annual productivity rates have been estimated from equipment specifications, material characteristics, spot and loading times, truck presentation and primary digging unit propel factors, scheduled hours per year, mechanical availability and use of availability. For PC3000 excavators, the estimated productivity is 1,950 tonnes per hour. For PC4000 excavators, the estimated productivity is 3,000 tonnes per hour.

For estimating truck numbers, haul profiles were used to estimate annual average travel times by different material movements. For the LoM schedules the material movements were divided into:

- Green waste (to waste rock dumps and TSF)
- Red waste (to waste rock dumps)
- Yellow waste (to waste rock dumps)
- Inferred (to stockpile)
- Ore (to crusher or to stockpile)
- Rehandle underground ore (to crusher)

A weighted average travel time was estimated for each period based on the quantities of each type of material moved in the period. This average travel time was then applied to the required material movement for the period to determine required truck hours. Table 16-20 shows the major mining equipment fleet required to achieve the mining schedule. The open pit mining fleet is relatively new and, accordingly, no replacement of mining equipment will be required. Rebuilds are schedule at appropriate intervals over the LoM timeframe.

A down the hole service will continue to be provided by an explosive's supplier.

Ancillary equipment to support the load and haul and drilling fleets includes six tracked and two rubber-tired dozers. In addition, three motor graders cover the pit, dump and surface roads. A FEL provides stockpile and extra loading capability. Three water trucks are assigned to roads and servicing drills. Other equipment includes lighting plants, sumps pumps, fuel truck compactor and light vehicles.

Table 16-20: Major Equipment Required to Achieve the Mine Schedule

Fleet	2021	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032	2033
PC4000 Excavator	2	2	2	2	2	2	2	2	2	1	-	-	-
PC3000 Excavator	1	1	1	1	1	1	1	1	1	1	1	1	-
Cat 993 Loader	1	1	1	1	1	1	1	1	1	1	1	1	1
Cat 777 Trucks	3	3	3	3	3	3	3	3	3	3	3	3	3
Cat 785 Trucks	3	-	-	-	-	-	-	-	4	-	-	-	-
Komatsu 730 Trucks	19	18	18	16	19	19	19	19	19	14	5	1	-
Sandvik DR410i Drill	4	4	4	4	4	4	4	4	4	3	1	-	-
Epiroc D65 Drill	3	3	3	3	3	3	3	3	3	2	1	1	-

Source: OceanaGold

16.1.8 Labor

Labor costs on an annual basis have been built up with reference to equipment unit numbers, the roster and requirements for management and technical staff. The roster is a continuous four panel crew roster of 12-hour shifts with two shifts per day. Rostered days off, leave, training, sick leave and absenteeism allowances are accounted for. Operator numbers are based on allocating specific numbers to each equipment item (generally three people on the basis of the three-panel roster). The manpower numbers assume an efficient workforce operating with high level of multi-skilling and flexibility. Table 16-21 shows the required workforce for the year 2021.

Table 16-21: Labor Levels in 2021

Labor Category	Year 2021
Management and Technical Services	
Mine Operations Management	4
Mine Engineering/Geology/Survey	45
Total	49
Operations Labor	
Mine Foreman/Supervisors	20
Operators	193
Blast Crew/ Explosives Ops	0
Holiday/Training/Sickness, etc	24
Total	233
Maintenance Labor	
Maintenance Super/Shift Foreman	10
Fitter/Welder/Electrician/Service man	69
Maintenance Planner	3
Maintenance Clerk	1
Total	83
Grand Total	369

Source: OceanaGold

The manpower numbers are then applied against the annual labor cost by job type. These costs have been supplied by Haile operations and are inclusive of on-costs.

16.1.9 Mine Dewatering

The Project area is located within the Carolina Terrane, also known as the Carolina Slate Belt, which is composed predominantly of metavolcanic and metasedimentary rocks. The Site occurs within a strongly deformed ENE-trending structural zone of the Carolina Terrane at or near the contact between metamorphosed volcanic and sedimentary rocks of Neoproterozoic to Early Cambrian age. The

relevant stratigraphy of the Project area includes (from youngest to oldest) the Coastal Plain Sands (CPS), saprolite, metasedimentary and metavolcanic bedrock, along with lamprophyre and diabase dikes.

The CPS unit was deposited within the last 100 million years and is discontinuous across the Site. It is present in the highland areas with a thickness of up to 37 m, has been eroded from drainages, and thins towards the west. The upper layer is a clean, tan to light brownish yellow, fine- to medium-grained quartz sand. The lower portion of the CPS consists of white to red sand with some clay and silt and the base of the lower layer is characterized as oxide-cemented coarse gravel and sand.

A thick layer of saprolite covers the majority of the Site, underlying the CPS or at the surface where CPS has been eroded. It is a red brown to white, dense, unconsolidated, kaolin-rich clay resulting from intense chemical weathering of bedrock. The saprolite does not exhibit any significant structural features. Saprolite ranges in thickness from 10 to 40 m and is thickest above metavolcanic rocks and along faults but is absent in isolated areas.

The metasedimentary rocks on Site are part of the Richtex Formation. The metasediments consist of bedded, calcareous, chloritic mudstone and silty mudstone that were deposited conformably on the underlying metavolcanics. The metavolcanics consist of andesitic metavolcanic and tuffaceous rocks and are part of the Persimmon Fork Formation that was formed 530 to 580 million years ago when the Carolina Terrane was formed as part of a subduction zone, oceanic island arc complex. The metavolcanics are strongly foliated and are metamorphosed to greenschist facies.

Mafic diabase dikes intruded the Carolina Terrane in the Triassic – Early Jurassic about 200 to 250 million years ago. The dikes strike northwest, dip steeply from 60 to 90 degrees and are dark gray, dense and medium grained. They range in thickness from 1 to 10 m but can be as thick as 30 m. Dike contacts can be faulted with tens of meters of dextral displacement. Lamprophyre dikes are also present, trend ENE, and range in thickness from less than 1 to 2 m.

During mining, groundwater flow directions in the CPS and bedrock hydrostratigraphic units generally reflect topography, except in the immediate vicinity of the pits where depressurization pumping has influenced flow direction and increased hydraulic gradients. Hydraulic testing results and geotechnical assessments suggest declining hydraulic conductivity (K) with depth and the division of bedrock into higher hydraulic conductivity (K), weathered, fractured unit and underlying lower K, unweathered, more competent unit. The tests completed at Snake Pit area suggest that metavolcanics is slightly more permeable than metasediments. High yielding water strikes in metavolcanics in Snake Pit depressurization borings seem to support slightly higher K in metavolcanics, at least in that area.

Based on monitoring of open pit mining operations data around Mill Zone and Snake Pit, weathered and fractured bedrock transmits the majority of the bedrock groundwater flux across the site. Although the underlying, unweathered/competent bedrock is of relatively low K, the unit can be expected to produce water, particularly as more saturated thickness is intercepted as mine development advances in accordance with the mine plan.

A numerical groundwater flow model was developed for the project. The model represents the identified hydrostratigraphic units as 11 model layers:

- Layers 1 - 2: CPS
- Layers 3 - 4: Saprolite
- Layers 5 - 6: Weathered, fractured bedrock


- Layers 7 - 11: Unweathered/competent bedrock with a gradational decrease in K with depth

Site stratigraphic data, meteorological data and groundwater pressure/level data from numerous monitoring wells and vibrating wire piezometers installed in each of the hydrostratigraphic units, and groundwater production data were used to develop the conceptual groundwater model and calibrate the numerical model.

After the model was calibrated under both steady-state and transient conditions, it was used to predict dewatering rates required to facilitate safe and efficient open pit and underground mining. The calibrated model predicts that total dewatering rates from the open pits and underground workings will range from approximately 4,600 to 7,400 m³/day (53 to 85 L/sec) and average around 6,100 m³/day (70 L/sec). The timing and volume of extracted groundwater from the open pits is expected to be manageable.

16.2 Underground Mining Methods

The Project is currently being mined as an open pit mine. Economic mineralization extends below and outside of the pit extents. Mineralization is concentrated in two main zones based on vertical position which form a “horseshoe” geometry over a vertical distance of 350 m. Both zones strike NE adjacent to the siltstone-dacite contact, however, the upper zone dips about 40°NW and the lower zone is near-vertical. The upper zone NW-dipping high-grade lenses of mineralization are focused along bedding-parallel foliation with intense silicification. The Horseshoe fault (NE strike, 40°NW dip) juxtaposes the hanging wall of upper Horseshoe against barren dacite with a sill-like geometry. This geometry extends southwestward into the nearby Snake pit. The steeply dipping Lower Zone is adjacent to the sub-vertical contact with barren dacite. This mineralization will be mined as an underground mine and is referred to as Horseshoe. Figure 16-11 shows the Horseshoe upper and lower mineralized zones.

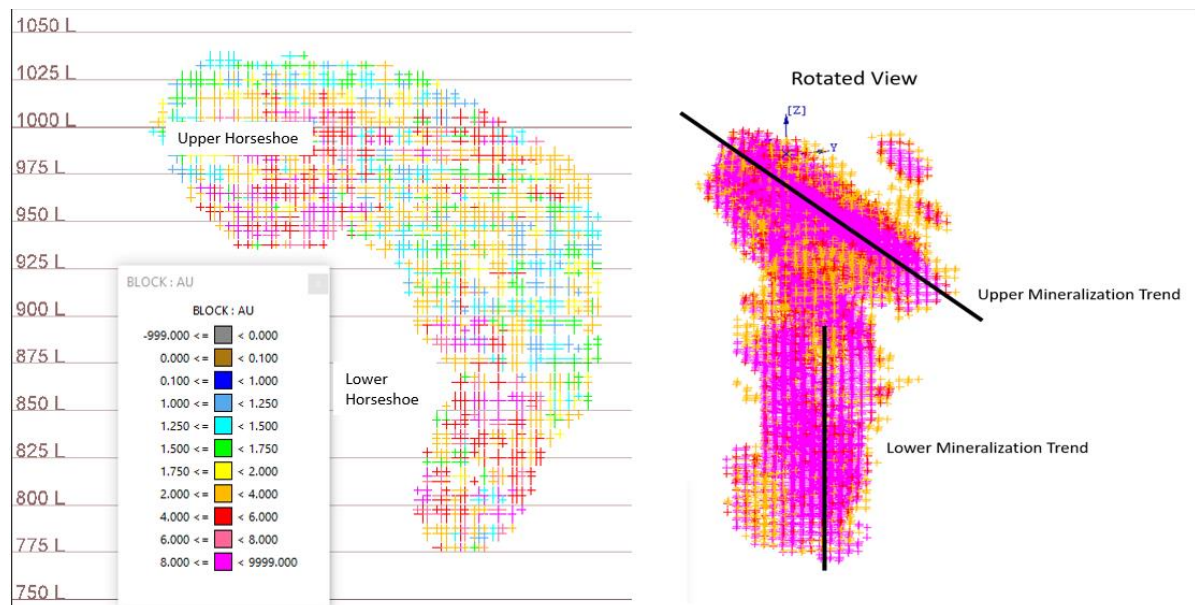

Source: SRK

Figure 16-11: Horseshoe Upper and Lower Mineralized Zones

Based on the orientation, depth, and geotechnical characteristics of the mineralization, a transverse sublevel open stoping method (longhole) with has been selected. The stopes will be 20 m wide and stope length will vary based on mineralization grade and geotechnical considerations. A spacing of 25 m between levels is used. Cemented rock fill (CRF) will be used to backfill the stopes. There will be an opportunity for some non-cemented waste rock to be used in select stopes based on the mining sequence. The CRF will have sufficient strength to allow for mining adjacent to backfilled stopes. Paste backfill could be used instead of CRF and there is ongoing work investigating this possible change.

16.2.1 Cut-off Grade Calculations

Current estimated project costs and the calculated Au CoG are shown in Table 16-22. For mine design, an elevated cut-off grade of 1.67 g/t Au was used, with adjacent lower grade stopes included in the design. Incremental material is included in the reserves based on an incremental stope cut-off grade of 1.29 g/t Au and an incremental development cut-off grade of 0.38 g/t Au.

Table 16-22: Underground Cut-off Grade Calculation


Parameter	Operating CoG	Incremental Stopping CoG	Marginal Development CoG	Unit
Mining cost ⁽¹⁾	44.98	38.39	-	US\$/t
Process cost	10.52	10.52	10.52	US\$/t
Tailings	2.44	2.44	2.44	
G&A	2.75	3.20	3.20	US\$/t
Total Cost	\$61.26	\$54.66	\$16.19	US\$/t
Gold price	1,500.00	1,500.00	1,500.00	US\$/oz
Average Au mill Recovery ⁽²⁾	88%	88%	88%	
Smelting & Refining	3.00	3.00	3.00	US\$/oz
CoG	1.44	1.29	0.38	g/t

Source: SRK, OceanaGold

(1) Includes backfill

(2) Average stated. Variable recovery is expected based on head grade based on the following equation: $(1 - (0.2152 \cdot \text{au grade}^{-0.3696})) + 0.025$


The basis for the FS mine design work is the underground resource model described in Section 15.2. The model is rotated 30° when in site (UTM NAD 83) coordinates to fit the general mineralization/foliation trends. Figure 16-12 shows the block model orientation and mineralized blocks in the underground coordinate system.

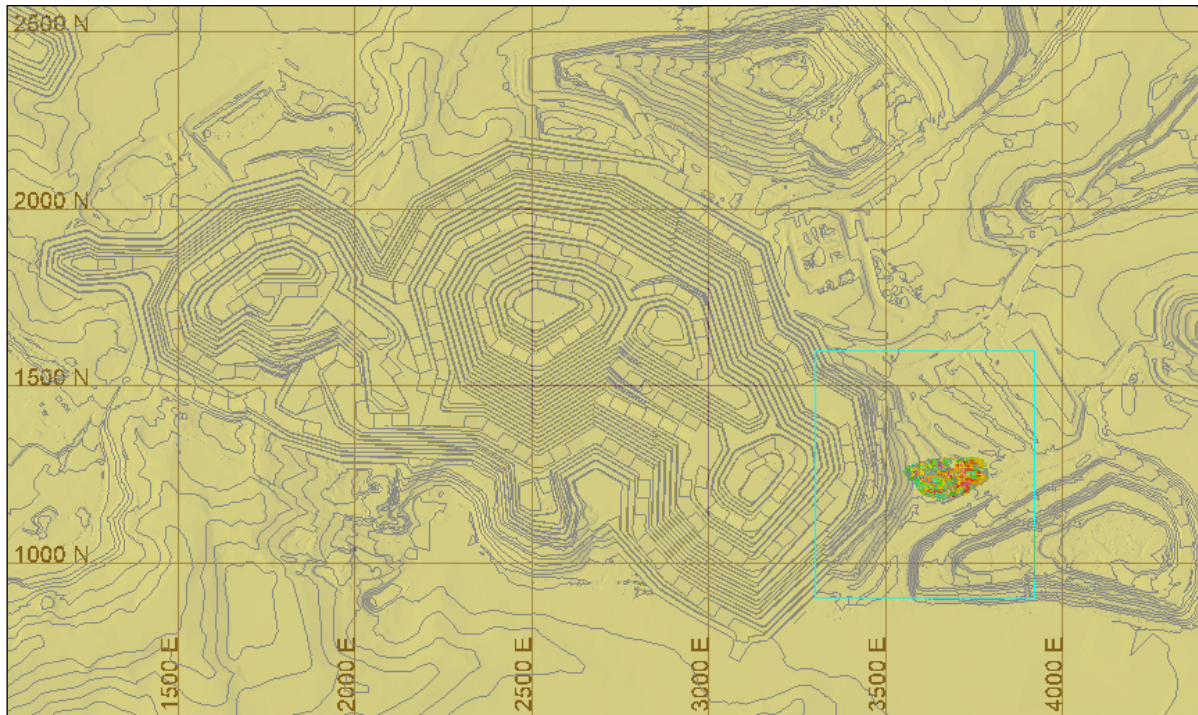

Source: SRK

Figure 16-12: Haile Underground Block Model and Mineralization Extents

Figure 16-13 shows a grade-tonnage curve for the Horseshoe deposit.

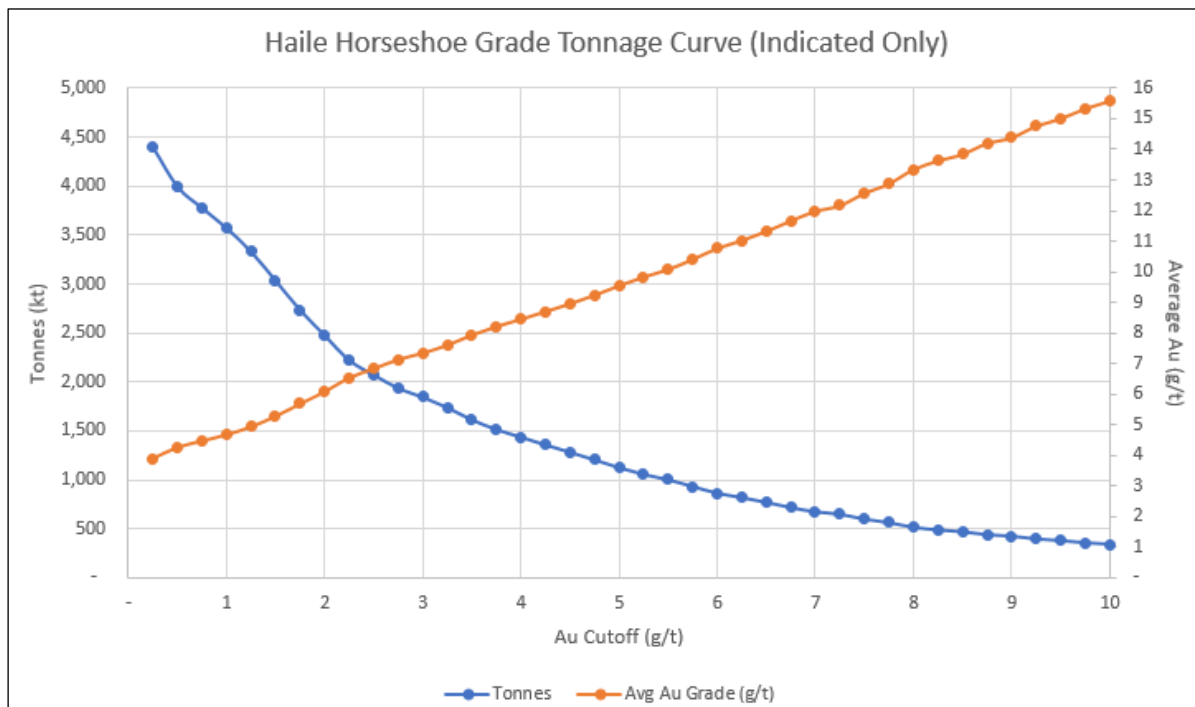

Source: SRK

Figure 16-13: Horseshoe Underground Model Grade/Tonne Curve Based on Au Cut-off

16.2.2 Geotechnical

The 2017 geotechnical field investigation consisted of 14 cored holes designed to examine rock mass fabric and structural features in and around the mineralized zone at different depths and orientations. Since that time, an additional three holes have been drilled/logged geotechnically (DDH-612, DDH-613, DDH-614) totally an additional 456 m.

Drillholes were drilled at varying orientations into the hangingwall, footwall, and mineralized rock. The field investigation included drilling of core, geophysical televiwer borehole logging of structural features, geotechnical core logging, core sample collection for laboratory strength testing. A total of 4,217 m of core was characterized. Two previous geotechnical characterization campaigns were conducted (Golder, 2011; SRK, 2016).

Data from all three campaigns have been combined into a single database. Table 16-23 is a summary of the 7,345 m of core that has been logged for geotechnical characterization. Since that time an additional 3 holes have been drilled/logged geotechnically (DDH-612, DDH-613, DDH-614) totally an additional 456 m. Data from these three holes have not been included in the current geotechnical data analysis. Since the coverage of data from the other 19 holes is adequate for FS design purposes, the geotechnical design parameters based on the database are still considered valid. The field program included in situ stress measurements. A summary of the laboratory testing program for rock strength is provided on Table 16-24.

Figure 16-14 shows a 3D perspective view of the 2017 underground workings with the as-drilled characterization core holes from each drilling campaign. The hole diameters have been enlarged to 40 m to simulate the representative coverage volume for each hole. This figure illustrates that most of the planned mining area and underground infrastructure has been covered by characterization. The updated workings are similar in spatial extents and the geotechnical drillholes have a similar coverage.

Table 16-23: Discontinuity Orientation Data for 2014 Geotechnical*


Drillhole ID	Drillhole Length (m)	Total Discontinuities		Total Discontinuities Logged
		Logged	ATV	
RCT-120	475.8	469	-	469
RCT-122	535.8	273	-	273
RCT-123	693.6	277	-	277
RCT-124	461.7	365	-	365
DDH-517	264.0	215	-	215
DDH-522	258.3	381	-	381
DDH-524	179.8	436	-	436
DDH-533	259.1	315	-	315
DDH-601	121.9	179	425	604
DDH-602	406.9	134	648	782
DDH-603	450.5	364	1,347	1,711
DDH-604	519.1	481	717	1,198
DDH-605	504.9	577	-	577
DDH-606	432.2	625	1,021	1,646
DDH-607	113.4	153	300	453
DDH-608	399.9	226	767	993
DDH-609	403.9	137	805	942
DDH-610	438.3	674	1,404	2,078
DDH-611	426.4	651	1,024	1,675
Total	7,345.5	6,932	8,458	15,390

*An additional 3 holes have been drilled/logged since totaling 456m.
Source: SRK, 2017

Table 16-24: Summary of the Laboratory Tests

Year	Laboratory	Rock Type	UCS	UCSM	TCS	BT	DSS	Total
2009 (Golder OP)	ATT	Metasediments	1	1	4		2	13
		Dike	1	1			-	
		Metavolcanics	2	1			-	
2011 (Golder UG)	ATT	Metasediments	12					12
		Dike						
		Metavolcanics						
2016 (SRK UG)	Agapito	Metasediments	7	8	5	1	3	37
		Dike	1	1			1	
		Metavolcanics	2	2	3	1	2	
2017 (SRK UG)	Agapito	Metasediments	11	9	10	10	6	125
		Dike	3	4		2	1	
		Metavolcanics	21	16	15	9	8	
Total			61	43	37	23	23	187

Source: SRK, 2017

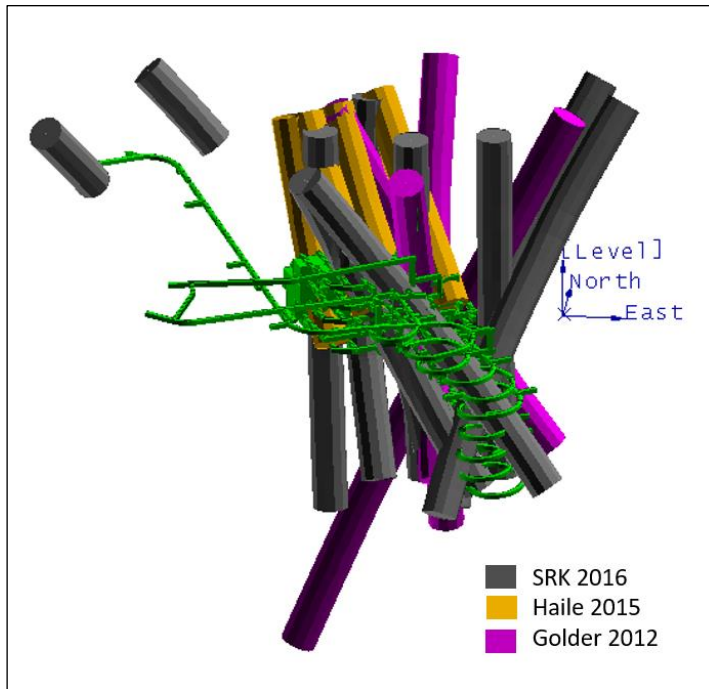


Source: SRK, 2020

Figure 16-14: Horseshoe 2020 Underground Workings with As-Drilled Characterization Core Holes

Rock Mass Characterization

Most of the rock quality designation (RQD) values indicate fair to good rock quality throughout the drillholes (i.e., RQD = 80 to 100). A total of 4,220.5 m of core length were logged with the majority being located within mineralized zone. Areas with lower RQD (i.e., RQD = 10 to 60) were mainly associated with weathered or altered rock and minor geological intrusions (e.g., weathered and fractured metasediments). Fracture frequency in the crown pillar ranged between 0 to 15 fractures per m with an average of 6.5 fractures per m. The fracture frequency in the orebody ranged between 0 to 8.3 fractures per m with an average of 2 fractures per m.

A northwest-southeast cross section through the geotechnical model is illustrated in Figure 16-15. The crown pillar (CP Zone) is the area above the mineralized zone in the fractured metasediments (MS) and metavolcanics (MV). The mineralized zone is in the metasediments. The hangingwall is in the metasediments and the footwall is in the metavolcanics.

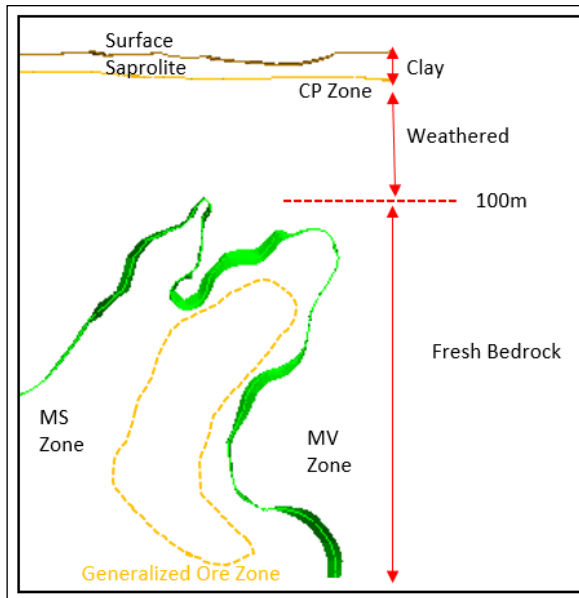

Source: SRK, 2017

Figure 16-15: Geotechnical Model Cross Section (Looking NE)

Drill core is fresh in areas within and adjacent to the Horseshoe orebody. Surficial rocks penetrated by the planned decline within 40 meters of the surface are variably weathered and clay-altered in saprolite. Field strength tests indicate that the fresh rock is, on average, strong (R4). Fresh rock breaks along pre-existing planes of weakness such as veins, bedding, foliation and dike contacts.

Laboratory uniaxial compression strength test (UCS) results show that the strength of the weathered metavolcanic rocks are in the medium-strong range (UCS = 40 to 78 MPa), and fresh metavolcanic strength range is very strong (UCS = 110 to 195 MPa). The strength of the foliated metasediments range is medium strong (UCS = 32 to 70 MPa), and the non-foliated metasediments strength is considered very strong (UCS = 107 to 150 MPa). The dikes are very strong (UCS = 100 to 190 MPa). Table 16-25 through Table 16-27 provides a summary of the laboratory testing results.

Table 16-25: Summary of Point Load (Is_{50}) Test Results

Geotechnical Unit		Mine Zone	UCS Lab (MPa)	K Value	UCS PLT (MPa)			Field Estimated Strength Category (ISRM)
Lithology	Weathering				Mean	Lower Boundary (Px<20%)	Upper Boundary (Px<80%)	
Metavolcanics	Weathered	Crown Pillar	60	18	50	13	85	R2-R3
	Fresh	Hanging Wall	153	27	106	70	145	R4-R5
		Orebody						
Metasediments	Fresh	Footwall	105	21	70	34	105	R3-R4
		Hanging Wall						
		Orebody						

Source: SRK, 2017

Table 16-26: Summary of Strength Properties (σ_{ci} and σ_t)

Geotechnical Unit		Density (t/m ³)	Laboratory Test		Intact Rock Properties from TCS		Elastic Constants	
Lithology	Weathered		σ_t (MPa)	UCS (MPa)	σ_{ci} (MPa)	mi	E _i (GPa)	ν
Metavolcanics	Weathered	2.60	4.4	60	61	14	21.9	0.28
	Fresh	2.70	12.7	153	158	13	73.4	0.24
Metasediments Foliated	Fresh	2.76	6.2	50.5	59	10	41.6	0.24
Metasediments Not Foliated		2.75	11.8	127.8	138	12	58.9	0.24
Dike	Fresh	2.92	12.94	146	-	-	78.7	0.22

Source: SRK

Table 16-27: Summary of Elastic Properties (E_i and ν)

Geotechnical Unit		Mine Zone	UCS (MPa)			E _i (GPa)	ν
Lithology	Weathering		Mean	Low Boundary (Px<20%)	Upper Boundary (Px<80%)		
Metavolcanics	Weathered	Crow Pillar	57	35	80	25.8	0.21
	Fresh	Hanging Wall	148	105	192	73.6	0.23
		Orebody					
		Footwall					
Metasediments	Fresh	Hanging Wall	92	65	120	62.6	0.21
		Orebody					
		Footwall					
Dike	Fresh		146	100	190	78.7	0.22

Source: SRK, 2017

The Rock Mass Rating (RMR₇₆) values ranged from 49 to 68 in the hangingwall rock, with Barton Q' values varying from 4.3 to 19, with most of the rock mass being of fair to good quality. In the footwall metavolcanics RMR₇₆ values were in the 64 to 88 range, with Q' values varying from 7.7 to 30, with most of the rock mass being of Good quality. The mineralized rock had the greatest RMR₇₆ variations, with values between 56 and 79, while Q' values ranged from 5.8 to 24. Table 16-28 summarizes the rock mass characterization data. Overall, the rocks are Fair to Good quality. The table also indicates the quantity of core in each domain.

Table 16-28: Summary of Rock Mass Quality by Domain


Geotechnical Domain	Lithology	Density (t/m ³)	IRS (MPa)	RQD (%)	Fracture Frequency (FF/m)	RMR76/ GSI	Q'
Crown Pillar (13%)	MV	2.60	13 to 86	61 to 100	0 to 15.0	45 to 69	2.8 to 13.5
	MS	2.63	26 to 64	41 to 91	1.2 to 19.2	43 to 62	2.3 to 8.3
	DB	2.91	22 to 140	72 to 100	0 to 11.8	47 to 68	2.2 to 11
Hanging Wall (22%)	MV	2.69	41 to 219	88 to 100	0 to 3.7	63 to 82	10.7 to 26
	MS	2.76	22 to 97	70 to 100	0 to 10.6	49 to 68	4.3 to 19
	DB	2.96	42 to 173	45 to 100	0 to 26.6	39 to 72	0.9 to 9.6
Orebody (50%)	MV	2.70	86 to 205	85 to 100	0 to 5.8	64 to 89	8.3 to 34
	MS	2.75	37 to 125	75 to 100	0 to 8.3	56 to 79	5.8 to 24
Footwall (15%)	MV	2.69	86 to 197	83 to 100	0 to 6.5	64 to 88	7.7 to 30
Decline	DCL<100m MV	2.60	13 to 121	64 to 100	0 to 15.7	46 to 74	1.7 to 18
	DCL>100m MV	2.70	33 to 159	69 to 100	0 to 9.8	52 to 83	5.2 to 27

Source: SRK, 2017

Mine Design Parameters


Transverse longhole mining has been selected as the mining method for the entire orebody. This method requires upper and lower access drifts to be developed from the footwall haulages with a proposed 25 m vertical spacing between levels. The total open stope height in 25 m with the overdrive drift above the open stope. The overall open stope dimensions are 20 m wide x 25 m high x 25 m long (maximum length).

Figure 16-16 is a plan view of the ultimate pit outline with the Horseshoe underground workings. The mine coordinate system has been rotated by 30° from true north to simplify the underground workings such that Horseshoe Underground grid north (HUG grid north) is the hangingwall of the deposit and HUG grid south is the footwall of the deposit. The orientation of the stopes is the same as the 2017 design, so the same geotechnical domains apply to the new design. The mining infrastructure (i.e., ramps, declines, ventilation raises, shops, etc.) are in the footwall offset from the stopes to minimize mining-induced stress damage. Figure 16-17 shows the same plan view, but without the pit outline and with the identified dikes as they traverse the orebody and planned mining. The ventilation system raises are in the low-stress stress shadow of stope mining to minimize potential of mining-induced damage.

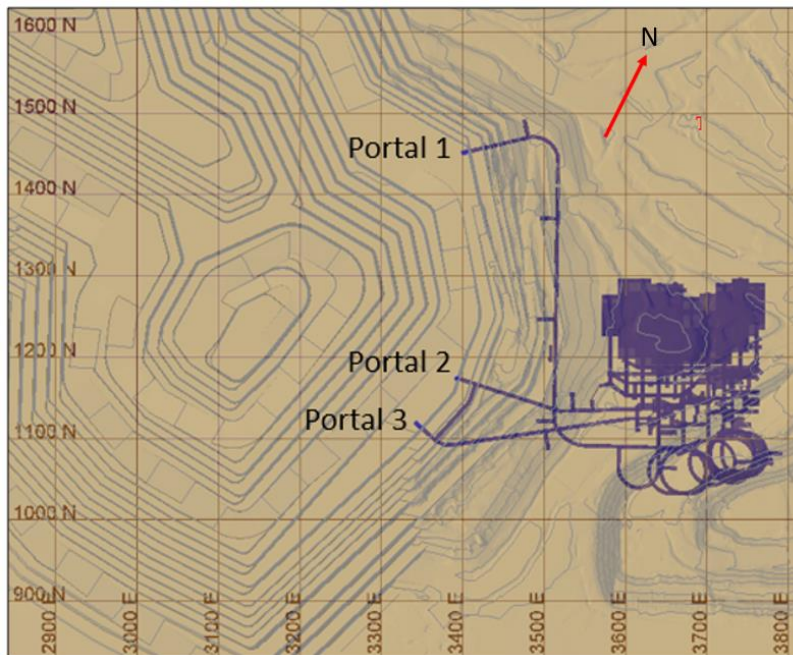

Source: OGC, 2020

Figure 16-16: Snake Pit Showing Slopes Above Proposed Horseshoe UG Portal Locations

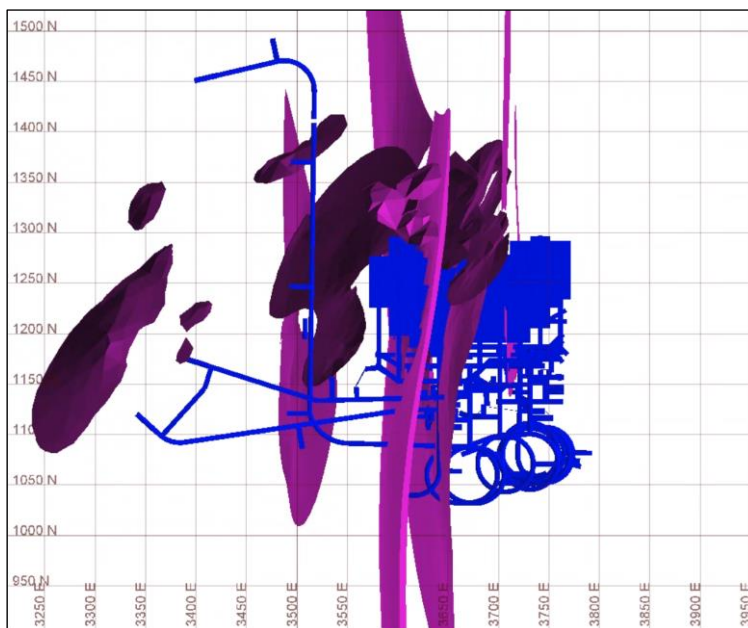

Source: SRK, 2020


Figure 16-17: Plan View of Planned Workings Showing Dikes (local grid)

Figure 16-18 is a plan section through the 930 Level showing proximity of footwall access drifts to planned stopes. To minimize mining-induced damage to long-term access drifts, the setback distances used in the design include:

- Haulage setback of 18 m to 22 m from stopes
- Main ramp setback of 64 m to 70 m from stopes

These values were also confirmed by the results from the numerical model by evaluating induced shear strain locations.

The MAP3D model results (OceanaGold, 2020b) indicate that the stand-off distance between stopes and footwall drives is adequate, but some footwall drives are likely to experience some stress damage as the stoping front retreats toward the south. Fibercrete is recommended for surface support in the footwall drives. The model result also indicates that the stand-off distance between the stopes and main decline is far enough that the ground conditions in the decline should not be affected by stoping. Welded wire mesh surface support will be adequate in the main decline.

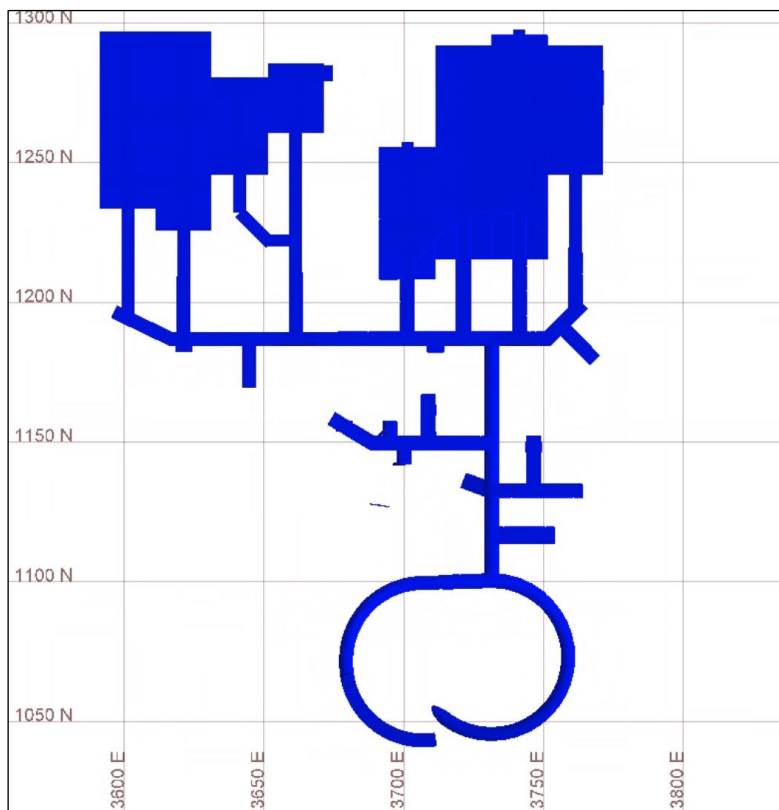

Source: SRK, 2020

Figure 16-18: Plan View of 930 Level Showing Proximity of Footwall Access Drifts to Planned Stopes

Empirical methods of stope design have been employed to evaluate stability conditions. The Stability Graph Method (Mathews et al., 1981), as modified by Potvin et al. (2001), is based on more than 480 case histories worldwide and has been used to size stopes so they remain stable during mining. The stability graph method plots the stability number (N') on the vertical axis against the hydraulic radius (wall area divided by wall perimeter) of the stope wall or back on the x axis. The stability number is calculated based on the rock mass quality (Q' system), geologic structure and induced stress conditions. The stability of the stope walls has been checked using Matthews method to ensure that

remote mining equipment can extract all the ore in an unsupported stope without being buried by falling ground.

Dilution was estimated using the method developed by Clark and Pakalnis (1997) based on an extensive set of case histories for open stopes. The method predicts the quantity of unstable wall rock for a given rock mass quality from a given stope size. The thickness of external dilution is estimated as equivalent linear overbreak/slough (ELOS). Table 16-29 summarizes the ELOS dilution assumptions used for mine planning purposes. ELOS estimates were made for open stopes in each geotechnical domain and at three stress conditions (shallow, medium and deep levels).

Table 16-29: Summary of Dilution ELOS Estimates

Type	ELOS Value (m)
Sidewalls (rock)	0.50
Sidewalls (backfill)	0.25
Endwalls (rock & backfill)	0.15
Bottom (backfill)	0.05

Source: SRK, 2020

Stability of the stopes for the updated underground workings have been checked using a mine-scale numerical model. The MAP3D numerical program was used to simulate the mining sequence. Results of the analysis confirm that the stopes are predicted to remain stable during active mining. The focus of this modeling was to assess the potential for mining double stack primary and secondary stopes. Conclusions from this stability analysis include the following.

- Stress damage to primary stope sidewalls could result in secondary stopes having backfill dilution when secondary stopes are mined, and this problem could be more serious in double-lift primaries since damage is predicted deeper in the sidewalls. If this is a major problem, then the sequence can be adjusted to either single-lift primaries and secondaries, or continuous retreat sequence where slender ore pillars are avoided.
- The model also indicates stress damage in secondary pillars which might result in drilling difficulties in the secondaries. This can be overcome by either using up-holes or going to “just-in-time” drilling to avoid re-drilling.
- Although modeled conditions need to be verified with experience from early stoping, the experience can be used to modify alternative ground support, stope design and stoping sequence to mitigate stress damage issues depending on actual conditions.

Backfill

The mining method employs primary/secondary stoping sequence. The primary stopes will be backfilled prior to mining the adjacent secondary stopes.

The required strength of cemented rockfill (CRF) placed in primary stopes has been checked for stability under the critical conditions of mining the adjacent secondary stopes. The secondary stopes must remain stable so remote equipment can safely muck the ore without being buried by ground fall. A numerical model was used to assess the minimum backfill strength requirements. The model results indicate that a minimum UCS strength of 0.7 MPa is required after 14 days of curing to accommodate the mining cycle. Laboratory tests results on batches of cemented rockfill indicate that this required strength can be achieved using 4% cement by mass and a water-to-cement ratio of 2.0 with aggregate from waste rock currently available. The CRF mix designs at Haile will be based on two cement contents: 3.8% and 4.8% GP cement by dry mass. The aggregate will consist of NAF waste that is

crushed and screened to -80 mm. It will also have a sufficient amount of fines to eliminate vuggy backfill and create a relatively low rill/beach angle for CFR, (i.e. less than 20° will be required to achieve 'tight-fill' conditions in the 'stope wings' located below the upper ore drive. Technically, this is cut and fill (CAF) backfill. The 4.8% CRF might have a 28-day UCS ranging from about 1.7 to 3 MPa if the placed mix is relatively free of vugs. For the sill pillar recovery, the curing time will be much longer than 28-days and will likely be even stronger than the 28-day UCS.

Recent testing is being conducted by Outotec (2020) on pastefill material as an alternative to CRF backfill. CRF is assumed as the base case backfill material for the FS design. Should testing indicate that the required 0.7 MPa UCS strength can be developed in 14-day curing, then the backfilling concepts will be advanced. A tradeoff study between CRF and pastefill was been recently conducted by AMC (2019). That study concluded that the improvement in safety of backfill operations, improvement in fill quality with reduced dilution and the ability to achieve tight filling for improved ground stability make the paste fill option the preferred choice for Haile underground mining options. Some credits from underground tailings disposal and extensions to the underground mine operations will further improve the economics of that choice. However, for this study, CRF is assumed as the base case backfill material.

Ground Support and Drift Stability

For Haile, fibercrete and welded wire mesh was only considered for surface support. Galvanized wire mesh was selected for the main decline and access drives. Black wire mesh was selected for ore drives and slot drives. These four types of drives account for most lateral development meters. Fibercrete was selected for all other types of excavations, e.g. stockpiles, decline intersections, sub stations, pump stations, backfill cuddies, escapeways, RAR/FAR breakthroughs, RAR drives, and footwall drives. These types of drives require more robust surface support for several reasons. For example, footwall drives will have truck loading bays and will also experience stress changes. RAR's have a high potential for steel corrosion. Pump stations and sub-stations cannot be easily rehabilitated once the infrastructure is installed.

In all lateral development, the surface support will extend down to the gradeline (nominally 1.5 m above the design floor elevation).

Ground support requirements were estimated using empirical support charts developed by Barton (1974). The method relates the rock mass quality (Q) to the equivalent dimension of the excavation (*De*). *De* is the ratio of the excavation width (D) to the excavation support ratio (ESR) index, which relates the use of the excavation to the degree of safety required. ESR parameters were assigned to each type of excavation within the framework of the empirical method. Table 16-30 is a summary of the drift dimensions for which ground support has been provided.

Table 16-30: Design Parameters for Different Drift Types

Excavation	Type Excavation	Opening Dimension W x H (m)	ESR	D	De
Decline <150 m depth	Long Term (LoM)	5.0 x 5.5	1.6	5.5	3.4
Main Ramp >150 m depth	Long Term (LoM)	5.0 x 5.5	1.6	5.5	3.4
Footwall Accesses	Medium Term (0.5 to 1 year)	5.0 x 5.0	2	5.0	2.5
Stope Accesses	Short Term (1 to 6 months)	5.0 x 5.0	2.5	5.0	2.0

Source: Barton, 1974

Various levels of support were specified for each range of rock quality. Table 16-31 is a summary of rock mass quality for each ground support type. The long-term ground support for access drifts in the footwall area have been specified to maintain safe access to infrastructure and ore haulage from the stopes back to the hoisting shaft while those drifts are still required.

Table 16-31: Summary of Rock Quality for Each Ground Support Type

Drift Type	Ground Condition Type	Rock Zone	Q			Support Category
			Class	Range	Portion of Drifting	
Decline	1	Metavolcanic Weathered	Very Poor	0.1 to 1	19%	IV
	2		Poor	1 to 4	47%	III2
	3		Fair	4 to 10	24%	II2
	4		Good	>10	10%	I2
Main Ramp	2	Metavolcanic Fresh	Poor	1 to 4	19%	III2
	3		Fair	4 to 10	39%	II2
	4		Good	>10	42%	I2
Footwall Access	5	Metavolcanic Fresh	Poor	1 to 4	19%	III1
	6		Fair	4 to 10	39%	II1
	7		Good	>10	42%	I1
Stope Access	8	Metavolcanics/	Poor	1 to 4	19%	III1
	9	Metasediments	Fair	4 to 10	39%	II1
	10	Fresh	Good	>10	42%	I1

Source: SRK, 2017

Specifications for each classification of ground support utilized in distinct types of ground have been revised since the 2017 FS design. The backs and upper sidewalls of capital development will use 2.4 m long by 25 mm diameter fully encapsulated resin bolts. The lower sidewalls of capital development will be supported with 1.8 m long by 46 mm diameter galvanized friction bolts (Split Sets). The resin bolts should have some type of corrosion protection, e.g. epoxy or galvanizing. These types of drives are expected to have a service life of between 2 to 10 years.

The backs and sidewalls of ore drives, and slot drives will be supported with 1.8 m long by 46 mm diameter black friction bolts. These drives are not expected to have a service life greater than two years, thus no need to consider corrosion protection.

Ground support recommendations for the 2020 design considers as “best practice” to install cable bolts at all lateral development intersections, spans wider than 7.5 m, stope brows wider than 4 m, and open stope backs (depending on the span and ground conditions) in accordance with Australian mining industry practices. The ground support design includes specific cable bolt designs using 2 to 15 mm

diameter strands of bulbed black cable (standard twin-strand cable bolts). The cable bulbs are 25 mm diameter and spaced every meter along the length of the cable. The cable bolt lengths will be standardized as either 6.3 m or 8.3 m twin-strand units. The standard borehole lengths will either be 6.0 m or 8.0 m long. A 0.3 m tail is required for tensioning one of the two strands with a steel plate, barrel and wedge.

The 8.3 m cable bolts are only used for supporting stope crowns. The 6.3 m cable bolts are used for stope brows, or in lateral development with spans exceeding 7.5 m, e.g. decline passing bays or 3-way intersections.

The cable bolt patterns for lateral development are assume a hypothetical volume of material above the backs. The volume is based on the geometric shape of a parabolic dome with a height equal to one-third of the span. The cable bolts are intended to provide long-term support for deep wedges that may loosen-up due to degradation over time, adjacent blasting, or mining-induced stress changes. The “parabolic dome” design method has been used described by geotechnical consultants in Australia (Rosengren), and in Canada (Pakalnis).


A series of drift layout and ground support drawings have been developed by HGM for the FS Underground project using the parameters in Table 16-30 (OceanaGold, 2020c). Figure 16-19 illustrates the ground support layout for level assesses and decline drifts (5W x 5.5H) with arched back. The following additional design drawings have been developed:

- Face Support (typical)
- Decline Passing Bay (10W x 5.5H)
- Decline Stockpile, Footwall Drive, Ore Drive (first 20 m), Pastefill Cuddy and FAD/RAD Drives (5W x 5.5H)
- Ore Drive beyond 20 m and Cross Cut (4.5W x 5H)
- Pump station Drive (5.5W x 5.5H)
- Escapeway Drive (4.5W x 5H)
- Loading Bay ((5W x 7H)
- Level Sump (5.5W x 5H)
- Slot Drive (5.5W x 5H)
- FAD RAD BT (6W x 5.5H)
- Substation (6W x 5H)
- CRF Stockpile (5W x 7.5H)
- Jumbo Starter Cuddy (6W x 4H)

GROUND SUPPORT QUANTITY AND SPECIFICATION

Nominal Cut Length = 4.3 m

JBAR BOLT	Diameter	25 mm
	Bolt Length	2.4 m
	Backs Bolt Spacing	1.2 m
	Walls Bolt Spacing	1.2 m
	Ring Spacing	1.2 m
RESIN	Size	30mmØ x 2.4m
FRICTION LOK	Diameter	46 mm
	Bolt Length	1.8 m
	Bolt Spacing	1.2 m
	Ring Spacing	1.2 m
WIREMESH	Size	2.8mW x 4.8mL x 5.3 mm Thickness
	Wire Opening	100mm x 100mm
FIXTURES	Combi Volcano Plate	(300mm x 300mm; 150mm x 150mm)
	Combi Dome Plate	(300mm x 300mm; 150mm x 150mm)
MINIMUM QUANTITIES PER CUT	JBar Bolt	21 pcs.
	Resin Cartridge	21 pcs.
	1.8m Friction Bolt	12 pcs.
	0.9m Friction Bolt	14 pcs.
	Wiremesh	5 pcs.
	Combi Volcano Plate	21 pcs.
	Combi Dome Plate	26 pcs.
INSTRUCTIONS: - Install wiremesh even to the Grade Line. - Wiremesh overlap must be at least 300mm or 3 mesh squares - Install additional ground support when required. - Face Support Standard is in a separate drawing		

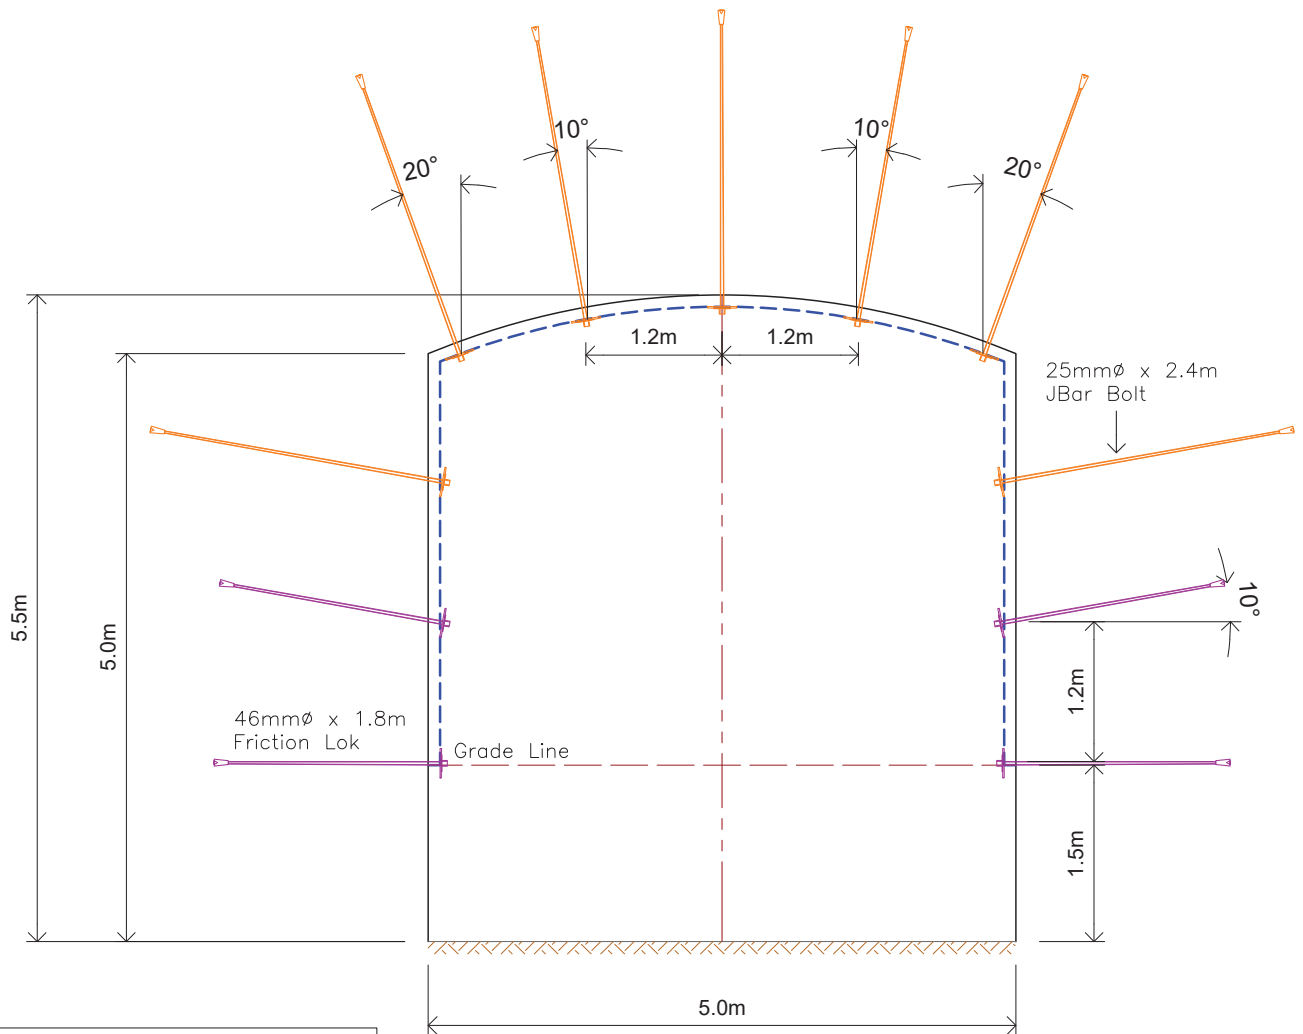

NOTE:
This profile will be used for Level Access and Decline drives.

DRIVE DESIGN (FRONT VIEW)

GEOLOGY SUPERINTENDENT.	OPERATIONS SUPERINTENDENT.	PROJECT MANAGER	PROJECT DIRECTOR	GSS_A_WM Level Access and Decline 5.0mW x 5.5mH Arched Back	
DATE :	DATE :	DATE :	DATE :		


Plotted By: Chidpa Geotechnical Team Cad File No: N:\D:\p1028 P10 Execution\Underground\GT Geotechnical\GT01_Working Folder\GT01_23 Desktop2 SOFTWARE\AutoCAD File\HUG Ground Support_v3.dwg

Figure 16 19: General Ground Support Drawing for Level Assesses and Decline Drifts with Arched Back

MAP3D numerical modeling results predict that altered dike intersections with lateral development should anticipate stress damage along ore drive sidewalls, backs, and footwall /over-drive bullnose pillars. The altered dike intersections with lateral development is only expected about once on each level. The stress damaged areas can be managed by using fibercrete for surface support.

Sill Pillar Stability

The updated design does not include leaving a 5 m permanent sill in the design. HGM has added to the updated design two temporary sills, shown on Figure 16-20, which will be extracted late in the life of the mine. This allows mining to spread out across three panels. For the CRF scenario, the recoveries of the temporary sill levels have been reduced by 25% because the sill will be mined by a room-and-pillar method (i.e. no filling) with island pillars on backfill or by small modified open stope method. This is due to not having top access and not being able to fill these stopes. If pastefilling is adopted, it will be easier to backfill these stopes since leaving unbackfilled areas is unfavorable for stability. Once mining experience is obtained, sill mining strategy will be reassessed.

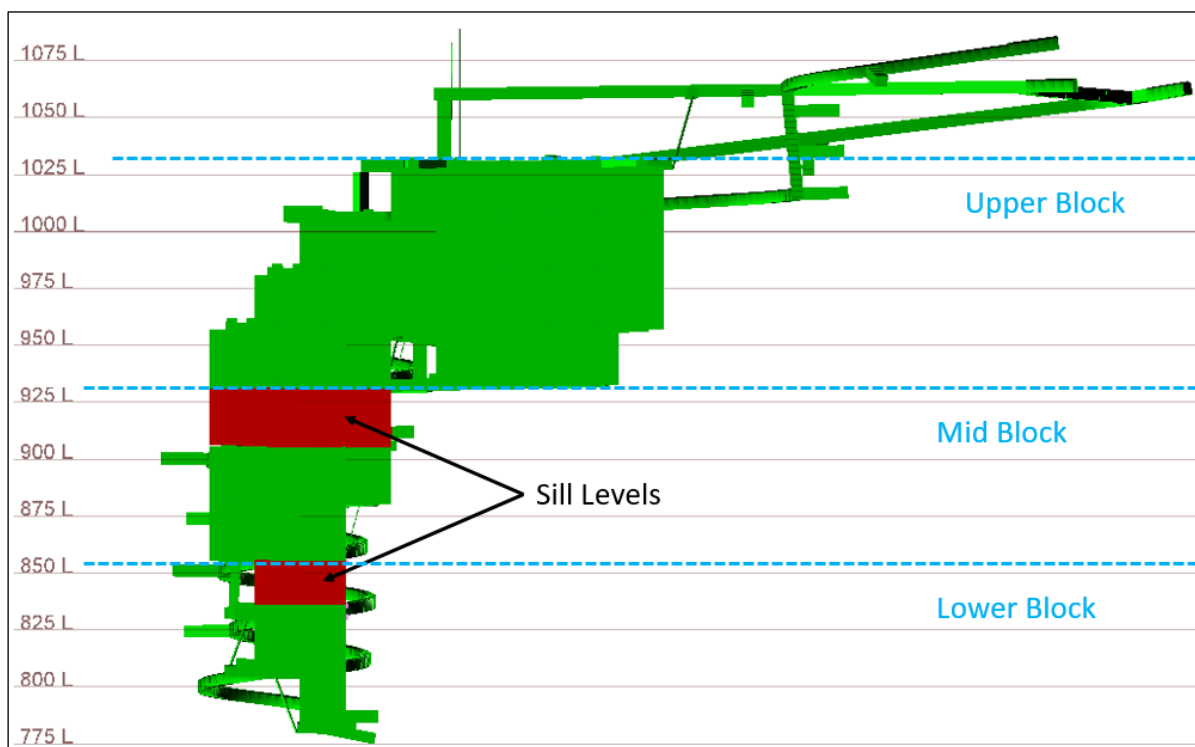

Source: HGM, 2020


Figure 16-20: Sill Pillars (Red Stopes) to be Extracted Late in Mining Sequence

Crown Pillar Stability

The crown pillar above the mine has been checked for stability against ground collapse back to the surface. The estimated factor of safety is estimated using empirical crown pillar stability methods (Carter, 1980) to be significantly greater than 1.5, especially considering the top stopes will be tightly backfilled. The stability was confirmed by numerical modeling, which predicts no rock mass failure in the crown pillar area above mining and the stress arch above stopes is maintained.

Surface subsidence has been analyzed in the FLAC3D numerical model to assess the potential for damage to the infrastructure above the mine or inflow of surface waters. Figure 16-21 shows the predicted subsidence above the underground mine. This analysis evaluated the 2017 stope layouts but results for the updated 2020 layout are expected to be very similar since stoping areas are similar, although the stoping sequence is slightly different. The extents of the nearby Snake pits are seen on the left-hand side of the figure as are the faults simulated in the model. The maximum predicted vertical subsidence above the mine will be less than 2 cm. The location of the maximum subsidence is influenced by movement along faults that intersect mining.

The recent MAP3D numerical modeling results indicate that relatively small zones of stress-damaged rock (up to 10 m) should be anticipated in the crown pillar, sill pillars and along abutments. These zones can be managed with cable bolts and backfill. Tight-fill in the stopes does not need to be perfect, but it is required to minimize dilution from the backs while extracting secondary stopes.

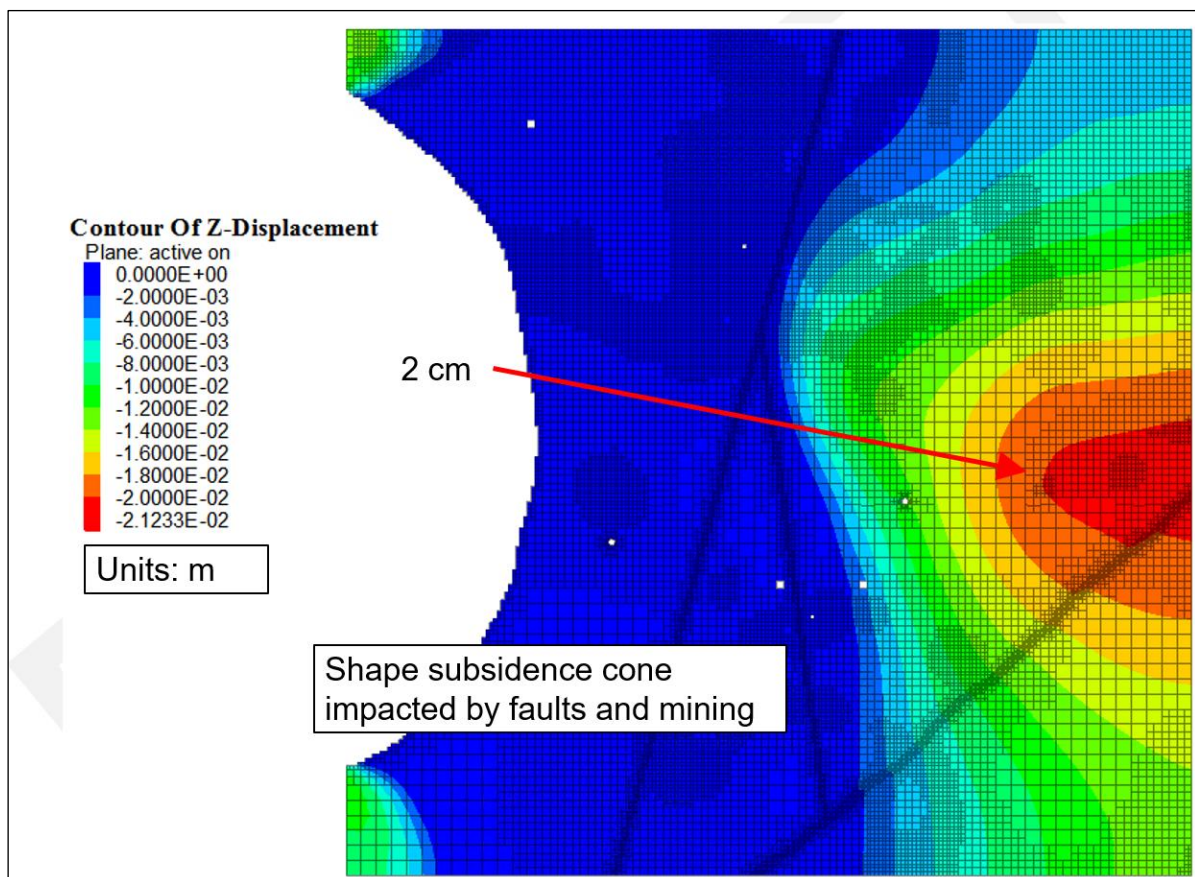

Source: SRK, 2020

Figure 16-21: Plan View of Vertical Displacements Representing Surface Subsidence

Portal Stability

Three access portals are planned, as shown on Figure 16-22. The most northern portal will be the first to be driven from the pit wall area. Batter face ground support design for Portal 1 includes the following (OceanaGold, 2020d):


- Shotcrete-sprayed safety bund (windrow) along the 1,100 m berm to provide additional catchment capacity and prevent falling rocks from rolling down the portal. The windrow will have built-in drainage holes to manage running water during rainfall events. The windrow has a nominal height of 1.5 m, and 20 m long. This can be extended if required.
- There are four rows of triple-strand 8.3 m cable bolts along 1,097 m, 1,093 m, 1,089 m, 1,085 m.
- The cable bolts are spaced 4 m vertical, and 2 m horizontal. The cable bolts will stabilize the largest wedges and can provide an FoS = >2 for all underground portals.
- Rock bolts and friction bolts will be installed along 1,087 m, 1,083.5 m and 1,082 m to provide ground support for smaller scale structural failures and to pin the drape mesh at the toe of the batter.
- The entire batter face, which has a dimension of 20.5 m slope distance and 20 m wide will be sprayed with 100 mm shotcrete. This will become an effective surface support.
- The entire batter face will be covered with drape mesh. The mesh will be pinned by cable bolt plates, rock bolt plates, and friction bolt plates.
- The batter of the portal will have effective drain holes. The drain holes are 12 m deep, to drain water at the back of the slope. The spacing of the drain holes is 4 m vertical and 4 m horizontal. The first row of drain holes is at 1,094 m and the second row is at 1,090 m. The friction bolts installed at the toe of the batter will serve as drain holes.

The ground support design for the decline (5.5W x 6H) at the Portal is illustrated on Figure 16-22.

GROUND SUPPORT QUANTITY AND SPECIFICATION

Nominal Cut Length = 2.5 m

JBAR BOLT	Diameter	25 mm
	Bolt Length	2.4 m
	Backs Bolt Spacing	1.4 m
	Walls Bolt Spacing	1.4 m
	Ring Spacing	1.2 m
RESIN	Size	30mmØ x 2.4m
TWIN-STRAND CABLE BOLT	Diameter	15.2 mm
	Cable Length	6.3 m x 2
	Cable Bolt Spacing	1.5 m
	Cable Ring Spacing	2.5 m
WIREMESH	Size	2.8mW x 4.8mL
	Wire Opening	100mm x 100mm
FIXTURES	Combi Volcano Plate	(300mm x 300mm; 150mm x 150mm)
	Combi Dome Plate	(300mm x 300mm; 150mm x 150mm)
	Flat Plate	200mm x 200mm x 12mm Thick
FIBRECRETE	Minimum Thickness	100 mm
	Minimum Shotcrete Volume	14 m3
MINIMUM QUANTITIES PER CUT	JBar Bolt	33 pcs.
	Resin Cartridge	33 pcs
	0.9m Friction Bolt	15 pcs
	Cablebolt	2 pcs.
	Wiremesh	5 pcs.
	Combi Volcano Plate	33 pcs.
	Combi Dome Plate	15 pcs.
	Flat Plate	2 pcs.
INSTRUCTIONS:		
- Spray Fibrecrete to the floor - Install Jbar Bolt 1.6m from the floor. - Install additional ground support when required. - Face Support Standard is in a separate drawing		

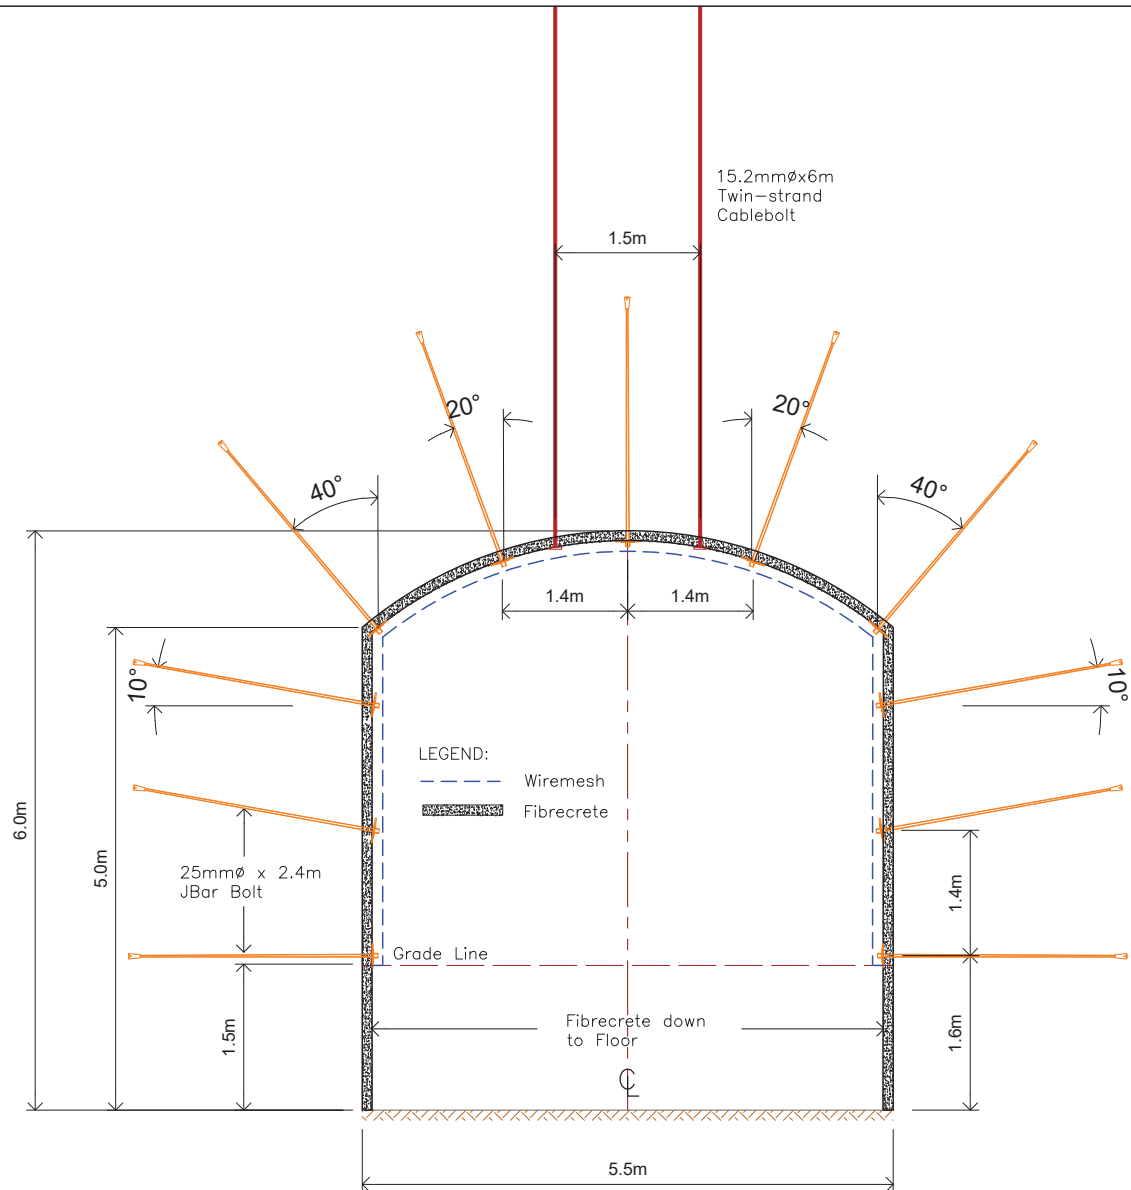

GEOLOGY SUPERINTENDENT.	OPERATIONS SUPERINTENDENT.	PROJECT MANAGER	PROJECT DIRECTOR	GSS_Z_FC Portal 5.5mW x 6.0mH Arched Back	
DATE :	DATE :	DATE :	DATE :		

Plotted By: Chidipriya Geotechnical Team Cad File No: N:\Dipriya\2024\PGO Execution\Underground\GT Geotechnical\GT01_Working Folder\GT01_23 Desktop2 SOFTWARES\AutoCAD File\FHG Ground Support_v3.dwg

Figure 16 22: Ground Support Drawing for Decline Drift at Portal 1

Similar design and approach will be implemented in Portal 2 and Portal 3. It is planned that all the ground support requirements of the batter be carried out during pit mining when actual ground conditions are known.

16.2.3 Hydrogeology and Mine Dewatering

The hydrogeology of the Site is summarized in Section 16.1.9. The planned underground mine workings will extend to a depth of approximately 380 m below ground surface and will be accessed by a decline from Snake Pit. The planned mine development will intersect the weathered, fractured bedrock and the underlying unweathered/competent bedrock hydrostratigraphic units. As described in Section 16.1.9, weathered, fractured bedrock will likely be the predominant source of groundwater inflows to the underground workings. Dewatering of the underground workings will be accomplished by capturing water entering the tunnels and pumping the water to the surface of the open pit where the water will be evacuated. Dewatering rates from the underground workings have been estimated using the groundwater numerical model (Section 16.1.9) and range from approximately 900 to 1,700 m³/day (11 to 21 L/sec), with an average rate of 1,300 m³/day (16 L/sec). The timing and volume of extracted groundwater from the underground workings is expected to be manageable.

16.2.4 Geochemical

The objective of the underground geochemical program was to determine the metal leaching (ML) and acid rock drainage (ARD) potential of development rock that would be generated from the underground operations, including tailings and cemented rock fill (CRF), from test programs that were done to evaluate the geotechnical and geochemical properties of materials being evaluated for underground backfill.

Previous Work

Development rock generated from mining at Haile has a range of ML and ARD potential, depending on lithology. For the underground work, the Schafer (2015) characterization categories are used.

The source of ARD is sulfide minerals, principally pyrite, deposited by the hydrothermal alteration that also deposited gold. Starting in 2008 and culminating in 2015, Schafer (2015) performed an extensive geochemical characterization program of existing and future mine development rocks to identify, manage and mitigate geochemical risks at Haile as part of the open pit plan. The characterization program included static testing of 4,911 samples as well as kinetic testing of nine samples of overburden and one tailings sample. The current development rock management plan employs three categories based on combinations of the total sulfur content (S_T) and net neutralization potential (NNP). The NNP is a measure of overall acid generation potential calculated as the difference between the neutralization potential (NP) and AP. The categories of potentially acid generating (PAG) development rock are:

- Red PAG – Strongly acid generating:
 - $NNP < -31.25 \text{ kg CaCO}_3/\text{t}$
- Yellow PAG – Moderately acid generating:
 - $S_T > 0.2 \%$ or NNP between 0 and $-31.25 \text{ kg CaCO}_3/\text{t}$
- Green – Not acid generating:
 - $S_T < 0.2 \%$ and $NNP > 0 \text{ kg CaCO}_3/\text{t}$

The geochemical categories, and their associated management approaches, of development rock and saprolite within 15 m (50 ft) of the bedrock contact are summarized in Table 16-32.

Kinetic testing of “Red” and “Yellow” PAG material confirmed the applicability of the development rock classification scheme based on results of static tests, which included:

- Test work over 140 weeks on Red PAG samples developed low pH values (1.6 to 2.2) and released sulfate corresponding to one-third to one-half of the pyritic sulfur originally contained in the sample.
- Yellow PAG samples also had acidic pH values, though generally higher than Red PAG. High concentrations of metals were also released from these samples. Cumulative sulfate leached was much lower than for Red PAG samples owing to the lower levels of pyritic sulfur.
- Green overburden samples maintained near neutral pH and also maintained low to non-detectable sulfate levels.

Table 16-32: Current Open Pit, and adopted UG Overburden Classification at Haile

Operational Testing Criterion	Overburden Abundance	Characteristics	Proposed Management
Red PAG - strongly acid generating overburden			
Found in Metasediment Unit. For Metasediment, NNP < -31.25 kg/t as CaCO ₃	About 38% of Metasediment unit	When oxidized, contact water will have low pH (< 3.0) and very high metals, sulfate and acidity (>5,000 mg/L)	Stored in geomembrane encapsulated PAG cell, placed in lifts, compacted and Saprolite-lined outside perimeter to reduce oxygen supply
Yellow PAG - moderately acid generating overburden			
Found in Metasediment and Metavolcanic Bedrock Units and Saprolite. For bedrock, Total S > 0.2% or NNP < 0 and NNP > -31.25 kg/t as CaCO ₃ . For Saprolite within 50 feet of bedrock contact, Total S > 0.2% and NNP > -31.25 kg/t as CaCO ₃	About 22% of Metasediment unit, 6% of Metavolcanic unit, and 5% Saprolite	If allowed to oxidize, contact water will have low pH (3.0 to 4.0) and low to moderate metals (mostly Fe & Al)	Managed as above then may be placed in lifts as subaqueous pit backfill (2 lbs/t lime added as needed and 5-ft saprolite cover)
Green Overburden - not acid generating			
Found in Metasediment and Metavolcanic Bedrock Units, Saprolite and Coastal Plain Sands. For Bedrock, Total S < 0.2% and NNP > 0 kg/t as CaCO ₃ . For Saprolite within 50 feet of bedrock contact, Total S < 0.2%. All Saprolite more than 50 feet above bedrock and all Coastal Plain Sand is Green Overburden.	40% Metasediment Unit, 94% Metavolcanics, 95% Saprolite and all Coastal Plain Sand	Contact water may have moderately acidic to alkaline pH (4.0 to 8.0), sulfate low (<1,000 mg/L) and metals non-detectable.	Placed in unlined overburden piles. Runoff will not require treatment assuming it meets storm water requirements as expected


Source: Schafer, 2015

Sample Collection - Development Rock

The initial sampling program completed for the PEA level characterization involved collection of 24 samples, including eight that are representative of the Horseshoe deposit (SRK, 2016b). The FS-level study was a continuation of the site wide geochemical characterization by previous investigators and the PEA level characterization of the three underground targets (Horseshoe, Mustang and Mill Zone Deep) performed by SRK in 2016, and expanded the scope to provide detailed geochemical characterization data for development rock from the Horseshoe underground area. The characterization work is also considered to adequately represent the development rock as defined in the recently updated mine plan. The FS SAP did not include collection and testing of tailings.

Based on the objectives of the FS-level characterization, 76 core samples were collected and selected for analyses. Samples were selected to provide the full range of the principal lithologies and to cover the vertical range of each area. All proposed samples are within approximately 50 m of the anticipated mining infrastructure.

The distribution of samples by lithology is shown in Figure 16-23. Samples were collected from all the lithologies within the potential mine infrastructure in approximately the same distribution as the anticipated volume of development rock estimated in the PEA (SRK, 2016a). Certain lithologies with potentially high ARD potential (such as pyritic laminated metasediment) were selected for analysis, even though they make up a small percentage of the total anticipated development rock stream. The design of the FS sampling and analysis program was documented in the FS SAP (SRK, 2016b).

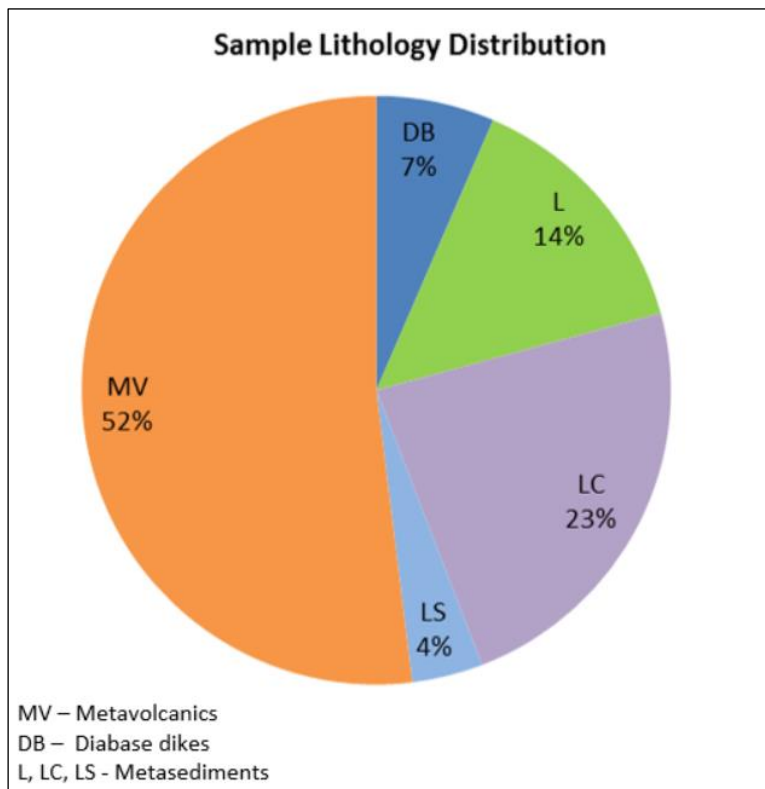

Source: SRK

Figure 16-23: Horseshoe FS/PEA Lithological Distribution of Samples

Sample Collection - Backfill Testing

There are currently two backfill options being considered: CRF and cemented paste backfill. In the initial mine plan, CRF was the primary option considered. As the mine plan evolved and more knowledge was gained regarding logistical requirements of the different options, OceanaGold began to favor the alternate backfill option of cemented paste backfill.

To generate geotechnical data needed to evaluate the initial CRF option, SRK's geotechnical engineers designed the backfill testing program to evaluate the properties of CRF generated from a surface plant using aggregate (development rock) from the open pits and underground development rock (SRK, 2017). After the geotechnical testing was completed, 18 samples of the material were tested at SGS (Canada) Inc. in Vancouver B.C. for ML/ARD potential. Table 16-33 shows the batch numbers that were analyzed, the corresponding material type, and the volume of cement that was added during the geotechnical testing.

Schafer Limited is currently evaluating the geochemical properties of the paste backfill option with a comprehensive suite of tests. The tests are still in progress, so no results are yet available to report. Preliminary indications are that the test results look favorable (B. Schafer, written commun).

Table 16-33: Backfill Samples

Sample ID	Material Type	Cement Content (%)
1	NAG metasediment	3.86
2	NAG metasediment	1.94
3	NAG metasediment	5.78
4	NAG metavolcanic	3.79
5	NAG metasediment	1.90
6	NAG metasediment	5.66
7	PAG metasediment	3.85
8	PAG metasediment	1.93
9	PAG metasediment	5.76
10	NAG metavolcanic	3.84
12	NAG metavolcanic	5.74
14	NAG metavolcanic	1.96
15	NAG metavolcanic	5.83
16	NAG metasediment	3.75
17	NAG metasediment	1.88
19	NAG metasediment	4.14
20	Sand	2.07
21	NAG metavolcanic	6.60

Source: SRK

Summary of Analytical Results

Samples were analyzed for static geochemical characteristics using methods similar to those used for the overburden geochemical characterization program (Schafer, 2015). A range of methods was used for sulfur species and sources of NP to evaluate the various sources of AP and NP, and potential differences between analytical methods. Samples were analyzed for the following parameters:

- Paste pH (Sobek et al., 1978)
- Sulfate via hydrochloric acid (HCl) digestion with ICP-OES analysis
- Total sulfur by LECO furnace
- Total carbon by LECO furnace
- Total inorganic carbon (HCl leach)

- Modified NP (Lawrence, 1989)
- NP (Sobek et al, 1978)
- Single addition net acid generation (NAG) test (AMIRA, 2002)
- Trace metal analysis, using aqua regia digestion with ICP-OES/MS analysis
- To obtain silicon data needed for the backfill geotechnical design, CRF samples were also analyzed for whole rock analysis by lithium metaborate fusion with x-ray fluorescence finish

The underground scope of work for the PEA did not include characterization of tailings. Nor did the underground program include characterization of the chemical interaction between potentially reactive surface areas of the mine and groundwater that might produce contact water with low pH and/or elevated concentrations of metals, acidity and sulfate that may require treatment.

PEA Program

Results of the PEA analytical program indicated that only one of the five laminated metasediment samples from the Horseshoe deposit contained S_T above the Haile management criterion of 0.2% (at 0.34% S_T) for “Yellow PAG”. The PEA level samples diabase and metavolcanic samples from the Horseshoe target were classified as not acid generating (NAG), based on both the Haile and industry classification criteria.

Paste pH

Paste pH of the development rock and CRF backfill samples was alkaline, indicating relatively low concentrations of acid generating secondary minerals. The distribution of pH did not vary considerably by lithology. The average paste pH for the sampled development rock lithologies ranged from 9.05 to 9.6. The lowest paste pH measured was 7.17 for a laminated metasediment sample. The backfill samples exhibited significantly higher paste pH values ranging from 9.72 to 12.2, presumably due to the cement content which ranged from 1.9% to 6.6% of the sample by weight.

Sulfur

Sulfur species and concentrations were determined by a range of methods to provide a comprehensive evaluation of potential sources of acidity. Observations based on the sulfur data include:

- Total sulfur in development rock ranged from less than 0.005% to 2.45%. Average concentrations varied significantly by lithologies with values of 0.10%, 0.7%, 0.43% and 0.06% for the DB, L, LC/LS and MV, respectively;
- Almost all sulfur occurs as sulfide, especially at higher total sulfur concentrations (SRK, 2017). Schafer (2015) showed in the overburden characterization that sulfide S levels average 94% of total S values. The FS program work revealed that sulfide ranges from 96% to 100% of total sulfur values.
- The highest sulfide values measured in development rock (2.37% and 2.45%) were in laminated metasediment samples collected from planned tunnels in the orebody connecting two stopes.
- The majority of sulfate values in development rock were below the PQL of 0.01%. Only three samples (all metasediments) had measurable sulfate, with a maximum concentration of 0.04%. The highest sulfate values occurred in samples with elevated total sulfur concentrations (1.1% to 2.45%).

- The CRF rock samples exhibited significantly greater total sulfur and sulfide concentrations than FS development rock. Sulfide in CRF samples ranged from 0.01% to 4.42%, with an average value of 1.94%. It was determined that overburden materials collected for CRF backfill testing were more representative of Red PAG rock than Green non-PAG rock, as originally intended.

Neutralization Potential

Neutralization potential was evaluated based on the concentration of total inorganic carbon as well as via the Sobek and Modified methods. Observations regarding the NP of the FS samples include:

- Total carbon is almost equal to total inorganic carbon (TIC), indicating that the concentration of organic carbon is low, and that total carbon is a good approximation for TIC.
- Sobek NP values are generally slightly higher than Modified NP, which is normal as the Sobek method tends to dissolve a greater portion of the neutralizing alumino-silicate minerals.
- NP determined by the Modified method and calculated from TIC are very similar with only few exceptions.
- NP in the CRF samples is comparable to that of the FS development rock.
- Virtually all the available NP is derived from carbonate minerals.
- The exact composition of the carbonates was not determined, but calcite (CaCO_3), dolomite ($\text{CaMg}(\text{CO}_3)_2$) and siderite (FeCO_3) are all principal country rock mineral phases (Schafer, 2010a).
- Sobek NP slightly overestimates NP since it tends to include a greater percentage of NP derived from silicate minerals, which vary widely in their contribution to NP.

Net Acid Generation


Net Acid Generation (NAG) pH values in development rock ranged from 2.45 to 6.92 and NAG pH values below 4.5 (indicative of PAG rock [AMIRA, 2002]) were observed in all lithologies except the DB (SRK, 2017). LS material had the highest fraction of PAG rock at 66%, followed by L (45.5%), LC (16.7%) and MV (5%).

NAG pH values in CRF material were comparable to development rock, ranging from 2.3 to 7.97, but a larger proportion of CRF samples (12 of 18) than development rock samples (12 of 78) reported NAG pH values less than 4.5. Overburden materials collected for CRF backfill testing were later found to be representative of Red PAG rock rather than Green non-PAG rock, as originally intended.

ARD Potential


The AP of the samples was determined using the site defined NNP criteria, as well as literature criteria for NPR and NAG pH. The classification scheme of the samples is summarized in employing the color-coding scheme (Red, Yellow, Green) used by Haile for NNP and total sulfur. The ML/ARD potential of the samples was also categorized using industry standard criteria for acid generating material (Price, 2009) based on: NPR: ≤ 1 is PAG, between 1 and 2 is uncertain acid generation potential, and > 2 is not PAG.

Figure 16-24 plots the Modified NP versus AP of development rock by lithology. Figure 16-25 presents a plot of NNP versus total sulfur using the Haile development rock criteria.

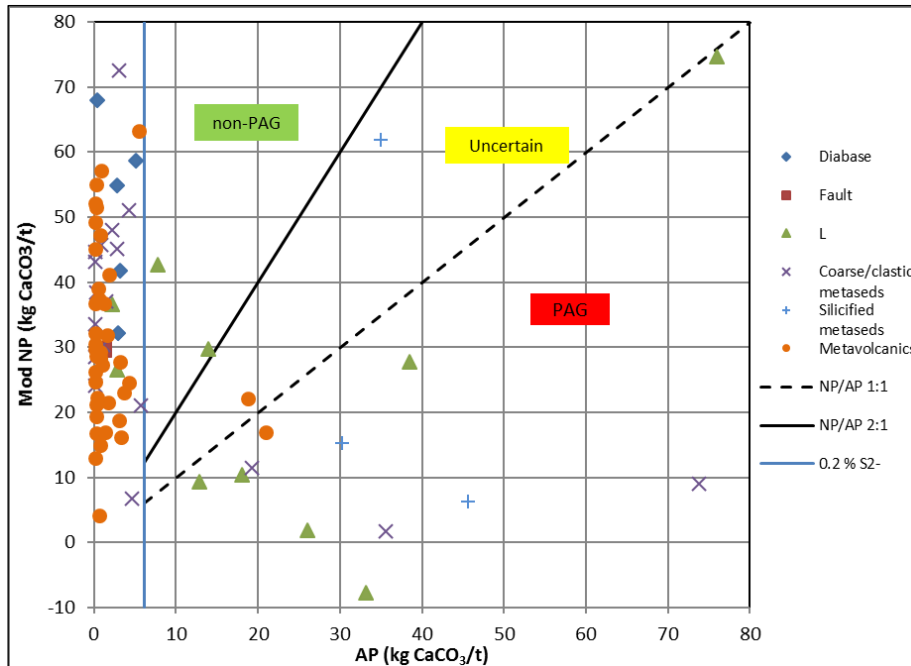

Source: SRK

Figure 16-24: NP/AP for Horseshoe Development Rock

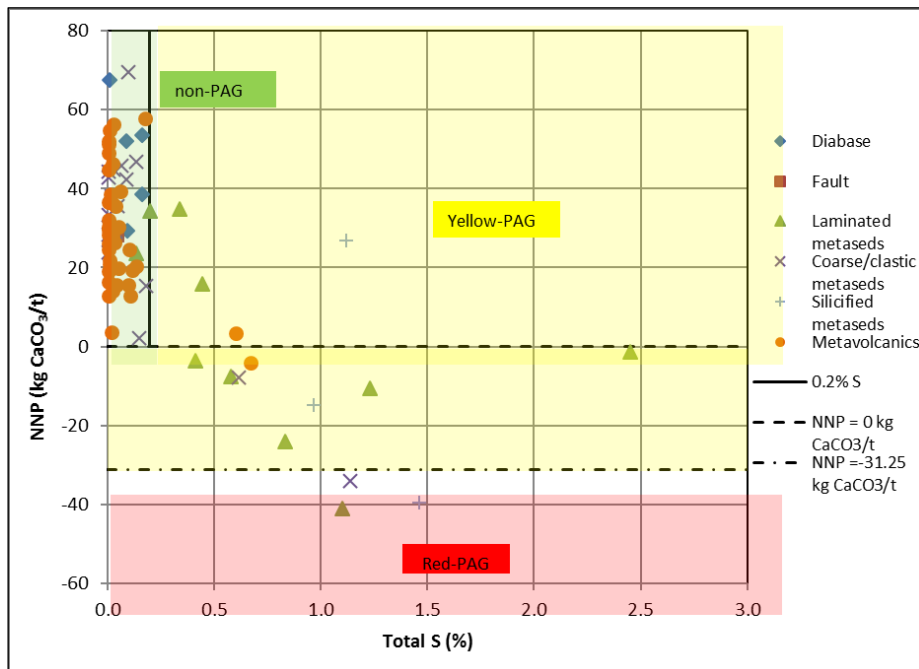

Source: SRK


Figure 16-25: NNP vs. Total Sulfur for Horseshoe Development Rock

Observations related to the potential for acid generation using the Haile criteria for NNP and total sulfur include:

- There is no apparent correlation between NP/AP and depth of samples.
- The majority of MV rock (95%) is non-PAG.
- Slightly more than half (63.6%) of the L samples are PAG.
- Most of the coarse/clastic metasediments (LC) are non-PAG, with 2 of the 18 samples (11%) falling into the PAG categories.
- The metasediments with secondary silicification are predominantly PAG (Red) or potentially PAG (Yellow) (66%).
- Three samples plot on the boundaries of different PAG classification schemes, including:
 - DDH0368-645 to 653 (L) exceeds Haile $S_T > 0.2\%$ but is not PAG based on NPR and NAG pH.
 - DDH0542-855.0 to 857.7 (LS) and DDH0370-931.8 to 934.4 (MV) exceeds Haile $S_T > 0.2\%$ but have $NPR > 0$ (Yellow PAG) and are not-PAG based on NAG results. NP/AP indicate the samples have “uncertain” acid generation potential.
- The CRF samples are predominantly Red PAG. The NAG metavolcanics of Batches 4, 10, 12, 14, and 15 are Green PAG, and Batches 3, 20 and 21 are Yellow PAG depending on the NNP method referenced.

The locations of the samples with ML/ARD potential were evaluated by plotting the geochemical characteristics, geology, and proposed infrastructure as shown in Figure 16-26, resulting in the following observations:

- The results of the geochemical analyses (i.e., PAG vs. non-PAG) reflect the mineralization and geology. All of the PAG samples are located at the contact between the metavolcanics and metasediments.
- All samples in the drifts southeast of the orebody, decline and spiral ramp were non-PAG, with the exception of a single sample in the metavolcanic area of the infrastructure (DDH0370-931 to 934) which had uncertain AP (ST of 0.6% and NPR of 3.3 kg $CaCO_3/t$). This sample was not PAG based on the NAG test.
- One sample near the previous ramp configuration was classified as Yellow PAG (DDH0370-931 to 934). However, given the borderline and ambiguous PAG classification of this sample and the average NNP and total sulfur for all MV samples of 28.9 kg $CaCO_3/t$ and 0.06%, respectively, the metavolcanic development rock from the Horseshoe infrastructure should be classified as non-PAG.
- The results of the FS geochemical characterization of the Horseshoe deposit are in good agreement with the results of the site wide overburden characterization.
- Overburden materials collected for CRF backfill testing were more representative of Red PAG rock than Green non-PAG rock as originally intended. If the CRF option is carried forward, controls will be needed to ensure that only Green non-PAG rock is used for CRF backfill.

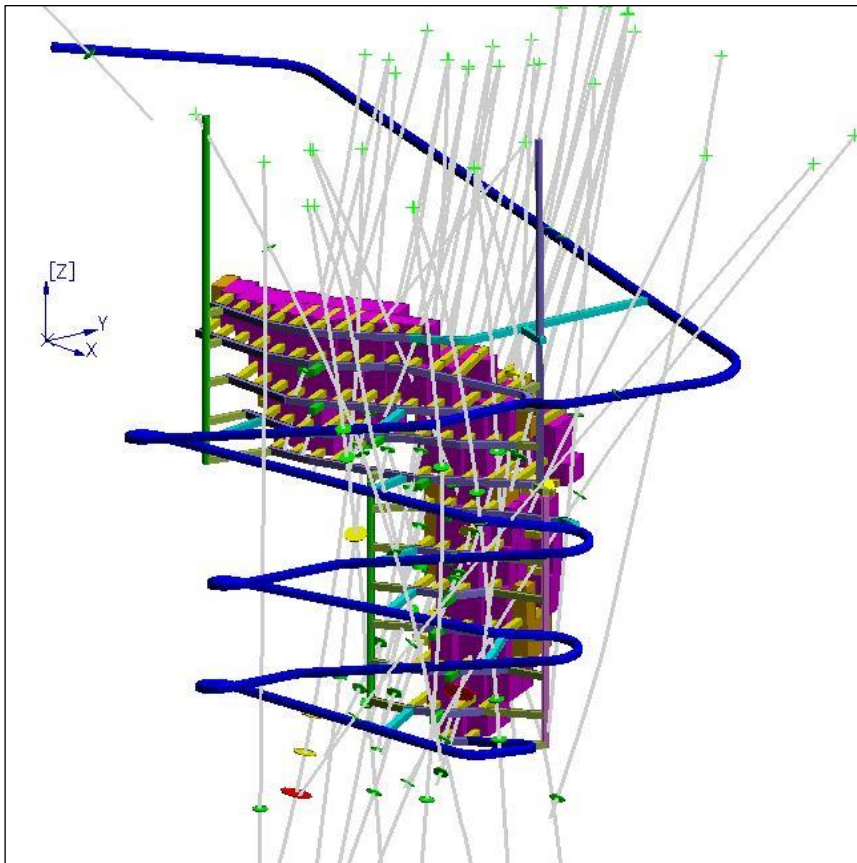

Source: SRK

Figure 16-26: Location of PEA and FS Geochemical Samples Color Coded using Haile Criteria

In summary, potential development rock requiring selective handling and management is expected to occur entirely from the laminated sediments in close proximity to the proposed stopes.

Total Element Concentrations

Total element concentrations in Horseshoe deposit samples were analyzed by aqua regia digestion and then compared to crustal averages for similar rocks (Price, 1997). The objective of the comparison is to identify development rock that carries elevated metal concentrations and therefore might leach metals after development. A statistical analysis of the data is reported in SRK (2017). The ML process can occur under both neutral and acidic conditions, depending on the element, mineralogy, sulfide oxidation rate and other factors.

The metavolcanic rocks were compared to high calcium granitic rock (an intrusive analog to andesite). The metasediments were compared to sandstones and shales, as the lithology of the metasediments represents a range of depositional environments. Metasediment samples were enriched in Sb, As, Cu, Co, Au, Mn, Mo, Ni, P, S, Se, Ag, and Zn when compared to their average crustal abundances in sandstone. The elements with median concentrations and/or greatest number of samples that exceeded ten times the crustal abundance for sandstone included Co, Cu, Au, Mn, Mo. When compared to average crustal abundance of elements in siltstone, only Au and Ag were enriched in the metasediment samples. The silicified metasediment sediments (LS) displayed a unique distribution

and concentration of metals, with all three samples exceeding ten times the average crustal concentration for Mo, Ni, Ag and Au. The metavolcanic samples were only enriched in Ag. Enrichment of As, Sb, Co, Hg and Se in metasediments with ARD potential are indicators of potential leaching of these metals from development rock that might have environmental impacts if the rock is not properly managed.

The characterization of metals in the overburden development rock (Schafer, 2010a) indicated that Au, S, As, Se, Mo were enriched in the laminated metasediments (excluding the silicically altered lithology). The silicically altered rocks were enriched in Au, S, Mo, As, Ag, Te and Se. The metavolcanic overburden rocks were enriched in Se, Au, S and As. The CRF materials show enrichment in As, Au, S, and Te.

Summary of Geochemical Testing Program

- Total sulfur in development rock ranged from less than 0.005% to 2.45%, equating to AP values from 0.16 to 76.6 kg CaCO₃/t. Average concentrations vary significantly by lithology with values of 0.10%, 0.7%, 0.43% and 0.06% for the DB, L, LC/LS and MV, respectively.
- Almost all sulfur occurs as sulfide, especially at higher total sulfur concentrations (SRK, 2017).
- The CRF rock samples exhibited significantly greater total sulfur and sulfide concentrations than FS development rock, with sulfide in CRF samples ranging from 0.01% to 4.42%, with an average value of 1.94%. Further investigation determined that overburden materials collected for CRF backfill testing were more representative of Red PAG rock than Green non-PAG rock.
- Virtually all the available NP is derived from carbonate minerals, so NP has been evaluated based on TIC rather than the Sobek (Sobek et al., 1978) or Modified (Lawrence, 1989) methods.
- NP ranges from 0.83 to 70.8 kg CaCO₃/t.
- NP in the CRF samples is comparable to that of the FS development rock.
- Paste pH results for development rock and CRF backfill samples were alkaline, indicating relatively low concentrations of acid generating secondary minerals.

The ML/ARD potential of the Horseshoe development rock and proposed backfill materials can be summarized as follows:

- The majority of MV rock (95%) is non-PAG.
- Slightly more than half (63.6%) of the L rock is PAG.
- The majority of the coarse/clastic metasediments (LC) are non-PAG.
- The metasediments with secondary silicification are predominantly PAG (Red) or potentially PAG (Yellow) (66%).
- All of the PAG samples are located at the contact between the metavolcanics and metasediments.
- Overburden materials collected for CRF backfill testing were more representative of Red PAG rock than Green non-PAG rock as originally intended. Controls will need to be implemented to ensure that only Green non-PAG rock is used for CRF backfill.
- Testing of tailings backfill materials is in progress. Only preliminary results are available but early indications are favorable (B. Schafer, written commun.).
- Development rock requiring selective handling and management is expected to occur entirely from the laminated sediments in close proximity to the proposed stopes.

- Access and vent workings proposed in the updated mine plan will be driven in the metasediments, which was extensively characterized by geochemical testing and is not believed to present a significantly greater risk than the same material in the earlier mine plan. However, sampling is recommended prior to and during development to obtain confirmatory data on the ML/ARD properties of the new areas.

16.2.5 Stope Optimization

Stope optimization was completed on prior versions of the model. Results from those prior runs were used for comparison during the mine design process.


16.2.6 Mine Design

Stope Design

For the design, vertical slices were created through the orebody along 2 m strike length intervals. The model was then interrogated, filtered on cutoff, and then the slices were combined to create minable stopes.

Both top and bottom stope access are designed, as mucking will occur from the lower access and drilling/backfilling will occur from the upper access. Slashing of drifts in necessary areas has also been included in the design. Stope accesses are expected to be in waste until they intercept the stoping block, but grade control will be used to determine the exact ore/waste boundary during mining.


A typical level in the upper zone is made up of approximately eight stopes across, while the lower zone has approximately two to four stopes across. The length of stopes is limited by geotechnical stability and often several stope cuts are taken as shown in Figure 16-27. A primary/secondary stoping sequence will be used where, on any given level, primary stopes must be separated by a secondary stope. Extraction of the secondary stope can only occur after the two immediately adjacent primary stopes have been mined, backfilled and have had time to cure. Backfilling will be an integral part of the mining cycle as there is a limited quantity of stopes available on each level.

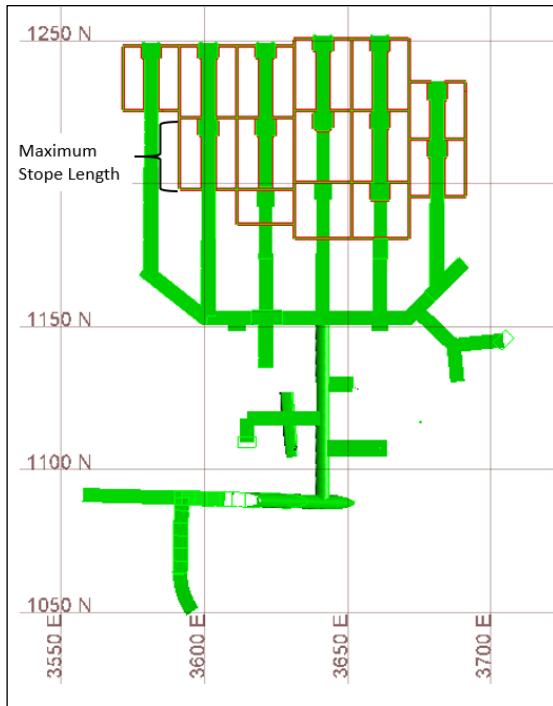

Source: SRK

Figure 16-27: Level Cross Section of Stopes

Figure 16-28 shows a cross section of the stopes.

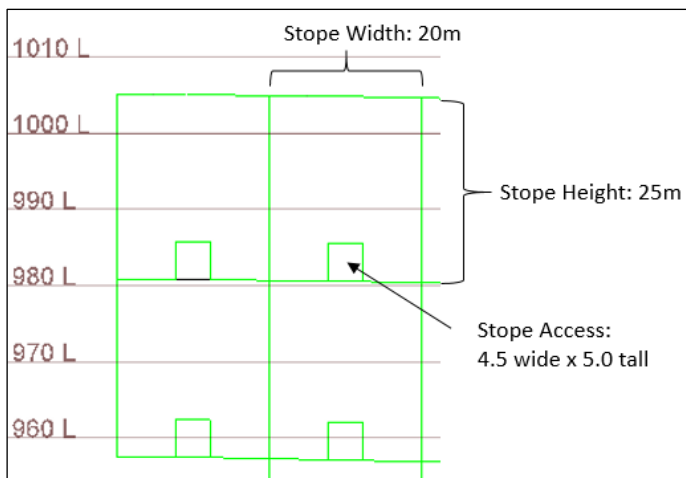


Source: SRK

Figure 16-28: Stope Cross Section

Stopes are developed using a slot as discussed in Section 16.2.9. Separate slot triangulations were not constructed for each stope, but the slot tonnage of each stope is separated out and a slot activity is used for scheduling.

Development Design


The underground mine is accessed via a decline from the surface. The decline portal is located on an open pit bench approximately 80 m below the natural surface as shown in Figure 16-29. Two ventilation drift portals are also located on an open pit bench.

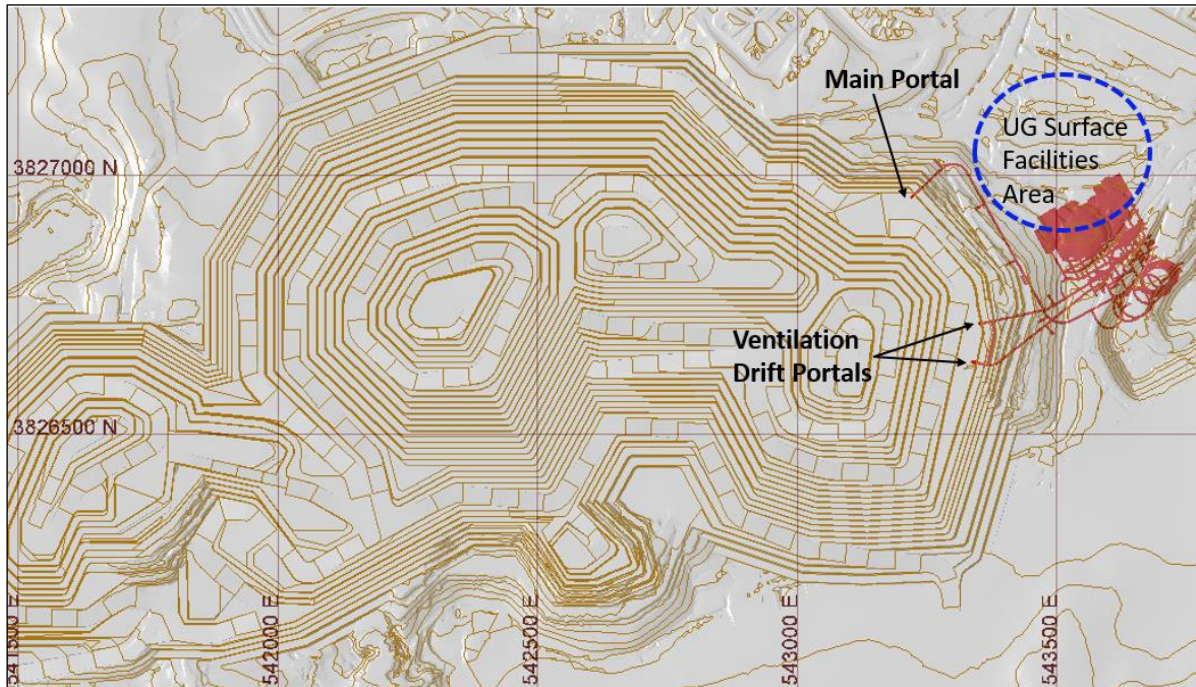

Source: SRK

Figure 16-29: Underground Portal Location (shown in the OP coordinate system)


The stope accesses are connected to a level access located in the footwall in waste material. The level accesses are offset a minimum of 25 m from the stopes. The level accesses connect to the interlevel ramp system which is located in the footwall and is offset approximately 75 m from the footwall accesses. Each level is connected to the ventilation system and emergency egress system. Figure 16-30 shows a typical level section.

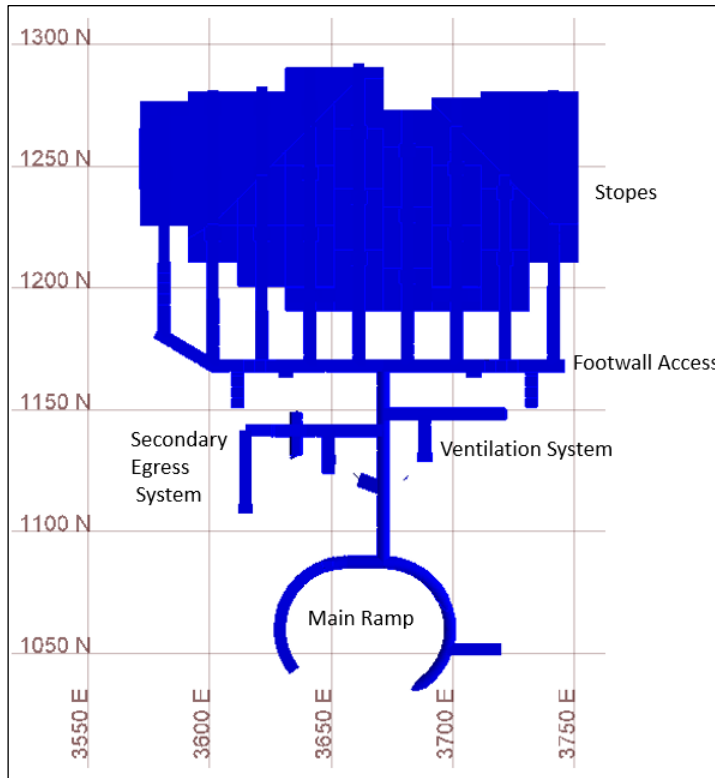

Source: SRK

Figure 16-30: Typical Level Section

The design completed is detailed and includes remucks, passing bays, sumps, etc. Figure 16-31 shows a portion of the main ramp with these items designed. As such, no additional allowances were applied to the design.

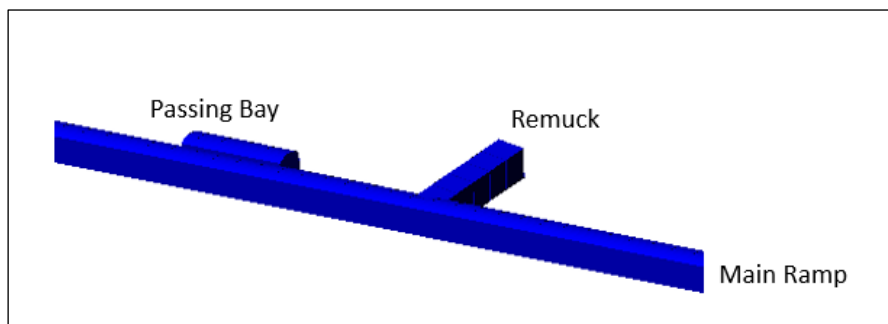


Source: SRK

Figure 16-31: Main Ramp Design Detail

All planned maintenance will be on the surface and underground shop facilities are not included in the design. The CRF facilities are also located on the surface and no additional infrastructure is required underground.

Where possible, accesses/ramps have been designed to be located in the metavolcanics and away from known dikes. Where ramps must cross a fault/dike, the crossing is designed perpendicular to the structure to minimize the length of development through these structures.

Figure 16-32 shows the completed mine design colored by Au.

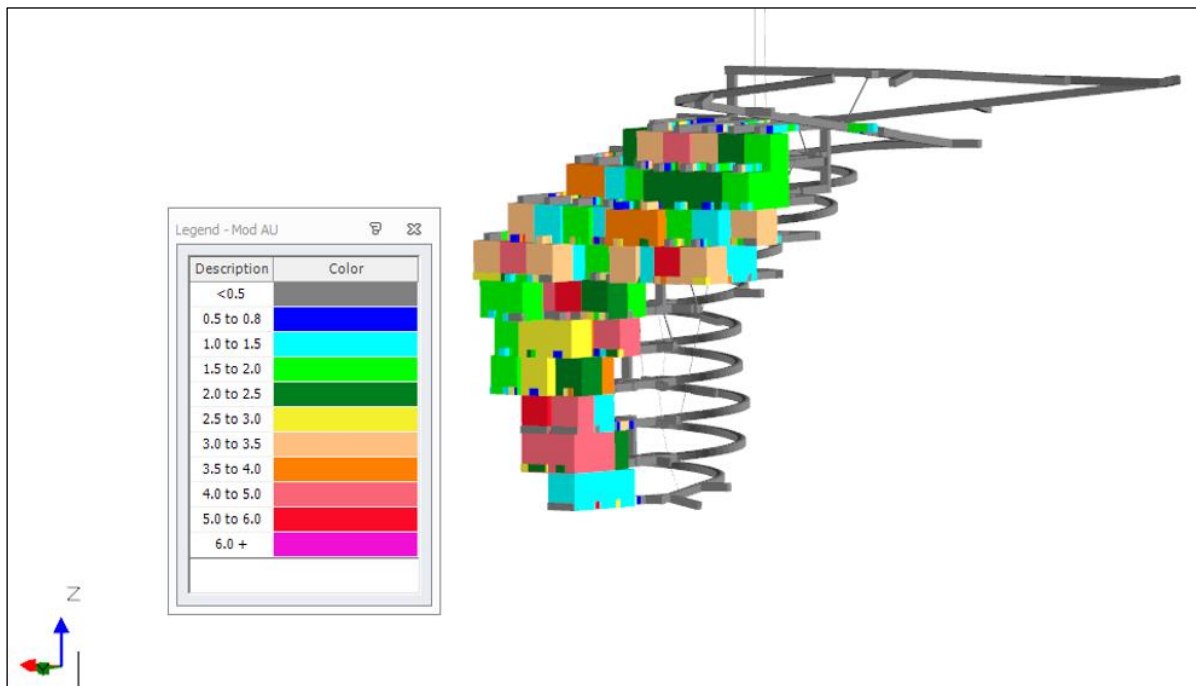

Source: SRK

Figure 16-32: Horseshoe Completed Mine Design, colored by activity type (looking South)

Table 16-34 summarizes the mine design by activity type.

Table 16-34: Mine Design Summary – by Activity Type

General Summary	Value
Ore Tonnes (kt)	3,416
Ore Au (g/t)	3.78
Waste Tonnes (kt)	822
Total Tonnes Moved (kt)	4,238
Ore Summary	
Development Ore Tonnes (kt)	262.8
Stope Production Tonnes (kt)	3,153.6
Horizontal Development Summary	
ACC - Level Access	697.1
CRF - CRF Stockpile	234.7
DEC - Decline	2,661.9
DSP - Decline Stockpile	261.4
EWD - Escapeway Drive	220.9
FAD - Fresh Air Drive	734.9
FWD - Footwall Drive	1,014.8
LSM - Level Sump	223.9
OD - Ore Drive	5,374.5
PSN - Pump Station Drive	36.0
RAD - Return Air Drive	798.8
SLD - Slot Drive	903.6
SUB - Substation	133.4
XCT - Crosscut	78.4
Total Horizontal Development Length (m)	13,374
Vertical Development Summary	
DH_ Drainhole	236.5
EWR - Escapeway Rise	292.5
FAR - Fresh Air Rise	106.3
FH_ Fill Hole	0.0
HV_ Cable Hole	0.0
OP_ Orepass	0.0
RAR - Return Air Rise	228.0
RMH_ Rising Main	306.6
SH_ Service Hole	235.9

Source: SRK

Waste material within the design was not characterized geochemically in detail, but rather a conservative approach was taken assuming 75% of the underground waste rock will be hauled to a PAG rock location on surface and that only 25% would go to the ROM pad and be used back underground as backfill. Geochemical samples taken near underground workings locations in a 2016/2017 study indicate many areas would be characterized as Green, non-PAG material. Further classification work of the waste rock should continue as the project moves forward.

16.2.7 Productivities

Productivities were developed from first principles. Input from mining contractors, blasting suppliers and equipment vendors was considered for key parameters such as drilling penetration rates, blast hole size and spacing, explosives loading time, bolt and mesh installation time, etc. The rates

developed from first principles were adjusted based on benchmarking and the experience and judgment of OceanaGold.

The productivity rates used for mine scheduling are shown in Table 16-35.

Table 16-35: Productivity Rates

Activity Type	Dimensions	Rate ⁽¹⁾
Level Access	5 m x 5.5 m	120 m/mo
Main Decline	5 m x 5.5 m	120 m/mo
Sumps, Remucks, Ventilation Drifts, Footwall and Stope Accesses	5 m x 5.5 m	120 m/mo
Escapeway Drifts	5 m x 5 m	120 m/mo
Stope Production Longhole Drilling		250 m/d
Stope Slot Raiseboring		4 m/d
Longhole Stopping		1,500 t/d
Ventilation Raises	6 mx 4 m	100 m/mo
Escapeway Raises	1 m dia	90 m/mo
Backfilling (CRF)		1,000 m ³ /d

Source: OceanaGold

(1) All rates are per face. Multiple areas/faces are mined together to generate the production schedule.

General Parameters

General schedule parameters applicable to all underground mining activities are presented in Table 16-36.

Table 16-36: Schedule Parameters for Underground Mining

Schedule Parameters	Units	Value
Annual mining days	days/year	365
Mining days per week	days/week	7
Shifts per day	shifts/day	2
Scheduled shift length	hrs/shift	12
Maximum productive hours for drills (60% utilization)	hrs/shift	7.2
Maximum productive hours for LHDs (55% utilization)	hrs/shift	6.6
Maximum productive hours for trucks (60% utilization)	hrs/shift	7.2

Source: OceanaGold

Key assumptions regarding ore and waste material characteristics are detailed in Table 16-37.

Table 16-37: Material Characteristics

Characteristic	Units	Value
Ore in situ density	t/m ³	2.80
Ore swell	%	40
Ore loose density	t/m ³	2.00
Waste in situ density	t/m ³	2.80
Waste swell	%	40
Waste loose density	t/m ³	2.00

Source: OceanaGold

For the purposes of developing productivity estimates and costs, the ground support requirements are as follows:

- The backs and upper sidewalls of capital development (decline, level access) will use 2.4 m x 25 mm fully encapsulated resin bolts. The lower sidewalls will be supported with 1.8 m x 46 mm galvanized friction bolts (split sets). The resin bolts will have corrosion protection, e.g.

epoxy or galvanizing. Capital drives are expected to have a service life of between 2 to 10 years.

- The backs and sidewalls of ore drives, and slot drives will be supported with 1.8 m x 46 mm black friction bolts. These drives are not expected to have a service life greater than two years, thus no need to consider corrosion protection.
- The rock bolt spacing required for openings supported with wire mesh (level access, decline, slot drive, ore drive) is dependent on the dimensions of the mesh sheet, thus the rock bolt spacing is approximately 1.2 m to 1.4 m. The rock bolt spacing in fibercrete has been designed at about 1.4 m. With both the wire mesh and the fibercrete, the design assumes that rock bolts will be installed at the gradeline so that the surface support terminates with a rock bolt.
- The ground support design includes specific cable bolt designs using 2 x 15 mm diameter strands of bulbed black cable (standard twin-strand cable bolts). The cable bulbs will be 25 mm diameter and spaced every meter along the length of the cable. The cable bolt lengths will be standardized as either 6.3 m or 8.3 m twin-strand units. The standard borehole lengths will either be 6 m or 8 m. A 0.3 m tail is required for tensioning one of the two strands with a steel plate, barrel and wedge.
- The 8.3 m cable bolts are only used for supporting stope crowns. The 6.3 m cable bolts are used for stope brows, or in lateral development with spans exceeding 7.5 m (e.g. decline passing bays or 3-way intersections).
- The ground support design includes face support. A temporary face in lateral development will be supported down to the gradeline with sacrificial sheets of black wire mesh and 0.9 m x 46 mm friction bolts. A permanent face in lateral development must be supported to the same ground support standard as the adjacent sidewalls.

The following is a description of the general and activity-specific parameters upon which the productivity rates are based.

Main Ramp Development (long-term development openings)

The main ramp is 5 m wide x 5.5 m high with an arched back. It will be developed with a twin-boom jumbo drilling 45 mm diameter blast holes. All jumbo holes will be drilled 4.9 m in length, which allows for an effective advance rate of 4.2 m per round. The drill pattern provides for 56 charged blast holes and four uncharged relief holes. Drilling times were calculated based on average penetration rates of 100 m/hour (hr). A 10% re-drill factor was assumed.

Use of a bulk emulsion explosive was assumed at 108.6 kg/m of advance. The blasting time considered tramming, setup and rig down, and loading holes.

Loading will be performed with an 8.4 m³ (14.9 t) load-haul-dump unit (LHD). Load, maneuver, dump and tramming times were considered in the overall cycle time calculation. It was assumed that 70% of the waste rock will be placed in muck bays and then will be rehandled into trucks and hauled to the surface (or to an empty secondary stope when available). For the remaining 30% of the waste rock, it was assumed that the LHD will load the truck directly (i.e. no rehandling from a muck bay).

For ground support installation, time allowances have been included for mobilization and setup, bolting/meshing/shotcreting as required, and demobilization. Cable bolts will be installed at intersections. Utility installation includes water line, drain line, ventilation tube, and electrical reticulation.

The mining schedule is based on an average decline advance rate of 120 m/month.

Level Access Drifts (medium-term development openings)

The level access drifts will be 5-m wide x 5.5-m high with flat backs. They will be developed with a twin-boom jumbo drilling 45 mm diameter blast holes. All jumbo holes will be drilled 4.9 m in length, which allows for an effective advance rate of 4.2 m per round. The drill pattern provides for 58 charged blast holes and four uncharged relief holes. Drilling times were calculated based on average penetration rates of 100 m/hr. A 10% re-drill factor was assumed.

Use of a bulk emulsion explosive was assumed at 112.5 kg/m of advance. The blasting time considered tramming, setup and rig down, and loading holes.

Loading will be performed with an 8.4 m³ (14.9 t) load-haul-dump unit (LHD). Load, maneuver, dump and tramming times were considered in the overall cycle time calculation. It was assumed that 70% of the waste rock will be placed in muck bays and then will be rehandled into trucks and hauled to the surface (or to an empty secondary stope when available). For the remaining 30% of the waste rock, it was assumed that the LHD will load the truck directly (i.e. no rehandling from a muck bay).

For ground support installation, time allowances have been included for mobilization and setup, bolting/meshing/shotcreting as required, and demobilization. Cable bolts will be installed at intersections. Utility installation includes water line, drain line, ventilation tube, and electrical reticulation.

The mining schedule is based on an average lateral development advance rate of 120 m/month.

Through the Stope Development Drifts (short-term development openings)

The stope development drifts will be 4.5 m wide x 5 m high with flat backs. They will be developed with a twin-boom jumbo drilling 45 mm diameter blast holes. All jumbo holes will be drilled 4.9 m in length, which allows for an effective advance rate of 4.2 m per round. The drill pattern provides for 59 charged blast holes and four uncharged relief holes. Drilling times were calculated based on average penetration rates of 100 m/hr. A 10% re-drill factor was assumed.

Use of a bulk emulsion explosive was assumed at 98.9 kg/m of advance. The blasting time considered tramming, setup and rig down, and loading holes.

Loading will be performed with an 8.4 m³ (14.9 t) load-haul-dump unit (LHD). Load, maneuver, dump and tramming times were considered in the overall cycle time calculation. It was assumed that 70% of the ore will be placed in muck bays and then will be rehandled into trucks and hauled to the surface. For the remaining 30% of the ore, it was assumed that the LHD will load the truck directly (i.e. no rehandling from a muck bay).

For ground support installation, time allowances have been included for mobilization and setup, bolting and meshing as required, and demobilization. Utility installation includes water line and ventilation tube.

The mining schedule is based on an average lateral development advance rate of 120 m/month.

Stoping

Stopes will be 25-m in height x 20-m in width and will have varying lengths. A longhole production drill will be used to ring drill the stope. Blast holes will be 89 mm in diameter and the estimated drilling rate is 30 m/hr. Twenty blast holes will be required per ring. The total drilling requirement is 220 m per ring (including 10% re-drill) and the ore blasted per ring is 2,100 t.

A bulk emulsion product will be used to blast the stopes and the powder factor will be 0.40 kg/t.

Loading will be performed with an 8.4 m³ (14.9 t) load-haul-dump unit (LHD). Load, maneuver, dump and tramming times were considered in the overall cycle time calculation. It was assumed that 90% of the ore will be placed in muck bays and then will be rehandled into trucks and hauled to the surface. For the remaining 10% of the ore, it was assumed that the LHD will load the truck directly (i.e. no rehandling from a muck bay).

The mining schedule is based on an average stope production rate of 1,500 t/day.

Ventilation Connections Between Levels

Ventilation rises will be 6.0 m wide by 4.0 m long and 25 m high. The ventilation rise will be drilled with 89 mm diameter holes and will break to a 1.1 m diameter raisebored hole. A total of 18 charged holes will be required for each ventilation rise.

16.2.8 Mine Production Schedule

The Horseshoe underground mine production schedule is based on the productivity assumptions shown in Table 16-38. The schedule was completed using Deswik scheduling software and is based on mining operations occurring 365 days/year, 7 days/week, with two 12-hr shifts each day. A production rate of approximately 2,000 t/d was targeted with ramp-up to full production as quickly as possible. Resource levelling was used on a monthly basis for ore tonnage and lateral development.


The scheduling work includes placing CRF in the mined-out stopes. Allowances were included for the time that will be required to cure the cement binder in the CRF. Specifically, a 14-day delay was assumed prior to mining adjacent or driving on top of a CRF filled stope.

Figure 16-33 presents the annual mining schedule based on the aforementioned scheduling assumptions.

Table 16-38: Horseshoe Mine Production Annual Mining Schedule

Year	Mineralized Tonnes (kt)	Au (g/t)	Waste Tonnes (kt)	Backfill Volume (m3)
2021			69.3	
2022	15.1	5.03	333.9	
2023	660.9	3.99	225.6	211,536
2024	750.9	4.07	128.1	263,313
2025	741.5	4.53	55.6	274,151
2026	738.2	3.26	7.1	293,306
2027	509.7	2.70	2.6	220,027
Total	3,416.3	3.78	822.1	1,262,333

Source: SRK

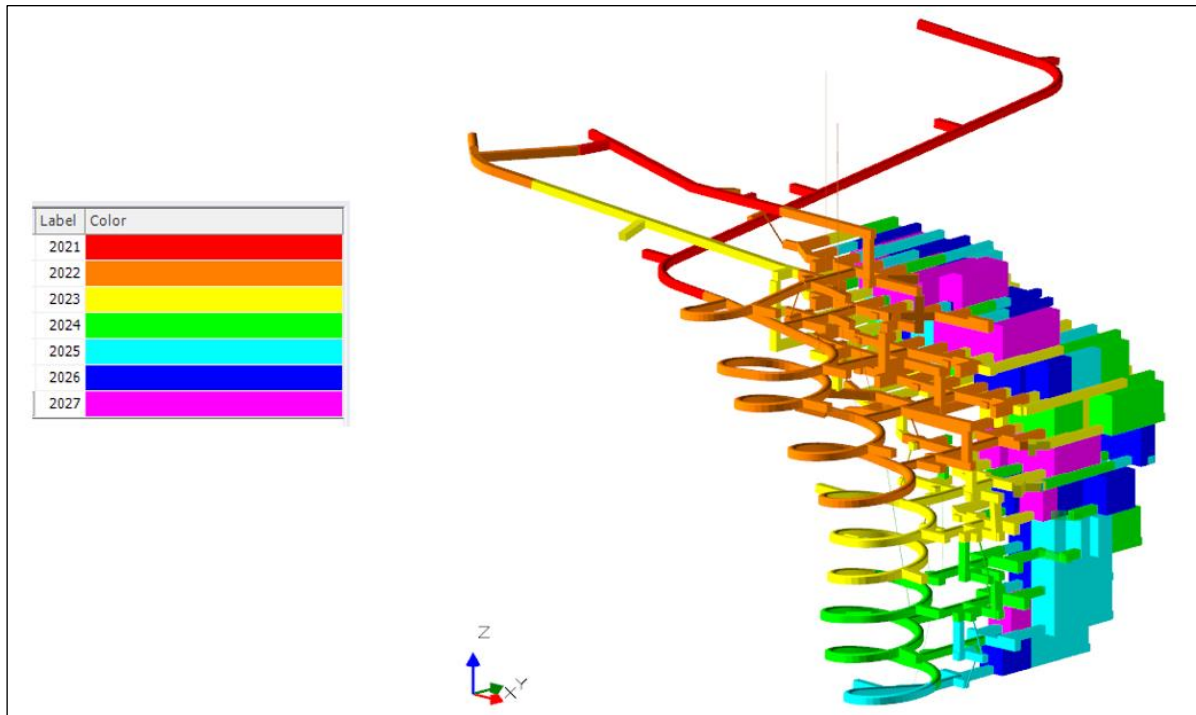


Source: SRK

Figure 16-33: Mine Production Schedule Colored by Year (looking NW)

The underground permitting process is expected to be complete by mid-2021 and, accordingly, underground portal development is scheduled to begin in August 2021. Prior to portal development, open pit mining in Snake Pit will have progressed sufficiently to allow access to the portal location. Portal development is assumed to occur before the decline access can begin. First production from the stopes is scheduled to occur in January 2023 and will continue through September 2027 based on the current Mineral Reserves.


Figure 16-34 and Figure 16-35 present additional summary information for the mine production schedule. Table 16-39 shows additional items in the production schedule summarized annually.

Haulage distances from each level underground to portal were calculated. Surface haulage distances for ore and waste were also calculated. The tonne-kilometer (TKM) is calculated and flagged in the production schedule to give hauling TKM's for each period for ore and waste material.

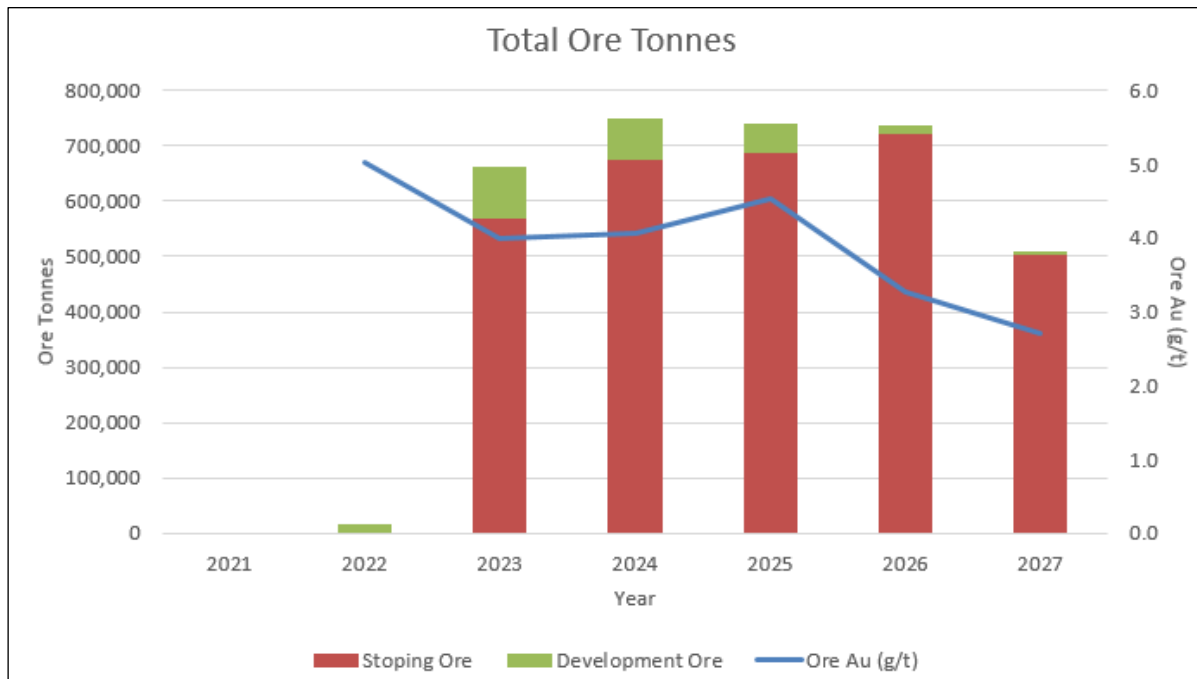

Source: SRK

Figure 16-34: Ore Tonnes by Activity Type

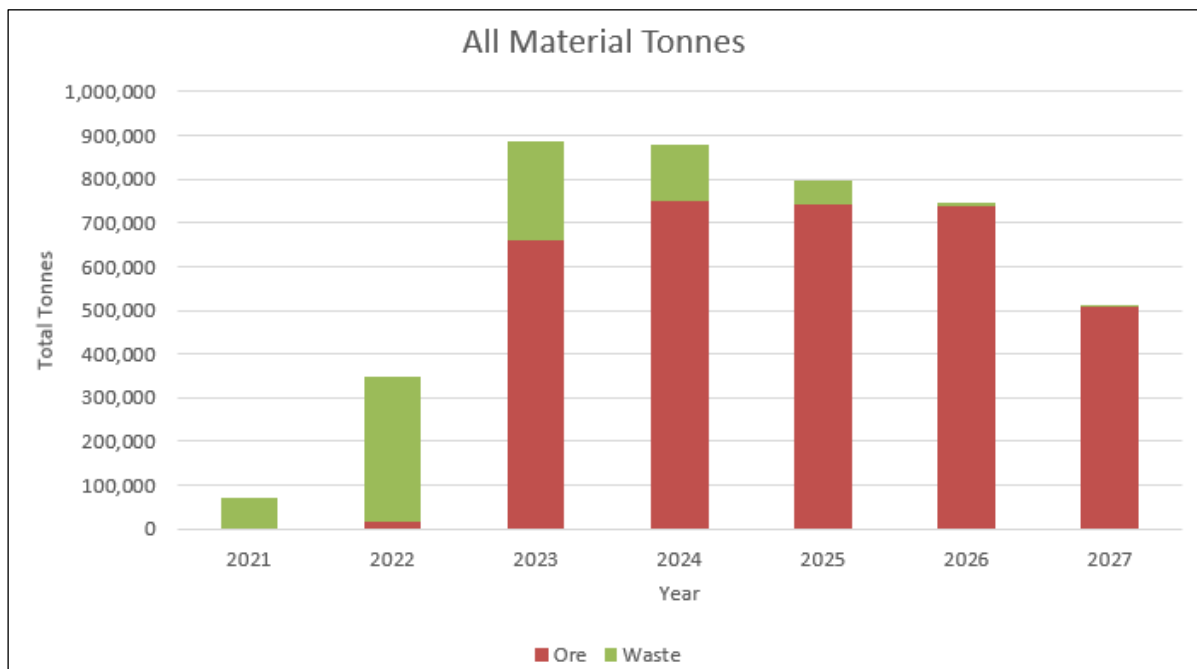

Source: SRK

Figure 16-35: All Material Tonnes

Table 16-39: Detailed Mine Production Schedule

	Totals	2021	2022	2023	2024	2025	2026	2027
General Summary								
Total Ore (t)	3,416,327	-	15,101	660,851	750,921	741,529	738,241	509,684
Total Waste (t)	-	69,277	333,862	225,587	128,092	55,570	7,087	2,623
Total Tonnes (t)	3,416,327	69,277	348,963	886,438	879,012	797,099	745,328	512,307
Total Lateral Development (m)	3,647	866	4,127	3,943	2,582	1,427	316	113
Total Metal - Au (oz)	415,144	-	2,442	84,776	98,188	108,001	77,465	44,273
Total Grade - Au (g/t)	3.78	-	5.03	3.99	4.07	4.53	3.26	2.70
Ore Breakout								
Stoping Ore (t)	3,153,566	-	-	568,430	673,275	686,312	721,955	503,594
Stoping Ore Grade - Au (g/t)	3.82	-	-	4.17	4.14	4.59	3.28	2.70
Development Ore (t)	262,761	-	15,101	92,421	77,645	55,217	16,286	6,091
Development Ore Grade - Au (g/t)	3.3	-	5.03	2.87	3.45	3.76	2.69	2.67
Development Summary								
Total Lateral Development (m)	13,374	866	4,127	3,943	2,582	1,427	316	113
Total Vertical Development (m)	1,406	-	665	239	373	129	-	-
Lateral Development Ore (m)	3,647	-	216	1,308	1,076	756	217	76
Lateral Development Waste (m)	9,727	866	3,911	2,635	1,507	671	99	37
Lateral Development Breakout								
ACC - Level Access	697.1	-	337	129	201	29	-	-
CRF - CRF Stockpile	234.7	-	144.4	45.3	30.0	15.0	-	-
DEC - Decline	2,661.9	559	1,052	438	465	148	-	-
DSP - Decline Stockpile	261.4	60	80	60	40	20	-	-
EWD - Escapeway Drive	220.9	14	88	43	40	36	-	-
FAD - Fresh Air Drive	734.9	22	357	351	4	-	-	-
FWD - Footwall Drive	1,014.8	-	641	273	54	43	-	4
LSM - Level Sump	223.9	23	116	39	24	22	-	-
OD - Ore Drive	5,374.5	-	794	2,177	1,274	864	216	50
PSN - Pump Station Drive	36.0	-	24	-	12	-	-	-
RAD - Return Air Drive	798.8	189	369	101	123	18	-	-
SLD - Slot Drive	903.6	-	16	262	240	226	100	59
SUB - Substation	133.4	-	84	20	25	5	-	-
XCT - Crosscut	78.4	-	24	4	50	-	-	-
Vertical Development Breakout								
DH - Drainhole	236.5	-	80	52	51	53	-	-
EWB - Escapeway Rise	292.5	-	140	52	49	51	-	-
FAR - Fresh Air Rise	106.3	-	-	86	20	-	-	-
RAR - Return Air Rise	228.0	-	105	49	50	25	-	-
RMH - Rising Main	306.6	-	179	-	128	-	-	-
SH - Service Hole	235.9	-	161	-	75	-	-	-

Source: SRK

16.2.9 Mining Operations

Mine Access

A mine access and material handling tradeoff study were completed for the Horseshoe deposit. Options considered included shaft access with ore hoisting, decline access with conveyor haulage, and decline access with truck haulage. The tradeoff study demonstrated that, given the deposit depth,

production rate, and anticipated mine life, the economically superior option is decline access with truck haulage.

The upper portion of the 5 m wide by 5.5 m high access decline is expected to be in weathered rock and therefore will require an increased level of ground support. After the decline has passed through the weathered rock, a less intensive level of ground support will be required. The decline is designed at a maximum gradient of 14%. A minimum turning radius of 27.5 m was used, which is suitable for the underground haul trucks contemplated for the operation.

The portal for the access decline will be located on an open pit bench approximately 80 m below the natural surface. The first 20 m of each portal will be mined 0.5 m wider and higher to accommodate greater ground support. An all-weather gravel surface will be established at the portal and portal bench area and drainage will be maintained away from the portal entrance to minimize water entering the portal and decline from the bench area.

Ventilation, power, water discharge, supply water, and communications will be installed at the portal and carried down the decline to support the initial development operation.

Secondary egress will be via 1.1 m diameter raisebored escapeway raises fitted with ladderways. The escapeway path begins at the fresh air portal, then across a link drive to the exhaust drive, then follows the fresh-air system to the 900mRL, then finally follows the return air system to the bottom of the mine.

Stoping

Stopes will be mined using the sublevel open stoping method. Individual stope blocks are designed to be 20 m wide, up to 25 m long, and will have a transverse orientation. Levels are spaced 25 m apart and each stope block will have a top and bottom access (5 m high x 5.5 m wide flat back drifts).

Stopes will be drilled using 89 mm diameter holes (stope slots will include 1.1 m diameter raise bored holes and, when the stopes will be situated on top of in-situ rock, a 15.5 m slot drive will be mined). In most instances, a bottom up, primary/secondary extraction sequence will be followed. Primary stopes will be backfilled with CRF and secondary stopes will be backfilled with RoM waste from the underground and open pit operations.

Stope extraction will occur in two steps. During the first step, a slot will be mined at the far end of the stope. The slot is required to create sufficient void space for the remainder of the stope to be blasted. During the second step, production rings will be blasted three rows at a time until the stope is completely extracted. The number of three-row blasts in each stope will depend on the length of the stope. All blasting will be with bulk emulsion.

Ore will be remotely mucked from the bottom stope access using a 14.9-t LHD. Cable bolts will be installed at the stope brow to ensure stability. The LHD will transport 90% of the ore to a muck bay to maximize the efficiency of the stope mucking operations. The remaining 10% of the ore will be mucked directly into a truck. A fleet of 51-t haul trucks will be used to transport ore to the surface. Multiple muck bays will be used on each level to avoid interference between the stope loader and the haul trucks.

At the surface, the haul trucks will dump onto a RoM ore stockpile and will then travel to an adjacently located backfill plant to be loaded with CRF. After being loaded, the haul trucks will return to the underground mine and will dump the CRF into a muck bay near the top of an empty primary stope. After dumping the load of CRF at the muck bay, the haul truck will return to the producing level to once

again be loaded with ore. An LHD will be used to transport the CRF from the muck bay to a dumping point at the top access of the empty stope.

Lateral Development

Lateral development includes interlevel ramps, level accesses, stope accesses, and short connecting drifts for ventilation. The interlevel ramp system will be a continuation of the main access decline and will have the same maximum gradient (14%). Level accesses will be 5 m wide by 5.5 m high with a flat back and will be mined higher at the muck bays to allow the haul trucks to be loaded by the LHD.

Interlevel ramps and levels accesses will be located in the footwall and have been designed to avoid crossing fault zones to the maximum extent possible. Stope accesses are oriented perpendicular to the strike of the orebody.

The lateral development is sized for the operation of the mining equipment fleet that has been selected for the operation. The development profiles include allowances for ventilation ducting and services.

Vertical Development

Ventilation rises will be 6 m wide x 4 m long and 25 m high. Each ventilation rise will be conventionally drilled and blasted but will break to a 1.1 m diameter raisebored hole.

Escapeways between levels will be sub-vertical and raisebored at a diameter of 1.1 m.

Rising main holes, electrical holes, service holes, pastefill holes, and drain holes will be drilled either by longhole or raisebore at variable diameters and lengths as required.

Truck Haulage

The mine plan assumes that LHDs will load 51-t haul trucks from muck bays that will be strategically located throughout the development workings. A small percentage of the ore and waste will be loaded directly into trucks (i.e., not rehandled from muck bays). Ore and waste haulage distances were accounted for in the productivity and cost calculations and are based on the mine production schedule. Ore haulage distances are approximately to 2 km to 3 km over the LoM timeframe. Waste haulage distances vary considerably depending on the time period and where the waste is being deposited. At the peak, six haul trucks are required to transport the ore, waste and CRF.

Backfilling

The CRF will use aggregate that is crushed and screened to -80 mm. The CRF crushing and screening sequence will work as follows:

- Contractors will load and haul material from a waste dump and deliver it to the Crushing and Screening Plant (CSP) located near the UG RoM area. Alternatively, waste rock can be delivered to the CSP directly from OP or UG sources.
- The CSP will be designed for 90 tonnes per hour with an availability of 90%.
- The average CSP output will be about 1,600 t/d with two shifts.
- The CSP will produce a coarse aggregate and a fine aggregate product for the CRF.
- This CSP will require one Cat 962G loader and one operator per shift.
- A typical annual CRF requirement of 264,000 m³ will require about 470,000 tpa of aggregate production, i.e. 294 days at 1,600 t/d.

The CRF batch plant will be located next to the CSP. The production sequence will work as follows:

- A second Cat 962G loader and plant operator will keep the aggregate bins topped-up.
- The automated batch plant mixer will make 5 x 5 m³ CRF batches per 50-t haul truck.
- Bulk density of the mix will be about 2 t/m³, thus 50-t loads per truck.
- The batching time will be about 10 minutes to make the 5 batches.
- The typical cycle time will be about 1 hour per truck between batch plant and the underground mine.
- The batch plant would typically produce 50 m³/hr x 20 hours per day, i.e. 1,000 m³/day.
- Typical annual requirement of 264,000 m³ would require 264 CRF days per year

The underground CRF production sequence will work as follows:

- The 50-t haul trucks will tip their loads into a CRF stockpile bay located on each footwall drive.
- The CRF stockpile will be equipped with an automated water spray to wash-down the tray after tipping each load.
- An LHD will move the CRF from the stockpile to the stope.

Two different CRF mix designs will be required: (1) low strength, and (2) high strength. The low strength mix will require about 3.8% cement by dry mass. The high strength mix will require about 4.8% by dry mass. The expected 28-day UCS of the low strength mix could range from 750 to 3,200 kPa with an average of 1,500 kPa. The high strength mix could range from 1,900 to 4,500 kPa with average of 3,000 kPa (Saw et al, 2017).

Figure 16-36 shows the crushing and screening plant and Figure 16-38 shows the CRF plant.


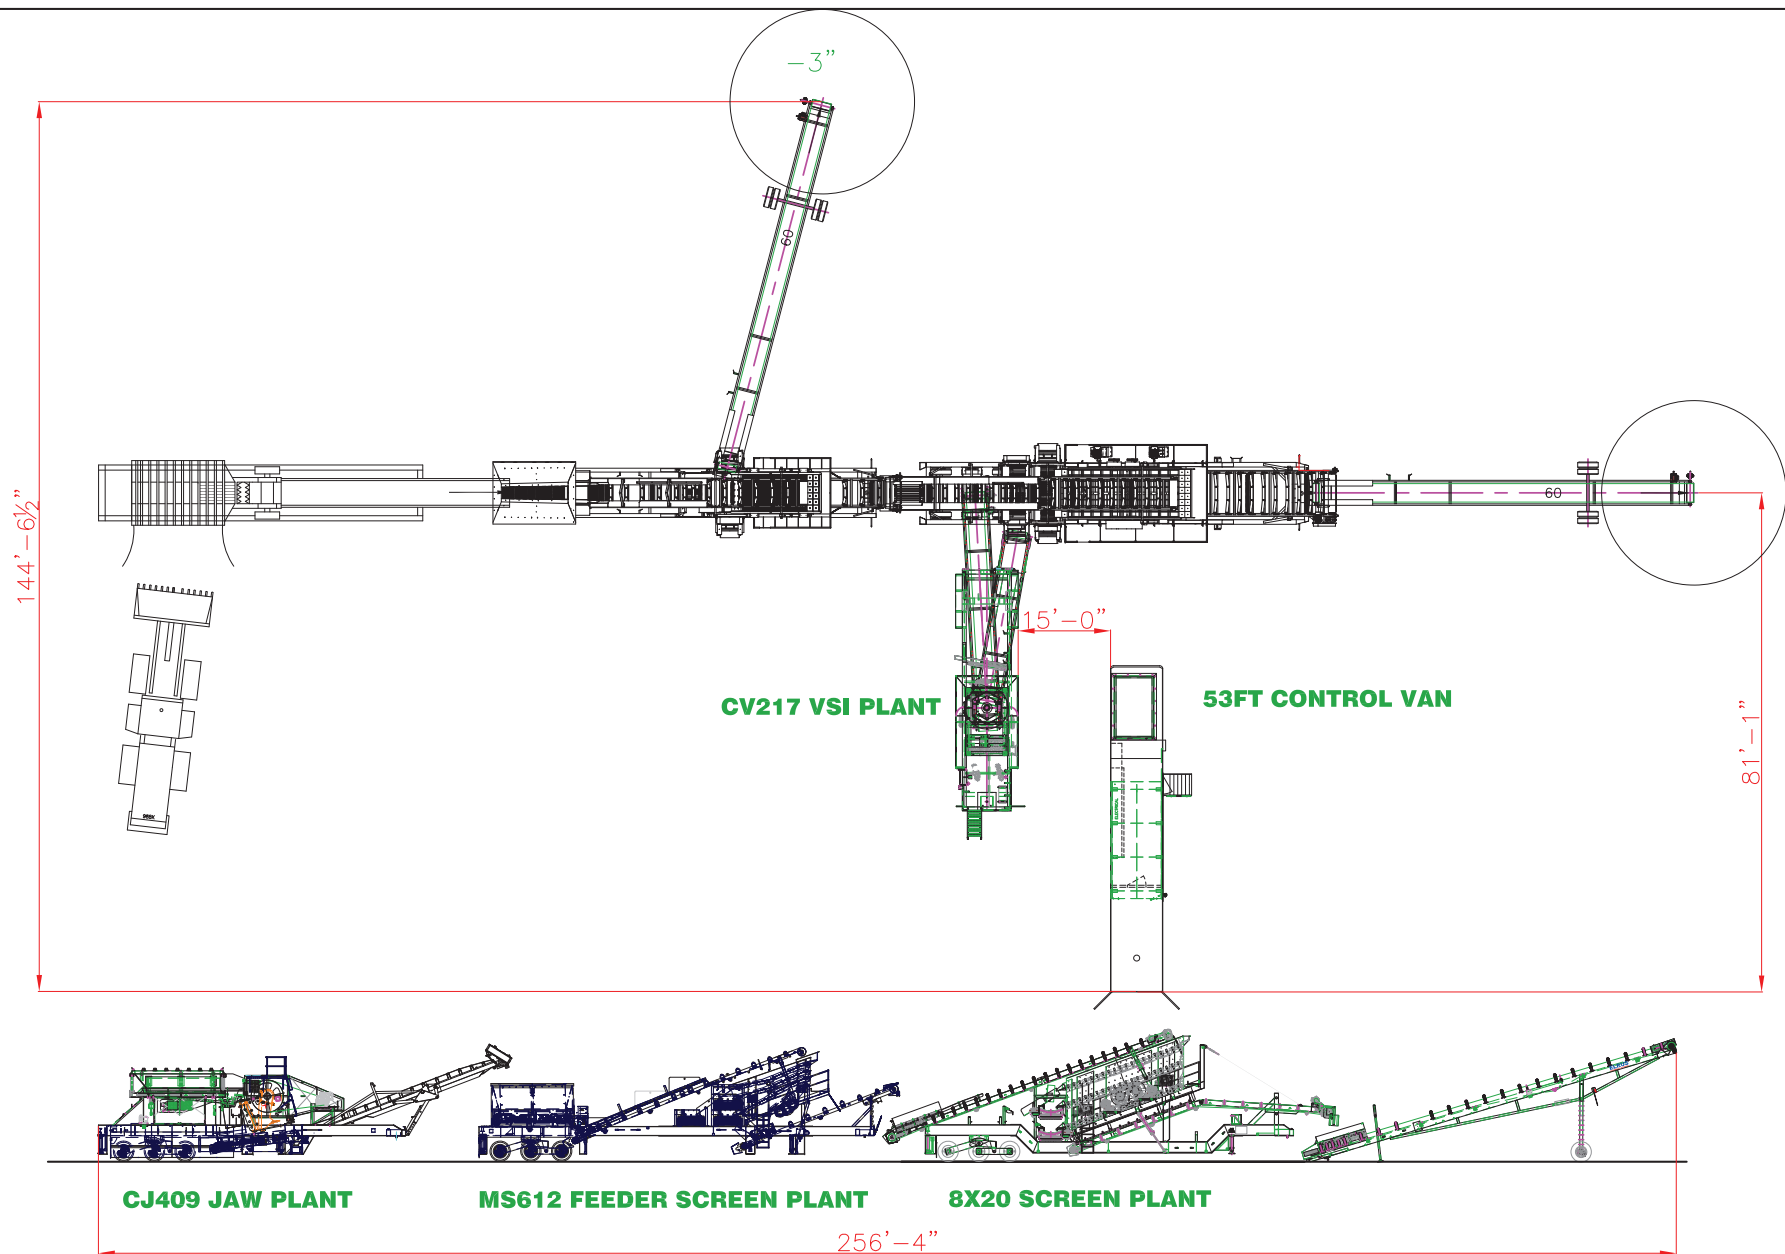


Figure 16-36: Crushing and Screening Plant for Backfill Aggregate

© 2020 by Elrus Inc. who claims proprietary rights of the material disclosed herein. This drawing is issued for engineering information only. It may not be reproduced nor may the information contained be used for manufacturing purposes without written permission from Elrus Inc.	DATE	APR 26 2020	DRAWN	KCH	 ELRUS WWW.ELRUS.COM
	DESIGNED BY	END USER	END USER		
	COMPANY				
UNIT NUMBER	DETAIL				SANDVIK MINING AND ROCK TECHNOLOGY PROPOSED SITE PLAN
DRAWING NO.	SCALE			DATE PLOTTED	
WORK ORDER NO.	QTY TO MAKE			REVISION	
					PIT BOSS SINCE 1976

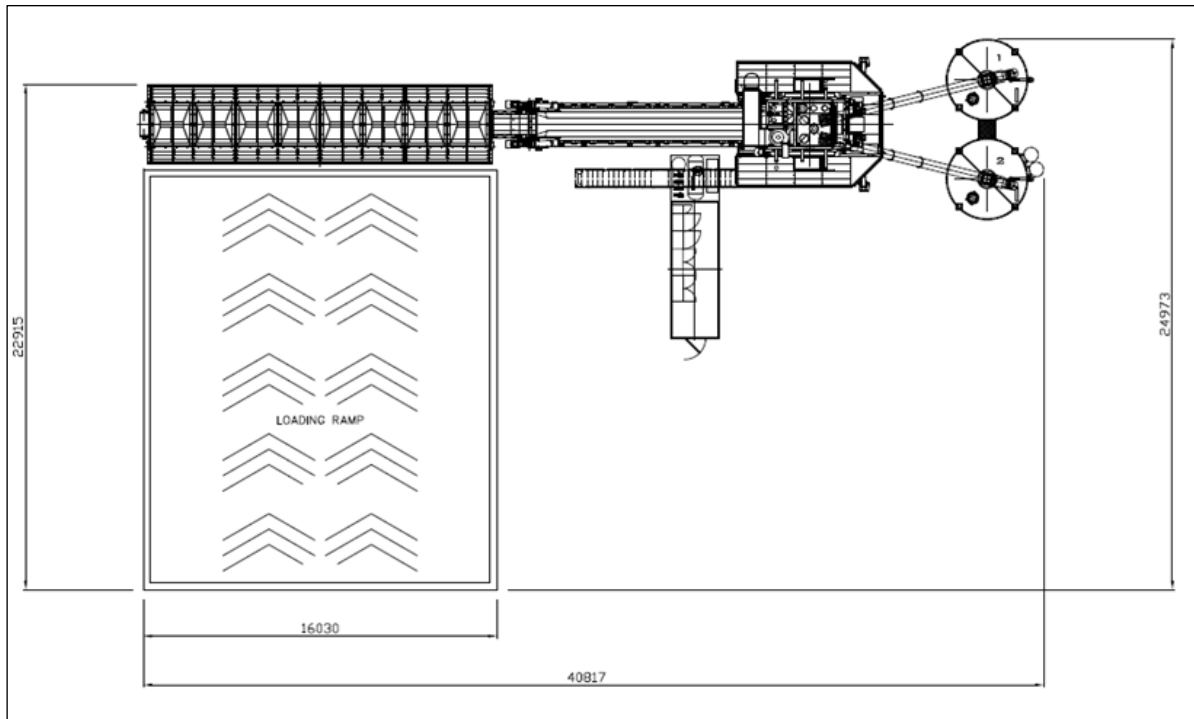

Source: OceanaGold

Figure 16-37: CRF Backfill Plant

Table 16-40 shows the total LoM volume breakdown of the rock fill (low strength) and CRF (high strength).

Table 16-40: LoM Backfill Quantities

Backfill Summary	(m ³)
Total Backfill Volume	1,131,988
CRF High Strength (4.8% cement)	152,219
CRF Low Strength (3.8% cement)	979,768

Source: OceanaGold

Waste Rock


Waste rock from the underground will be hauled to the surface to be used in the production of CRF. Although there is scope to haul some waste to secondary stopes, it is not included in this study.

Grade Control

The characterization of ore versus waste and further geochemical waste classification will be completed through diamond core drilling of the stope accesses prior to mining. Once the footwall level access is established, a mobile drill rig will drill an uphole and a downhole from each ore-drive access. Drilling will occur on every second level (the downhole from each collar location removes the need to drill from the level below). Each stope will have a drillhole pierce both the hangingwall and the footwall. The drilling in 2023 totals approximately 10,000 m and follows the development schedule. This will drill out the deposit to an adequate drill density for accurate grade control estimation.

The core will be logged, sampled and analyzed to provide grade control and geochemical waste classification information. Geologic and block models will be updated with this information and ore/waste grade boundaries will be pre-determined prior to mining the stope accesses. Areas considered to be waste will be characterized geochemically to determine which stockpile the material should be sent to. Geochemical sampling techniques for the underground mine will follow existing open pit sampling techniques. Initially, all stope accesses will be drilled and sampled to ensure adequate definition for each stope.


The existing onsite lab, Kershaw Minerals Lab (KML) analyzes Au, Ag, total carbon, and total sulfur. LECO is used to determine total carbon/sulfur on a percentage of production samples for detailed carbon and sulfur speciation. Lab turnaround time is expected to be 18 to 26 hours.

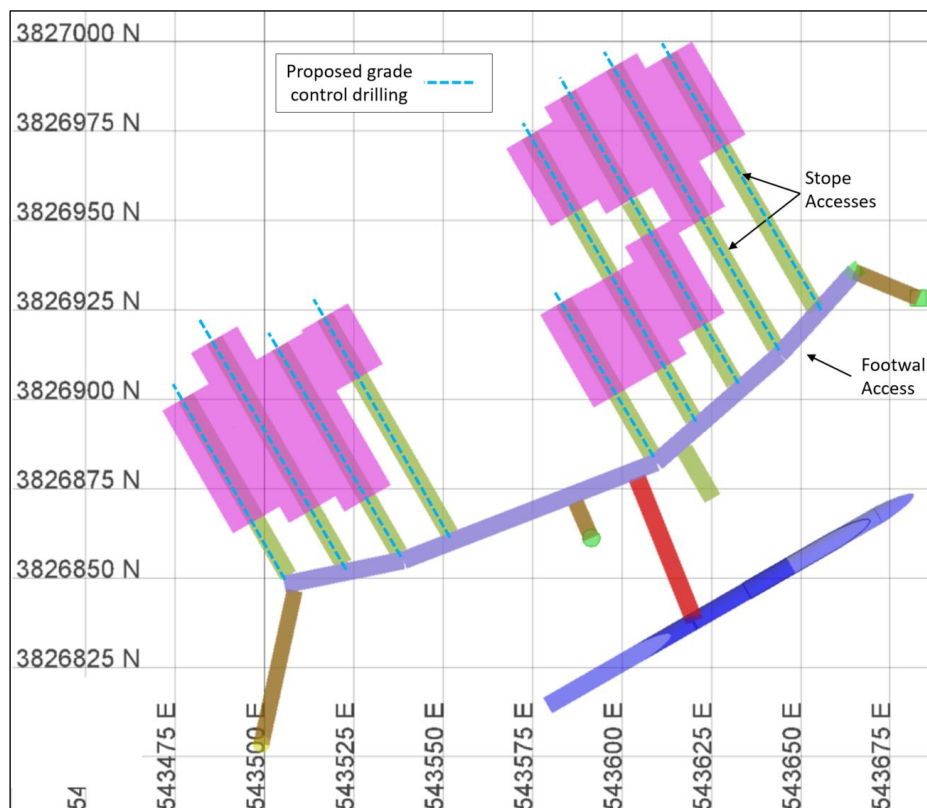

Source: SRK, 2017

Figure 16-38: Level Section Showing Planned Diamond Drilling from Footwall Access Drifts

Additionally, as the stope accesses are being mined, a mine geologist will observe, map and channel sample the exposed rock on each rib. Typically, the predominant fabric of the mineralization will display an inclined orientation on the ribs and the channel samples will need to be oriented normal to this fabric as shown in Figure 16-39.

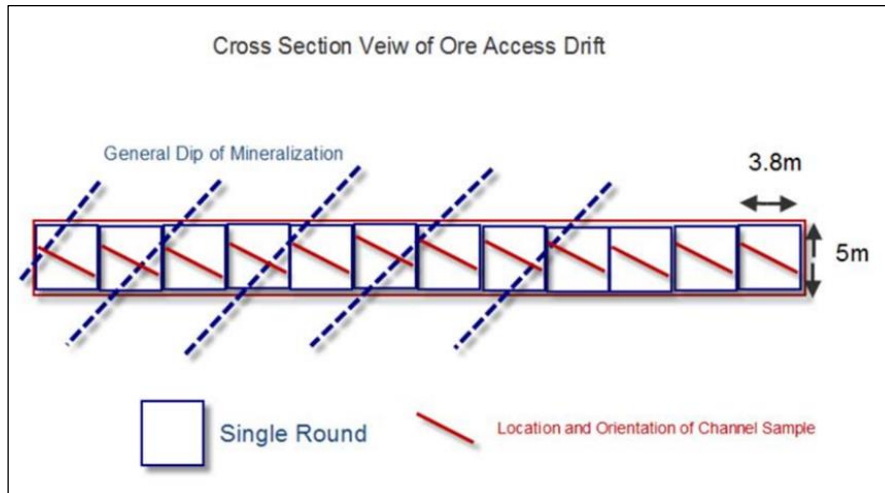

Source: SRK, 2017

Figure 16-39: Cross Section View of Development Rounds and Proposed Channel Sampling Locations

The mine geologist will identify the presence of silicification or sulfidation and utilize these alterations to determine where sample breaks will occur. Using the inclined channel sample orientation, samples lengths for each cut will be 4 to 5 m in length. Samples will be collected as continuous channels at nominal 1 to 2 m lengths depending on the observations of the geologist. Channels can be sawn or chipped depending on the nature of the rock being collected. Sample breaks will be made at lithologic or alteration contacts.

Once mining has progressed to a point where sufficient testing has shown that estimated grades based on core samples reconcile to channel sampling during actual mining, a portion of the diamond drilling or channel sampling may be eliminated.

16.2.10 Ventilation

The ventilation system has been designed to support the development and production activities for the underground mine. The total life-of-mine analysis includes the predicted distribution of airflow and pressure. The design is detailed in a life of mine development model. A 3D ventilation model was created using Ventsim Design 5.3.

Input Parameters

The location of the mine is in a very temperate area with the average low temperature in January of 1.3°C (average high 11.8°C), and an average high temperature in July of 32.6°C (average low 19.8°C). Combined with the shallow depth and apparent lack of geothermal activity, this mine does not appear to present thermal stress related issues, so studies in these areas were not developed.

No harmful strata gases are expected to be encountered at this site. No crushers or fixed ore/waste conveyances (continuous acute dust sources) are currently designed underground. Strategies for controlling dust while loading and hauling ore/waste are an important operational consideration with little impact at this design stage. The configuration of the system is as an exhausting ventilation system, which minimizes the blast clearance time/possibility of exposure to blast-generated gases by maintaining the ramp clear of blasting fumes.

Airway dimensions are as per the mine design, with the main ramp being 5 m x 5.5 m and the raises to surface at 4 m x 6 m (blast hole design with offsets on each level). Oval equivalent duct of 1.65 m equivalent was modeled for the main decline development, with 1.4 m duct used for the fresh air and exhaust access developments. Model friction factors, resistances, shock losses, etc. were used based on available data and standard best practice as shown in Table 16-41.

Table 16-41: General Ventilation Modeling Parameters

Design Point	Friction Factor (kg/m ³)	Resistance (Ns ² /m ⁸)	Notes
Level Access Drive	0.011		Standard base value for general horizontal development
Ramp	0.014		Slightly elevated friction factor to represent the additional losses associated with the spiral development
Drop Raise	0.018		Elevated friction factor associated with the construction methodology
Single Steel Equipment Door, "Kennedy Door"		20	Steel doors to be used on all level accesses to the fresh air and exhaust raise transfers to allow for easy infrequent mucking of sloughage and spill material.

Source: SRK

Airflow Requirements

The expected equipment load was calculated based on the equipment list. A generic airflow dilution value of 0.04 m³/s per kW power for diesel engines has been used for this study because of the decision to use Tier 4 diesel equipment, and the assumption that all equipment listed in the fleet summary would be used in the mine and listed with a 100% utilization value. The high utilization value provides for some conservativeness in the evaluation. A general leakage value of 20% was assumed to provide the minimum airflow requirement. Airflow for individual pieces of equipment in the mine will need to meet the requirements of CFR57.5067 which refers to the nameplate dilution values determined by MSHA/NIOSH testing, or meet the EPA requirements. Overall, the minimum airflow requirement for the mine is approximately 250 m³/s for the CRF design or 190 m³/s for the paste fill design as shown in Table 16-42 and Table 16-43. For the paste fill design, ample time will need to be given in the production cycle before mining adjacent to the filled stopes to allow for the heat from the fill to be dissipated.

Table 16-42: Cemented Rock Fill Equipment Load and Minimum Airflow Calculation

Equipment (Main Equipment Only)	Rated Power (kW)	Measured and Indicated Reserve Schedule							Inferred Add On	
		2021	2022	2023	2024	2025	2026	2027	2028	2029
LHD (LH517i) - Tier 4	315	1	2	3	3	3	3	3	3	3
Haul Truck (TH 551i) - Tier 4i	515	1	2	6	6	6	6	6	6	6
Spray Mech - Tier 3	110	1	1	1	1	1	1	1	1	1
Agi Truck - Tier 3	170	1	1	1	1	1	1	1	1	1
Large IT - Tier 4	180	1	1	1	1	1	1	1	1	1
Small IT - Tier 4	122	1	1	1	1	1	1	1	1	1
12k Grader - Tier 4	140	1	1	1	1	1	1	1	1	1
Charde-Up - Tier 3	120	1	1	2	2	2	2	2	2	2
Scissor Lift - Tier 3	120	1	1	1	1	1	1	1	1	1
Water Truck - Tier 3	155	1	1	1	1	1	1	1	1	1
Diesel Dilution @ 0.04 m³/s/kW (m³/s)		78	111	211	211	211	211	211	211	211
General Leakage Allowance		10%	10%	20%	20%	20%	20%	20%	20%	20%
Total Minimum Airflow Requirement (m³/s)		86	122	253	253	253	253	253	253	253

Source: SRK

Table 16-43: Paste Fill Equipment Load and Minimum Airflow Calculation

Equipment (Main Equipment Only)	Rated Power (kW)	Measured and Indicated Reserve Schedule							Inferred Add On	
		2021	2022	2023	2024	2025	2026	2027	2028	2029
LHD (LH517i) - Tier 4	315	1	2	2	2	2	2	2	2	2
Haul Truck (TH 551i) - Tier 4i	515	1	2	4	4	4	4	4	4	4
Spray Mech - Tier 3	110	1	1	1	1	1	1	1	1	1
Agi Truck - Tier 3	170	1	1	1	1	1	1	1	1	1
Large IT - Tier 4	180	1	1	1	1	1	1	1	1	1
Small IT - Tier 4	122	1	1	1	1	1	1	1	1	1
12k Grader - Tier 4	140	1	1	1	1	1	1	1	1	1
Charde-Up - Tier 3	120	1	1	2	2	2	2	2	2	2
Scissor Lift - Tier 3	120	1	1	1	1	1	1	1	1	1
Water Truck - Tier 3	155	1	1	1	1	1	1	1	1	1
Diesel Dilution @ 0.04 m³/s/kW (m³/s)		78	111	157	157	157	157	157	157	157
General Leakage Allowance		10%	10%	20%	20%	20%	20%	20%	20%	20%
Total Minimum Airflow Requirement (m³/s)		86	122	188	188	188	188	188	188	188

Source: SRK

Auxiliary Ventilation Systems - Development

The decline and main access development auxiliary ventilation systems are sized to ventilate the simultaneous operation of a truck and LHD.


- The fresh air and exhaust accesses will be developed with single 1.5 m, 150 kW fan and will be able to support the operation of one truck and one LHD. The development length will be approximately 300 m. A single 1.4 m diameter duct will be required.
- The main access decline will be approximately 600 m and will require a slightly different ventilation system for development. Two 1.5 m, 150 kW fans mounted outside of the portal in series blowing into a 1.65 m oval equivalent duct will be able to provide ventilation for one LHD and a single truck. The single 1.65 m oval equivalent duct can be used to develop the initial decline. In the immediate development face area, a length of supplemental duct can be attached to the main duct to provide ventilation directly at the face during blasting, and during loading. The supplemental duct is advanced with the face and is not left incorporated within the long-term duct installation.

Stope Ventilation

For the stope auxiliary ventilation system, auxiliary fans will be located in “cutouts” in the ramp and will then draw the airflow to the active stope areas. The initial trunk line duct will be approximately 100 m (1.4 m diameter), with two approximate 160 m (1.2 m diameter) ducts delivering the airflow to the stope faces. The level ventilation fan will be required to operate at approximately 40 m³/s at 1.5 kPa, 80kW (allowing for approximately 15% leakage).

Ventilation Model

The life of mine ventilation model was developed to represent two options: measured/indicated reserves and measured/indicated/inferred reserves. Two different levels of airflow were examined; CRF equipment load and paste fill equipment load. The basic ventilation circuit remains the same for all scenarios. The mine is split into two operating zones; upper and lower. The upper zone is ventilated by fresh air drawn in from the ramp from the surface and exhausted into the exhaust raise system through a connection at the ramp midpoint, and the lower zone is ventilated by airflow that is drawn into the ramp through a fresh air raise system and exhausts into the main exhaust raise system at the bottom of the mine. This provides two distinct mining areas that are split and provides a degree of compartmentalization. The basic ventilation layout is shown in Figure 16-40.

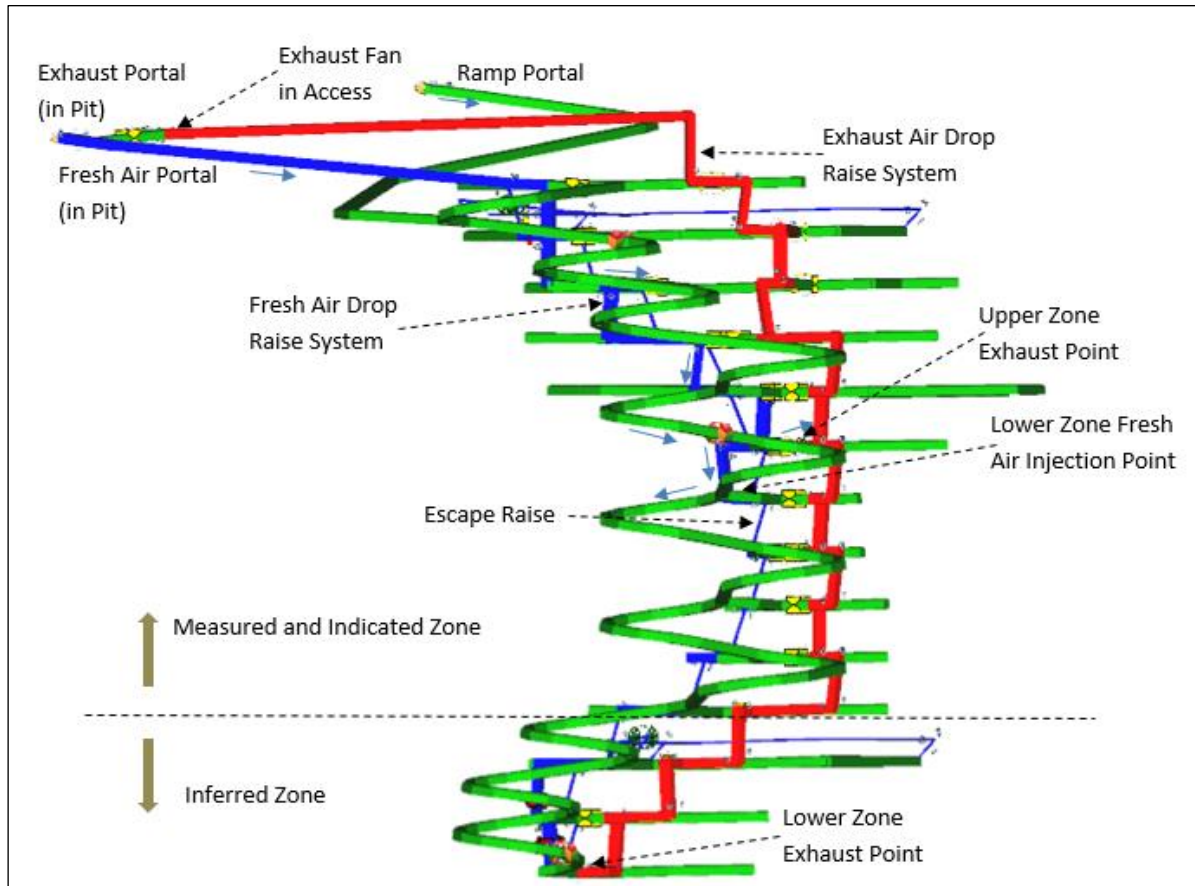

Source: SRK, 2020

Figure 16-40: Ventilation System Layout

Each of the connections between the levels and the fresh air raise system and exhaust raise system is isolated by a set of manual doors so that infrequent mucking of the transfer levels can be accomplished. This results in a possible increase in leakage if the doors are not maintained, but will be necessary to allow for access. Secondary egress will be by way of a separate raise system.

The required main fan operating points for the surface exhaust fans are identified in Table 16-44. A parallel exhaust fan system (2 fans) should be considered for this system. This will allow for some amount of redundancy in the event of a fan outage (when one fan of a parallel fan installation is in operation generally approximately 70% of the original airflow can be achieved). The Paste Fill scenario will require a main fan installation consisting of two fans mounted in parallel with a diameter of approximately 2 m, and the CRF scenario will require approximately 2.15 m. The fans should also be installed with variable frequency drives so that the rotational speed can be modified which will increase the efficiency and adaptability of the ventilation system. This will allow the system to be easily modified as it grows.

Table 16-44: Main Fan Requirements

Scenario	Total Fan Requirement						Parallel Fan Installation (Single Fan Duty Point)			
	Airflow (System) (m ³ /s)	Bulkhead Pressure (kPa)	Inlet/Outlet Losses (kPa)	Total Pressure (kPa)	Efficiency (%)	Power (kW)	Airflow (per Fan) (m ³ /s)	Total Pressure (kPa)	Efficiency (%)	Power (kW)
M & I CRF	255	1.26	0.25	1.51	75%	513	128	1.51	75%	257
M & I Paste Fill	190	0.71	0.25	0.96	75%	242	95	0.96	75%	121
M, I & I CRF	270	1.49	0.25	1.74	75%	626	135	1.74	75%	313
M, I & I Paste Fill	205	0.87	0.25	1.12	75%	307	103	1.12	75%	154

Source: SRK

16.2.11 Mine Services

Dewatering

The dewatering system will be built in phases as the mine develops and consists of a portable development system and permanent level pump stations. The system is designed to handle a capacity of 31.5 L/sec.


The system will pump from the underground workings through steel and HDPE pipes to a surface pond where the water will be returned through an existing system to the existing water treatment plant at the processing plant.

The portable development system will be used from the portal to the 1025 level where a permanent pump station will be constructed. A rising main hole will be drilled from surface to the 1025 pump station. Once commissioned, the portable pumping system will pump to the 1025 pump station, and from there to surface. The option also exists to pump from the 1025 pump station through the fresh air intake portal to a sump in the Snake Pit, where existing diesel pumps and infrastructure will pump to the surface pond.

As the mine progresses deeper, second and third permanent pump stations will be established on the 950 and 825 levels, respectively. Rising main holes will be drilled to connect each pump station directly.

Level sumps will be established on each level to catch water generated from mining activities on the levels and pump water to the nearest pump station in stages. Drain holes will be drilled between level sumps to help prevent overflowing of water onto the decline if pump failure occurs.


The location of the underground dewatering infrastructure is shown in Figure 16-41.

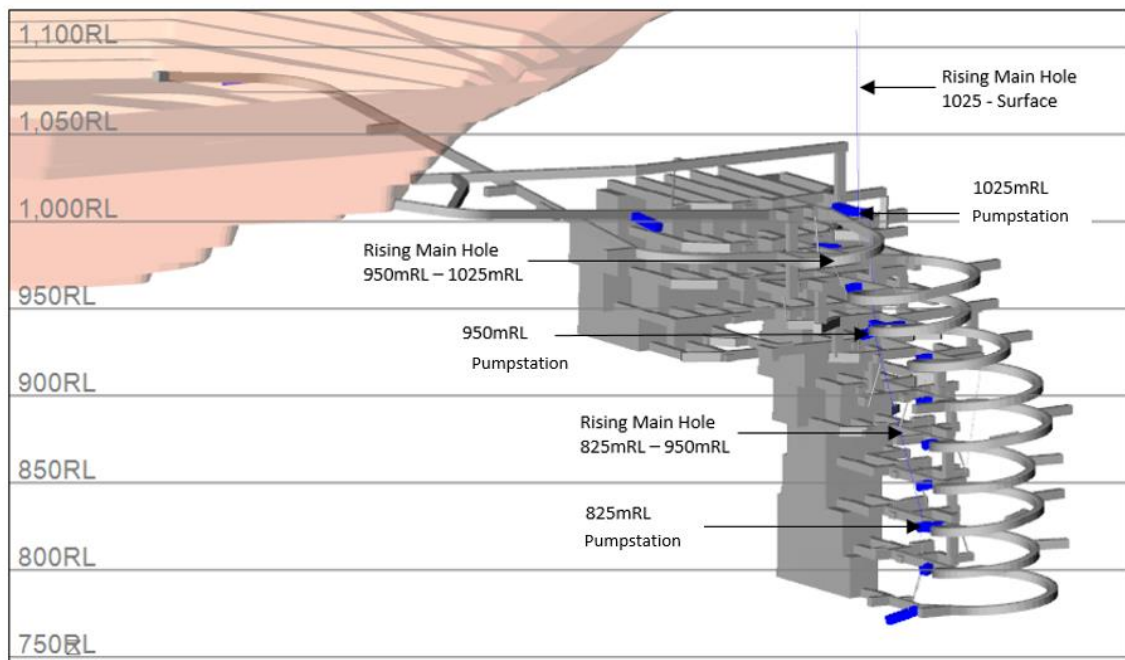

Source: OceanaGold

Figure 16-41: Dewatering System Layout

The primary pumping system will consist of pump skid stations as shown in Figure 16-42. Each skid station has two pumps, with a nominal flow capacity of 20 L/s per pump. The pumps are powered by 75 kW motors and are capable of 240 m of maximum head.

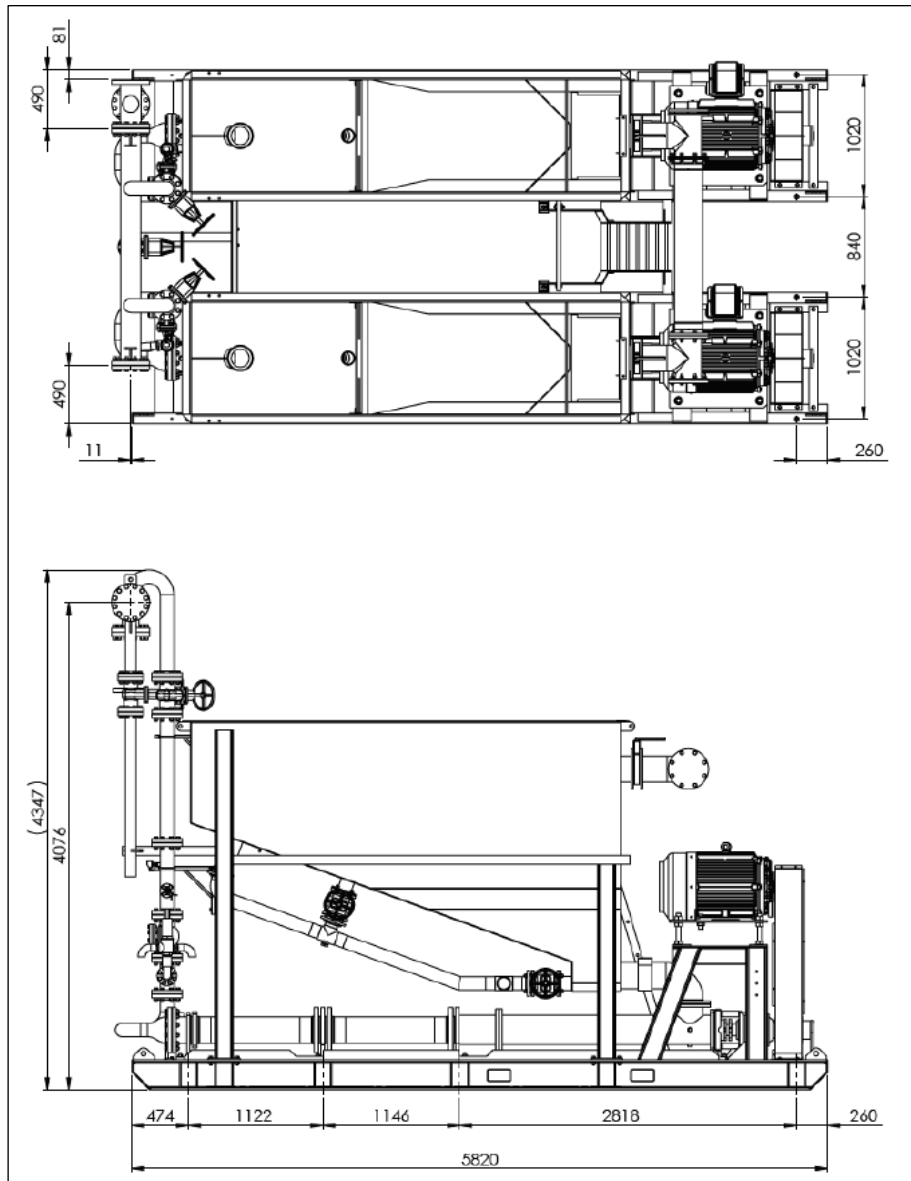

Source: Challenge Pumps, 2020 (units shown in millimeters)

Figure 16-42: Portable Pumping Skids

Surface dewatering will be ongoing during the time of underground production and a surface dewatering well is anticipated to be located near the main decline to minimize water encountered during development.


Electrical

Initially, power will be provided by a generator located at the portal location for the portal fans, mine pump system, and mine equipment required during the initial development of the mine.

Once mine development has progressed to the 1000mRL and the first substation cuddy is developed, the mine electrical system will be supplied from the existing power line from the main substation at the processing plant through the 24.9 kV power line. Electrical holes will be drilled from surface to the 1000mRL substation, establishing high voltage reticulation underground.

Power will be carried deeper as the mine progresses in power cables fed through additional electrical holes between each substation in order to keep high-voltage cables off the decline. The substations will step the power down to distribution boards and jumbo boxes located in cuddies on the footwall drives of each level to feed the underground mobile equipment, fans and pumps.

Locations of electrical underground infrastructure is shown in Figure 16-43.

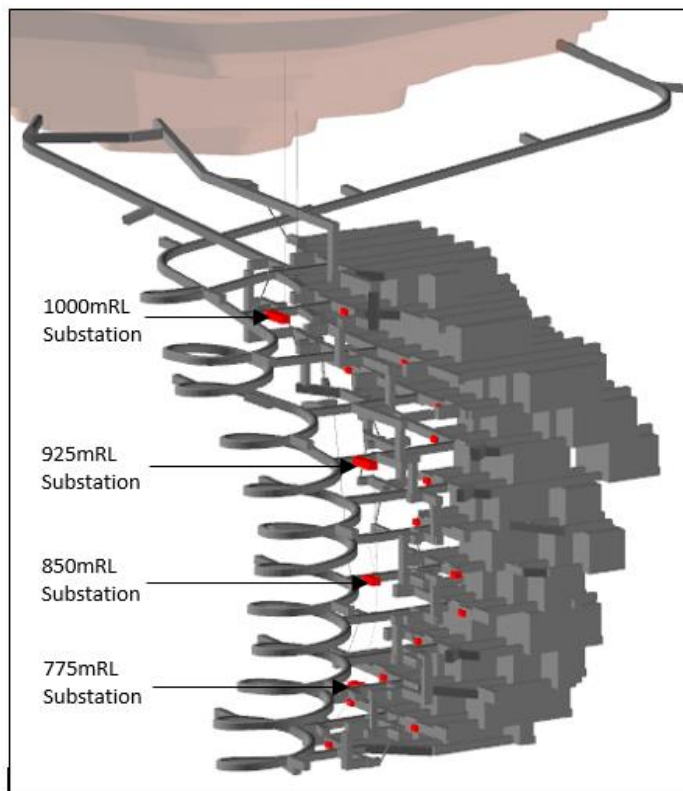

Source: OceanaGold

Figure 16-43: Electrical System Layout

Once stoping commences in 2023, the average power usage is 1.65 million kWhr per month with an average operating load of 2.32 MW.

Health & Safety

The mine design incorporates MSHA safety standards for secondary egress, which will be via 1.1 m diameter raisebored escapeway raises fitted with ladderways. Additionally, three 12-person and one six-person mobile refuge chambers are included and will be located in active working areas over the LoM.

The mine will have a communications system that has both mine phones and wireless communication. A mine rescue team will support the operation. The mine safety program will integrate with local providers in case of any mine emergency. A stench gas emergency warning system will be installed in the mine's intake ventilation system. This system can be activated to warn underground employees of a fire situation or other emergency whereupon emergency procedures will be followed.

Manpower

Manpower levels are estimated based on the production schedule and associated equipment operating requirements. The estimate is based on a mine operating schedule consisting of 12 hours per shift, two shifts per day, and seven days/week. Each 12 hr shift is supported by a four-crew rotation.

The management and technical team will work five eight-hour days per week.

Table 16-45 shows the required workforce by year.

Table 16-45: Mine Labor by Year

Category	2021	2022	2023	2024	2025	2026	2027
Supervision	12	13	10	9	9	9	6
Tech Services	5	15	18	18	18	18	10
Maintenance	11	27	55	53	50	45	33
Lateral Dev.	12	48	42	31	21	16	12
Vertical Dev.	0	0	0	0	0	0	0
Production	0	0	35	35	34	38	28
Material Handling	0	0	0	0	0	0	0
Backfill	0	0	18	26	26	26	17
Mine Services	0	3	17	17	14	11	8
Total	42	105	195	189	172	163	114

Source: OceanaGold

The distribution of owner and contractor labor is shown in Table 16-46.

Table 16-46: Owner and Contractor Workforce Distribution

Category	2021	2022	2023	2024	2025	2026	2027
Contactors	22	46	37	4	0	0	0
OGC Employees	20	59	158	185	172	163	114
Total	42	105	195	189	172	163	114

Source: OceanaGold

Mine Mobile Equipment

The mine mobile equipment requirements as summarized in Table 16-47 are based on the production schedule.


Table 16-47: Mobile Equipment Fleet

Category	Make	Model	Max Units
Development Drill	Sandvik	DD421-60C	2
Bolter	Sandvik	DS421C Bolter	1
Longhole Drill	Sandvik	DL421-7C	2
LHD	Sandvik	LH517	4
Truck	Sandvik	TH551	6
Shotcreter	Spraymec	6050WP	1
Transmixer	UTIMEC	MF 500	1
Wheel Loader	Caterpillar	962H	3
Wheel Loader	Caterpillar	938K	1
Grader	12K	12K	1
Hilux	Hilux	Hilux	1
Charge-up	Charmec	MC 605	2
Scissor Lift	UTIMEC	Scissor	1

Source: OceanaGold

16.3 Combined Open Pit and Underground Production Schedule

Figure 16-44 and Table 16-48 and show the combined open pit and underground production schedule annually.

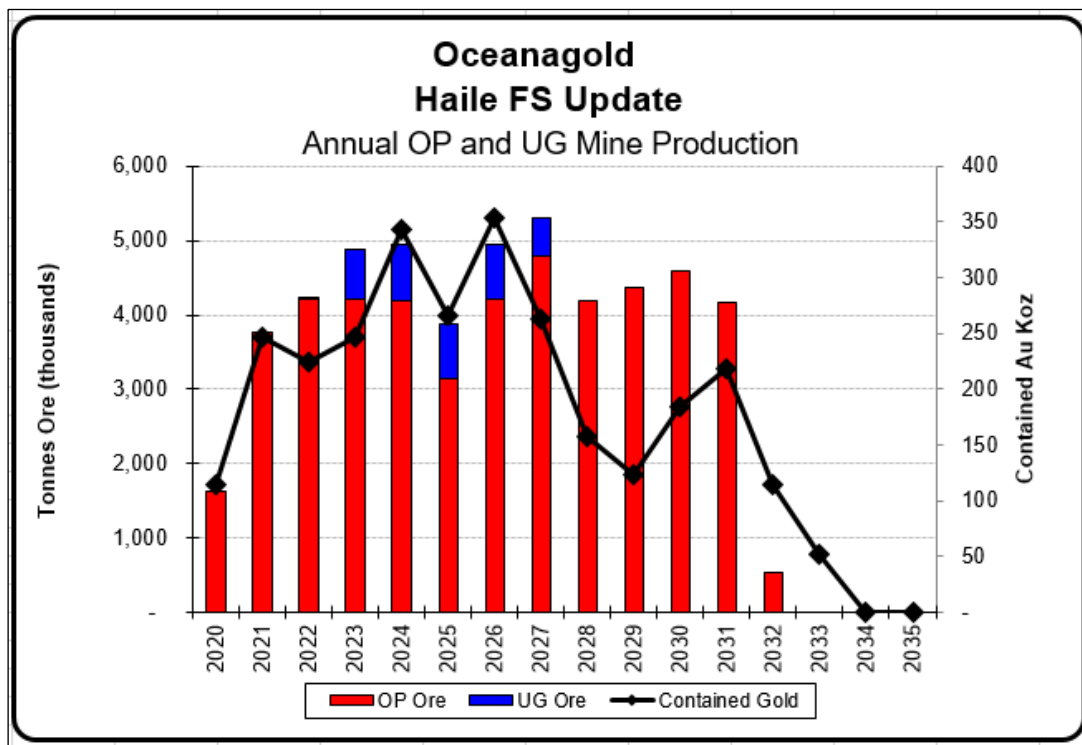

Source: SRK

Figure 16-44: Combined Open Pit and Underground Production

Table 16-48: Combined Open Pit and Underground Production Schedule*

Year		2020	2021	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032	2033	LoM Total
Total Production																
Ore	kt	1,638	3,769	4,222	4,871	4,951	3,875	4,941	5,306	4,200	4,371	4,588	4,176	539	-	51,447
Ore	t/d	4,487	10,327	11,567	13,345	13,564	10,615	13,537	14,538	11,507	11,976	12,571	11,440	1,477	-	10,842
Au Grade	g/t	2.15	1.81	1.66	1.67	2.27	2.12	2.44	1.61	1.14	0.93	1.32	1.65	3.00	-	1.73
Contained Au	koz	113	220	225	262	361	265	387	276	154	130	195	222	52	-	2,861
Ag Grade	g/t	2.04	2.02	2.27	2.04	2.19	2.06	2.13	2.18	2.11	2.35	2.50	2.62	3.04	-	2.23
Contained Ag	koz	107	245	308	320	348	257	338	373	285	331	369	351	53	-	3,685
Underground																
Ore	kt	-	-	15	661	751	742	738	510	-	-	-	-	-	-	3,416
Ore	t/d	-	-	41	1,811	2,057	2,032	2,023	1,396	-	-	-	-	-	-	1,560
Au Grade	g/t	-	-	5.03	3.99	4.07	4.53	3.26	2.70	-	-	-	-	-	-	3.78
Contained Au	koz	-	-	2.4	84.8	98.2	108.0	77.5	44.3	-	-	-	-	-	-	415.1
Ag Grade	g/t	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Contained Ag	koz	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
Waste	kt	-	69	334	226	128	56	7	2	-	-	-	-	-	-	822
Open Pit																
Ore	kt	1,638	3,769	4,207	4,210	4,200	3,133	4,203	4,797	4,200	4,371	4,588	4,176	539	-	48,031
Ore	t/d	4,487	10,327	11,525	11,535	11,507	8,584	11,514	13,141	11,507	11,976	12,571	11,440	1,477	-	10,122
Au Grade	g/t	2.15	1.81	1.65	1.31	1.94	1.56	2.29	1.50	1.14	0.93	1.32	1.65	3.00	-	1.58
Contained Au	koz	113.00	219.52	222.99	177.53	262.45	156.68	309.72	231.23	154.31	130.07	195.29	221.53	51.93	-	2,446.24
Ag Grade	g/t	2.04	2.02	2.28	2.36	2.58	2.55	2.50	2.42	2.11	2.35	2.50	2.62	3.04	-	2.39
Contained Ag	koz	107.4	245.3	307.9	320.0	348.1	257.0	337.6	372.6	284.9	330.9	369.1	351.2	52.6	-	3,684.7
Strip Ratio	t/t	11.77	10.76	9.57	9.59	9.59	13.00	9.63	8.44	9.59	9.25	4.37	0.88	0.30	-	8.47
Waste	kt	19,282	40,553	40,258	40,357	40,299	40,719	40,478	40,497	40,284	40,427	20,067	3,658	161	-	407,040

*Does not include stockpile material

17 Recovery Methods

A conventional flotation and cyanide leaching flow sheet is used at HGM. The process commenced commercial operation in 2017 with a nameplate capacity of 2,300,000 t/a, with a progressive debottlenecking process undertaken to upgrade the plant to the current capacity of 4,000,000 t/a.

In general, the response of the ore treated to the plant flowsheet has been within expectations with gold deportment and leach extractions observed to be in accordance with that predicted through the original feasibility program. Mill throughput has exceeded predictions with mill specific energy requirements lower than that originally forecast and in line with updated competency-based power modelling predictions.

17.1 Processing Methods

Progressive debottlenecking and upgrades to the processing plant proceeded following successful commissioning of the process plant. The flowsheet and unit operations did not change as part of the upgrades with the target of 4,000,000 t/a capacity increase achieved with a reduced scope than that expected during the optimization study completed in 2016.

Benchmarking surveys of the grinding circuit were completed in 2017/18 along with additional competency testing of future ore sources. Power modelling of the circuit with several external consultants identified the Haile ore requires approximately 30% less energy than that predicted from power modelling and SMC test results. A site-specific comminution model was developed with a strong correlation between SMC test parameters and Bond ball mill work index with SAG specific energy requirements. The work provided confidence to proceed with installation of the pebble crusher and did not need secondary crushing of SAG feed for the majority of the ore types in the mine plan tested to achieve desired annualized throughput of 4 mt/a.

The key additions to the process plant for the expanded capacity included:

- Upgrade to apron feeder motors for the crusher and emergency feeder
- Speed upgrade to the SAG feed conveyor to achieve 600 t/h rate
- Pebble crushing installation on existing SAG mill scats recycle
- Installation of a Nippon Eirich ETM-1500 tower mill (1.2MW) and 10-inch cyclone pack
- Installation of an M10000 Isamill (3MW) and six cyclone pack
- Installation of a larger 14 m diameter high rate pre-aeration thickener
- Replacement of the flotation tailings thickener feed well and rakes with an Outotec Vane Feedwell system,
- Installation of a third cyanide destruction tank and upgrades to the agitators of the existing two tanks
- Modifications to the strip circuit automation, barren tank management and cyanide strength to reduce cycle time to under 10 hours
- Motor upgrades to the flotation tailings and cyanide recovery thickener underflow pumps
- Upgrade to the final tailings pumps in the plant
- Installation of a tailings pump booster station at the tailings storage facility to accommodate the raising of the dam wall and discharge around the entire dam perimeter at higher tonnage

- Implementation of the Andritz expert system to cover SAG mill, ball mill, cyclone, thickening and cyanide destruction circuits to maximize throughput

The process plant consists of the following major components:

- Crushing and conveying
- Storage and stockpiling of ore and reclaim
- Grinding
- Flotation
- Fine grinding of concentrate
- Carbon in leach (CIL) recovery of precious metal values from reground flotation concentrate and flotation tailings
- Acid washing and elution of precious metal values from CIL loaded carbon
- Electrowinning and refining of precious metal value
- Thermal regeneration of eluted carbon and recycle to CIL
- CIL tailing thickening, cyanide recovery, detoxification and pumping of slurry to storage

The following section describes the plant operation currently in operation at Haile.

A relatively compact Run of Mine (ROM) area is provided for storage and re-handling of ore allowing blending to minimize variation of head grade (sulfur and gold) and rock type, into the crusher. Ore is rehandled into the crusher dump pocket by Front End Loader (FEL).

Ore is reclaimed by an apron feeder onto a vibrating grizzly that delivers scalped oversize to the primary jaw crusher to reduce the ore size from RoM to minus 150 mm. Crushed ore is conveyed for surge and storage of the recombined grizzly undersize fines and primary crushed ore in a coarse ore surge bin or diverted on to an open conical emergency stockpile for later reclaim by Front End Loader (FEL) into a reclaim bin.

Ore is reclaimed from either the surge or reclaim bins, separately or simultaneously, using apron feeders onto a SAG mill feed conveyor belt delivering into the SAG mill feed chute.

Ore is milled in the SAG–Ball Mill–Pebble Crusher (SABC) circuit. The SAG mill operates in closed circuit with a vibrating discharge screen and a pebble return circuit incorporating a surge bin and Sandvik CH-440 cone crusher. The ball mill operates in closed circuit with hydrocyclones to produce the desired grinding product size of 75 microns.

Selected flotation reagents are added in the grinding circuit. A portion of the grinding circuit ball mill circulating load is treated in a flash flotation cell with the concentrate going to the regrind circuit.

The grinding circuit product passes to a bank of bulk rougher flotation cells to recover the balance of the sulfide mineralization. Thereafter, the combined flash and rougher flotation concentrates are reground in a two-stage circuit utilizing an ETM-1500 tower mill in closed circuit with cyclones to a P_{80} under 40 microns and then followed by an M10000 Isamill in closed circuit with cyclones to a target P_{80} of 13 microns.

The reground concentrate slurry is dewatered in a high-rate thickener prior to transfer to a tank for the pre-aeration step followed by cyanide leaching in a Carbon-in-Leach (CIL) circuit to dissolve gold and silver and adsorb the precious metal values from the solution onto activated carbon.

The flotation tailings slurry is thickened to recycle process water to the grinding circuit. The thickened tails slurry will be combined with the leached concentrate stream and processed in an extension of the carbon in leach circuit to recovery any leachable gold and silver contained in the float tail.

The loaded carbon is removed via screens from the CIL circuit and after further treatment by acid washing to reduce calcium scaling, precious metals are stripped with hot caustic-cyanide solution. The gold and silver are recovered by electrowinning from this solution and the stripped carbon is heated in a kiln under a reducing atmosphere for thermal reactivation of its adsorption capability before being returned to the CIL tanks for reuse.

The precious metal sludge from the electrowinning cells is dried and blended with fluxes and smelted to produce gold-silver doré bars, which are the final product of the ore processing facility.

The tailing slurry exiting the CIL is dewatered in a similar thickening stage to the flotation tailings for recovery of the cyanide solution and reduction of the volume of slurry needing to be treated by oxidation of the residual cyanide.

The detoxified tailing slurry is pumped for long-term storage in a lined Tailings Storage Facility (TSF) and supernatant water in the pond is recycled for reuse back at the plant.

The plant has facilities for the storage, preparation, and distribution of reagents to be used in the process.

Reagents include flotation reagents i.e., Sodium isobutyl xanthate (SIBX) and frother, as well as sodium cyanide, caustic soda, flocculant, copper sulfate, ammonium bisulfite, hydrochloric acid, lime and anti-scalants.


Small amounts of fresh and potable water make-up are required in the process, but the main water requirements are satisfied by internal recycle from the thickeners and tailings decant water returned from the TSF.

The process plant also operates the water treatment plant (WTP) treating contact water from the mine active pits, seepage from the PAG cells and surface water runoff from the active PAG cells. A two-stage process is utilized with pH raised to a target of 9 to precipitate out metals followed by clarification for solids removal, then pH is raised to 10 to precipitate out other heavy metals. This is followed by clarification, microfiltration, pH adjustment back to a 7-8 range and is then discharged to the environment.

The WTP utilizes lime from the main plant ring main for pH control along with local mixing of flocculant, coagulants and metals precipitants as required.

17.2 Processing Flowsheet

The overall simplified process flow sheet for the proposed expanded plant is shown in Figure 17-1.

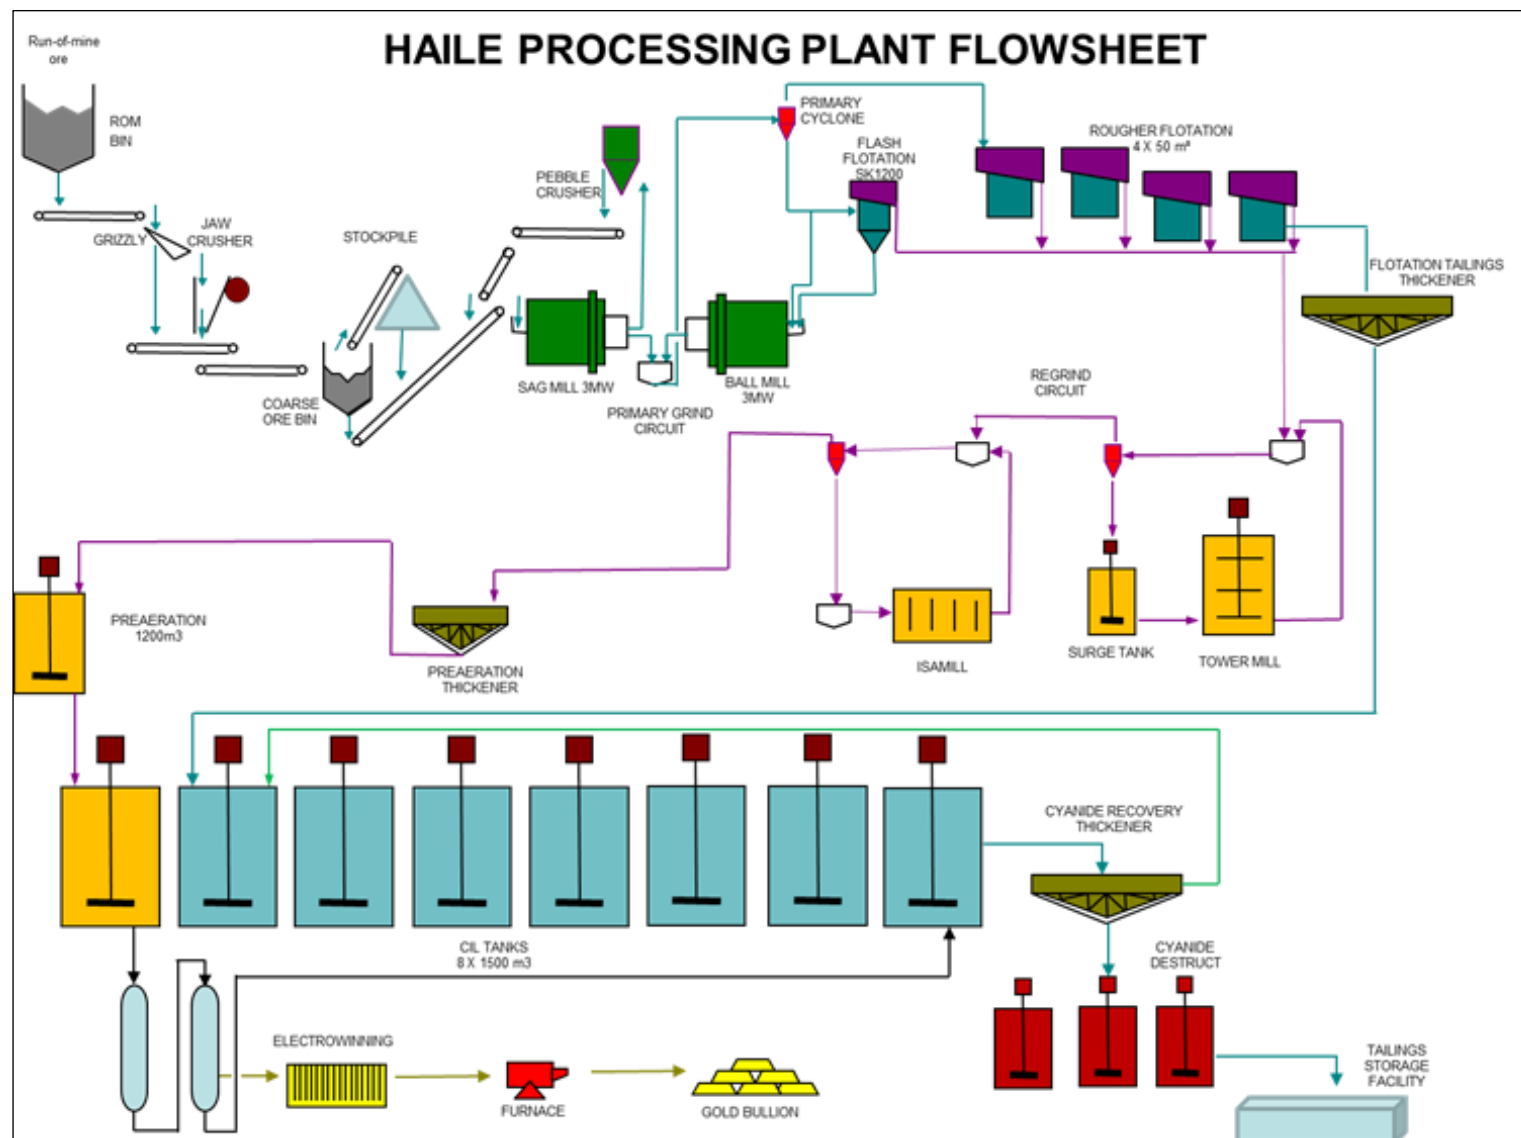


Source: OceanaGold

Figure 17-1: Haile Process Flow Sheet

17.3 Operational Results


Mill throughput ramped up following plant commissioning with nameplate of 285 t/h achieved within approximately six months. Following identification of key bottlenecks and circuit modelling with external consultants, a pebble crusher was commissioned in July 2018 along with an upgrade to the flotation tailings thickener. Mill throughput was then progressively increased as downstream restrictions were addressed. Production history and monthly throughput are shown below in Figure 17-2. The current budget throughput rate is 485tph and this has been achieved in Q1 2020.

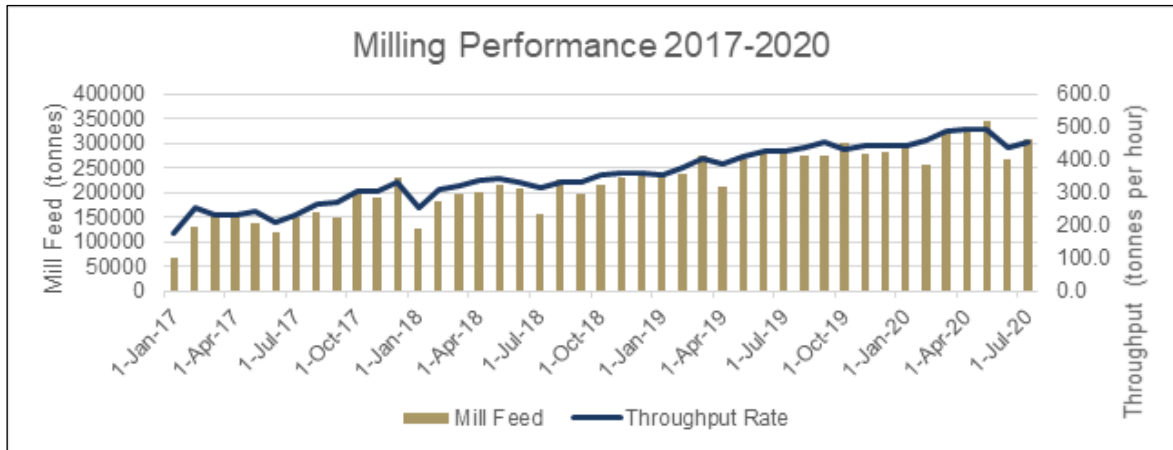

Source: OceanaGold

Figure 17-2: Mill Throughput Performance Since Startup


SAG mill utilization has progressively improved since startup with unplanned downtime reducing as rectification of circuit design has taken place to address high wear issues in the plant. Several extended shutdowns have occurred in July 2018 and April 2019 to tie in major upgrades to the pebble crushing, thickeners and regrind circuits. Historical utilization data since start up is shown in Figure 17-3.

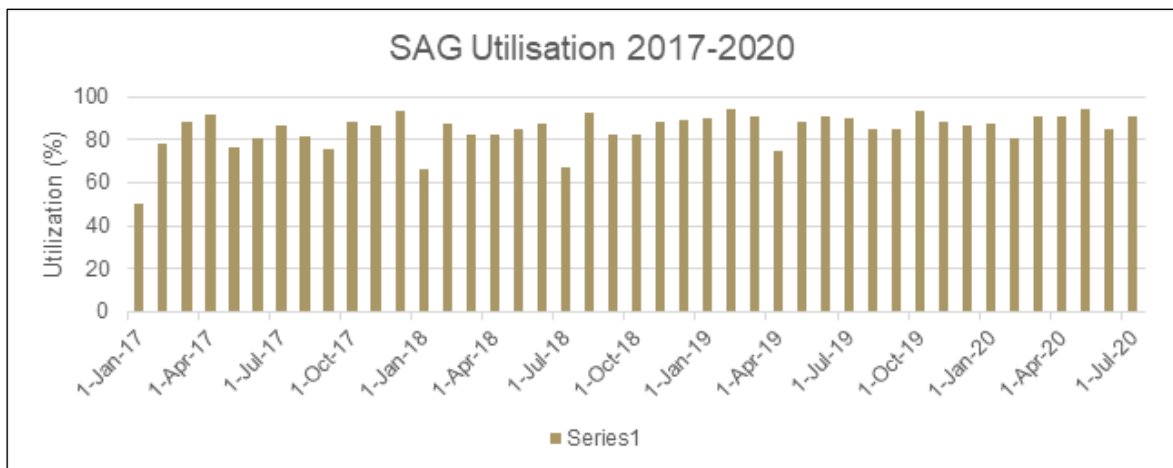

Source: OceanaGold

Figure 17-3: SAG Mill Utilization Since Startup

Flotation performance was affected post commissioning due to the bottleneck of the regrind circuit. The original circuit with two trains of three SMD mills proved unable to achieve the target P80 of 13 microns in open circuit reducing the mass pull that could be achieved. The SMD circuit was converted to closed circuit in late 2017 and changes to the maintenance strategy and media feed systems were made to maximize usable power. The sulfur recovery of the flotation circuit is shown in Figure 17-4 with regrind capacity constraining mass pull and recovery of pyrite to concentrate to around 60% until the regrind circuit upgrade was completed in May 2019 when it then approached the target 80%. Improvements in mill throughput further complicated the issue with regrind capacity prior to Q2 2019. Q2 2020 has seen larger portions of oxide ore in the feed blend bringing down sulfide recovery.

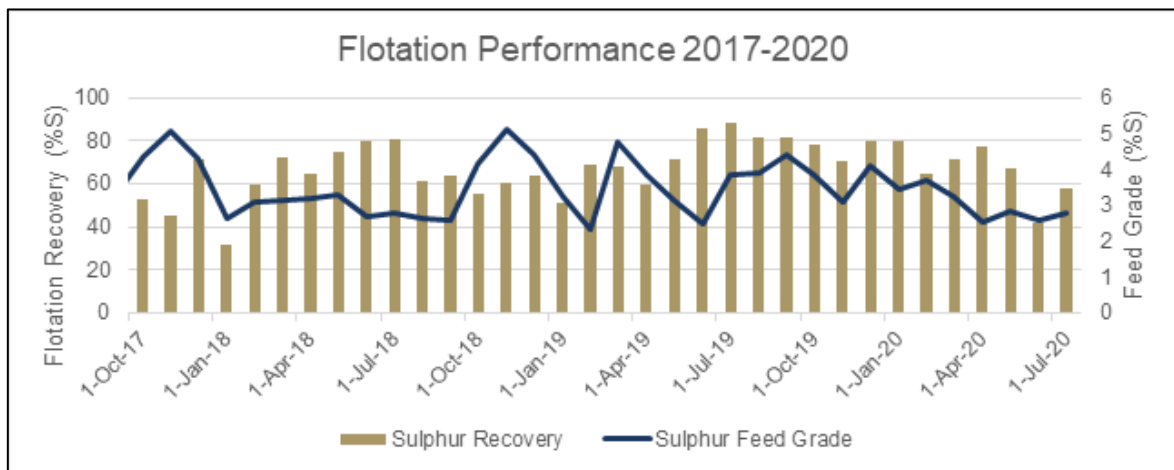

Source: OceanaGold


Figure 17-4: Flotation Circuit Recovery

Gold recovery had trended at or below the feasibility study model as a function of feed grade since startup. A number of key drivers to poor recovery have been identified and progressively rectified including:

- Short circuiting in the CIL tank connecting launder requiring modification and installation of downcomers completed in 2019
- Reduced flotation recovery due to regrind capacity allowing pyrite coarser than target to reach the CIL circuit in the flotation tailings stream with poor gold liberation and reduced leach residence time. This has been progressively addressed through 2019 as regrind capacity increased
- Coarser than design regrind product reaching the CIL circuit reducing liberation of gold, optimization of the new regrind circuit has been progressing over the last 12 months with the target 13 microns now regularly achieved
- Issues with the regeneration kiln effective operation and utilization have had a significant impact on carbon activity leading to low levels of solution loss. Changes to equipment in the circuit has increased utilization of this circuit
- Blending of oxide ore sources with the plant feed as plant throughput ramped up faster than mine output impacting the flotation recovery. Since May 2020 the feed strategy has changed to campaign processing any oxide material on its own straight to CIL

- The operation of the pre-aeration stage ahead of concentrate leach has been examined both internally and with external laboratories under a range of conditions and in practice does not achieve the savings in reagents envisaged. The tank was bypassed in June 2020 leading to lower leach residue grades and a subsequent reduction in cyanide destruction reagent costs from the change in process chemistry. Initial data in the 10 weeks since the change indicates an improvement in leach recovery.

The leach recovery since startup is shown in Figure 17-5 along with the feasibility model and plant head grade.

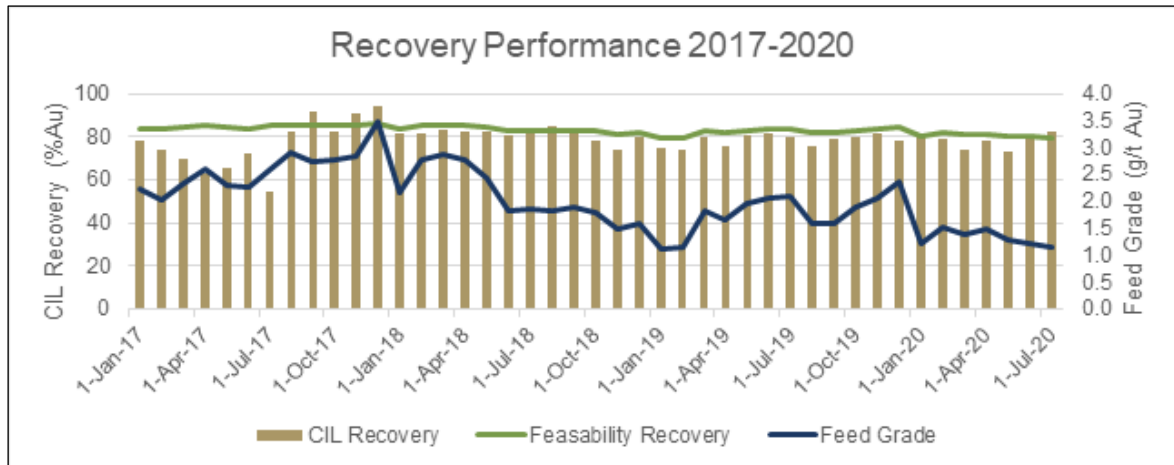

Source: OceanaGold

Figure 17-5: Gold Recovery Performance Since Startup

A number of ongoing process improvement projects have been instigated to further improve recovery based on plant and laboratory test work. These include:

- Implementation of expert system control to maintain target cyanide concentration in the first three CIL tanks
- Installation of a Gekko Carbon Scout to allow improved carbon management to maximize gold loadings and minimize solution loss
- Installation of froth cameras and control on the rougher flotation cells to maximize mass pull
- Monthly composite analysis by MLA and diagnostic leach tests of key process streams to understand circuit performance and gold loss opportunities
- Ongoing monthly mineralogical analysis and diagnostic leach test work on composites of key process streams to quantify circuit loss causes and allow rectification planning.

17.4 Process Unit Costs


Process unit cost history is shown in Figure 17-6 below since operations commenced. Unit cost compliance to budget has improved in the last 18 months from a combination of increased throughput on the fixed cost base and improvements in maintenance planning processes and increasing knowledge of component service life. During 2017 and 2018, modifications and replacement of components occurred to address high wear or material compatibility issues inflating unit costs. The impact of this type of expenditure is now significantly decreased.

Forward budgeting is based on a zero-order buildup based on drivers of feed tonnage or operating time. Operating experience over the last three years has allowed benchmarking of key consumable rates going forward. Key consumable consumption rates are shown in Table 17-1, the production driver metric for treating sulfide ore. Power usage models for the process plant are established to calculate electrical power demand. Long-term maintenance schedules are used to identify reline activities, major overhauls and expected contractor costs.

Table 17-1: Key Consumable Consumption Rates

Consumable		Consumption Rate
2" Ball Mill Balls	kg/tonne ore	0.398
5 SAG Balls	kg/tonne ore	0.330
.75" Tower Mill Balls	kg/tonne ore	2.22
2.5mm ISA Mill Media	kg/tonne ore	1.35
Carbon	kg/tonne ore	0.040
Promoter	kg/tonne ore	0.013
Frother	kg/tonne ore	0.004
SIBX	kg/tonne ore	0.070
CuSO4	kg/tonne ore	0.160
Flocculant- Float Tails Thickener	kg/tonne ore	0.010
Flocculant- CN Recovery Thickener	kg/tonne ore	0.011
Flocculant- Concentrate Thickener	kg/tonne ore	0.055
NaCN	kg/tonne ore	0.60
Dry Lime	kg/tonne ore	1.95
Conditioner & Preaeration	kg/tonne ore	0.85
CIL	kg/tonne ore	0.86
Ammonium Bisulfate	kg/tonne ore	1.06
HCl	kg/tonne ore	1250
Caustic	kg/tonne ore	800
Natural Gas	kg/tonne ore	3600

Source: OceanaGold

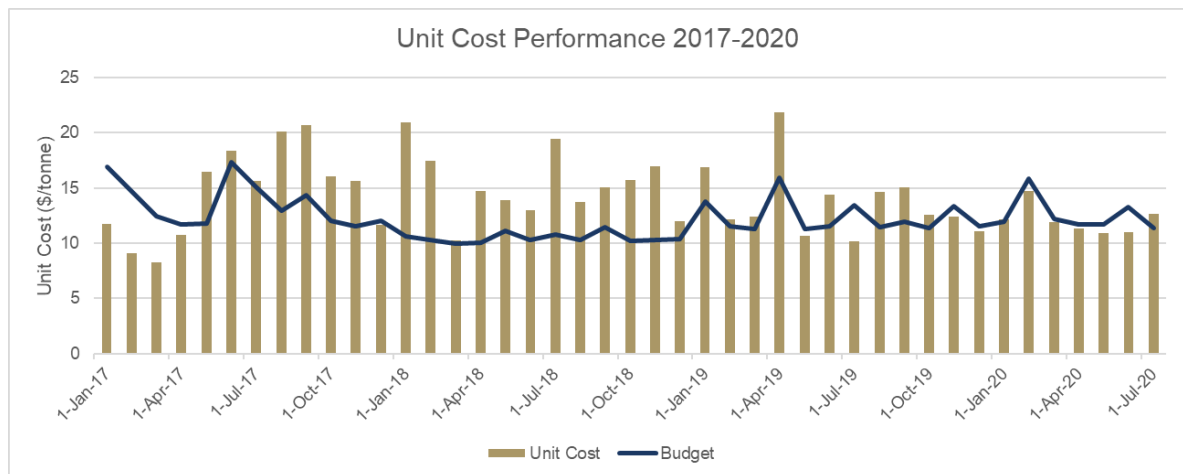

Source: OceanaGold

Figure 17-6: Process Unit Cost History Since Startup

The completion of the cyanide destruction circuit upgrade in Q1 2020 and implementation of expert control on the CIL and cyanide destruct process is seeing further reduction in reagent usage and costs.

At the current forecast mill throughput rates of 4 mt/a process costs are budgeted at an average of \$9.98/tonne of ore milled over the LoM. Unit costs are modelled to progressively reduce from historical levels from:

- Reduced reagent consumption rates for cyanide from improved advanced control and instrumentation installed in the CIL circuit
- Removal of the concentrate pre-aeration stage ahead of the first CIL tank reducing the amount of free iron produced consuming cyanide
- Reduced usage of Ammonium Bisulphite in the cyanide destruction circuit from reduced overall cyanide consumption in the leach circuit and increased residence time from the upgraded circuit.
- Feed grades of sulfur decrease from 2026 reducing the mass pull to flotation concentrate leading to reductions in regrind media, power and cyanide addition to the first CIL tank
- Impact of plant throughput achieving a consistent 4.0 Mtpa rate reducing the fixed cost component on the overall unit cost

Unit costs have allowed for a progressive increase in water treatment plant capacity from the current 1,100 gpm to 2,400 gpm by the end of 2021 and the associated increased chemical consumption.

18 Project Infrastructure

18.1 Tailing Storage Facility

To meet the revised tailings storage capacity requirement, NewFields has evaluated the permitted ultimate Duckwood TSF design and has determined that the embankment crest elevation needs to be raised from the current permitted height of 192 m to 204 m. As a result, the overall storage capacity of Duckwood TSF will increase from 36 Mt to 63 Mt. During this evaluation, NewFields sloped the embankment crest in the north corner of the facility, which is outside the predicted limits of the maximum storm water pond, to optimize tailings storage capacity. All other design concepts, which include basin lining, embankment section and materials, tailings deposition scheme and freeboard requirements, will remain the same as the permitted facility. The revised Duckwood TSF layout with ultimate footprint is presented in Figure 18-1. The construction of the Duckwood TSF will be phased in 6 stages as presented in Figure 18-2 and includes Stages 1 and 2 which are already constructed.

In addition to raising the embankment, the footprint of the ultimate facility will require the following improvements that will be constructed during Stage 5:


- Realign portions of the following local roads and highways:
 - US Highway 601
 - Duckwood Road
 - Old Jefferson Highway
 - Estridge Avenue
 - Pit a Tat Road
 - Crossbow Lane
- New haul truck overpass over the realigned Highway 601
- Reconstruct all perimeter runoff collection channels
- Relocate and construct a new channel for upper Camp Branch creek.
- Remove existing stormwater sediment collection basin P2 and the current TSF

Underdrain Collection Pond

- Reconstruct perimeter stormwater sediment collection basins: P1, P3 and P4
- Repurposing the existing P4 stormwater sediment collection basin into the new TSF
- Reshape the Existing TSF Growth Media Stockpile
- Relocate the Hilton Archaeological Site


The deposition of tailings into the TSF will be via a HDPE pipeline located around the perimeter of the embankment crest. Deposition will occur from multiple spigots inserted along the tailings distribution line. The deposition locations will be moved progressively along the distribution line, as required, to maintain slightly graded deposition of tailings towards the decant pond that is located in the southeast corner of the facility. Water from the decant pond will be recycled back to the mill for make-up water and will be reclaimed by utilizing skid mounted pumps to be located on the ramp within the southern end of the decant pond.

The TSF is designed as a zero-discharge facility. In addition to the anticipated tailing storage and operating pool requirements, the facility is designed to contain the Probable Maximum Precipitation (PMP) storm event and an additional four feet of freeboard at all times. Note, the existing large supernatant pond has been accounted for in the TSF design. The goal is to reduce this via enhanced evaporation and additional mill use as much as possible before construction of Stage 5.

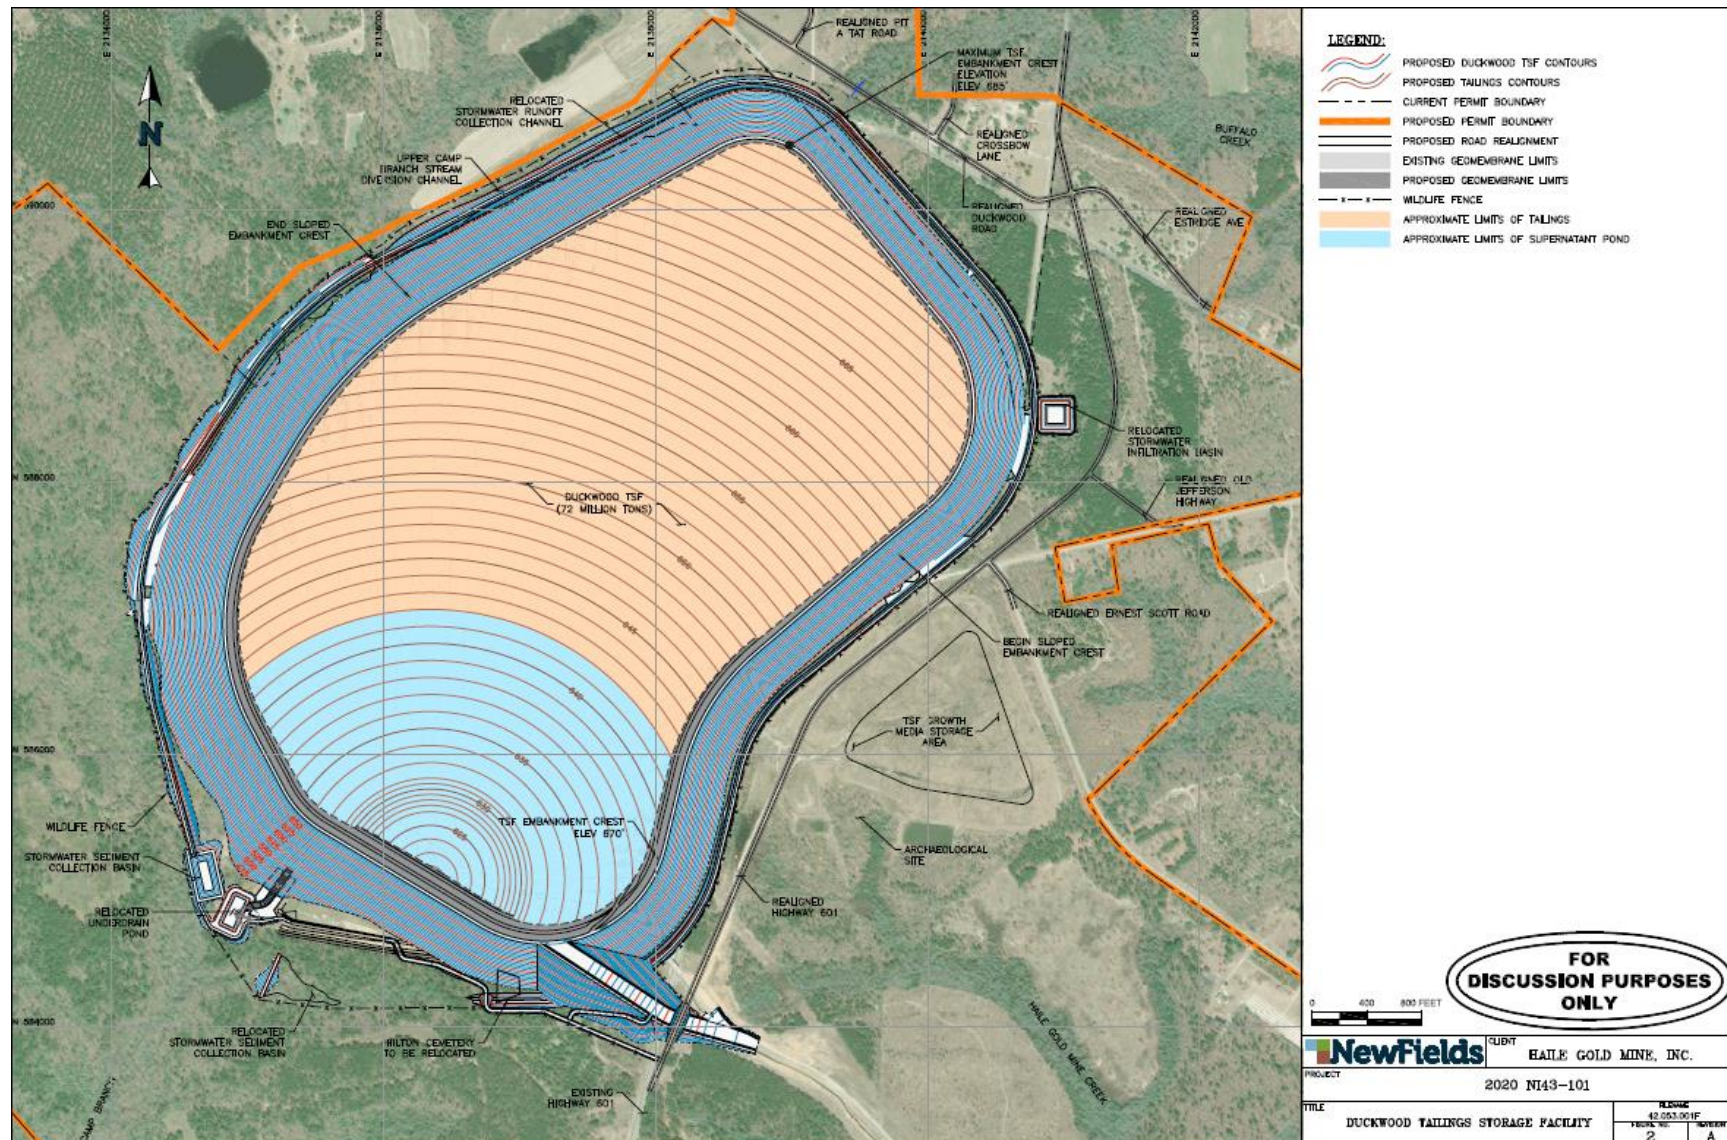

Source: OceanaGold

Figure 18-1: Tailing Storage Facility Layout

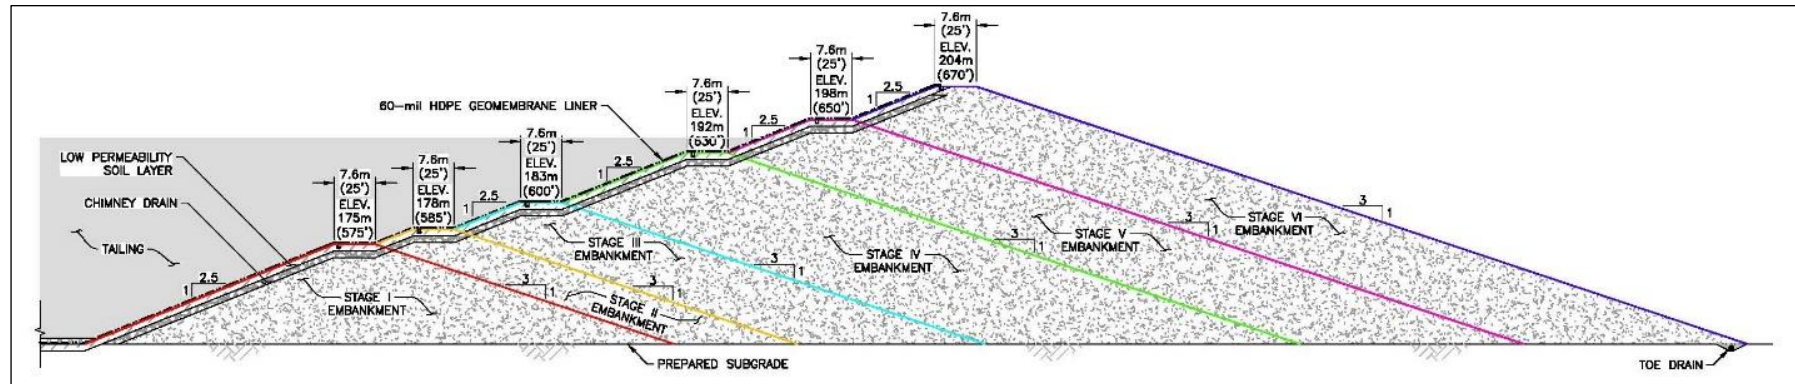

Source: OceanaGold

Figure 18-2: Tailing Storage Facility Typical Section

18.2 Overburden Storage

During the mine life from the present, five different Overburden Storage Areas (OSAs) and pit backfill will be utilized for the storage of approximately 407 million tonnes of additional material generated from the pit development. The material generated from the development of the pits will be classified as either potentially acid generating (PAG) or non-acid generating overburden material. 196 million tonnes of PAG material will be stored in either East or West PAG OSAs, or in mined out pits. A new non-acid generating OSA, South OSA, along with the existing Ramona and James OSAs, are designated for storing the remaining 211 million tonnes of non-PAG material. The OSAs will be developed according to the pit progression and the final footprint of the OSAs is presented in Figure 18-3.

Prior to construction of the non-acid generating OSAs, the footprints will be timbered. Grass lined sediment collection control channels will be constructed around the footprint of each OSA. Sediment control structures will be constructed at the outfall of the sediment control channels for each facility. Water retained within the ponds is routed through a low-level riser pipe to an adjacent drainage. All of the OSAs will be developed with a final reclaimed overall 3(H):1(V) slope.



Figure 18-3: Overburden Storage Areas Plan

18.3 Potential Acid Generating (PAG) Overburden Storage Areas

The expansion of the open pit is expected to increase the amount of PAG material that is required to be stored in fully geomembrane lined facilities. Under the current mining permit, Johnny's PAG (JPAG) OSA is designated as the dedicated facility for storing PAG material with maximum capacity of 41.7 Mt. In addition, the first phase of the East PAG OSA was constructed in 2020 and is designed to hold 15 Mt of which approximately 10 Mt has been placed. It is estimated that the revised mine plan will generate an additional 196 Mt of which 106 Mt will need to be stored above ground. This will require the expansion of the East PAG OSA and JPAG OSA. The westward expanded area of JPAG is known as West PAG OSA.

The West PAG OSA, presented in Figure 18-4, has a total capacity of 70 Mt. Similar to the permitted JPAG facility, the expanded base pad of West PAG will be lined with a composite lining system utilizing a low permeability soil layer overlain by a geomembrane. The geomembrane will be covered with a 600 mm drainage layer. A pipe network will be installed within the drainage layer to collect and transmit infiltration through the PAG material and direct flow into the contact water collection ponds.


The West PAG OSA requires two new contact water collection ponds, one for each expansion phase. The pond included in the first north expansion is referred to as the 541 Pond and is sized to contain 210 million litres (ML), including an extra 115 ML for additional contact water storage for staging to the water treatment plant (WTP). The remaining 95 ML is sized to the predicted runoff from the 100 year/24-hour storm event on the first phase. This pond will replace the proposed 29 Pond, presented in the SEIS, which was sized to handle the additional contact water staging before the WTP. The second south expansion will drain to the 475 Pond that will replace the 455 Pond. The 475 pond is sized to hold 95 ML which equates to the predicted runoff from the 100 year/24-hour storm event for the second phase. When complete, the perimeter runoff collection channels for the full West PAG build out will drain to either the 465 (existing), 541 or 475 Pond. The PAG solution and storm water collected in the 465 and 475 Ponds will be pumped to the 541 Pond, and from there to the existing 19 Ponds for treatment and release, or for use in the milling process.

The ultimate footprint of West PAG OSA will have an overall footprint of approximately 126 ha and the PAG material will be loaded with an overall slope of 3(H):1(V).

East PAG OSA will be expanded to both the south and north (See Figure 18-5). These expansions will provide a total remaining storage of 36 million tonnes in addition to the 10 Mt placed, and drain to the existing 500 Pond Cell A and to be constructed Cell B.


The East PAG expansion, West PAG and pit backfill will account for all of the predicted life-of-mine PAG storage requirements.

Prior to construction of East and West PAG OSAs, the footprint will be stripped of vegetation and topsoil. Topsoil materials will be stored in growth media area for future use in accordance with the HGM reclamation plan.

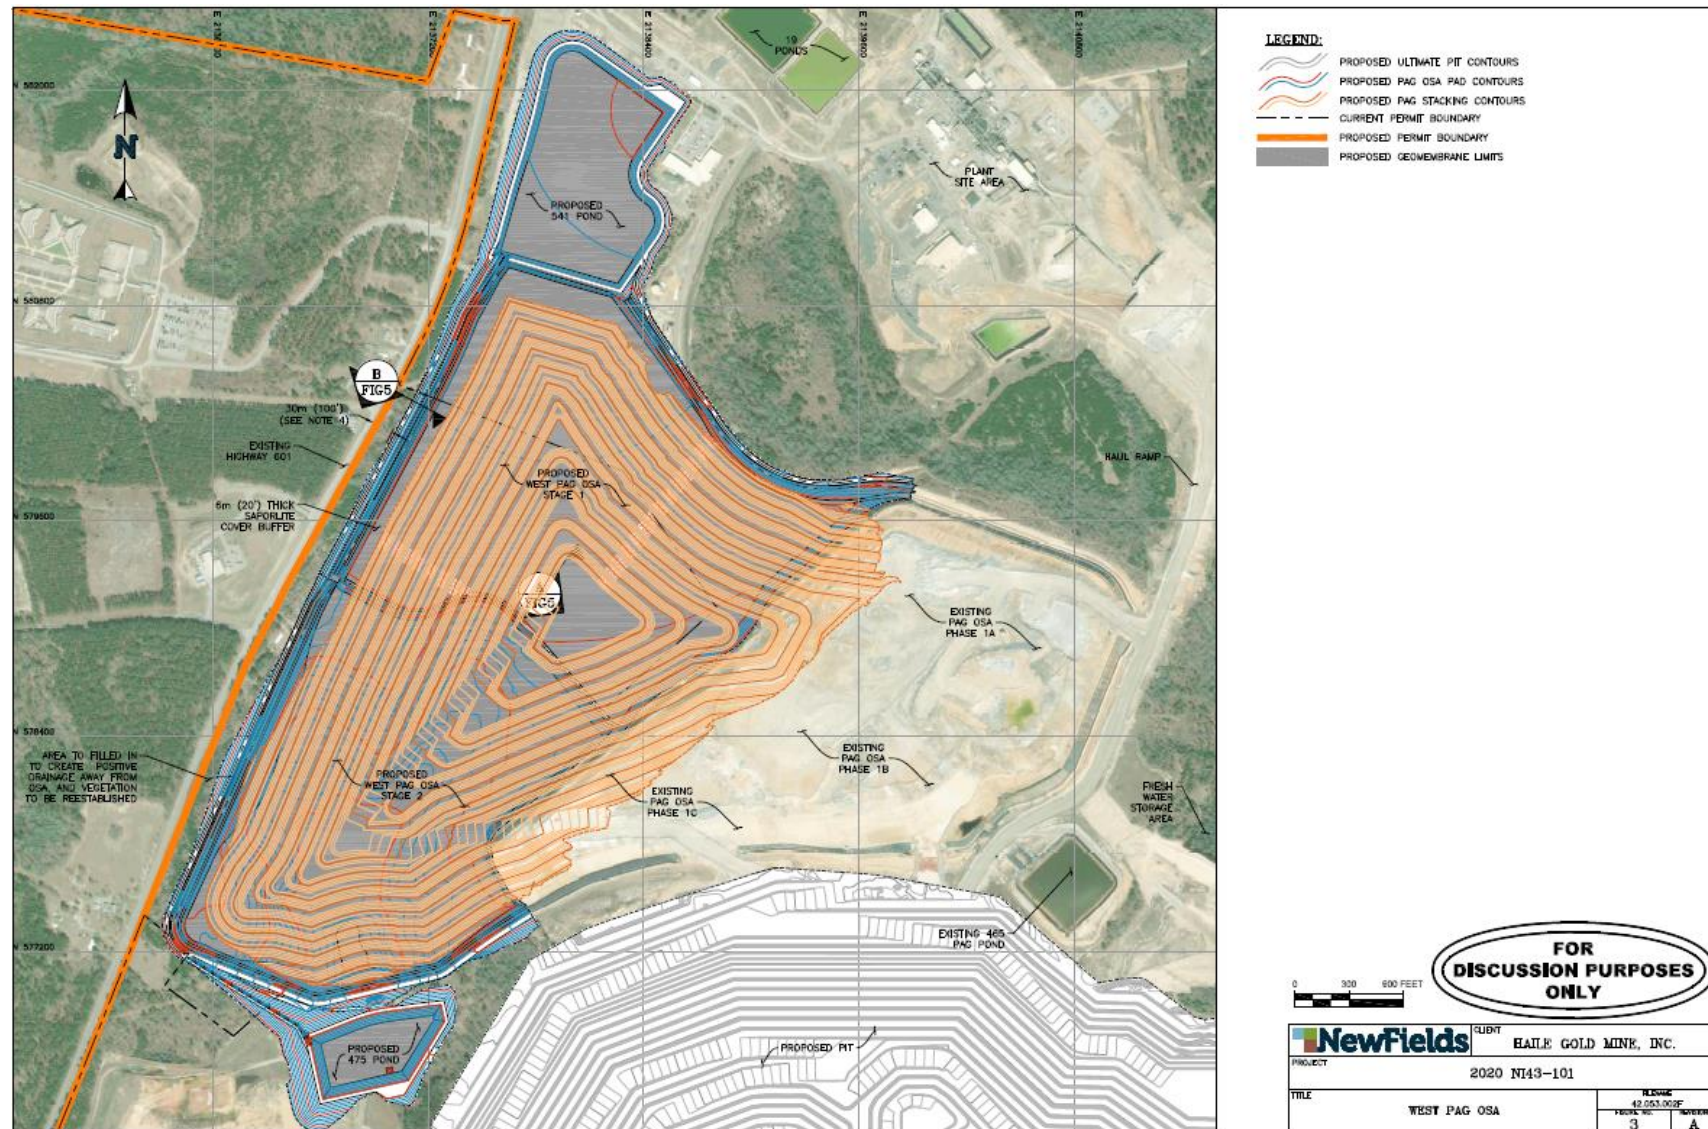

Source: OceanaGold

Figure 18-4: West PAG Overburden Storage Area

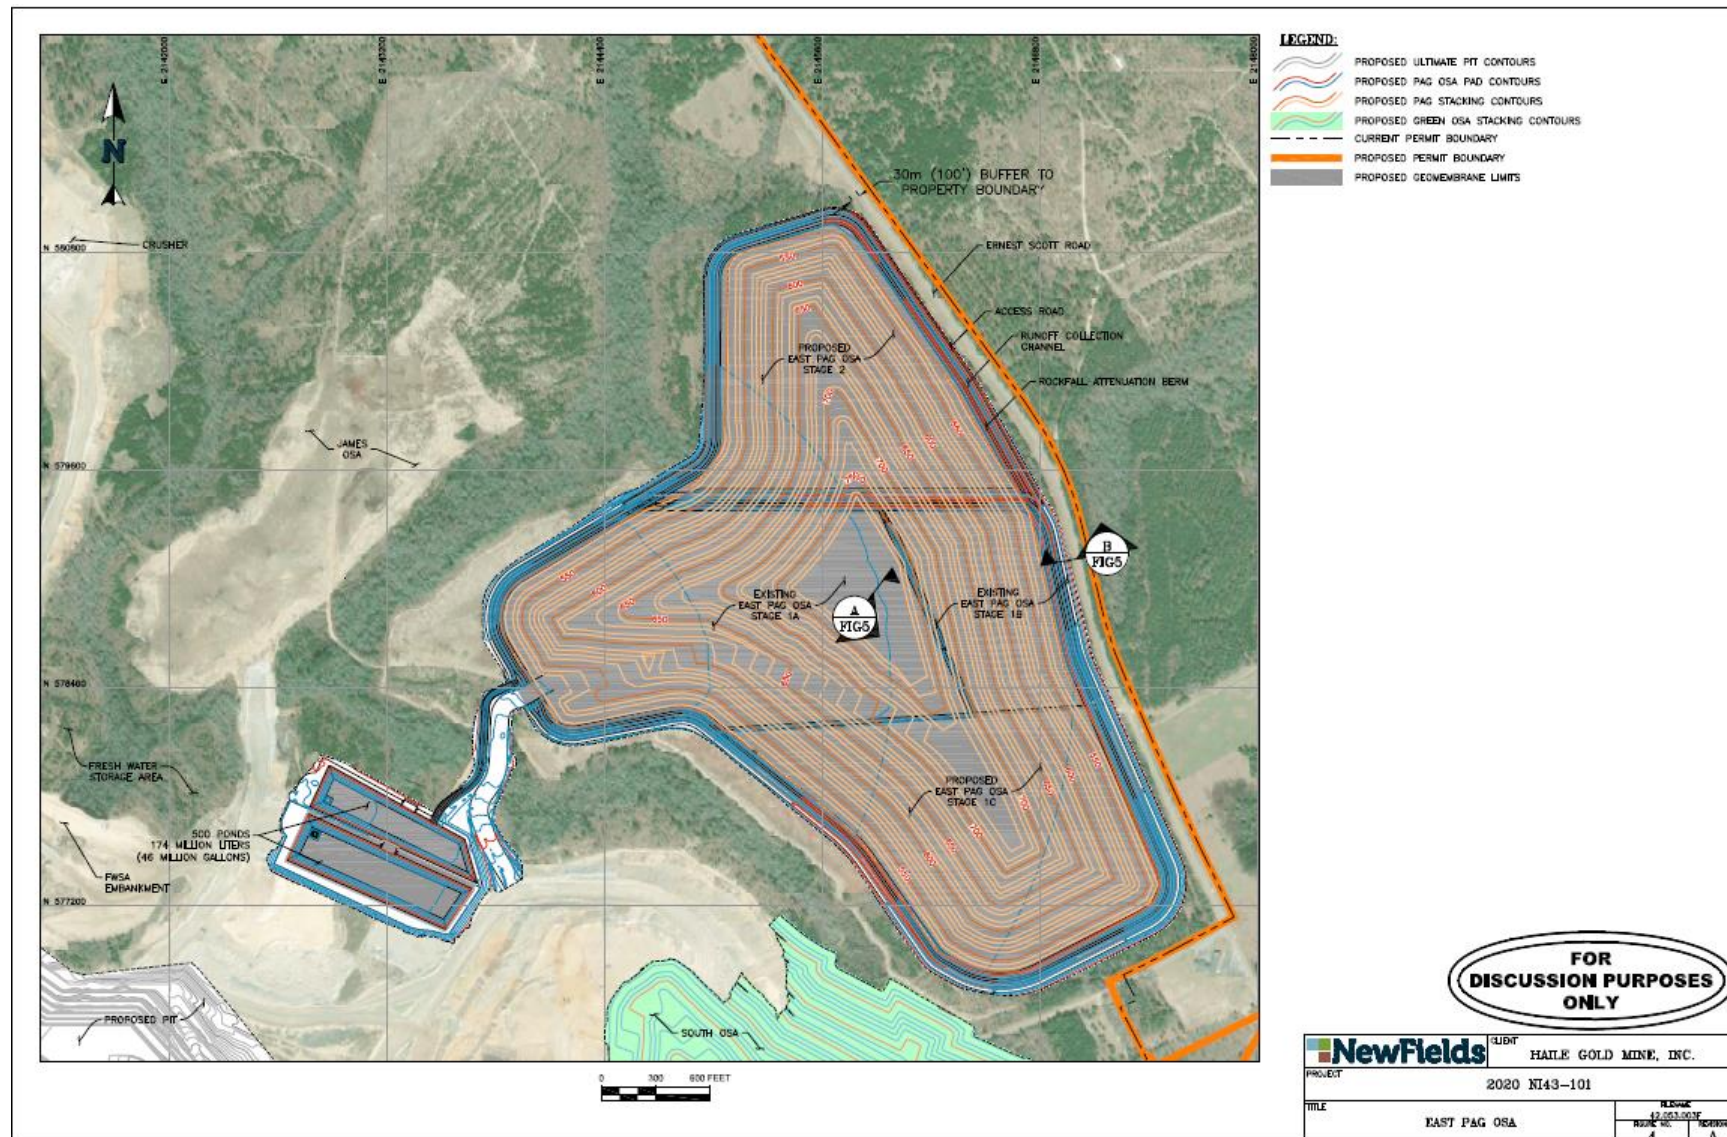


Source: OceanaGold

Figure 18-5: East PAG Overburden Storage Area Expansion

18.4 Site Wide Water Management

The existing site wide water management plan will be updated to reflect changes to the mine plan. With the revised mine plan, the incoming water from Upper Haile Gold Mine Creek will be detained by the existing Fresh Water Storage Dam (FWSD) at the upper reaches of the watershed (currently permitted as a detention dam only). The as-built dam is shown in Figure 18-6. Water from the FWSD is pumped around the pits using the existing pumps and pipelines installed with the embankment. The pumps are sized to maintain the water storage elevation below 143 m to allow for sufficient freeboard for the 100-year storm event within the upper Haile Gold Mine Creek watershed. Low flow pumps are included to maintain the minimum flow of 15.9 L/s in Haile Gold Mine Creek, per the existing mining permit. The FWSD has capacity to store approximately 590 ML of fresh water. Should the FWSD level reach elevation 148 m, an emergency spillway is sized to pass the $\frac{1}{2}$ PMP event safely into the pits to allow ample time for evacuation.

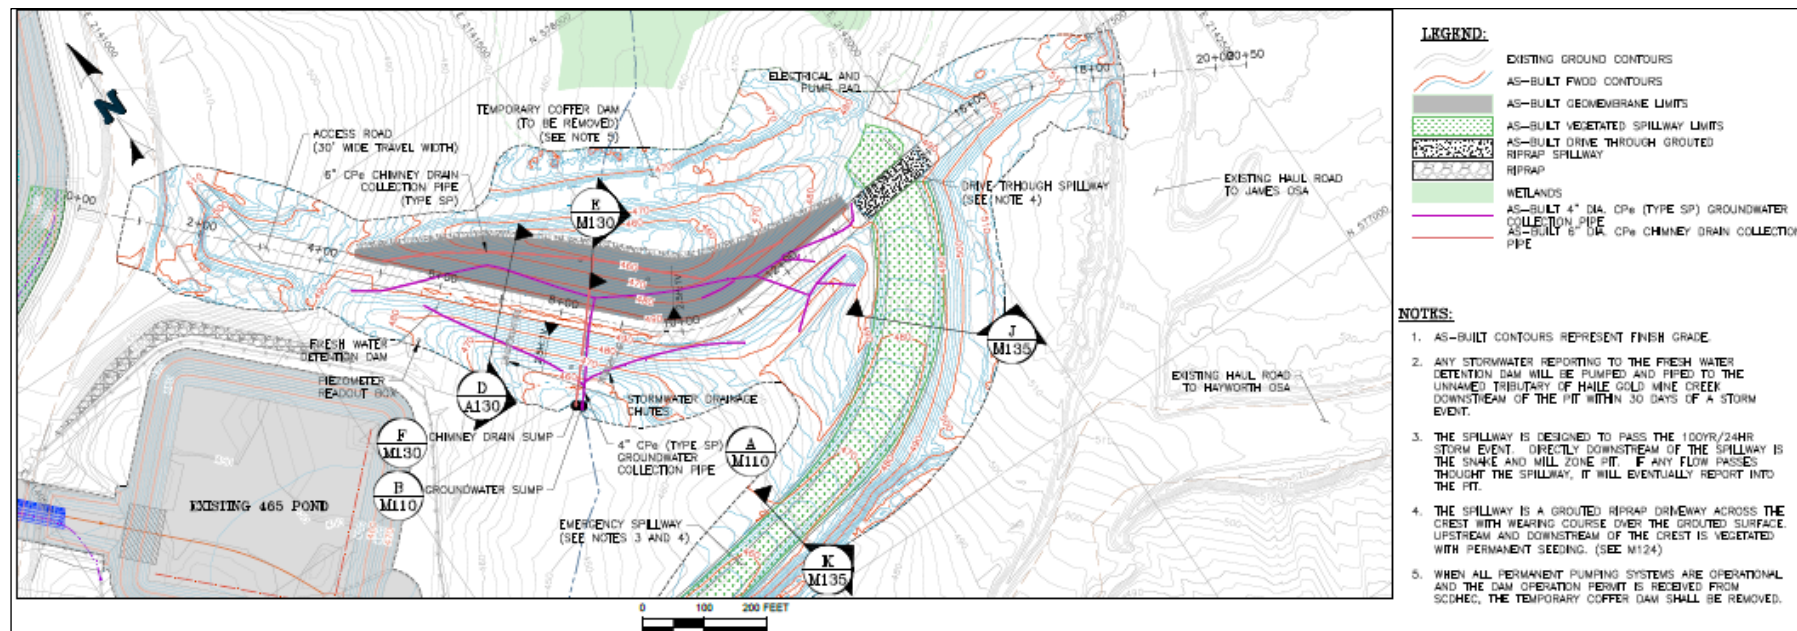

Source: OceanaGold

Figure 18-6: As Built Fresh Water Storage Dam

18.5 Site Wide Water Balance

The site wide water balance was developed for planned Haile operations as a tool to aid in the planning, design, and operations of the Mill, TSF, contact water treatment plant (CWTP) and water management facilities. These probabilistic analyses looked at multiple possible scenarios covering a range of potential occurrences. Results from the study provide a variety of potential outcomes allowing risk-based decision making. The balance includes all major facilities that are expected to add water to the system, facilities that store water facilities that use water and facilities for water treatment.

Sources of water can be considered to the balance via three sources: process water, contact water and non-contact water. Contact water requires treatment before it can be released but can be used in the process. Process water includes water in the mill process or TSF which cannot be released; process water is recycled to minimize the amount of water required at the mine.

Process water comes from:

- Free water in the TSF
- Underdrain from the TSF
- Any water in the Mill process stream
- Natural moisture in the processed ore after it enters the process circuit

Contact water comes from:

- Runoff and underdrain from PAG OSA and Low-Grade Ore Stockpile
- Direct precipitation and runoff accumulating in the active and inactive pits
- Crusher pad and coarse ore stockpile containment areas
- Water pumped from the underground workings

Contact water can be used in the process as make up water or be treated in the CWTP and discharged.

Non-contact water includes water that does not require treatment (beyond sediment control, as required that can be released to the environment. Sources of non-contact water include:

- Groundwater from pit depressurization
- Municipal water
- Runoff from Topsoil Stockpiles
- Runoff from Non-PAG Overburden Storage Areas
- Runoff from Undisturbed Ground
- Run-on from Upgradient Areas
- Runoff from TSF Outer Perimeter
- Runoff from the Plant Site (process water is contained within the process)

The results of the site wide water balance analysis indicate that under normal and moderately extreme conditions, there is expected to be adequate storage in the TSF to contain process and anticipated meteorological water. Municipal supplies and non-contact water generated on site are expected to be sufficient to meet water demands and the planned expanded capacity of the CWTP will be sufficient to manage the accumulation of contact water within the system.

18.6 Surface Roads and Bridges

The existing Highway 601 overpass provides both a traffic crossing and a means of carrying the tailings delivery line across Highway 601 from the Process Plant.


The existing overpass will be upgraded to allow fully loaded 175 tonne haul trucks to deliver random fill from the Mine to the TSF for the construction of TSF Stage 4.

TSF Stage 5 will require both Highway 601, and the existing overpass, to be relocated.

18.7 Underground Access

The underground will be accessed through the highwall in the Snake pit with a total of three portals. The haul road accessing the portals will be from an open pit ramp that will tie into the haul road from the plant to the Snake pit. The haul road and bench from the open pit will create enough width to allow the installation of required fans and portable substations during the construction of the portals and declines as well as ventilation fans. Figure 18-7 shows the underground access route, with the locations of the production portal and intake/exhaust portals annotated.


The haul road will be used to deliver underground waste to the CRF plant located above Snake Pit. The haul road and bench at the 80 RL production portal location will house a portable electrical substation, ventilation fan, compressor, laydown area, parking and stockpiling facilities to provide support for the portal and underground decline development. These portable units will be removed once additional mining has been completed for permanent underground infrastructure to be utilized.

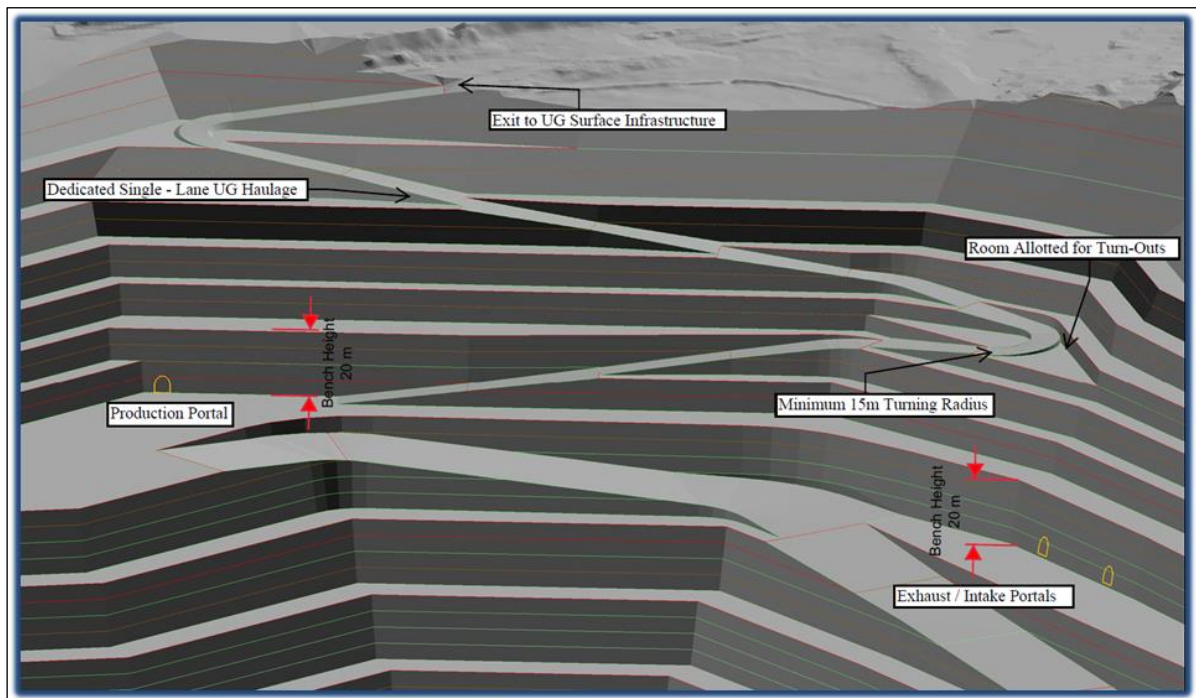

Source: OceanaGold

Figure 18-7: Portal Access (Looking North)


Figure 18-8 shows the layout of the planned facilities outside the production portal.

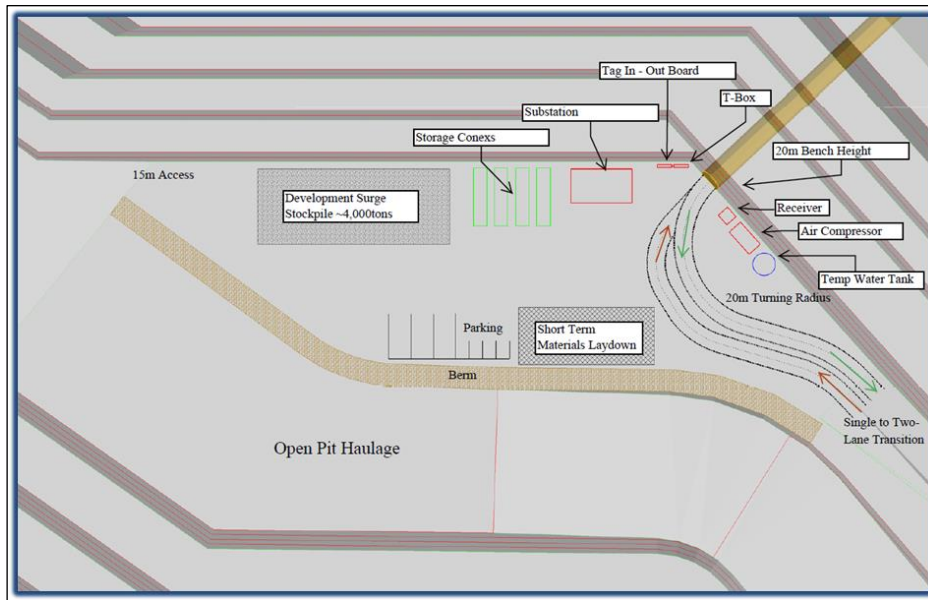

Source: OceanaGold

Figure 18-8: Production Portal Layout

Figure 18-9 shows the layout outside of the ventilation portals.

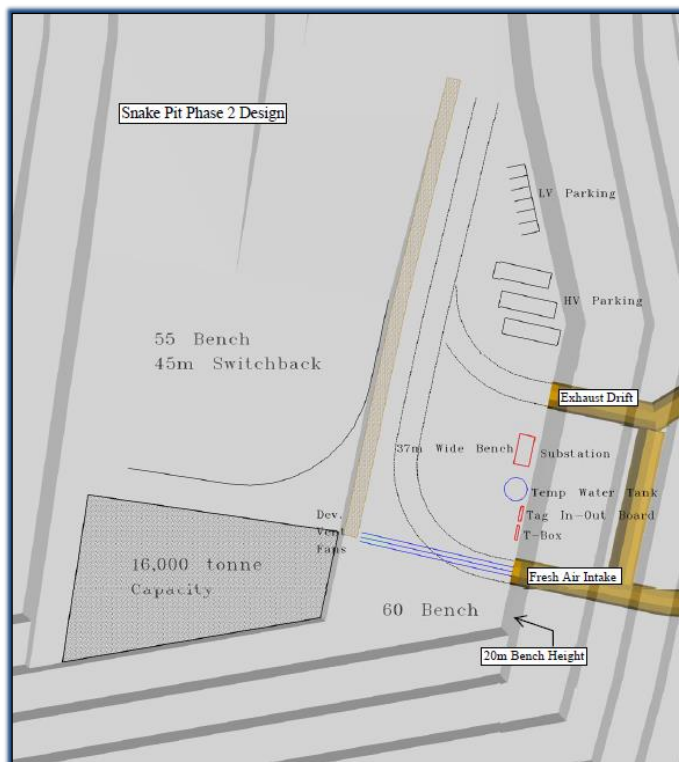


Source: OceanaGold

Figure 18-9: Layout for Ventilation Portals Area

18.8 Ancillary Facilities

The project will utilize existing facilities such as maintenance workshop, truck shop and offices to support open pit and process plant operation.

The underground operation will be supported by a main laydown and infrastructure yard that will contain the underground ore stockpile, underground waste stockpile, crushing/screening plant, CRF plant, shotcrete plant, wash bay, fuel bay, mobile maintenance shop and office, warehouse, contact sediment pond, contractor office, electrical transformers, and an underground maintenance shop as shown in Figure 18-10. The design has been developed to minimize interaction between the underground mobile equipment and the surface haul road traffic.

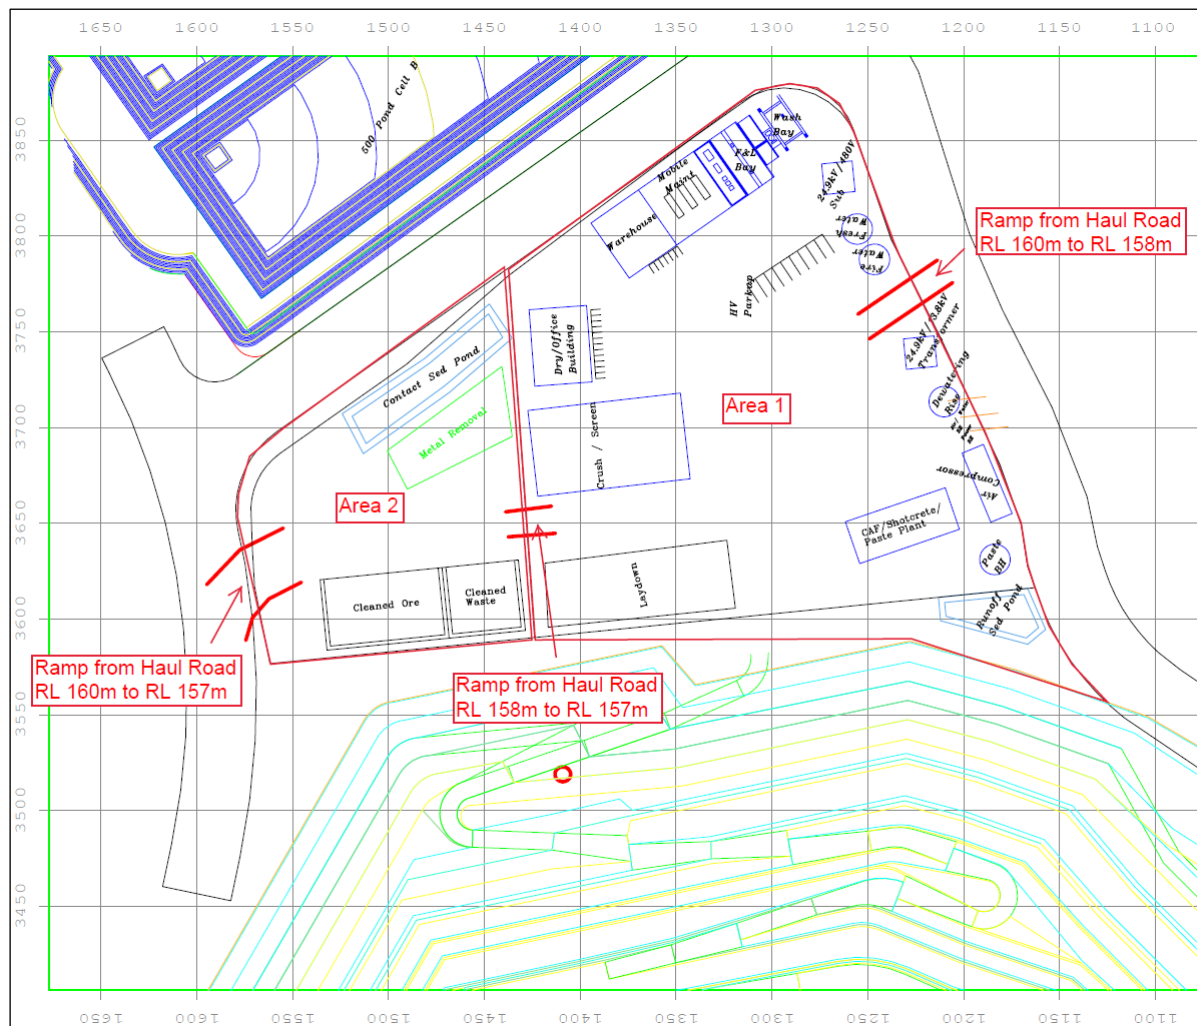

Source: OceanaGold

Figure 18-10: Underground Surface Infrastructure Detail

The ROM Pad (Area 4) has been designated for stockpiling all underground ore, PAG and Green non-PAG waste rock material. Ore and PAG material will be rehandled into surface trucks and transported to either the processing plant or surface PAG dumps. Green waste rock from the underground will be either processed into CRF or hauled to the appropriate waste storage area. The facility also has an

area allocated for extraction of waste metal, will be clay lined, and contain a HDPE lined sediment pond to control drainage. Water contained within the ROM Pad area will be pumped from the sediment pond to the 500 Pond.

The fuel and lube bay and wash bay facilities are located opposite the surface workshops. The refueling facility will consist of a double banded tank, electric fuel pumps, oil water separator and concrete foundation.

18.9 Power Supply

The total power demand for the site (including Horseshoe underground operation) is estimated to be 23 MVA. The study undertaken by Lynches River Electric Cooperative confirmed the availability of power to site with some minor upgrades to the existing 69 kV substation and transmission line (costs associated with this is +/- 300K).

For the underground operation, the existing power line from the main substation to Pond 465 will be extended to the underground yard and a 24.9 kV to 13.8 KV transformer will serve the CRF plant. Two additional transformers (24.9kV to 480V) will provide power to the aboveground facilities on the surface. A separate take off point will feed a 5 MVA (24.9 to 13.8 kV) transformer to provide power to the underground operation. This transformer will be located on the surface and feed the underground distribution system.

18.10 Water Supply

Fresh water required for dust suppression and the process plant will be supplied by the pit dewatering wells. The excess water from the dewatering wells will be pumped to the FWSD before releasing to the environment. Mill make up water will be supplied by the return water from the tailings facility. Surface runoff into the pits and PAG OSAs can also be used as mill make up water when available. For the underground operation, a fresh water supply line (HDPE) will be constructed from the water treatment plant to the underground yard. A water storage tank will then provide clean water down the decline for underground mining equipment and water use at the underground yard.

The site is connected to the town of Kershaw municipal water system for potable water supply.

19 Market Studies and Contracts

General

Haile Gold Mine has been operating continuously since 2016 and has current contracts and purchase arrangements in place for doré refining and other goods and services required for the operation.

Bullion Production and Sales

The market for gold doré is well established. Market predictions and discussions for gold are beyond the scope of this document. The impacts of gold price volatility on the mine plan and process operation are well understood.

- A contract is in place with Metalor USA Refining Corporation, located in North Attleboro, Massachusetts for the refining of doré bullion (Metalor). This company is a subsidiary of Metalor Technologies SA which is a well-known and established precious metal refiner. Metalor Technologies SA is a subsidiary of Japan's Tanaka Kikinzoku Group and is headquartered in Marin, Switzerland.

The contract has a two-year term starting with an Effective Date of January 31, 2020, subject to termination by either party. This contract also sets a range of prices and surcharges for refining the doré under terms and conditions which generally comply with industry norms. It is assumed that these contract terms will be renewed through the LoM operation without changes or will be negotiated with a new refiner if necessary.

Hedging and Forward Sales Contracts

Haile currently has no forward sales, hedge, gold loans, offtake or similar type agreements. OceanaGold does from time to time enter into group wide pre-sales agreements. Currently, these represent a relatively minor component of total gold production. OceanaGold has in total four mines across which these can be spread.

Key contracts and status include:

- Komatsu Financial Limited
 - Open pit mining equipment
 - Registered Address: Rolling Meadows, Illinois
 - End Date of Contract: 19 April 2024
- Caterpillar Financial Service Corporation
 - Open pit mining equipment
 - Registered Address: Nashville, Tennessee
 - End Date of Contract: 18 August 2021
- Dyno Nobel Inc.
 - Explosives Products
 - Registered Address: Salt Lake City, Utah
 - End Date of Contract: 19 August 2021
- Lynches River Electric Cooperative Inc
 - Electrical power
 - Registered Address: Kershaw, South Carolina

- End Date of Contract: 23 April 2020 (continuing under former terms while renewal is arranged)
- The Chemours Company
 - Sodium cyanide
 - Registered Address: Wilmington, Delaware
 - End Date of Contract: 31 December 2018 (continuing under former terms while renewal is arranged)
- Bridgestone Americas Tire Operations
 - Heavy equipment tires
 - End Date of Contract: 31 December 2025
- Magotteaux
 - Registered Address: Franklin, Tennessee
 - Grinding media
 - End Date of Contract: 1 August 2018 (continuing under former terms while renewal is arranged)

Fuel also represents a major consumable. Fuel is purchased from Roberts Shell, Kershaw, South Carolina. No formal contract is in place.

20 Environmental Studies, Permitting and Social or Community Impact

Haile's current mine plan is based on construction, mining operation, closure, and reclamation of eight open pits, with three of those pits being left as pit lakes (Champion, Small and Ledbetter) and one as a partial pit lake (Snake). On May 24, 2018, Haile applied to the US Army Corp of Engineers (USACE) to initiate the National Environmental Policy Act (NEPA) process and launch a Supplemental Environmental Impact Statement (SEIS). United States Army Corp of Engineers (USACE) has jurisdictional responsibility for all Waters of the United States and works cooperatively with US Environmental Protection Agency (US EPA), and South Carolina Department of Health and Environmental Control (SC DHEC) for modifications such as this that have impacts to wetlands, groundwater and surface water conditions and air emissions. Since that time, Haile has submitted a Project Description, Alternatives Analysis, and 127 additional technical reports in support of this application. These technical reports cover a wide range of topics including impact assessments to the wetlands, air, land, vegetation, groundwater, surface water, flora and fauna, cultural heritage sites, socioeconomic conditions, and reclamation plans.

In order to adjust current and supplemental mine plans, it is anticipated that a modified application to the 404 Permit - Clean Water Act will once again be required. It is also assumed that the USACE will again be the lead federal Agency to oversee the NEPA process. The level of anticipated impacts to the environment from the adjusted mine plan will determine the appropriate level of review under NEPA. Various permitting approvals/certifications will also be required from SC DHEC, including modification of Haile's Mine Operating Permit, Reclamation Plan, TSF Dam Safety Permit, Air Permit, NPDES permits and 401 Water Quality certification.

In addition, there will be approvals required from other federal and state agencies, including: United States Environmental Protection Agency (EPA), United States Fish and Wildlife Service (US FWS), South Carolina Department of Natural Resources (SC DNR), South Carolina State Historic Preservation Office (SC SHPO), South Carolina Department of Transportation (SC DOT) and Catawba Indian Nation. NEPA also allows non-governmental organizations (NGOs) and other interested parties an opportunity for review and comment on the anticipated impacts.

Haile is unique in that it occurs wholly on private land owned by HGM and does not impact federal/public (BLM or USFS) lands that would be subject to projected modifications from these surface management agencies.

There is a significant amount of existing background and environmental baseline data available for the Project. This data continues to be collected and reported to the regulators as part of operational controls. Additional data and environmental studies (Section 20-3) will be of technical interest to the federal and state agencies in evaluating a request to expand the current mining operation.

Permits currently held by HGM may be kept, modified, terminated, or replaced during the SEIS expansion process and it is anticipated that these same permits will be adjusted for subsequent changes outlined in this document.

Table 20-1 is a summary of the current HGM permits as issued under the 2014 EIS process.

Table 20-1: Mine Permits

Agency	Permit/Authorization Number	Date Received	Description
US Army Corps of Engineers	404 Permit – SAC-1992-24122-4IA	27 Oct, 2014	Permit to affect wetlands and streams per the approved Mine Plan.
U.S. Army Corps of Engineers	Permit 2004-1G-157	16 Oct, 2007	Permit to fill a portion of the old North Fork Creek
Mine Safety and Health Administration (MSHA)	MSHA ID: 38-00600	5 Feb, 2010	Operate mine within MSHA standards
Federal Communications Commission	Call Sign: WQJB814	18 Jul, 2008	Base station frequency, ten local frequencies
South Carolina Department of Health and Environmental Control (SCDHEC), Bureau of Water	401 Water Quality Certification	23 Oct, 2014	Water Quality certification to construction and operate a gold mine on HGMC, Camp Branch Creek, unnamed tributaries and adjacent wetlands.
SCDHEC, Division of Mining and Solid Waste Management	Mining/Operating Permit No. I-000601	5 Nov, 2014	Mine Operating Permit – Regulation of closure and reclamation.
SCDHEC, Bureau of Solid and Hazardous Waste Management	Permit No. SCD987596806	12 Apr, 1993	Conditionally large quantity generator
SCDHEC, Industrial Wastewater (IW) Permitting Section	National Pollutant Discharge Elimination System Discharge Permit No. SC0040479	7 Oct, 2013	Permit to discharge treated water from the mine operation / reclamation areas from Outfall 003.
SCDHEC, Industrial Wastewater Permitting Section	WTR-Wastewater Construction Permit Permit No. 19852-IW	30 Jan, 2015	Permit to construct sewer lines
SCDHEC, Bureau of Water, Industrial, Agricultural, and Storm Water Permitting Division	Dams & Reservoirs Safety Permit 29-0007 (Issued October 7, 2013)	7 Oct, 2013	Dam Safety Permit – Significant Hazard (Construction). Stability during earthquake-induced ground motion was evaluated by SCDHEC prior to issuance of the TSF construction permit. SC DHEC completed evaluation of the seismic stability study pursuant to the International Commission of Large Dam (ICOLD) design and performance standards.
SCDHEC, National Pollutant Discharge Elimination System (NPDES) Program, Water Facilities Permitting Division	General Permit for Stormwater Discharges for Small and Large Construction (Activities Permit) SCR100000	1 Jan, 2013	Discharge of stormwater in connection with construction of structures not covered under the Industrial General Permit – requires submittal of Storm Water Pollution Prevention Plan (SWPPP) and public notice prior to construction
SCDHEC, NPDES Program, Water Facilities Permitting Division	Stormwater discharges associated with industrial activity SCR000000, Permit No. SCR004763	1 Jan, 2011	Discharge of stormwater in connection with industrial activities, Industrial General Permit

Agency	Permit/Authorization Number	Date Received	Description
SCDHEC, Office of Environmental Quality, Bureau of Air Quality	Bureau of Air Quality, State Construction Permit No. 1460-0070-CA	4 Oct, 2013	Authorizes construction of the proposed facility and equipment specified in HGM's application for a Department of Army permit; a permit to operate also is required.
Lancaster County Council	Floodplain Development Permit June 27, 2013	27 Jan, 2013	Floodplain Administrator oversees and implements the provisions of the Flood Damage Prevention Ordinance.
Lancaster County Council	Ordinance 2013-1207	1 Jan, 2015	Rezoned the Haile property within the permit boundary to the M, Mining District designation.
SCDOT	177006	14 Jan, 2015	Encroachment Permit

Source: OceanaGold

20.1 Required Permits and Status

Table 20-2 is a summary of the permits necessary to start modification of the Open Pit Mine Plan, adjust the Underground Mine Plan, and installation of additional equipment for the Process Plant optimization. HGM will submit permit applications at the conclusion of the required Environmental Studies.

Table 20-2: Environmental Permits

Application	Permit Required	Regulatory Agency
Open Pit Mining Modification	Mining Operating Permit No. I-000601	SCDHEC, Division of Mining and Solid Waste Management
	Fill or modify wetlands	US Army Corps of Engineers
	Surface water impacts to Haile Gold Mine Creek, Camp Branch Creek, and Little Lynches River	SCDHEC, Bureau of Water
	Modification HGMC diversion dam	SCDHEC, Bureau of Water, Dams & Reservoirs Safety
	Expand current Mine Permit Boundaries	SCDHEC, Division of Mining and Solid Waste Management with cooperation from US EPA, US FWS, SC SHPO, and SC DNR, and Catawba Indian Nation
	New and modified existing Potentially Acid Generating (PAG) Storage Facilities and Collection Ponds	SCDHEC, Division of Mining and Solid Waste Management with cooperation from US EPA; and SCDHEC, Bureau of Water
	Additional Mine Equipment Incl. Haul Trucks, Excavators, Water Carts, Graders, Light Trees, and Generators	SCDHEC, Office of Environmental Quality, Bureau of Air Quality
	Fuel Storage and Distribution	SCDHEC, Office of Environmental Quality, Bureau of Air Quality and SCDHEC, Division of Mining and Solid Waste Management
	Explosive storage, loading and distribution	SCDHEC, Office of Environmental Quality, Bureau of Air Quality; SCDHEC, Division of Mining and Solid Waste Management; US BATF
Underground Mine	Mining Operating Permit	SCDHEC, Division of Mining and Solid Waste Management
	Ventilation Emissions, Stockpiles,	SCDHEC, Office of Environmental Quality, Bureau of Air Quality

Application	Permit Required	Regulatory Agency
	Cement Plant Permit	SCDHEC, Office of Environmental Quality, Bureau of Air Quality and SCDHEC, Division of Mining and Solid Waste Management
	Groundwater disturbance	SCDHEC, Bureau of Water
	Underground Depressurization Water Wells	SCDHEC, Division of Mining and Solid Waste Management and SCDHEC, Bureau of Water
	Additional Mine Equipment Incl. Haul Trucks, Excavators, Water Carts, Graders, Light Trees, and Generators	SCDHEC, Office of Environmental Quality, Bureau of Air Quality
	Explosive storage, loading and distribution	SCDHEC, Office of Environmental Quality, Bureau of Air Quality; SCDHEC, Division of Mining and Solid Waste Management; US BATF
Process Plant Optimization	Additional Process Plant Equipment, Modified ROM Pad, and Modified Stockpile storage	SCDHEC, Office of Environmental Quality, Bureau of Air Quality and SCDHEC, Bureau of Water
	Modified Equipment Run Rate	SCDHEC, Office of Environmental Quality, Bureau of Air Quality and SCDHEC, Division of Mining and Solid Waste Management
	Expand Tailing Storage Facility surface area	And SCDHEC, Division of Mining and Solid Waste Management and SCDHEC, Office of Environmental Quality, Bureau of Air Quality
	Modified Tailing Storage Facility Dam Height	SCDHEC, Bureau of Water, Dams & Reservoirs Safety and SCDHEC, Division of Mining and Solid Waste Management
	Re-route Highway 601	SC DOT
	Modification to Earnest Scott and Duckwood Roads	Lancaster County DOT
Extended Support Services	Extended Operation of Water Treatment Plant	SCDHEC, Bureau of Water
	Extended Site-wide Monitoring	SCDHEC, Division of Mining and Solid Waste Management

Source: OceanaGold

20.2 Environmental Studies

Table 20-3 is a summary of the environmental studies initiated by HGM to support the approval process.

Table 20-3: Environmental Studies

Study	Scope of Work
Air Emissions	Assess impact to air pollution loading based on additional operating conditions and new equipment on active point sources – engine exhausts, conveyor drop points, discharge stacks, ventilation shafts, dust controls, blast gasses, cement plant, etc.
Aquatic Resources – plants and animals	Review and assess Carolina Heel Splitter mussel fish and macroinvertebrate studies to quantify impacts to aquatic species over LoM.
Cultural & Historical Resources	Review and assess potentially impacted cultural and historical sites from surface disturbances. Relocate any potential gravesites.
Economic Impact to Local Community	Social and economic effect on the state and local economy – effect on local businesses, wages, local resources, emergency services, and external jobs.
Emergency Response Plans	Assessment of coordination with available local emergency support services.
Floodplain Assessment	Assess surface water impacts (flows and water quality) based unanticipated concurrent failures of the TSF, storage ponds, and Process Plant containment areas.


Study	Scope of Work
Geochemistry Analysis	Update OMP for PAG material placement, ARD control, and underground cut and fill practices.
Geology and Soils Assessment	Update an assessment of suitable materials for future reclamation actions.
Groundwater Modelling	Assess potential impacts to neighborhood wells, ponds and springs.
Hazardous Materials and Waste Inventory	Review of the chemicals, reagents, fuels, and hydrocarbon products transportation, storage, distribution, and disposal.
Health and Safety Assessment	Review of industrial hygiene monitoring and potential impacts to employee health.
Hydrology Assessment	Identification of direct and indirect impacts on local wetlands, wells, and streams.
Impacted Wetland Assessment	Assess potentially impacted wetland areas – vegetation and stream flow.
Land Use	Assess alternatives to potentially impacted land masses and identify future potentially higher value applications.
Noise and Vibration Study	Identify potential impacts from noise and vibration sources, including blasting activities, mobile equipment operating at elevated surfaces, crushing and grinding equipment, TSF evaporators, and mine equipment (haul trucks, dozers, and excavators)
Reclamation Plan	Pit closure and remediation plans, surface controls, revegetation plans, stormwater control plans, surface run-off plans, timelines, and sequence for surface reclamation activities.
Socioeconomic Impacts	Assess the socioeconomic impacts to state and local communities.
Stormwater Plans	Create Stormwater plans for sediment ponds, borrow pits, location for BMP ¹ devices, assessment locations, and site controls.
Surface Water Impacts	Assess impact to surface water flows – volume, dissolved oxygen, chemistry, pH and conductivity. Assess drainage patterns and develop recommendations for additional monitoring and measurement stations, if required.
Terrestrial Resources – Plant Life	Perform terrestrial plant evaluations, specifically in impacted areas and areas of significant disturbance.
Terrestrial Resources – Wildlife	Perform seasonal terrestrial studies on migratory endangered wildlife, such as species of bats and raptors.
Transportation & Traffic / Road Impacts	Perform a traffic study and predict road patterns and potential impacts based on employment and support service usage.
Vibration Analysis	Develop vibration predictions based on underground blasting and changes in surface contours and geological morphology.
Visual Impact Studies	Assess visual impacts along major thoroughfares: Highways, County Roads, Neighborhoods and Public spaces
Water Quality Assessment	Assess current and future impacts to changes in water quality based on volume changes, available precipitation and evaporation, and geochemical leach studies.
Wetland Delineation	Create surface maps with jurisdictional delineations. These will include necessary 50-ft (15.25-m) offset boundaries.
Wetland Delineation and Marking	Set the visual markers around the 50-ft offset. Measure the final size of wetland delineation.
Wildlife Assessment	Biological assessment of primary and secondary wildlife species and identify impacts and changes to migratory patterns, mortality changes and secondary food sources.

Source: OceanaGold

¹ Best Management Practice Devices – 1) Erosion Prevention – slope surfaces, seeding, and erosion controls; and 2) Sediment Control - check dams, sediment dams, sediment ponds, and silt fencing.

20.3 Environmental Issues

As required by Haile's Mine Operating Permit, a progressive US\$55 million (M) Bond and a \$10M Reclamation Trust Agreement is in place between HGM and SCDHEC. Currently, \$37M has been paid under the agreed upon schedule. Under the SEIS, the proposed bond is increased to \$78M. It is to provide financial assurance to the State of South Carolina that funds will be available (in the event of default by HGM) to implement and complete the Reclamation Plan and for implementing, maintaining, repairing, or enhancing any aspect of reclamation, closure, and post closure activities. The financial assurance is in the form of surety bonds and an interest-bearing trust account. Under the changes outlined in the NI43-101, the bond requirements are anticipated to increase to \$84M, as shown in Figure 20-1, predominately associated with reclamation of the larger PAG facilities.

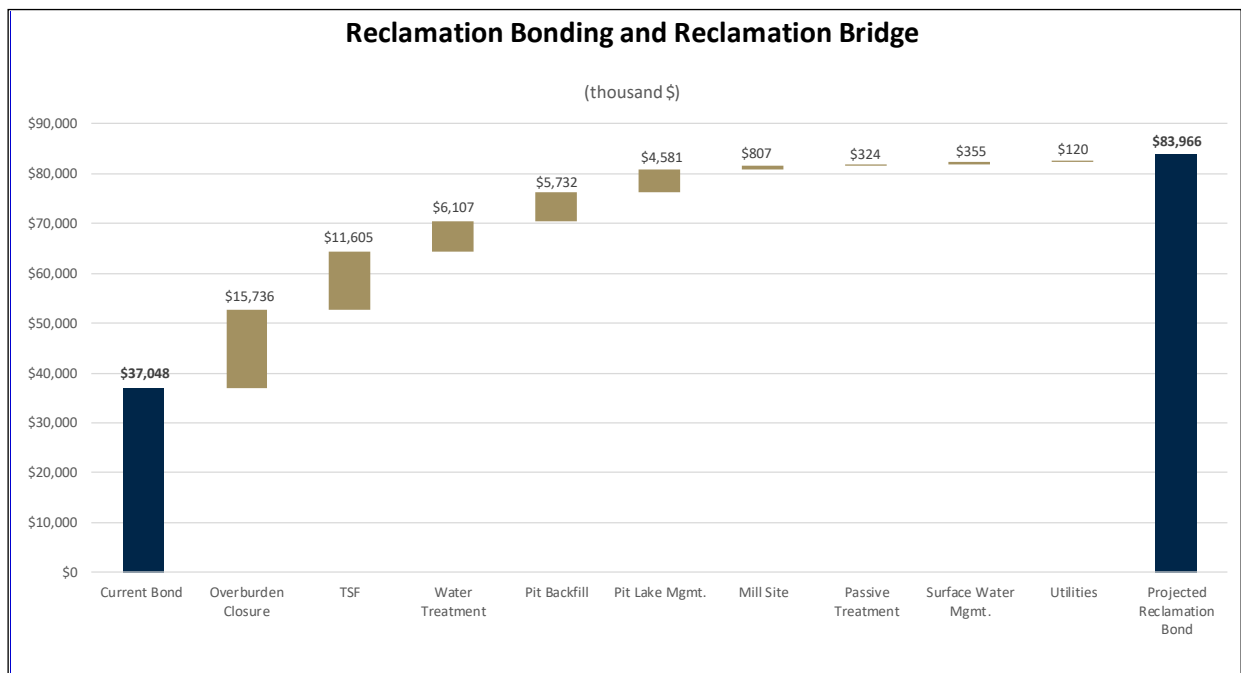

Source: OceanaGold

Figure 20-1: Reclamation Bond and Reclamation Bridge

21 Capital and Operating Costs

21.1 Capital Cost Estimates

A summary of the total capital cost is provided in Table 21-1; the basis of the capital cost estimate is discussed below.

Table 21-1: Total Capital Cost Summary (US\$000)

Description	Initial Capex	Sustaining Capex	Total
Land Acquisitions	-	5,925	5,925
Permitting	-	1,542	1,542
On-Site Exploration Drilling	6,679	-	6,679
Op Capitalized Pre-Strip	281,838	-	281,838
Capital Leases: Sustaining	-	-	-
Capital Leases: Non-Sustaining	-	-	-
OP Mining PP&E	19,969	6,850	26,819
OP Tech Services PP&E	720	-	720
Pit Dewatering	15,868	-	15,868
Site Works	1,975	7,722	9,697
PAG Cell Development	-	88,077	88,077
TSF Lift Design	138,857	33,329	172,186
Underground Mining: Non-Sustaining	-	79,413	79,413
Underground Mining: Sustaining	17,091	-	17,091
Mill PP&E	793	13,020	13,814
Commercial	54	14	68
Total Net Capex	\$483,844	\$235,894	\$719,738
Reclamation/Closure ⁽¹⁾	-	68,280	68,280
Total LoM Net Capex	\$483,844	\$304,173	\$788,017

Source: SRK, 2020

(1) Captured as Capex in Cashflow

21.1.1 Basis for Capital Cost Estimates

The capital cost estimates throughout this section has a base or effective date of June 30, 2020. All values are in United States dollars (US\$), and no foreign currencies have been considered in the estimates. Contingencies applied to capital estimates are considered appropriate and have been variably applied to reflect the source of the estimate.

Open Pit

All major mining equipment is supplied, and sustaining maintenance carried out, under operating lease arrangements. For financial reporting purposes, leases are treated as Indirect costs. LoM equipment costs under lease arrangements in place and assumed are as provided in Table 21-2.

Table 21-2: Open Pit Mining Equipment Capital Leasing – Indirect Costs

Item	Units	LoM Total
Principal Payment - Capital Leases: Non-Sustaining	\$000s	108,810
Principal Payment - Capital Leases: Sustaining	\$000s	12,089
Interest Expense - Capital Leases	\$000s	11,226
Total – Capital Leases	\$000s	132,126

Source: OceanaGold

Main open pit capital items include capitalized pre-stripping and supporting equipment and infrastructure not covered by capital lease arrangements, as provide in Table 21-3. Pit dewatering

and site work include items to support the highwall depressurization and overall site wide water management.

Table 21-3: Open Pit Mining Capital

Item	Units	LoM Total
OP Capitalized Pre-Strip	\$000s	281,838
OP Mining PP&E	\$000s	26,819
OP Tech Services PP&E	\$000s	720
Pit Dewatering	\$000s	15,868
Site Works	\$000s	9,697
Total	\$000s	334,942

Source: OceanaGold

Underground

Projected capital costs for underground mining are summarized in Table 21-4.

Total initial capital costs are estimated to be US\$95.7 million. Total sustaining capital costs are estimated to be US\$28.1 million.

The underground capital estimate includes capitalized development, mine infrastructure and equipment not sourced under capital leasing arrangements.

Table 21-4: Underground Capital Cost Summary

Description	Initial (US\$000's)	Sustaining (US\$000's)	Total Cost (US\$000's)
Supervision and Control	15,847	3,359	19,206
Lateral Development	19,718	8,201	27,919
Vertical Development	831	993	1,823
Production	92	-	92
Material Handling	686	893	1,579
Mine Services	2,119	1,130	3,249
Diamond Drilling	783	-	783
Purchase and Replacements	3,281	120	3,401
Rebuilds	-	-	-
Infrastructure - Underground	7,636	1,130	8,766
Infrastructure - Surface	27,700	245	27,945
Light Vehicles	720	1,020	1,740
Total	79,413	17,091	96,503

All capital costs incurred after production commences in January 2023 are considered sustaining capex.

Source: OceanaGold

Process Plant

The Haile process plant has been progressively upgraded from 2017 to 2019 to increase milling rates to the target 4.0 Mtpa rate and improve gold recovery to the design rates. Work is substantially completed on the process upgrades over the last three years. Process plant sustaining capital over the remaining life of mine totaling US\$13.8M is principally related to:

- Progressive infrastructure upgrades to support tailings dam lifts and the associated impact on tailings pumping.
- Expansion of the contact water treatment plant to 2,400 gpm capacity.
- Debottlenecking and minor pumping upgrades within the plant to maintain 4.0 Mtpa milling rates.

- Upgrades to the stripping circuit to increase rates with higher gold production >200 koz pa.

Cost estimates are based on preliminary scopes or vendor estimates for upgrades to the water treatment plant. A progressive tailings pumping study was completed in 2019 to confirm pumping requirements for each stage of the dam raising at the higher 4.0 Mtpa milling rate and provided required changes to the pumping systems.

Infrastructure – Tailings/Overburden

Infrastructure capital associated with tailings/overburden is estimated to be US\$260 million for the LoM. Infrastructure capital has been estimated internally by OceanaGold or provided by external consultants. The major capital items are PAG storage, tailings storage facility expansion, and Non-PAG OSA and minor water management facilities. Note the total costs for the PAG OSA and TSF include the EPAG Phase 1C and TSF Stage 3, which are currently under construction.

The remaining capital items have been sourced from the 2020 Haile LoM plan. The major infrastructure items, such as the original JPAG and EPAG first phase, tailings storage facility Stage 1 and 2, FWSD and other water management and open pit dewatering, which were budgeted in the 2016 Haile LoM plan, are excluded as these have been completed.

The site works category in the open pit capital cost carries the Green OSA storm water pollution prevention plan controls (SWPPP).

Other Capital

Other capital required for the life of mine plan is as shown in Table 21-5, and covers land acquisitions, permitting and surface drilling.

Table 21-5: Other Capital

Item	Units	LoM Total
Land Acquisitions	\$000s	5,925
Permitting	\$000s	1,542
On-Site Exploration Drilling	\$000s	6,679
Commercial	\$000s	68
Total	\$000s	14,214

Source: OceanaGold

21.2 Operating Cost Estimates

The total RoM operating cost unit rate of US\$28.40/t processed is summarized in Table 21-6.

Table 21-6: RoM Operating Cost Summary

Description	US\$000's	US\$/t Ore Processed
OP Mining (\$/t rock mined) - All Material	909,308	2.00
OP Mining (\$/t rock mined) - Operational Material	627,469	2.05
UG Mining (\$/t ore mined)	161,073	47.15
Subtotal Mining (Operational Material Only)	788,542	14.94
Processing	526,811	9.98
G&A Cost	175,478	3.32
Refining/Freight Costs	8,213	0.16
Total Operating Costs	\$1,499,044	\$28.40

Source: SRK, 2020

There are several important cost items excluded from the operating cost, as detailed in Table 21-7, which OceanaGold does not consider to be direct operating costs but the operation does incur.

Table 21-7: RoM Indirect Costs Summary

Description	US\$000's	US\$/t Ore Processed
Endowment & Reclamation Fund	18,778	0.36
Environmental Bond	7,645	0.14
Interest Expense - Capital Leases	11,226	0.21
Principal Payment - Capital Leases: Sustaining	12,089	0.23
Principal Payment - Capital Leases: Non-Sustaining	108,810	2.06
Regional Business Units	18,032	0.34
Total Non-Operating Costs	176,580	\$3.35

Source: SRK, 2020

21.2.1 Basis for Operating Cost Estimates

The operating cost estimates throughout this section has a base or effective date of June 30, 2020. All values are in United States dollars (US\$), and no foreign currencies have been considered in the estimates. No contingency has been applied to operating cost estimates for open pit mining, processing or G&A. Contingencies have been variably applied as appropriate to operating cost items for underground mining.

Open Pit

Projected operating costs for mining have been developed based on mine production and equipment schedules over the life of the mine, with reference to current actual costs, adjustments for 2020 one-off, non-recurring costs, and assumed productivity improvements from 2022 onwards.

Mining costs are forecast to reduce to \$2.04/t of total material in 2021 from \$2.44/t in 2020 through:

- Termination of short-term contracts for earthmoving, grade control drilling and haul truck equipment hire which are no longer required to meet production schedules due to the direct acquisition of suitable equipment for owner-operation.
- Removal of 2020 one-off costs including RC grade control drilling assays, overhead powerline removal, and waste storage remediation works.
- Reduced maintenance unit costs due to the timing of major component rebuilds and reduction in unplanned maintenance, in part through the introduction of new mining equipment, principally the Komatsu 730E truck fleet.

Productivity improvements have been assumed from 2022 that will result in further unit cost reductions over the LoM. In part, these will be as a result of the realization of the full benefits of the new excavation and haulage and drill fleets. In addition, key initiatives will include:

- Construction of all-weather surface haul roads to reduce lost time due to weather events, increase haulage fleet travel speeds and improve haulage fleet tire life.
- In-pit water management addressing pre-mining dewatering bores, bench drainage and on-bench road construction to reduce lost time due to groundwater and weather events.
- Increased equipment utilization realized through practices to reduce standing time during shift breaks and at shift change.
- Utilization of remote and autonomous operation capabilities of the blasthole drill fleet, reducing labor costs and increasing operating hours.

- Implementation of real-time payload monitoring technology on the primary excavator fleet to consistently meet target haulage fleet payloads.
- Modifications where appropriate to primary excavator configurations to better suit bench height, material and grade control applications.
- Increased excavator productivities, through upskilling of operators, reduction in hang and queue times, double-side loading, and improved material fragmentation.

The average mining cost over the life of the mine is \$2.00 per tonne of total material. The cost by activity is presented in Table 21-8.

Table 21-8: Open Pit Mining Cost Summary

Description	\$/t mined ⁽¹⁾	Total \$000
Drill and Blast	0.32	144,031
Load and Haul	0.44	199,607
Ancillary	0.26	118,263
Maintenance	0.71	321,642
Management	0.09	42,101
Technical Services	0.18	83,664
Total	2.00	909,308

Source: OceanaGold

⁽¹⁾Ore + Waste

Underground

Projected operating costs for underground mining have been developed based on the LoM production schedule. The average cost of underground ore mining is US\$47.15/t and the cost by activity is presented in Table 21-9.

Table 21-9: Underground Mining Cost Summary

Description	US\$/t-ore Mined	US\$000's
Diamond Drilling	0.16	547
Supervision and Control	13.35	45,612
Lateral Development	5.49	18,740
Vertical Development	0.40	1,367
Production	8.27	28,269
Material Handling	4.02	13,720
Backfill	10.84	37,046
Mine Services	4.62	15,773
LoM UG Mining Costs	47.15	161,073

Unit costs are based on 3,416,327 t of ore mined, which includes 15,101 t of pre-production ore mined during Nov and Dec 2022.

Source: OceanaGold

Process Plant

The power cost component of the estimate is based on current power consumption for each area of the plant with allowance for increased loads from planned equipment upgrades. The current unit energy cost rates in the existing power supply agreement with the power supplier to the current operation (Lynches River Authority) were used.

Labor costs were developed based on the current staffing plan for the plant reflecting the four-panel operations roster and maintenance support roles with a total head count of 90 people, using the current labor rate schedules.

The reagent and grinding media consumption estimates are based on forecasts used in the current Haile LoM plan, adjusted for concentrate mass pull predictions from head grades and expected improvements from improved control of the CIL and cyanide destruct circuits.

Crusher and mill liner replacement costs are based on vendor pricing for current supply of components and a long-term reline schedule for the life of mine based on life predicted on tonnage treated developed over the last three years of operation.

Maintenance costs are based on forecast consumable rates for each area of the plant from operating experience since startup. Contractor costs are based on expected usage based on recent experience to support shutdown and rebuild activities.

Miscellaneous costs cover assay laboratory charges assigned to the process plant and other minor ad-hoc expenses such as software license and lease fees, technical consultancy services, development test work and advisors fees, etc.

The breakdown of the processing operating cost estimate is summarized in Table 21-10.

Table 21-10: Summary of Process Operating Costs

Description	\$/t milled	US\$000's Per Annum
Power	0.85	3,387
Labor	2.23	8,919
Grinding Media	1.12	4,486
Reagents	3.31	13,221
Mill Liners	0.24	949
Maintenance Materials	1.35	5,414
Miscellaneous	0.54	2,146
Assay	0.35	1,398
Total	9.98	39,920

Source: OceanaGold

Selling and Refining

Sales refining charges are charges incurred in the sale and transport of material to the refiner and are listed below. These total \$8.2M over the LoM or \$0.16/t processed.

Gold

- 99.996% payable Au
- US\$0.93/troy oz Au treatment charge
- US\$0.24/troy oz Au + US\$7850/shipment freight costs.

Silver

- 99.0% payable Ag
- US\$0.70/troy oz Ag treatment charge
- US\$0.24/troy oz Ag freight cost.

General and Administration

General and administration (G&A) costs have been sourced from Haile 2020 actual expenditures, of which a high-level summary is shown in Table 21-11. G&A costs are flat in general terms from 2020 to 2021, minus one-off consulting expenses during the 2020 year. Then, costs decrease by approximately -10% per annum from 2022 thereafter based on improvements in site efficiencies, as well as reductions in corporate overheads.

The total G&A will reduce considerably in 2030 and beyond, when economic mining is completed, and the plant facility is processing low grade stockpile in alignment with the mine stockpile plan.

The overall life of mine total is US\$175M or \$3.32/t processed.

Table 21-11: General and Administration Cost Summary (US\$000's)

Description	2021	2022 to 2030 p.a. OP + UG	2030+ p.a. Stock only
General Administration	6,622	5,900	1,575
Commercial	646	576	153
Community Relations	619	552	147
Environmental	2,037	1,815	483
Human Resources	1,464	1,304	347
Information Technology	926	825	219
Health and Safety	2,986	2,661	708
Supply Chain	1,806	1,609	428
Total	17,106	15,242	4,060

Source: OceanaGold

Indirect Costs

Indirect costs are estimated to be US\$176.6 million for the LoM or \$3.35/t processed. These costs have been sourced from the 2020 actual expenditures. Indirect costs include rehabilitation, closure, mitigation and finance lease payments and are summarized in Table 21-12.

Table 21-12: Indirect Cost Summary

Description	Total Cost (US\$000's)
Endowment & Reclamation Fund	18,778
Environmental Bond	7,645
Principal/Interest Payment – Capital Leases	132,126
Regional Business Unit Costs	18,032
Total	176,580

Source: OceanaGold

22 Economic Analysis

22.1 Principal Assumptions and Input Parameters

The indicative economic results summarized in this section are based upon work performed by SRK and OceanaGold in 2020. The metrics reported in this volume are based on the annual cash flow model results. The metrics are on both a pre-tax and after-tax basis, on a 100% equity basis with no Project financing inputs and are in Q3 2020 U.S. constant dollars.

Key criteria used in the analysis are discussed in detail throughout this section. Principal Project assumptions used are summarized in Table 22-1.

Table 22-1: Basic Model Parameters

Description	Value
TEM Time Zero Start Date	July 1, 2020
OP Operations Commercial Production Start	July 1, 2020
UG Capital Spend Start	August, 2020
UG Mine Production Start (estimate)	November, 2022
OP Mine Life	14
UG Mine Life	5 years
Discount Rate	@ 5%

Source: SRK, 2020

All costs incurred prior to July 2020 are considered sunk with respect to this analysis.

The selected Project discount rate is 5% as directed by OceanaGold. A sensitivity analysis of the discount rate is discussed later in this section.

Foreign exchange impacts were deemed negligible as most, if not all, costs and revenues are denominated in US dollars.

22.2 Cashflow Forecasts and Annual Production Forecasts

TEM inputs/results for the Cashflow Forecasts are summarized on a LoM basis in this section while a full LoM annual cash flow forecast is presented in Appendix B.


22.2.1 Mine Production

Table 22-2 is a summary of the estimated mine production over a 14-year mine life for the combined open pit/underground operations. Ore mined refers to Proven and Probable Mineral Reserves. Figure 22-1 and Figure 22-2 show LoM production by year for OP and UG operations.

Table 22-2: Life-of-Mine Production Summary


Description	Units	Value
OP Ore Mined	kt	48,031
OP Waste Mined	kt	407,040
OP Total Material Mined	kt	455,070
OP Mined Gold Grade	g/t	1.58
OP Mined Silver Grade	g/t	2.39
OP Contained Gold	koz	2,446
OP Contained Silver	koz	3,685
UG Ore Mined	kt	3,416
UG Waste Mined	kt	821.76
UG Mined Gold Grade	g/t	3.78
UG Mined Silver Grade	g/t	0.00
UG Contained Gold	koz	415
UG Contained Silver	koz	0
Total Ore Mined	kt	51,447
Waste Mined	kt	407,862
Total Material Mined	kt	455,070
Mined Gold Grade	g/t	1.71
Mined Silver Grade	g/t	2.21
Total Contained Gold	koz	2,907
Total Contained Silver	koz	3,746

Source: SRK, 2020

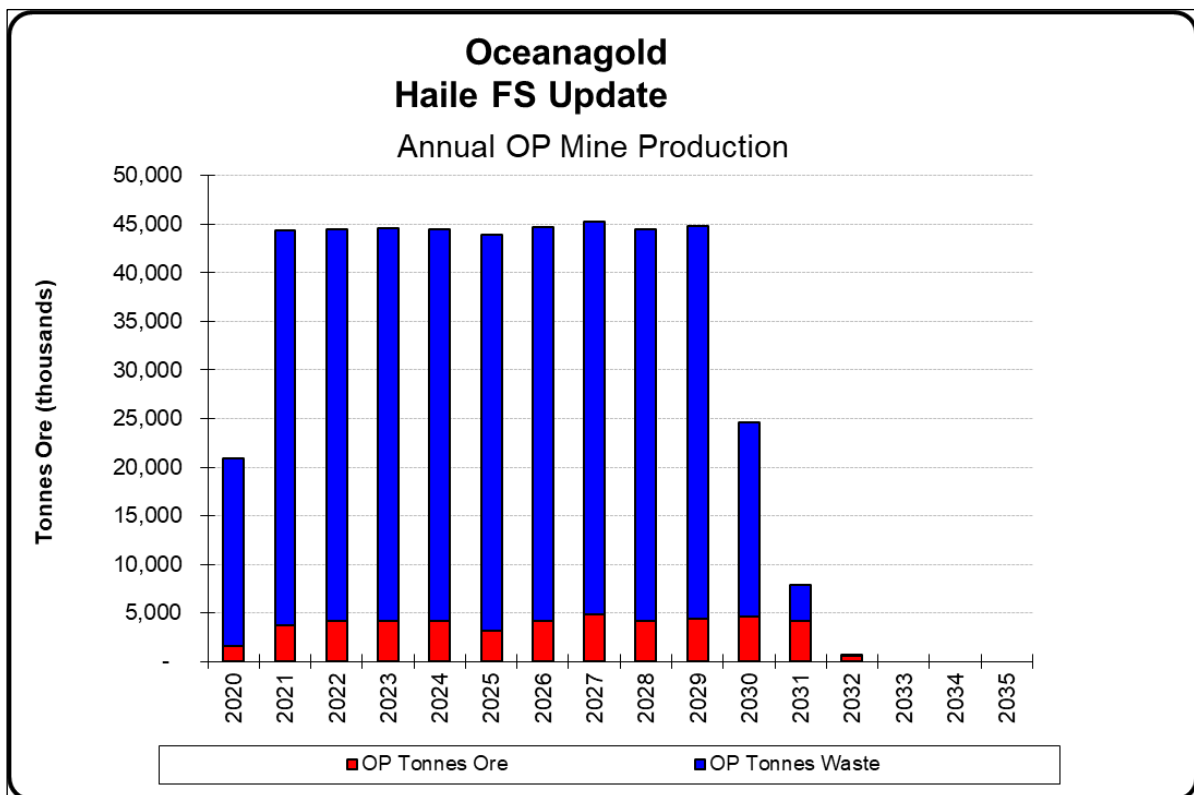

Source: SRK, 2020

Figure 22-1: Annual Open Pit Mine Production

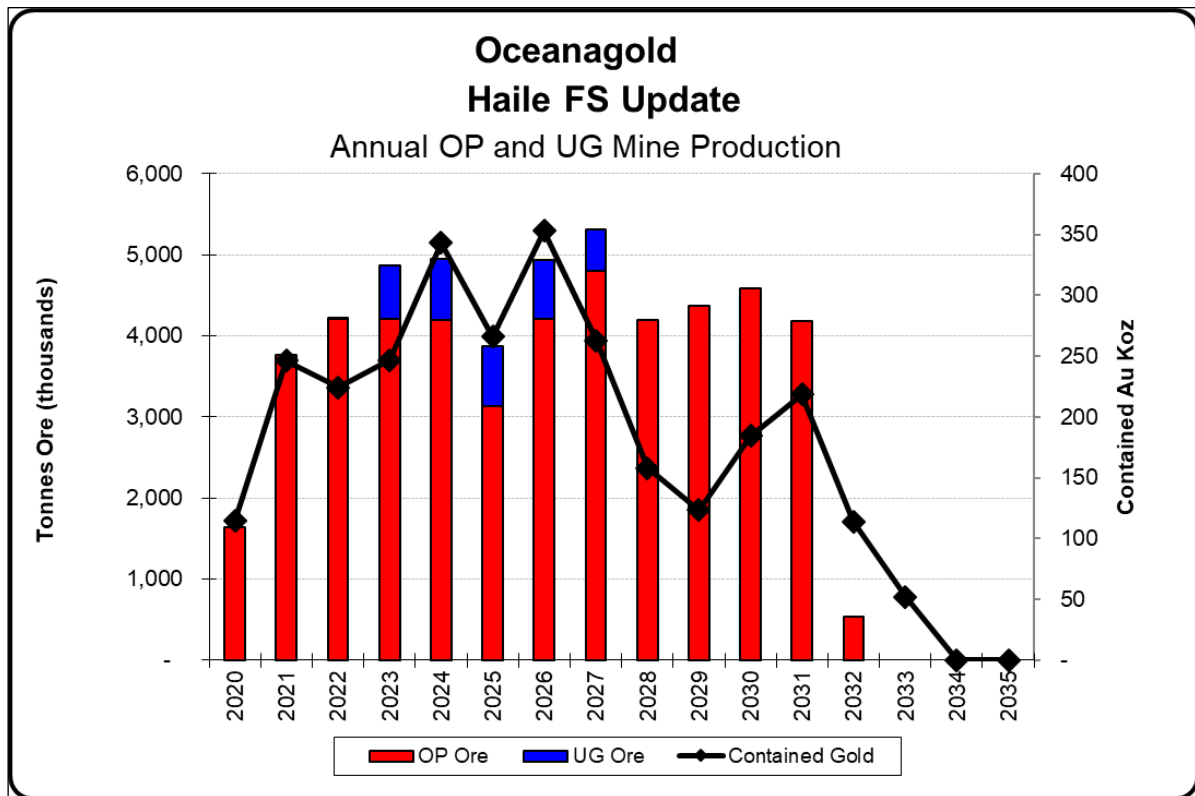

Source: SRK, 2020

Figure 22-2: Annual Open Pit and Underground Ore Production


22.2.2 Mill Production

A summary of the estimated process plant production for the Project is contained in Table 22-3 for a 14 year operating life. Figure 22-3 shows LoM production by year with a 4.0 Mtpa capacity. Ore processed refers to Proven and Probable Mineral Reserves.

Table 22-3: Life-of-Mine Process Production Summary

Description	Units	Value
Total Ore Processed	kt	52,785
Daily Process Capacity	t/d	10,959
Processed Grade	g/t	1.71
Contained Gold	koz	2,907
Contained Silver	koz	3,746
Gold Recovery	%	85.0%
Silver Recovery	%	81.0%
RoM Recovered Gold	koz	2,470
RoM Recovered Silver	koz	3,033

Source: SRK, 2020

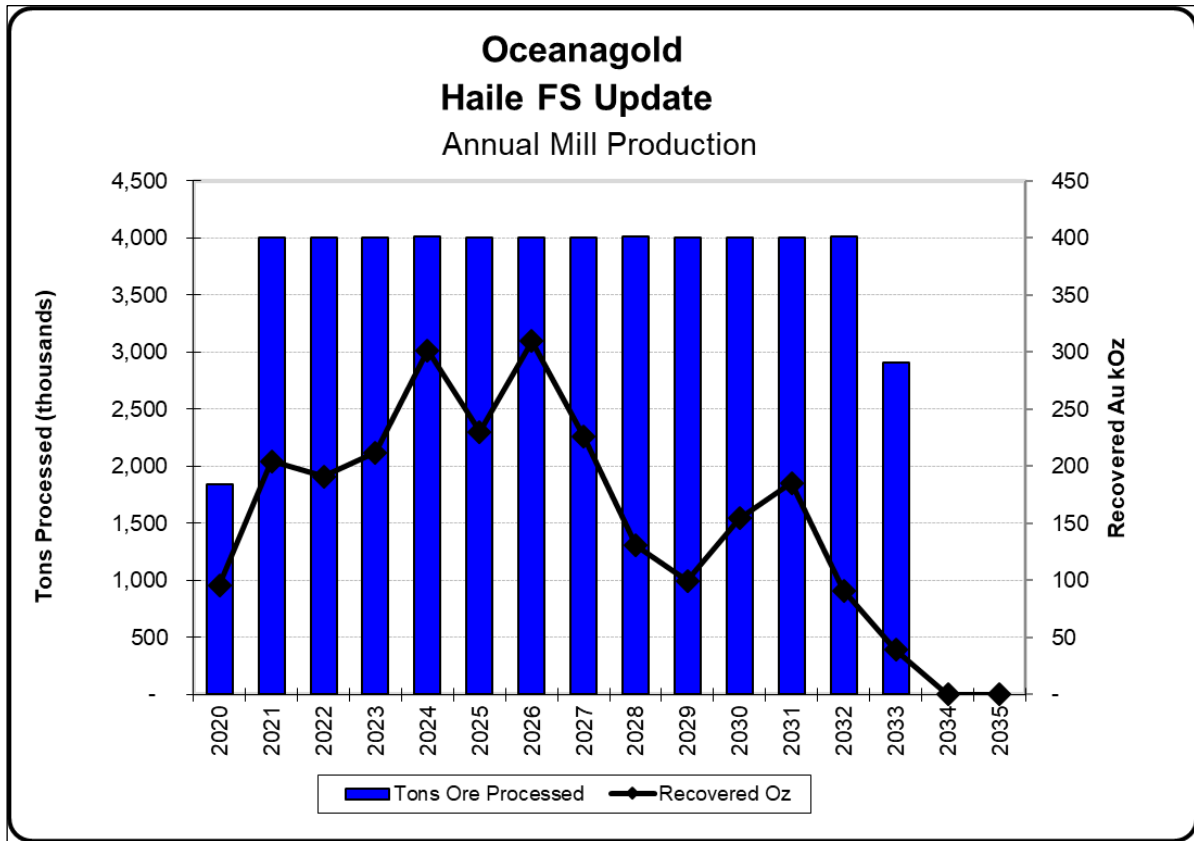

Source: SRK, 2020

Figure 22-3: Annual Process Plant Production

22.2.3 Revenue

Gold pricing assumptions used in the economic analysis include a constant base case LoM gold price of US\$1,500/troy oz.

Doré refining/freight costs are modeled as follows:

- 99.996% payable Au
- US\$0.93/troy oz Au treatment charge
- US\$0.24/troy oz Au + US\$785/shipment freight costs.

Silver is also included in current the Mineral Resource or Reserve estimates.

The silver by-product credit in the TEM is calculated by using a constant silver price of US\$17/troy oz and an average recovery of 81%. The additional silver related doré refining costs are as follows:

- 99.0% payable Ag
- US\$0.70/troy oz Ag treatment charge
- US\$0.24/troy oz Ag freight cost.

The silver by-product credit of US\$51 million over LoM represents of 1.4% of revenue over LoM for the Project.

22.2.4 Operating and Capital Costs

No contingency was applied to capital and operating costs within the economic model.

The total RoM operating cost unit rate of US\$28.40/t processed is summarized in Table 22-4.

Table 22-4: RoM Operating Cost Summary

Description	US\$000's	US\$/t Ore Processed
OP Mining (\$/t rock mined) - All Material	909,308	2.00
OP Mining (\$/t rock mined) - Operational Material	627,469	2.05
UG Mining (\$/t ore mined)	161,073	47.15
Subtotal Mining (Operational Material Only)	788,542	14.94
Processing	526,811	9.98
G&A Cost	175,478	3.32
Refining/Freight Costs	8,213	0.16
Total Operating Costs	\$1,499,044	\$28.40

Source: SRK, 2020

There are several important cost items excluded from the operating cost, which are detailed in Table 22-5, that OceanaGold does not consider to be direct operating costs but which the operation does incur.

Table 22-5: RoM Indirect Costs Summary

Description	US\$000's	US\$/t Ore Processed
Endowment & Reclamation Fund	18,778	0.36
Environmental Bond	7,645	0.14
Interest Expense - Capital Leases	11,226	0.21
Principal Payment - Capital Leases: Sustaining	12,089	0.23
Principal Payment - Capital Leases: Non-Sustaining	108,810	2.06
Regional Business Units	18,032	0.34
Total Non-Operating Costs	176,580	\$3.35

Source: SRK, 2020

Total LoM capital costs totaling US\$788 million including reclamation and closure costs are summarized in Table 22-6. The capital expenditure items have been separated into sustaining and non-sustaining categories per guidance from OceanaGold. Non-sustaining capital is primarily related to the development of the underground mine and associated infrastructure and totals US\$304 million over life of mine.

Table 22-6: Life-of-Mine Capital Costs (000's)

Description	Initial Capex	Sustaining Capex	Total
Land Acquisitions	-	5,925	5,925
Permitting	-	1,542	1,542
On-Site Exploration Drilling	6,679	-	6,679
Op Capitalized Pre-Strip	281,838	-	281,838
Capital Leases: Sustaining	-	-	-
Capital Leases: Non-Sustaining	-	-	-
OP Mining PP&E	19,969	6,850	26,819
OP Tech Services PP&E	720	-	720
Pit Dewatering	15,868	-	15,868
Site Works	1,975	7,722	9,697
PAG Cell Development	-	88,077	88,077
TSF Lift Design	138,857	33,329	172,186
Underground Mining: Non-Sustaining	-	79,413	79,413
Underground Mining: Sustaining	17,091	-	7,091
Mill PP&E	793	13,020	13,814
Commercial	54	14	68
Total Net Capex	\$483,844	\$235,894	\$719,738
Reclamation/Closure ⁽¹⁾	-	68,280	68,280
Total LoM Net Capex	\$483,844	\$304,173	\$788,017

Source: SRK, 2020

(1) Captured as Capex in Cashflow

The assumptions used for working capital for this estimate are as follows:

- Accounts Receivable (A/R): 5-day delay;
- Accounts Payable (A/P): 30-day delay; and
- Zero opening balance for A/P and A/R

Annual adjustments to working capital levels are made in the TEM with all working capital recaptured by the end of the mine life resulting in a LoM net free cash flow (FCF) impact of US\$0.


22.2.5 Economic Results

The TEM metrics are prepared on an annual after-tax basis, the results of which are summarized in Table 22-7. A full LoM annual cash flow forecast is presented in Appendix B. The results indicate that at a US\$1,500/oz gold price the Project returns an after-tax NPV 5% of US\$891.9 million. Note that because the project is operating and is valued on a total project basis with prior capital treated as sunk, and not by an incremental analysis of the UG and mill expansions, an IRR value is not relevant in this analysis. Figure 22-4 presents annual cash flow metrics versus recovered gold production and shows that the project does not generate much positive free cash flow in the remainder of 2020 and 2021 due to the level of capital expenditures being made during that time.

Table 22-7: Indicative Economic Results

Description	US\$000's
Market Prices	
Gold (US\$/oz)	\$1,500
Payable Gold (koz)	2,470
Revenue	
Gross Gold Revenue	3,705,121
Silver By-Product Credit (@ US\$17 / oz Ag)	51,040
Total Gross Revenue	\$3,756,161
Operating Costs	
OP Mining	(627,469)
UG Mining	(161,073)
Processing	(526,811)
Site G&A	(175,478)
Selling/Refining	(8,213)
Non-Operating Costs	(176,580)
Total Operating Costs	(\$1,675,624)
Operating Margin (EBITDA)	\$2,080,537
Taxes	
Income Tax	(52,544)
Total Taxes	(\$52,544)
Working Capital	0
Operating Cash Flow	\$2,027,992
Capital	
Sustaining Capital	(483,844)
Non-Sustaining Capital	(304,173)
Total Capital	(\$788,017)
Metrics	
Pre-Tax Free Cash Flow	\$1,292,519
After-Tax Free Cash Flow	\$1,239,975
Pre-Tax NPV @ 5%	\$929,844
After-Tax NPV @ 5%	\$891,906

Source: SRK, 2020

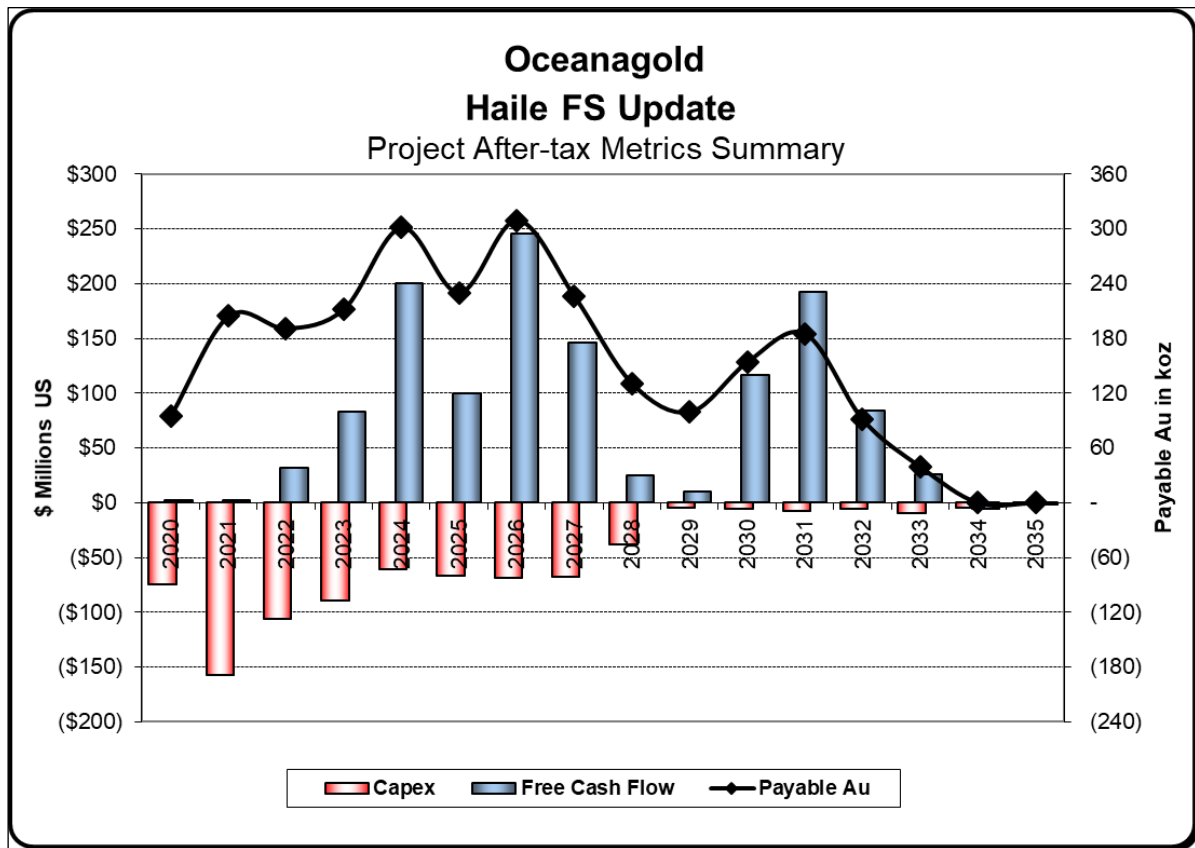

Source: SRK, 2020

Figure 22-4: Project After-Tax Metrics Summary

Table 22-8 shows the build-up of a RoM AISC of US\$799/oz Au, net of a US\$21/oz silver by-product credit, over the 14-year life of the Project.

Table 22-8: RoM AISC Contribution


Total RoM Payable Gold Sales in koz		2,470
Description	US\$000's	US\$/oz
OP Mining	627,469	254
UG Mining	161,073	65
Processing	526,811	213
Site G&A	175,478	71
Selling/Refining/Freight	8,213	3
Direct Cash Costs Before By-Product Credit	\$1,499,044	\$607
Silver By-Product Credit	(51,040)	(21)
Direct Cash Costs After By-Product Credit	\$1,448,004	\$586
Royalties	-	-
Endowment Liability - State of SC (Removed)	-	-
Environmental Bond (Removed)	-	-
Reclamation Fund Payments (Removed)	-	-
Interest Expense - Capital Leases	11,226	5
Principal Payment - Capital Leases: Sustaining	12,089	5
Regional Business Units	18,032	7
Non-Operating Cash Costs	41,347	17
Sustaining Capex ⁽¹⁾	483,844	196
Total RoM AISC	\$1,973,195	\$799

Source: SRK, 2020

Per OGC Accounting Standards:

- (1) OceanaGold treat TSF works completed with 5 years from commissioning as non-sustaining capital which for this analysis amount to US\$33.3 million. If these costs are included, the LoM AISC would be US\$812/oz.

Figure 22-5 shows the annual RoM AISC trend during the mine operations against an overall average RoM AISC of US\$799/payable oz over the 14-year LoM at an annual average production rate of 195 koz Au per year during full years of operation. The AISC variations are mainly driven by annual gold production levels and can range from US\$388 to US\$1,330 per oz in a given year.

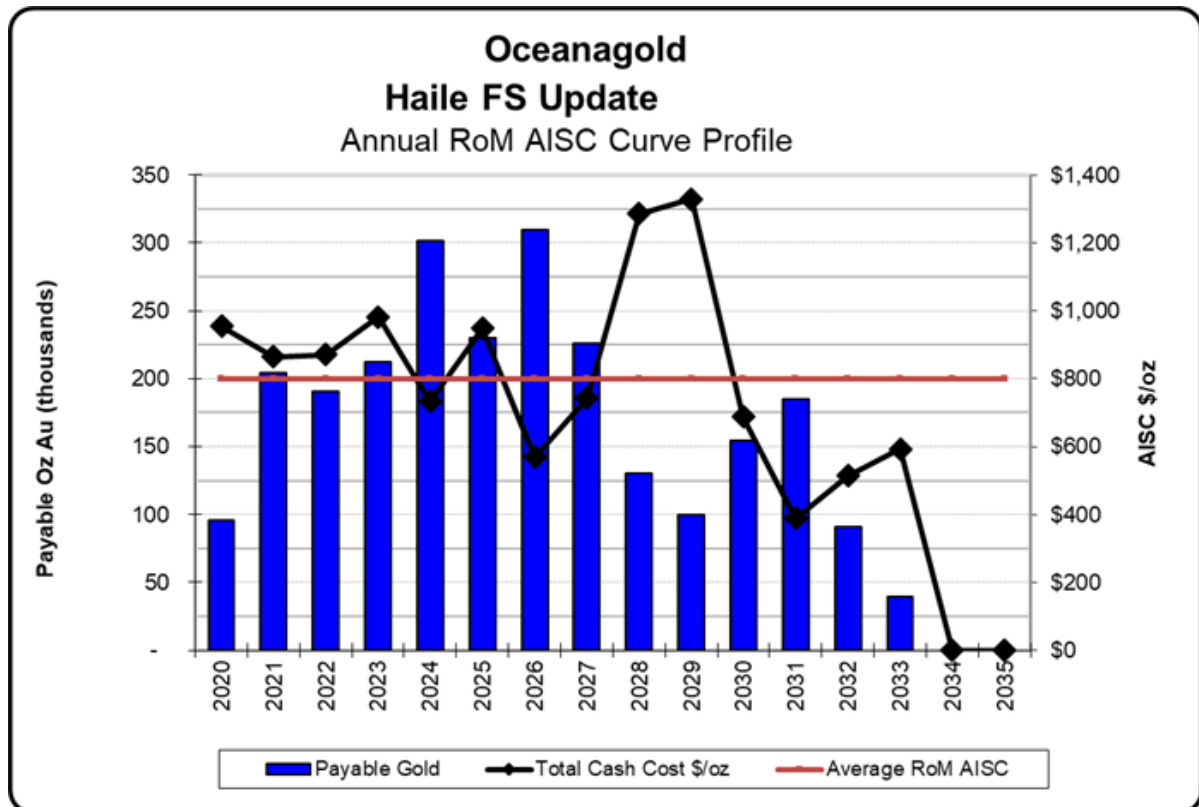

Source: SRK, 2020

Figure 22-5: Annual AISC Curve Profile

22.3 Taxes, Royalties and Other Interests

As the project is currently in operations, a comprehensive tax analysis for the remainder of the mine life was provided by OceanaGold for incorporation into the TEM on a whole year basis. As the TEM begins in mid-July and contained variable monthly, quarterly and annual periods, some minor adjustment was required for inclusion in the TEM. The project after tax forecast includes benefits associated with net operating losses (NOL) carried forward which are available. The assumptions used in the methodology are described in this section whereas a full taxation model is shown in Appendix C. The main taxation assumptions are as follows:

- Corporate Income Tax (CIT) rates are 21% for Federal and 5% for South Carolina;
- Net Operating Losses (NOL) are accounted for.
- Federal Depletion allowance is calculated for each period by determining:
 - 15% percentage depletion of Gross Income from Mining (subject to 50% of Net Income from Mining limit)
- A Tax Depreciation allowance schedule was provided by OceanaGold based on the following methods:
 - Modeled project capital is depreciated via seven-year 150% declining balance.
 - Previously spent capital is depreciated via seven-year 150% declining balance and 15-year 150% declining balance depending upon asset classification.

- The tax depreciation schedule provided yields US\$728 million of depreciation from the whole year 2020 through life of mine excluding the depreciation potential of end of life closure expenditure.
 - The total tax deductions calculated for the operation from 2020 through the life of mine are presented in Table 22-9 below.

Table 22-9: Haile Tax Deductions (US\$000)

Tax Deductions	LoM US\$(000)
Stock Movement	66,970
\$162 Expenses in Capex Budget	21,946
Mine Development Amortization \$616	436,061
Mine Exploration/Forward Amortization \$617	27,049
Tax Depreciation \$168	728,892
Permitting Amortization \$197	95,814
Feasibility Amortization \$167	13,904
RBIL Carryover Allowable	15,706
§ 461 Reclamation Deduction	68,280
South Carolina State Tax	13,211
Total Tax Deductions	1,487,832

Source: OceanaGold

- OceanaGold U.S. Holdings Inc. currently has an approximately US\$250 million debt facility payable to OceanaGold Corporation. These funds are lent through intercompany advance to Haile Gold Mine and are serviced by Haile Gold Mine cashflows. The interest expense from this facility is deducted from taxable income. SRK notes that the principle and interest payments for this facility are not considered elsewhere in the economic analysis as it is a loan from the parent company.
- FDII deduction is applicable as the tax model assumes that all product is sold outside the U.S.


There are no third-party government or private royalties or government severance taxes due on the Project during LoM.

The TEM was created on a project level basis and no fractional ownership, if applicable, was considered in the result.

22.4 Sensitivity Analysis

22.4.1 Operational Sensitivity

After-tax sensitivity analyses for key operational parameters are shown in Figure 22-6. Not surprisingly, the Project is nominally most sensitive to gold grade. The Project's sensitivities to capital and operating costs are similar but slightly more susceptible to operating costs.

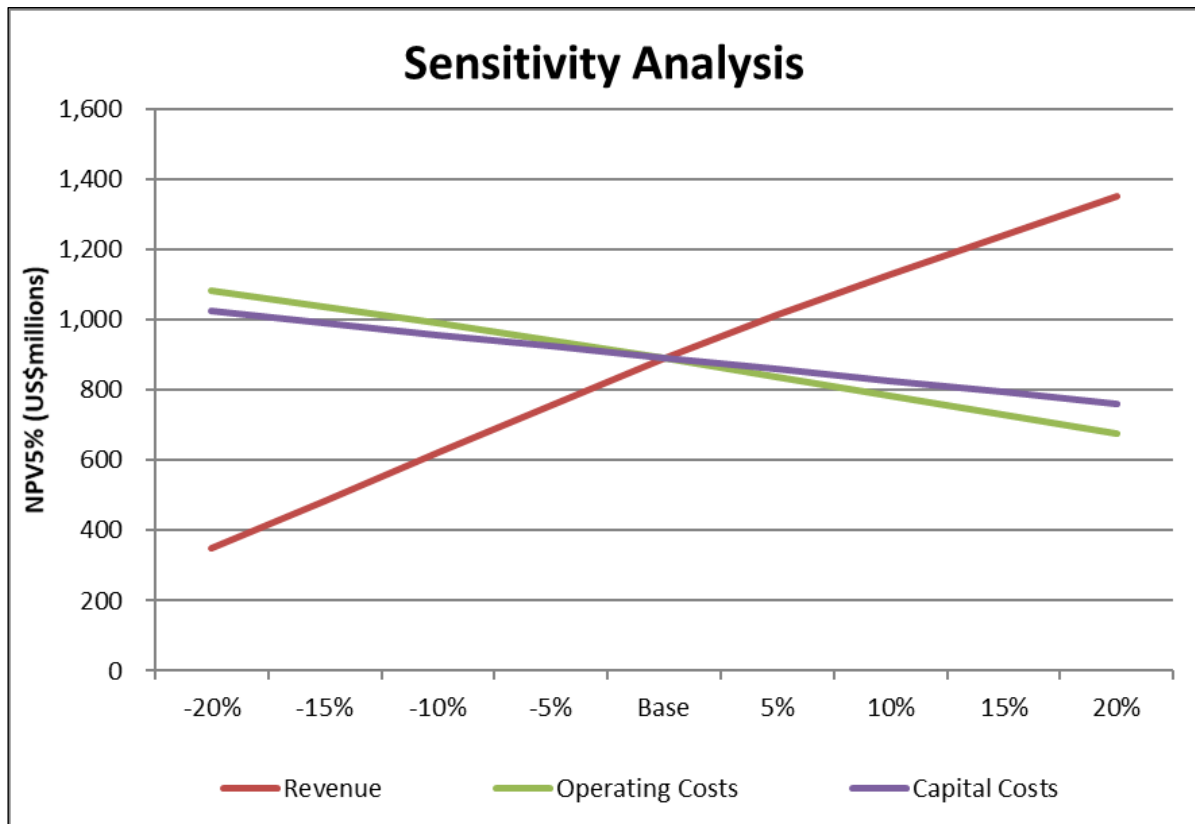

Source: SRK, 2020

Figure 22-6: Operational Sensitivity Analysis

22.4.2 Gold Price Sensitivity


Additional gold price sensitivity analyses are shown with after-tax Project NPV 5% at constant “Robust” prices of US\$1,750/oz, constant “Distressed” price of US\$1,250/oz, and a Consensus Economics’ Consensus Market Forecast (CMF), which show a five year forecast with gold prices reaching US\$1,500/oz in 2024 and constant from 2025 onward as follows:

- 2020: US\$1,850
- 2021: US\$1,850
- 2022: US\$1,750
- 2023: US\$1,650
- 2024: US\$1,500
- 2025+: US\$1,500

The silver price per ounce used in the consensus price deck is as follows:

- 2020: US\$24.00
- 2021: US\$20.00
- 2022+: US\$19.00

Figure 22-7 shows the gold price sensitivity analysis.

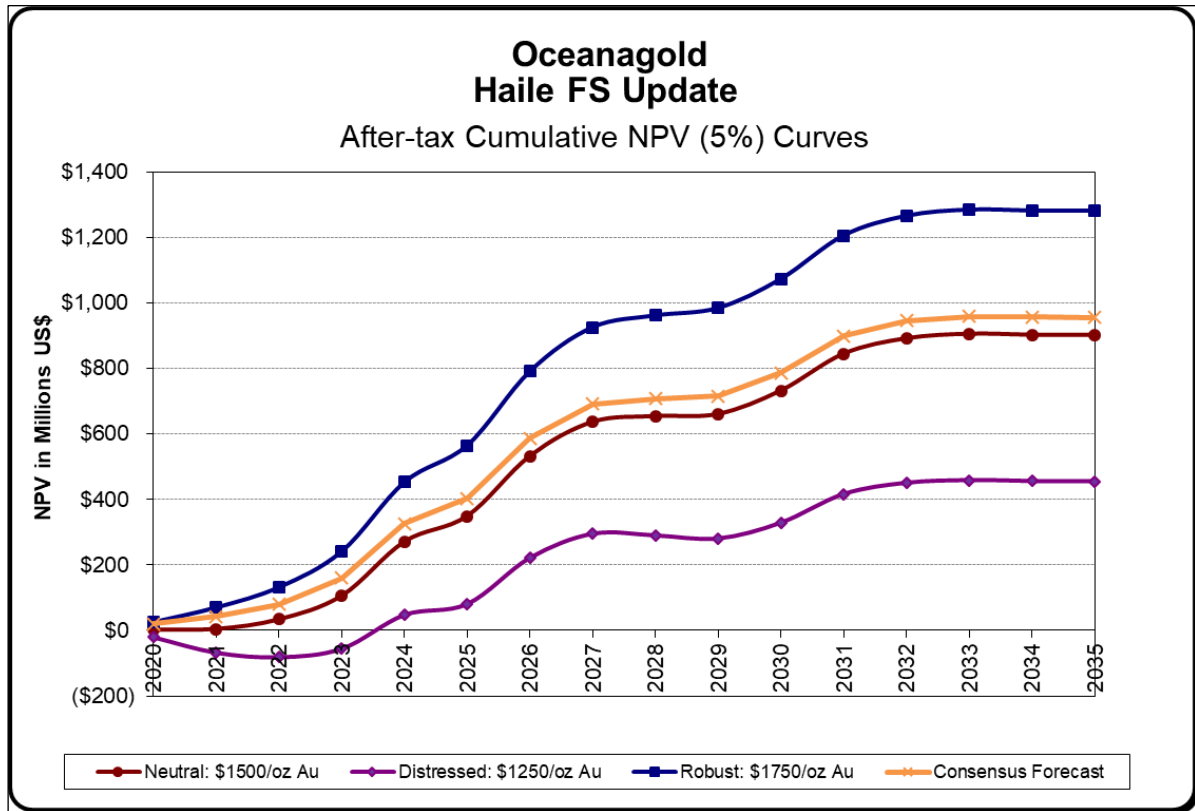

Source: SRK, 2020

Figure 22-7: Gold Price Sensitivity Analysis

22.4.3 Consensus Pricing Model Result

As the current gold price environment differs from the pricing used to evaluate the reserves at the Project and in recognition that this may potentially penalize the value of the project, the modeled indicative economic results are presented in Table 22-10 at the CMF price profile.


Table 22-10: Indicative Economic Results (Consensus Pricing)

Description	US\$000s
Market Prices	
Payable Gold (koz)	2,470
Revenue	
Gross Gold Revenue	3,889,690
Silver By-Product Credit	57,652
Total Gross Revenue	\$3,947,343
Operating Costs	
OP Mining	(627,469)
UG Mining	(161,073)
Processing	(526,811)
Site G&A	(175,478)
Selling/Refining	(8,213)
Non-Operating Costs	(176,580)
Total Project Costs	(\$1,675,624)
Operating Margin (EBITDA)	\$2,271,719
Taxes	
Income Tax	(72,527)
Total Taxes	(\$72,527)
Working Capital Delta (LoM) ¹	0
Operating Cash Flow	\$2,199,192
Capital	
Sustaining Capital	(483,844)
Non-Sustaining Capital	(304,173)
Total Capital	(\$788,017)
Metrics	
Pre-Tax Free Cash Flow	\$1,483,701
After-Tax Free Cash Flow	\$1,411,175
Pre-Tax NPV @ 5%	\$1,107,020
After-Tax NPV @ 5%	\$1,053,144

⁽¹⁾Model assumes zero open balance
Source: SRK

22.4.4 Discount Rate Sensitivity

A sensitivity analysis of discount rates presented in Figure 22-8 shows that the Project as currently modeled would be NPV positive through a 20% discount rate.

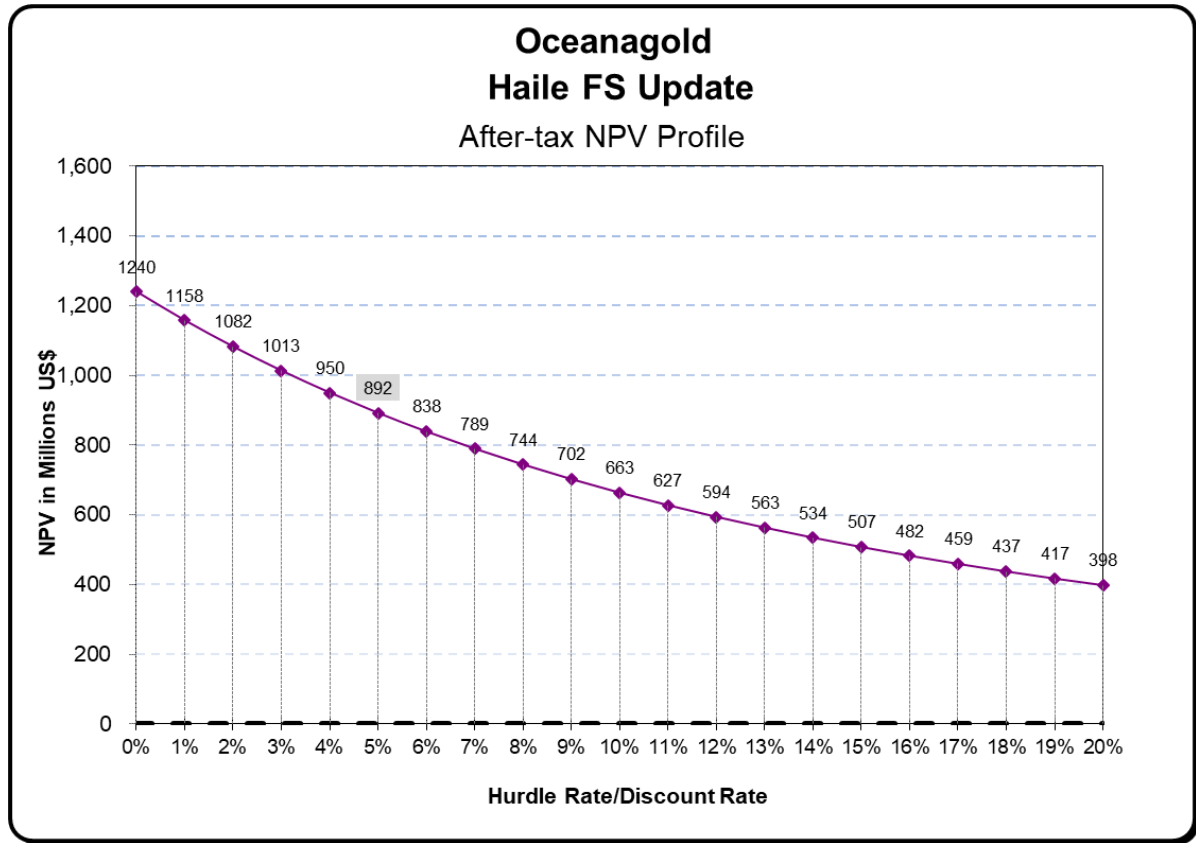

Source: SRK, 2020

Figure 22-8: Discount Rate Sensitivity Analysis

23 Adjacent Properties

The Carolina terrane contains numerous historical gold mines and mining districts. Over 1,500 gold prospects have been documented. Most of these deposits were discovered in the 1800s. Significant gold deposits in South Carolina include the Haile, Ridgeway, Brewer, and Barite Hill Mines. Numerous quartz vein-hosted mines of the Gold Hill and Cid Mining Districts occur in neighboring North Carolina. Some gold deposits have similar geologic and mineralization features to Haile, and several are polymetallic with Cu, Ag, Pb and Zn.

23.1 Ridgeway Mine

The Ridgeway Mine is located 8 km east of Ridgeway, South Carolina and 40 km north of Columbia, South Carolina. Kennecott produced 1.5 Moz (46,655 kg) of gold from 1988 to 1999 from two open pits in low-grade oxide and sulfide ore from siliceous deposits in the Richtex Formation. The Ridgeway deposit has strong geological similarities to Haile (Gillon et al., 1995, 1998). The saprolite, volcanic and metasedimentary rocks are quartz-sericite-pyrite altered in mineralized areas. Post-mineral mafic and diabase dikes crosscut the deposit and are often accompanied by shearing and/or faulting. Gold grade is related to lithology, cleavage development, pyrite grain size and abundance, and silica content. Molybdenite is also associated with the mineralization.

The mine and mill had a production capacity of 13,608 tonnes per day. Ore was milled to minus 200-mesh, then fed into a modified carbon-in-leach circuit. Carbon was stripped of gold, electroplated onto steel wool cathodes, and then transferred to electro-refining cells where gold was plated onto stainless steel plates. Mine closure and reclamation were successfully completed in the early 2000s.

23.2 Brewer Mine

The Brewer gold mine is located 12 km northeast of Haile in Jefferson County. Brewer rocks include schist, volcanics, and granite overlain by 40-60 feet of saprolite and sand. Gold mineralization is associated with quartz-sericite-pyrite altered schist, strong silicification and brecciation, and >2% pyrite. Gold ore was produced from a breccia body of hydrothermal origin and a related smaller body of fault-controlled ore. Pyrite content is generally 2-5%, unevenly distributed as aggregates and individual crystals in quartz veins. Gold grades were reported in the 1.41 g/t to 4.06 g/t range with associated silver, copper, tin, and bismuth. Brewer is classified as a high sulfidation breccia pipe hosted in the Persimmon Fork volcanics and may have deep porphyry roots.

Like Haile and other mines in the region, the mine produced gold intermittently, first as a placer, then as a surface and underground mine, and finally as a low-grade, heap leach operation in the 1980s. In 1987, Westmont Mining estimated a non-NI 43-101 compliant reserve for Brewer of 4.6 million tonnes grading 1.4 g/t gold (188,000 oz) (Scheetz, et al. 1991). The most recent production was from 1987 to 1995 by Westmont Mining/Costain Ltd Group. Ore was mined using conventional truck and loader open pit methods and ore was processed using cyanide leaching.

Brewer has been managed by the EPA as an active Superfund site since 1999 due to Acid Rock Drainage (ARD). Westmont mined and heap leached 12 Mt of ore with dilute cyanide solutions from 1987 to 1995. Heavy rains in April 1990 broke the tails dam; over 10 Mt of cyanide solution flowed into Little Fork Creek and downstream into Lynches Creek. The tails dam was repaired in 1991 and mining

continued until 1995 when reserves were mined out. Mine reclamation commenced in 1995 with SCDHEC guidance. Barite Hill Mine

The Barite Hill Mine is located 4 km southwest of McCormick, South Carolina. It is within the Lincolnton-McCormick Mining District, which includes other small mines and prospects of gold, silver, copper, zinc, lead, kyanite, and manganese.

23.3 Barite Hill Mine

The Barite Hill Mine is located 4 km southwest of McCormick, South Carolina. It is within the Lincolnton-McCormick Mining District, which includes other small mines and prospects of gold, silver, copper, zinc, lead, kyanite, and manganese.

The Barite Hill deposit was mined from 1989 to 1994 by Nevada Goldfields, Inc. The mine produced 59,000 oz of gold (1.8 million grams) and 109,000 oz (3.4 million grams) of silver, mainly from oxidized ore in the 20-acre (8 ha) Main Pit and the 4-acre (1.6 ha) Rainsford Pit. The mine used conventional open pit mining methods and an on/off pad heap leach process.

In June 1999, Nevada Goldfields Inc. filed for Chapter 7 bankruptcy, and abandoned the property. The property came under control of the South Carolina Department of Health and Environmental Control and the site became part of the EPA Superfund program. Reclamation and closure work began in October 2007.

The Barite Hill deposit is hosted by sericitized felsic metavolcanic and metasedimentary rock of the Persimmon Fork Formation. The deposit occurs along the contact between upper and lower pyroclastic units. Mafic to intermediate post-mineralization dikes and sills cross-cut NE-trending mineralized zones. Multiple Main Pit ore zones are associated with lenses of siliceous barite rock and pyrite-quartz altered breccias, some of which are offset by normal faulting. Rainsford Pit ore zones are associated with silicified rock and chert. The Barite Hill deposit is interpreted to be the result of a Kuroko-type submarine volcanogenic base-metal sulfide system followed by epithermal precious metal deposition (Clark, 1999).

24 Other Relevant Data and Information

SRK knows of no other relevant data or information available at this time, other than what has been presented, to make the technical report understandable and not misleading.

25 Interpretation and Conclusions

Geologic controls for Haile ore bodies are well understood and are documented by mapping and drilling in 3,295 drillholes including 1,255 core holes for 394,771 m (57% m) and 2,040 RC holes for 294,216 m (43% m). Mineralization is relatively continuous for reliable grade models constrained by geological controls (sand, dikes, volcanic-sediment contacts). En echelon mineralized zones strike ENE as mostly stratiform lenses within a 3.5 km long by 1 km wide area. Stratigraphic controls in the upper Persimmon Fork Formation comprise mostly unmineralized tuffs and dacite flows adjacent to mineralized siltstone that dips 30-60° NW. Younger unmineralized units include crosscutting Triassic diabase dikes and Cretaceous sand cover. Dominant structural controls reflected by foliation, faults, and shear zones strike ENE and dip 30-60° NW sub-parallel to bedding. Alteration is characterized by strong quartz-sericite-pyrite alteration in mineralized areas flanked by barren sericite and propylitic carbonate-chlorite alteration. Saprolite and oxidation are 10 to 40 m deep. Gold mineralization is poorly developed in saprolite. The Haile mine area is partly covered by an unmineralized southeast-thickening apron of Coastal Plain Sands.

25.1 Geology and Mineralization

Similar timing for gold mineralization and peak magmatism in the Haile and Ridgeway deposits indicates that the hydrothermal systems that produced these deposits were driven by magmatism and were not a product of North American accretion or metamorphism. Timing of gold mineralization coincides with a major tectonostratigraphic change from intermediate volcanism and tuffaceous sedimentation to basinal turbiditic sedimentation. Haile is classified as a low-sulfidation epithermal, sediment-hosted, disseminated gold deposit with proximal quartz-sericite-pyrite (QSP) alteration and distal carbonate-chlorite alteration overprinted by regional greenschist facies metamorphism. Haile is hosted by reduced siliciclastic rocks with less permeable volcanic caprocks and is structurally dismembered.

25.2 Resource Estimation

25.2.1 Open Pit

The drillhole database and resource estimation methodology are appropriate for the purposes of estimating the open pit gold resources. This is supported by the resource model to mine-to-mill reconciliation performance, which while variable on an annual basis shows very reasonable long-term performance.

OceanaGold will continue to optimize gold estimation but the focus will move to capturing geometallurgical characteristics in the block model. This is likely to include integrating drillhole information such as intensity of silicification, clay content, silver grade, sulfur grade and lithology.

25.2.2 Underground

The drillhole database and resource estimation methodology are appropriate for the purposes of estimating the underground gold resources. OceanaGold has completed an industry standard resource definition drilling at both Horseshoe and Palomino underground deposits to support the current Mineral Resource estimation. The work has been accompanied by an industry standard QA/QC program showing good quality analytical results. OceanaGold has conducted extensive core logging

resulting in a high-quality geologic model. The results of the drilling, sampling, analytical testing, core logging and geologic interpretation provide good support for an industry standard resource estimation.

25.3 Status of Exploration, Development and Operations

Resource definition drilling at Haile by Romarco Minerals and OceanaGold has increased the resources more than five-fold since 2007. Reserve growth has been stimulated by 3D geologic models, higher gold prices, and aggressive and deeper drilling of a previously underexplored gold system. This has been recently exemplified by pre-development of the Horseshoe underground reserve (0.44 Moz) in 2017 and announcement of a maiden inferred resource at Palomino in 2020 (0.6 Moz). In-house core drilling continues by OceanaGold at 15 km per year, focused along pit design margins and high-grade underground targets proximal to the sedimentary-volcanic contact. Underground development of the Horseshoe deposit in 2022 to 2023 will facilitate access for underground drill stations along the prospective 2 km long Horseshoe-Palomino trend. Regional exploration for Haile-like deposits is ongoing.

25.4 Mining and Reserves

25.4.1 Open Pit

The Project confirms a positive cash flow using only Measured and Indicated resources for the conversion of reserves using a US\$1,500/oz gold price. The mine design supports the style and size of equipment selected for operations.

The mine operating and capital costs have been estimated from first principles and operational knowledge from current mine operations. The equipment is sized to meet minimum SMU requirements that support the dilution and mine recovery factors while providing bulk earthwork capability for the expected production rates.

The LoM production schedule includes provision for careful control of potentially acid generating overburden and appropriate material handling costs have been included in the mining cost estimate.

The mine plan is based on a specific set of assumptions and therefore the results of this Technical Report are subject to many risks including, but not limited to: commodity prices and foreign exchange assumptions (particularly relative movement of gold and oil prices), unanticipated inflation of capital or operating costs, significant changes in equipment productivities, geotechnical assumptions in pit designs, ore dilution or loss, throughput and recovery rate assumptions.

SRK knows of no existing environmental, permitting, legal, socio-economic, marketing, political, or other factors that might materially affect the Mineral Reserve estimate.

25.4.2 Underground

Geotechnical

A geotechnical field characterization program has been undertaken to assess the expected rock quality. This program included logging core, laboratory strength testing, in situ stress measurements and oriented core logging of jointing. The results of this program have provided adequate quantity and quality data for feasibility-level design of the underground workings.

A geotechnical assessment of the orebody shape and ground conditions has determined that longhole open stoping mining is an appropriate mining method. Stopes have been sized to maintain stability once mucked empty. A primary/secondary extraction sequence with tight backfilling allows optimization of ore recovery while maintaining ground stability. Primary stopes will be backfilled with cemented rockfill, while secondary stopes will be backfilled with uncemented waste rock.

The design has been laid out using empirical design methods based on similar case histories. The stability of the design has been checked with 3D numerical stress-strain models of the workings which included consideration for mine-scale faulting. The modeling results confirm that stopes and access drifts are predicted to remain stable during active mining.

Mining

Longhole stoping is seen as the appropriate mining method for the deposit geometry. The large stope sizes minimize cost and grades are not overly diluted. Mine planning work considered revenue for Au and a CoG of 1.44 g/t Au was used. A 3D detailed mine design was completed.

The underground mine is accessed via ramp, with the ramp portal is located on an open pit bench approximately 80 m below natural surface. Two ventilation drift portals are also located on an open pit bench.

Productivities were developed from first principles. Input from mining contractors, blasting suppliers and equipment vendors was considered for key parameters such as drilling penetration rates, blast hole size and spacing, explosives loading time, bolt and mesh installation time, etc. The rates developed from first principles were adjusted based on benchmarking and the experience and judgment of OceanaGold. Equipment used in this study is standard equipment used worldwide with only standard package/automation features.

The UG production schedule was completed using Deswik scheduling software and is based on mining operations occurring 365 days/year, seven days/week, with two 12-hr shifts each day. A production rate of approximately 2,000 t/d was targeted with ramp-up to full production as quickly as possible. Resource levelling was used on a monthly basis for ore tonnage and lateral development.

25.5 Mineral Processing and Metallurgical Testing

The Haile process plant has been in operation for approximately 3.5 years and has been progressively upgraded from its original nameplate capacity of 2.3 Mtpa to approximately 4.0 Mtpa through utilizing existing inherent capacity and addition of targeted equipment. The plant is now approaching a steady state of operations following upgrading meeting throughput, utilization and recovery expectations.

No novel, experimental or unproven technologies are used for the Haile process plant.

25.6 Recovery Methods

There has been no effective change to the existing plant recovery method for the plant following its expansion compared to the original circuit configuration. Ongoing metallurgical development will continue to target improvements in gold recovery and focusing on controlling unit costs.

25.7 Project Infrastructure

25.7.1 Underground Support Infrastructure

The underground support infrastructure is relatively straightforward including construction of a new dry/meeting building, new underground yard, an upgrade and addition to the power distribution system, water supply system, movement of an existing shop on site to the new underground yard, and installation of a portable crusher/screen plant and CRF plant at the underground yard.

25.8 Environmental Studies and Permitting

There is a significant amount of existing background and environmental baseline data available for the Project. This data continues to be collected and reported to the regulators as part of operational controls. Additional data and environmental studies (Section 20-3) will be of technical interest to the federal and state agencies in evaluating a request to expand the current mining operation.

Permits currently held by the HGM may be kept, modified, terminated, or replaced during the expansion process.

OceanaGold will work closely with all key stakeholders to ensure that the permitting of the mine expansion meets all of the federal and state requirements.

25.9 Economic Analysis

The Project consists of an operating mine with a mill capable of processing 4.0 Mtpa of material. The milling facility is mainly fed by the OP mine. The mill feed is also supplemented with ore from a five-year UG 2,150 t/d max annual capacity high grade operation that begins production at the end of 2022.

The Project is expected to produce 2.47 Moz of payable gold over a 14-year mine life at a rate of 195 koz Au per year during full production years with a RoM AISC of US\$799/oz Au.

The Project is expected to incur sustaining capital in the amount of US\$483.8 million over the modeled life and a non-sustaining capital spend, including closure costs, of US\$304.2 million for total capital expenditure of US\$788.0 million.

Project metrics using a constant US\$1,500/oz gold price include pre-tax and after-tax NPV 5% values of US\$929.8million and US\$891.9 million, respectively. Because the project is operational and is valued on a total project basis and not by an incremental analysis of the UG start up, an IRR value is not relevant in this analysis. In terms of sensitivity, the Project is not surprisingly most sensitive to gold grade and price following by operating costs and capital costs.

26 Recommendations

26.1 Recommended Work Programs

26.1.1 Geology and Mineralization

Open Pit

Haile 3D geologic models are updated twice a year based largely on core drilling and pit mapping to reflect controls to mineralization. Lithologic and structural interpretations are aided by pXRF geochemistry. Lithology, alteration, and mineralogical data are being integrated with geotechnical, overburden storage and metallurgical evaluations to optimize reserve growth and mill recoveries. Rising gold prices drive potential pit expansions that will be evaluated with more drilling to assess economic potential.

Underground

Resource drilling coupled with Snake pit mapping has significantly improved the interpretation of the diabase dikes, lithologic contacts and faults. A deposit scale re-interpretation was completed in 2019 in light of new lithological units. Re-logging of historic drilling has indicated a newly recognized rhyodacitic dikes and sills that partly replace previously interpreted sediments.

Recommended Programs Include:

A broad development and drilling strategy are recommended to extend resources southwestward towards the Snakeshoe Zone.

Evaluate if portable XRF testing or/other technologies can be used to further refine the geology interpretation (in tandem with in-pit studies).

Status of Exploration; Development and Operations

OceanaGold will continue to expand resources adjacent to open pit and underground reserves in the Haile district through core drilling aligned with LoM plans. Systematic target generation and rationalization supported by mapping, drilling, geochemistry, and geophysics is expected to yield new discoveries during the next five years, particularly for underground deposits.

26.1.2 Resource Estimation

Open Pit

OceanaGold will continue to optimize the gold estimation methodology via reconciliation analysis and geological review, but the focus will move to capturing geometallurgical characteristics in the block model. This is likely to include integrating drillhole information such as silicification intensity, clay content, silver grade, sulfur grade and lithology.

Underground

Pre-production infill drilling at 15 m x 15 m spacing will be conducted from underground development to provide additional confidence in the tonnes and grade to support a Measured Mineral Resource and refine the mine design. A small number of longitudinal holes will better define cross-cutting barren diabase dike swarms sub-parallel to existing drilling. Future capital development and resource infill drilling will further improve the geological interpretation.

- Study grade control strategy by investigating the potential for underground, reverse circulation, grade control drilling.
- Close spaced, short, ore-drive parallel diamond drilling has been chosen as the preferred option for grade control drilling.
- Additional carbon-sulfur Leco analyses will be conducted to refine the waste model and to improve sulfur grade schedules for the process plant.

26.1.3 Status of Exploration; Development and Operations

OceanaGold will continue to expand resources adjacent to open pit and underground reserves in the Haile district through core drilling aligned with LoM plans. Systematic target generation and rationalization supported by mapping, drilling, geochemistry, and geophysics is expected to yield new discoveries during the next five years, particularly for underground deposits.

26.1.4 Mining and Reserves

Open Pit

Equipment productivities, drill and blast efficiency and costs are all part of internal continuous improvement processes.

Implementation of the mining plan will include:

- Confirmation of the larger mining fleet selected as appropriate for the operation as more representative mining data becomes available
- Sterilization drilling of the overburden storage areas due to the change in footprint
- Infill drilling will likely move material from inferred resource to measured and indicated category
- Similar changes are possible for increased confidence in the classification of PAG material
- Additional drilling will target ultimate pit toe locations, particularly where mineralization is controlled by hard boundaries or limited by inferred resources
- Refining the mine designs to an operational level, including further optimization of the material movements and the ultimate ramp systems
- Further geotechnical analysis of pit design criteria as operating experience is gained and additional drilling information becomes available
- Pursuit of productivity and cost reduction initiatives, including:
 - Upgrading of in-pit and surface haul roads to all-weather trafficability to reduce time lost to wet weather
 - In-pit water management practices to reduce time lost to wet weather
 - Reviewing manning practices at shift change, crib breaks and other times to increase equipment utilization
 - Utilization of remote and autonomous operation capabilities of the blasthole drilling fleet
 - Implementation of real time payload monitoring technology on the primary excavator fleet
 - Other initiatives to increase excavator productivities
- Pursuit of initiatives relating to grade control, dilution and ore loss, including:
 - Review of blast hole sampling practices

- Modifications where appropriate to primary excavator configurations to better suit bench height, material and grade control applications
- Pursuit of initiatives to increase the accuracy of definition of waste types and reduce overall production of waste with PAG classifications , including those relating to:
 - Confirmation sampling techniques
 - Grade control and excavation practices in waste areas
 - Alternatives to the LECO testing currently employed
 - Opportunities for reclassification of some areas of Yellow PAG waste to Green

Underground

- Infill drilling at 15 m x 15 m spacing will provide additional confidence in the tonnes and grade of the production schedule to support a Measured Mineral Resource.
- Close spaced Grade Control drilling has been designed and scheduled ahead of stope production.
- A small number of longitudinal holes angled NE or SW will better define the locations of cross-cutting barren diabase dike swarms that are sub-parallel to existing drilling.

The key recommendations relating to the underground project include:

- Categorization of waste rock material as data is available.
- Grade control drilling to delineate ore/waste and guide material destination.
- Investigate UG RC drilling

26.1.5 Mineral Processing and Metallurgical Testing

The process plant flowsheet is effectively fixed and established on site. Ongoing mineralogical and diagnostic leach work on monthly composites should continue to track gold deportment and losses as each pit stage is processed to track variability and understand the impact of regrind size impact for each stage.

Infill drilling presents the opportunity to continue test work on available core samples to confirm recovery estimates for any new reserves that are defined. This should occur as material becomes available to de-risk the use of the current recovery model.

26.1.6 Project Infrastructure

Open Pit Infrastructure

A significant portion of the required open pit infrastructure is in place as part of the existing operation. Infrastructure, such as expit haul roads and water management infrastructure, will be added as necessary. The maintenance workshop should be expanded to support the mining fleet. These costs have been included appropriately in either operating or capital costs. The remaining requirements are waste storage facilities and the costs for these are included as sustaining capital.

Underground Infrastructure

Although the base case design considers cemented waste rock fill material for backfilling stopes, the option for using pastefill is still under consideration. If the pastefill solution is chosen, the necessary underground infrastructure should be re-evaluated.

Tailings and Overburden Infrastructure

The tailings infrastructure will require several road relocations that will need to be coordinated with the State of South Carolina. The Underdrain Collection Pond and run-off collection channels will need to be relocated. Expansion of the West PAG OSA will require the relocation of utility and site infrastructure. Additional geotechnical information may be needed.

26.1.7 Environmental Study Results

Table 26-1 is a summary of the environmental studies initiated by HGM to support the approval process.

Table 26-1: Environmental Studies

Study	Scope of Work
Air Emissions	Assess impact to air pollution loading based on additional operating conditions and new equipment on active point sources – engine exhausts, conveyor drop points, discharge stacks, ventilation shafts, dust controls, blast gasses, cement plant, etc.
Aquatic Resources – plants and animals	Review and assess Carolina Heel Splitter mussel fish and macroinvertebrate studies to quantify impacts to aquatic species over LoM.
Cultural & Historical Resources	Review and assess potentially impacted cultural and historical sites from surface disturbances. Relocate any potential gravesites.
Economic Impact to Local Community	Social and economic effect on the state and local economy – effect on local businesses, wages, local resources, emergency services, and external jobs.
Emergency Response Plans	Assessment of coordination with available local emergency support services.
Floodplain Assessment	Assess surface water impacts (flows and water quality) based unanticipated concurrent failures of the TSF, storage ponds, and Process Plant containment areas.
Geochemistry Analysis	Update OMP for PAG material placement, ARD control, and underground cut and fill practices.
Geology and Soils Assessment	Update an assessment of suitable materials for future reclamation actions.
Groundwater Modelling	Assess potential impacts to neighborhood wells, ponds and springs.
Hazardous Materials and Waste Inventory	Review of the chemicals, reagents, fuels, and hydrocarbon products transportation, storage, distribution, and disposal.
Health and Safety Assessment	Review of industrial hygiene monitoring and potential impacts to employee health.
Hydrology Assessment	Identification of direct and indirect impacts on local wetlands, wells, and streams.
Impacted Wetland Assessment	Assess potentially impacted wetland areas – vegetation and stream flow.
Land Use	Assess alternatives to potentially impacted land masses and identify future potentially higher value applications.
Noise and Vibration Study	Identify potential impacts from noise and vibration sources, including blasting activities, mobile equipment operating at elevated surfaces, crushing and grinding equipment, TSF evaporators, and mine equipment (haul trucks, dozers, and excavators)
Reclamation Plan	Pit closure and remediation plans, surface controls, revegetation plans, stormwater control plans, surface run-off plans, timelines, and sequence for surface reclamation activities.
Socioeconomic Impacts	Assess the socioeconomic impacts to state and local communities.
Stormwater Plans	Create Stormwater plans for sediment ponds, borrow pits, location for BMP ¹ devices, assessment locations, and site controls.
Surface Water Impacts	Assess impact to surface water flows – volume, dissolved oxygen, chemistry, pH and conductivity. Assess drainage patterns and develop recommendations for additional monitoring and measurement stations, if required.

Study	Scope of Work
Terrestrial Resources – Plant Life	Perform terrestrial plant evaluations, specifically in impacted areas and areas of significant disturbance.
Terrestrial Resources – Wildlife	Perform seasonal terrestrial studies on migratory endangered wildlife, such as species of bats and raptors.
Transportation & Traffic / Road Impacts	Perform a traffic study and predict road patterns and potential impacts based on employment and support service usage.
Vibration Analysis	Develop vibration predictions based on underground blasting and changes in surface contours and geological morphology.
Visual Impact Studies	Assess visual impacts along major thoroughfares: Highways, County Roads, Neighborhoods and Public spaces
Water Quality Assessment	Assess current and future impacts to changes in water quality based on volume changes, available precipitation and evaporation, and geochemical leach studies.
Wetland Delineation and Marking	Set the visual markers around the 50-ft offset. Measure the final size of wetland delineation.
Wildlife Assessment	Biological assessment of primary and secondary wildlife species and identify impacts and changes to migratory patterns, mortality changes and secondary food sources.

Source: OceanaGold

¹ Best Management Practice Devices – 1) Erosion Prevention – slope surfaces, seeding, and erosion controls; and 2) Sediment Control - check dams, sediment dams, sediment ponds, and silt fencing.

26.1.8 Economic Analysis

The current metal price environment is extremely strong. If prices are forecast to remain elevated for long periods, the project reserves and resources should be updated and fed into an economic model at a revised price deck reflective of the long-term price forecasts.

26.2 Recommended Work Programs Costs

Table 26-2 lists the estimated costs for the recommended work described in section 26. Note that these costs are included in the cost schedules presented in Section 21.

Table 26-2: Summary of Costs for Recommended Work

Discipline	Program Description	Cost (US\$)	No Further Work is Recommended Reason:
Geology and Mineralization	External reviews	30,000	
Status of Exploration, Development and Operations	OceanaGold exploration programs and development drilling. External assay laboratories used.	100,000	
Mineral Processing and Metallurgical Testing	External laboratory testing	80,000	
UG Exploration at Snakeshoe	Diamond drilling from UG development	1,000,000	
pXRF analyses to augment geological interpretation	Collect more data and analyze	50,000	
Mineral Resource Estimate – Open Pit	Develop Geometallurgical model		Salaries only
Mineral Resource Estimate – Underground	Sulfur data collection	100,000	
Mineral Resource Estimate – Underground	Dike definition drilling	250,000	
Mineral Reserve Estimate – Underground	Investigate UG RC drilling (site visit)	50,000	
Mining Methods – Open Pit & Underground	Further mine fleet and mining method analysis	150,000	
Open Pit Mining	Geotechnical Analysis	100,000	
Open Pit Mining	Productivity and cost initiatives	50,000	
Open Pit Mining	Grade control, ore loss and dilution initiatives	50,000	
Open Pit Mining	PAG Waste definition and classification	80,000	
Recovery Methods			Plant constructed and operational
Mineral Processing	Test work to confirm metallurgical recovery assumptions for future ore sources	150,000	
Project Infrastructure	Detailed design of bridge, road relocations tailings and waste storage facilities expansions, and UG requirements	1,500,000	
Environmental Studies and Permitting	Additional studies and legal support	500,000	
Capital and Operating Costs/Economic Analysis			OceanaGold internal
Total US\$		\$4,240,000	

Source: OceanaGold 2020

27 References

- AMIRA (2002). ARD Test Handbook. Project P387A: Prediction and Kinetic Control of Acid Mine Drainage.
- Ayuso, R. A., Wooden, J. L., Foley, N. K., Seal, R. R., and Sinha, A. K., 2005, U-Pb Zircon Ages and Pb Isotope Geochemistry of Gold Deposits in the Carolina Slate Belt of South Carolina: *Economic Geology*, v. 100, p. 225-252.
- Barker, C. A., Secor, D. T., Pray, J. R., and Wright, J. E., 1998, Age and Deformation of the Longtown Metagranite, South Carolina Piedmont: A Possible Constraint on the Origin of the Carolina Terrane: *Journal of Geology*, v. 106, p. 713-725.
- BGC Engineering Inc., 2017. "Haile Gold Mine Optimization Study - Open Pit Slope Designs", Final report issued to OceanaGold Corp. July 21, 2017
- Butler, J. R., and Secor, D. T., 1991, The Central Piedmont, *in* Horton, W., and Zullo, V., eds., *The Geology of the Carolinas*: Knoxville, TN, University of Tennessee Press, p. 59-78.
- CIM (2014). Canadian Institute of Mining, Metallurgy and Petroleum (CIM) Standards on Mineral Resources and Reserves: Definitions and Guidelines, May 10, 2014.
- Clark, L., (1998). Minimizing Dilution in Open Stope Mining with a Focus on Stope Design and Narrow Vein Longhole Blasting. M.Sc. thesis, Department of Mining and Mineral Process Engineering, The University of British Columbia, 316 p.
- Clark, L., and R. Pakalnis (1997). An Empirical Design Approach for Estimating Unplanned Dilution from Open Stope Hangingwalls and Footwalls. Presentation at 99th Canadian Institute of Mining annual conference, Vancouver, B.C.
- Clark, S., 1999, Geologic Maps and Block Diagrams of the Barite Hill Gold-Silver Deposit and Vicinity, South Carolina and Georgia: U.S. Geological Survey Open-File Report 99-148A
- Dooley, R. E., and Smith, W. A., 1982, Age and magnetism of diabase dikes and tilting of the Piedmont: *Tectonophysics*, v. 90, p. 283-307.
- Daniels, D., 2005 South Carolina Aeromagnetic and Gravity Maps and Data: USGS Open-File Report 2005-1022
- Feasibility Level Pit Slope Evaluation, Golder Associates, October 2010. Environmental Impact Statement, Haile Gold Mine Project, July 2014
- Feiss, P. G., Vance, R. K., and Weslowki, D. J., 1993, Volcanic rock hosted gold and base metal mineralization associated with Neoproterozoic-Early Paleozoic back-arc extension in the Carolina Terrane, southern Appalachian Piedmont: *Geology*, v. 21, p. 439-442.
- Foley, N. K., Ayuso, R. A., and Seal, R. R., 2001, Remnant colloform pyrite at the Haile gold deposit, South Carolina: A textural key to genesis: *Economic Geology*, v. 96, p. 891-902.
- Foley, N. K., and Ayuso, R. A., 2012, Gold deposits of the Carolina slate belt, southeastern United States: Age and origin of the major gold producers: USGS open file report 2012-1179
- First Quarter 2017 Results April 27, 2017 www.oceanagold.com

- Fullagar, P. D., and Butler, J. R., 1979, 325 to 265 Ma-old granitic plutons in the Piedmont of the southeastern Appalachians: *American Journal of Science*, v. 279, p. 161-185
- Gillon, K.A., Spence, W.H., Duckett, R.P., and Benson, C.J., 1995, Geology of the Ridgeway gold deposits, Ridgeway, South Carolina: *Society of Economic Geologists Guidebook Series*, v. 24, p. 53–94.
- Gillon, K.A., Mitchell, T.L., Dinkowitz, S.R., Barnett, R.L., 1998, The Ridgeway gold deposits -A window to the evolution of a Neoproterozoic intra-arc basin in the Carolina Terrane, South Carolina: *South Carolina Geology*, 40, p. 29–70.
- Gillon, K., 2000, Final observations from the Ridgeway North Pit, and their bearing on a tectonic development model for the Ridgeway gold deposits, Carolina Terrane, SC: *GSA abstract*, March 2000, Vol. 32, Issue 2, pp. 21
- Golder (2010). Haile Gold Mine, Lancaster County, South Carolina, Report on Feasibility Level Pit Slope Evaluation, Project No. 093-91767.300, October 2010.
- Golder (2012). Preliminary Geotechnical Investigation, Horseshoe Deposit, Haile Gold Mine, Lancaster County, South Carolina, Appendix A: Rock Core Logging Data, Project No. 11390150, January 5, 2012.
- Haile Gold Mine Addendum to Baseline Geochemistry Report, Schafer Limited LLC, November 2010.
- Haile Gold Mine Baseline Hydrologic Characterization Report, Schlumberger Water Services, November 2010.
- Haile Gold Mine Depressurization and Dewatering Feasibility Study, Schlumberger Water Services, December 2010.
- Haile Gold Mine Project NI 43-101 Technical Report Feasibility Study Lancaster County, South Carolina. M3 Engineering & Technology Corporation, 10 February 2011.
- Haile Gold Mine Project Resource Estimate NI 43-101 Technical Report Lancaster County, South Carolina. M3 Engineering & Technology Corporation, March 13, 2012.
- Haile Power Supply Recommendations for Feasibility Study, Haile Gold Mine, Inc., December 2010.
- Hardy, L. S., 1989, Hydrothermal potassium feldspar at the Haile gold mine, South Carolina: *Economic Geology*, v. 84, p. 2307-2310.
- Hatcher, R. D., Bream, B. R., and Merschat, A. J., 2007, Tectonic map of the southern and central Appalachians: A tale of three orogens and complete Wilson cycle: *in* Hatcher, R. D., Carbon, M. P., McBride, J. H., and Martínez Catalán, J. R., eds., *Framework of Continental Crust: Geological Society of American Memoir*, v. 200, (Eds.), 2007. 4D Framework of Continental Crust. Geological Society of America, Memoir, vol. 200. 641 pp., p. 595-632.
- Hayward, N., 1992, Controls on syntectonic replacement mineralization in parasitic antiforms, Haile gold mine, Carolina Slate Belt, U. S. A.: *Economic Geology*, v. 87, p. 91-112.
- Hibbard, J. P., Shell, G., Bradley, P., Samson, S., and Wortman, G., 1998, The Hyco shear zone in North Carolina and southern Virginia: implications for the Piedmont zone-Carolina zone boundary in the southern Appalachians: *American Journal of Science*, v. 298, p. 85 - 107.
- Hibbard, J.P., van Staal, C.R., and Rankin, D.W., 2010, Comparative analysis of the geological evolution of the northern and southern Appalachian orogen: Late Ordovician-Permian: *in* Tollo, R.P., Bartholomew,

- M.J., Hibbard, J.P., and Karabinos, P.M., eds., From Rodinia to Pangea: The Lithotectonic Record of the Appalachian Region: Geological Society of America Memoir 206, p. 51-69.
- Hibbard, J.P., Stoddard, E. F., Secor, D. T., and Dennis, A. J., 2002, The Carolina Zone: overview of Neoproterozoic to early Proterozoic peri-Gondwanan Terranes along the eastern flank of the southern Appalachians; *Earth Science reviews* vol. 57, pp. 299-339.
- Hibbard, J. P., Pollock, J., and Bradley, P., 2013, One Arc, Two Arcs, Old Arc, New Arc: An Overview of the Carolina Terrane in Central North Carolina, *in* Hibbard, J., and Pollock, J., eds., One Arc, Two Arcs, Old Arc, New Arc the Carolina Terrane in Central North Carolina, Carolina Geological Society Annual Meeting
- Intermediate List of Vascular Plant Species Noted During Surveys of the Haile Gold Mine Properties May 2008 to August 2010, Ecological Services and Consulting, September 2010.
- Jory, J., 2019, Haile legacy 1975-1994 drillhole data validation 2019, OGC internal report, 11 p.
- Jory, J., 2020, Haile 2020 density data evaluation, OGC internal report, 7 p.
- Larson, A., and Worthington, J., 1989, Geophysical mapping at the Haile mine: report for Piedmont Mining Company, January 1989, 22p.
- Lawrence, R.W., Poling, G.W. and Marchant, P.B., (1989). Investigation of predictive techniques for acid mine drainage. Report on DSS Contract No. 23440-7-9178/01-SQ, Energy Mines and Resources, Canada, MEND Report 1.16.1(a).M3 (2014). Haile Gold Mine Project: NI 43-101 Technical Report Project Update.
- M3, 2015. Haile Gold Mine Project, NI 43-101 Technical Report Project Update, Lancaster County, South Carolina. October 13, 2015.
- Maddry, J.W., and Kilbey, T.R., 1995, Geology of the Haile gold mine, selected mineral deposits of the Gulf Coast and southeastern United States: Part II. Gold deposits of the Carolina slate belt: Society of Economic Geologists Guidebook Series, v. 24, p. 147–172.
- Maher, H.; Sacks, P.E.; Secor, Donald T. (1991). "The eastern Piedmont in South Carolina". *Geology of the Carolinas: Carolina Geological Society 50th Anniversary*. University of Tennessee.
- Mathews, K.E., Hoek, E., Wyllie, D.C. and Stewart, S.B.V. (1981). Prediction of stable excavations for mining at depth below 1,000 m in hard rock. CANMET Report DSS Serial No. OSQ80-00081, DSS File No. 17SQ.23440-0-9020. Ottawa: Dept. Energy, Mines and Resources.
- McCauley, C. K., and Butler, J. B., 1966, Gold resources of South Carolina, Bulletin 32, State Development Board, South Carolina, 76 p.
- Memorandum on the Report on Survey for mollusks on Camp Branch of the Little Lynches River, Lancaster County, South Carolina, Eugene P. Keferl, September 2010.
- Metso Minerals Industries, Inc., (Metso), York, Pennsylvania, December 7, 2009, Test Plant Report No. 20000134-135.
- Mine Water Treatment Plant Preliminary Design Report, Schlumberger Water Services, December 2010.
- Mobley, R.M., Yogodzinski, G.M., Creaser, R.A., and Berry, J.M., 2014, Geologic History and Timing of Mineralization at the Haile Gold Mine, South Carolina: *Economic Geology*, v. 109, p. 1863-1881.

- Moye, R., 2012, Evidence of synkinematic magmatism and mineralization in the Neoproterozoic sediment-hosted Kennecott Ridgeway Au-Ag-Mo deposit, South Carolina, Geological Society of America *Abstracts with Programs*. Vol. 44, No. 7, p.198
- Newton, Edmund; Gregg, D.B.; Mosier, McHenry. (1940). "Operations at the Haile gold mine, Kershaw, SC" Information Circular: Volume 7111, U.S Department of the interior: Bureau of Mines.
- Nystrom, P. G., Jr., Willoughby, R. H., and Price, L. K., 1991, Cretaceous and Tertiary stratigraphy of the upper Coastal Plain, South Carolina: *in* Horton, J. W., Jr., and Zullo, V. A. eds., *The Geology of the Carolinas*: Knoxville, Tennessee, The University of Tennessee Press, p. 221-240
- OceanaGold, 2020, OceanaGold provides annual resource and reserve statement update; OceanaGold website, March 28, 2021
- OceanaGold, 2020b, Horseshoe Underground Numerical Stress Modeling, Unassigned document ID, May 14, 2020
- OceanaGold, 2020c, Horseshoe Underground Portals Ground Support, Unassigned document ID, May 20, 2020
- OceanaGold, 2020d, Horseshoe Underground Portals Batter Ground Support, Unassigned document ID, May 20, 2020
- Pardee, J.T.; Park Jr., C.T. (1948) Gold deposits of the southern Piedmont: USGS Professional Paper 213.
- Potvin Y. & J. Hadjigeorgiou (2001). The Stability Graph Method for Open Stope Design. Chapter 60 in *Underground Mining Methods*. Hustrulid & Bullock Eds. Society of Mining Engineers, pp. 513-520
- Price, (2009). Prediction Manual for Drainage Chemistry from Sulfidic Geologic Materials.
- Price, W.A. (2009). Prediction Manual for Drainage Chemistry from Sulfidic Geologic Materials. Price, W.A. (1997). Guidelines and Recommended Methods for the Prediction of Metal Leaching and Acid Rock Drainage at Mine sites in British Columbia—DRAFT. British Columbia Ministry of Employment and Investment. Smithers, BC. April 1997.
- Price, W.A., (1997). Guidelines and Recommended Methods for the Prediction of Metal Leaching and Acid Rock Drainage at Mine sites in British Columbia—DRAFT. British Columbia Ministry of Employment and Investment. Smithers, BC. April 1997.
- Reclamation Plan Overview, HGM, December 2010.
- Record of Decision, Haile Gold Mine Project, October 27, 2014
- Robert, F., Brommecker, R., Bourne, B., Dobak, P., McEwan, C., Rowe, R., and Zhou, X., 2007, Models and exploration methods for major gold deposit types, *Ore deposits and exploration technology: in Proceedings of Fifth decennial international conference on mineral exploration*, ed. B. Milkereit, p. 691-711
- Romarco Minerals, 2010, Press Release - Romarco Announces In-Shell Resource Estimate, November 7, 2010, http://www.romarco.com/news/2010/index.php?&content_id=332
- Romarco Minerals, Inc. Flash Flotation, Cyanide Destruction & Leaching of Concentrate and Tailing for Haile Composites, Resource Development Inc., (RDi), Wheat Ridge, Colorado, May 27, 2010.

- Romarco Minerals, Inc. Haile Gold Project, Metallurgical Report, Resource Development Inc., (RD), Wheat Ridge, Colorado, September 16, 2009.
- Romarco Minerals, Inc. Metallurgical Testing of Ledbetter Extension Samples, Resource Development Inc., (RD), Wheat Ridge, Colorado, March 31, 2010.
- Romarco Minerals, Inc. Optimization of Leaching of Flotation Concentrate, Resource Development Inc., (RD), Wheat Ridge, Colorado, September 27, 2010.
- Romarco Minerals, Inc. Work Index Data for Haile Composite Sample, Resource Development Inc., (RD), Wheat Ridge, Colorado, March 31, 2010.
- Schafer Limited LLC (2015). Revised Haile Gold Mine Overburden Management Plan. September 2015. 25 pp.
- Schafer Limited LLC, (2015). Revised Haile Gold Mine Overburden Management Plan
- Schafer Limited LLC. (2010a). Haile Gold Mine Baseline Geochemistry Report. October 2008, Revised November 2010. 78 pp.
- Schafer Limited LLC. (2010b). Haile Gold Mine, Addendum to Baseline Geochemistry Report. November 2010. 63 pp.
- Schafer Limited LLC. (2012). Haile Gold Mine, Second Addendum to Baseline Geochemistry Report. March 2012. 60 pp.
- Schafer Limited LLC. (2013). Haile Gold Mine, Third Addendum to Baseline Geochemistry Report. January 2013. 69 pp.
- Scheetz, J.W., Stonehouse, J. M., and Zwaschka, M. R., 1991, Geology of the Brewer Gold Mine in South Carolina: Mining Engineering, pp. 38-42
- Search for Federal Threatened and Endangered Species and State Species of Concern on the Duckwood Tract, Needham Environmental Inc., October 2010.
- Secor, Donald T. Jr., and Snoke, Arthur W., 1986: Character of the Alleghanian orogeny in the Southern Appalachians: Part II. Geochronological constraints on the tectonothermal evolution of the eastern Piedmont in South Carolina: GSA Bulletin, Volume 97, Number 11.
- Secor, D.T., and Snoke, A.W., 1978, Stratigraphy, structure, and plutonism in the Central South Carolina Piedmont: in Snoke, A.W., ed., Geological Investigations of the Eastern Piedmont, Southern Appalachians: Carolina Geological Society Guidebook for 1978 Annual Meeting, p. 43–63.
- Secor, D. T., Jr., and Wagener, H. D., 1968, Stratigraphy, structure and petrology of the Piedmont in Central South Carolina: Columbia, South Carolina: South Carolina Geological Survey, Geologic Notes, v. 12, p. 67-84.
- Secor, D. T., Samson, S. L., Snoke, A. W., and Palmer, A. R., 1983, Confirmation of the Carolina Slate Belt as an Exotic Terrane: Science, v. 221, p. 649-651.
- Sobek, A., Schuller, Freeman, W.J. and Smith, R. (1978). Field and Laboratory Methods Applicable to Overburdens and Minesoil, West Virginia Univ., Morgantown College of Agriculture and Forestry. EPA report no. EPA-600/2-78-054 p.47-50. O’Kane Consultants, 2015. Project Queenstown: AMD Review and Waste Block Modeling. March 9, 2015. 41 pps.

- Speer, W. E., and Maddry, J. W., 1993, Geology and recent discoveries at the Haile gold mine, Lancaster County, South Carolina: *South Carolina Geology*, v. 35, p. 9-26.
- Spence, W. H., Maddry, J. W., Worthington, J. E., Jones, E. M., and Kiff, I. T., 1980, Origin of the gold mineralization at the Haile gold mine, Lancaster County, South Carolina: *Mining Engineering*, v. 32, p. 70-73.
- SRK Consulting (2016a). NI 43-101 Technical Report: Preliminary Economic Assessment, Haile Gold Mine, Lancaster County, South Carolina. September 8, 2016, 126 pp.
- SRK Consulting (2016b). Sample Selection and Analysis for Geochemical Testing, Haile Underground Scoping Study.
- SRK Consulting (2017). Geochemical Summary Report, Feasibility Study, Haile Gold Mine, Lancaster County, South Carolina. Report prepared for OceanaGold Corporation. June 2, 2017, 68 pp.
- Stein, H. J., Markley, R. J., Morgan, J. W., Hannah, J. L., Zak, K., and Sundblad, K., 1997, Re-Os dating of shear-hosted Au deposits using molybdenite: *in* Papunen, H., ed., *Mineral Deposits, Research and Explorations: Where Do They Meet? Proceedings of the Fourth Biennial SGA Meeting*, Turku, Finland, 11-13 August 1997, p. 313-317.
- Tailing and Process Water Management Bankable Feasibility Study, AMEC Earth and Environmental, November 19, 2010.
- Tomkinson, M. J., 1988, Gold mineralization in phyllonites at the Haile Mine, South Carolina: *Economic Geology*, v. 83, p. 1392-1400.
- Vandergriff, J., 2016, KML bias investigation memo: OceanaGold report, Oct. 11, 2016, 4p.
- Weis, T., 2016, Extended Haile geophysical interpretation: report for OceanaGold, December 2016, 143 p.
- Whitney, J.A., Paris, T.A., Carpenter, R.H., and Hartley, M.F., 1978: Volcanic evolution of the southern slate belt of Georgia and South Carolina - a primitive oceanic arc, *Journal of Geology*, vol. 86, p137-192.
- Worthington, J. E., 1993, The Carolina slate belt and its gold deposits: Reflections after a quarter century, *South Carolina: Geology*, v. 35, p. 1-8.
- Worthington, J. E., and Kiff, I.T., 1970, A suggested volcanogenic origin for certain gold deposits in the slate belt of the Carolina piedmont: *Economic Geology*, v. 65, p. 529-537.

28 Glossary

The Mineral Resources and Mineral Reserves have been classified according to CIM (CIM, 2014). Accordingly, the Resources have been classified as Measured, Indicated or Inferred, the Reserves have been classified as Proven, and Probable based on the Measured and Indicated Resources as defined below.

28.1 Mineral Resources

A **Mineral Resource** is a concentration or occurrence of solid material of economic interest in or on the Earth's crust in such form, grade or quality and quantity that there are reasonable prospects for eventual economic extraction. The location, quantity, grade or quality, continuity and other geological characteristics of a Mineral Resource are known, estimated or interpreted from specific geological evidence and knowledge, including sampling.

An **Inferred Mineral Resource** is that part of a Mineral Resource for which quantity and grade or quality are estimated on the basis of limited geological evidence and sampling. Geological evidence is sufficient to imply but not verify geological and grade or quality continuity. An Inferred Mineral Resource has a lower level of confidence than that applying to an Indicated Mineral Resource and must not be converted to a Mineral Reserve. It is reasonably expected that the majority of Inferred Mineral Resources could be upgraded to Indicated Mineral Resources with continued exploration.

An **Indicated Mineral Resource** is that part of a Mineral Resource for which quantity, grade or quality, densities, shape and physical characteristics are estimated with sufficient confidence to allow the application of Modifying Factors in sufficient detail to support mine planning and evaluation of the economic viability of the deposit. Geological evidence is derived from adequately detailed and reliable exploration, sampling and testing and is sufficient to assume geological and grade or quality continuity between points of observation. An Indicated Mineral Resource has a lower level of confidence than that applying to a Measured Mineral Resource and may only be converted to a Probable Mineral Reserve.

A **Measured Mineral Resource** is that part of a Mineral Resource for which quantity, grade or quality, densities, shape, and physical characteristics are estimated with confidence sufficient to allow the application of Modifying Factors to support detailed mine planning and final evaluation of the economic viability of the deposit. Geological evidence is derived from detailed and reliable exploration, sampling and testing and is sufficient to confirm geological and grade or quality continuity between points of observation. A Measured Mineral Resource has a higher level of confidence than that applying to either an Indicated Mineral Resource or an Inferred Mineral Resource. It may be converted to a Proven Mineral Reserve or to a Probable Mineral Reserve.

28.2 Mineral Reserves

A **Mineral Reserve** is the economically mineable part of a Measured and/or Indicated Mineral Resource. It includes diluting materials and allowances for losses, which may occur when the material is mined or extracted and is defined by studies at Pre-Feasibility or Feasibility level as appropriate that include application of Modifying Factors. Such studies demonstrate that, at the time of reporting, extraction could reasonably be justified.

The reference point at which Mineral Reserves are defined, usually the point where the ore is delivered to the processing plant, must be stated. It is important that, in all situations where the reference point is different, such as for a saleable product, a clarifying statement is included to ensure that the reader is fully informed as to what is being reported. The public disclosure of a Mineral Reserve must be demonstrated by a Pre-Feasibility Study or Feasibility Study.

A **Probable Mineral Reserve** is the economically mineable part of an Indicated Mineral Resource, and in some circumstances, a Measured Mineral Resource. The confidence in the Modifying Factors applying to a Probable Mineral Reserve is lower than that applying to a Proven Mineral Reserve.

A **Proven Mineral Reserve** is the economically mineable part of a Measured Mineral Resource. A Proven Mineral Reserve implies a high degree of confidence in the Modifying Factors.

28.3 Definition of Terms

The following general mining terms may be used in this report.

Table 28-1: Definition of Terms

Term	Definition
Assay	The chemical analysis of mineral samples to determine the metal content.
Capital Expenditure	All other expenditures not classified as operating costs.
Composite	Combining more than one sample result to give an average result over a larger distance.
Concentrate	A metal-rich product resulting from a mineral enrichment process such as gravity concentration or flotation, in which most of the desired mineral has been separated from the waste material in the ore.
Crushing	Initial process of reducing ore particle size to render it more amenable for further processing.
Cut-off Grade (CoG)	The grade of mineralized rock, which determines as to whether or not it is economic to recover its gold content by further concentration.
Dilution	Waste, which is unavoidably mined with ore.
Dip	Angle of inclination of a geological feature/rock from the horizontal.
Fault	The surface of a fracture along which movement has occurred.
Footwall	The underlying side of an orebody or stope.
Gangue	Non-valuable components of the ore.
Grade	The measure of concentration of gold within mineralized rock.
Hangingwall	The overlying side of an orebody or slope.
Haulage	A horizontal underground excavation which is used to transport mined ore.
Hydrocyclone	A process whereby material is graded according to size by exploiting centrifugal forces of particulate materials.
Igneous	Primary crystalline rock formed by the solidification of magma.
Kriging	An interpolation method of assigning values from samples to blocks that minimizes the estimation error.
Level	Horizontal tunnel the primary purpose is the transportation of personnel and materials.
Lithological	Geological description pertaining to different rock types.
LoM Plans	Life-of-Mine plans.
LRP	Long Range Plan.
Material Properties	Mine properties.
Milling	A general term used to describe the process in which the ore is crushed and ground and subjected to physical or chemical treatment to extract the valuable metals to a concentrate or finished product.
Mineral/Mining Lease	A lease area for which mineral rights are held.
Mining Assets	The Material Properties and Significant Exploration Properties.
Ongoing Capital	Capital estimates of a routine nature, which is necessary for sustaining operations.
Ore Reserve	See Mineral Reserve.

Term	Definition
Pillar	Rock left behind to help support the excavations in an underground mine.
RoM	Run-of-Mine.
Sedimentary	Pertaining to rocks formed by the accumulation of sediments, formed by the erosion of other rocks.
Shaft	An opening cut downwards from the surface for transporting personnel, equipment, supplies, ore and waste.
Sill	A thin, tabular, horizontal to sub-horizontal body of igneous rock formed by the injection of magma into planar zones of weakness.
Smelting	A high temperature pyrometallurgical operation conducted in a furnace, in which the valuable metal is collected to a molten matte or doré phase and separated from the gangue components that accumulate in a less dense molten slag phase.
Stope	Underground void created by mining.
Stratigraphy	The study of stratified rocks in terms of time and space.
Strike	Direction of line formed by the intersection of strata surfaces with the horizontal plane, always perpendicular to the dip direction.
Sulfide	A sulfur bearing mineral.
Tailings	Finely ground waste rock from which valuable minerals or metals have been extracted.
Thickening	The process of concentrating solid particles in suspension.
Total Expenditure	All expenditures including those of an operating and capital nature.
Variogram	A statistical representation of the characteristics (usually grade).

28.4 Abbreviations

The following abbreviations may be used in this report.

Table 28-2: Abbreviations

Abbreviation	Unit or Term
%	percent
~	approximately
°	degree
°C	temperature in degrees Celsius
°F	temperature in degrees Fahrenheit
2D	two-dimensional
3D	three-dimensional
AA	atomic absorption
AHK	AHK Geochem
AISC	All-In Sustaining Cost
ALS	ALS Limited
AP	acid generating potential
Ar	argon
ARD	acid rock drainage
ASTM	American Society for Testing and Materials
Au	gold
bhp	brake horsepower
BLM	United States Department of the Interior Bureau of Land Management
BM	Bond ball mill
Breccia	brecciated rocks
CaCO ₃	Calcium carbonate
Cat	Caterpillar
cfm	cubic feet per minute
CIL	Carbon-In-Leach
CIT	Corporate Income Tax
cm ³	cubic centimeter
CoG	cut-off grade
CPLEX	IBM ILOG CPLEX Optimizer

Abbreviation	Unit or Term
CPS	coastal plain sands
CRF	cemented rock fill
CRM	Certified Reference Materials
CV	coefficient of variation
Cyprus	Cyprus Exploration Company
DB	intrusive dikes
DDH	diamond drilling
DHEC	Department of Health and Environmental Control
DSS	direct shear strength
EIS	Environmental Impact Statement
ELOS	equivalent linear overbreak/slough
EPCM	Engineering, Procurement and Construction Management
Excel	Microsoft
FA	fire assay
FDD	Fresh dikes
FF	Fracture frequency
FF/m	frequency fracture per meter
Fill	back-fill from historical mining
FMS	Fresh metasediment
FMV	Fresh metavolcanic
FoS	factor of safety
FS	feasibility study
ft	foot (feet)
g	gram
g/t	grams per tonne
g/t	grams per tonne
geology data	GL
GPa	gigapascal
gpm	gallons per minute
ha	hectares
Haile	Haile Gold Mine
HDPE	height density polyethylene
HGM	Haile Gold Mine, Inc.
HMC	Haile Mining Company
HMV	
hp	horsepower
hr	hour
ICP-MS	inductively coupled plasma mass spectrometry
IDW ²	Inverse Distance Weighting Squared
IMC	Independent Mining Consultants
in	inch
IP	Induced polarization
IRR	initial rate of return
IRS	intact rock strength
ISO/IEC	International Electrotechnical Commission
ISO-9001	International Organization for Standardization
ISRM	International Society of Rock Mechanics
Ja	joint alteration
Jn	joint number
JPAG	Johnny's PAG
Jr	joint roughness
kg	kilogram
km	kilometer
KML	Kershaw Mineral Lab
KML	Kershaw Mineral Lab
kN	kilonewton
kN/m ³	kilonewton per cubic meter
koz	thousand troy ounce
KS	Kolmogorov-Smirnoff

Abbreviation	Unit or Term
kt	thousand tonnes
kV	kilovolt
kW	kilowatt
L	liter
lb	pound
Leapfrog	ARANZ Leapfrog® Geo software
LECO	LECO Corporation
LHD	long-haul-dump
LoM	life-of-mine
m	meter
m/d	meter per day
m ³	cubic meter
Ma	mega-annum
MI	laminated metasediments
MIBC	methyl isobutyl carbinol
min	minute
ML	metal leaching
mm	millimeter
MOA	Memorandum of Agreement
MPa	megapascal
MS	metasediments
Ms	silicified metasediments
Mst	million short tons
Mtpa	million tonnes per annum
MV	metavolcanics
MW	million watts
N'	stability number
N	north
NGO	non-governmental organization
NI 43-101	Canadian National Instrument 43-101
NN	nearest neighbor
NNP	net neutralization potential
NOL	Net Operating Losses
NP	acid neutralization potential
NPDES	National Pollutant Discharge Elimination System
NPR	neutralization potential ratio
NPV	net present value
OC	oriented core data
OceanaGold	OceanaGold Corporation
OK	Ordinary Kriging
OMP	Overburden Management Plan
OP	open pit
OSA	overburden storage area
oz	ounce
PAG	potential acid generating
PAX	potassium amyl xanthate
PEA	preliminary economic assessment
Piedmont	Piedmont Mining Company
PLT	point load test
PMP	Probable Maximum Precipitation
Project	Haile Gold Mine
POF	probability of failure
ppb	parts per billion
ppm	parts per million
QA	Quality Assurance
QC	Quality Control
QP	Qualified Persons
QSP	quartz-sericite-pyrite
RC	reverse circulation

Abbreviation	Unit or Term
rd	rounds
RDl	Resource Development Inc.
RM	rock mass
RMI	Romarco Minerals, Inc.
RMR	Rock Mass Rating
RoM	run-of-mine
RQD	rock quality designation
S	Sulfur
SAG	Semi-Autogenous Grinding
SAP	sampling and analysis plan
SAP	Saprolite
SCDHEC	South Carolina Department of Health and Environmental Control
sec	second
SMC	Sag Mill Comminution
SMU	selective mining unit
SO ₂	Sulfur dioxide
SRF	stress reduction factor
SRK	SRK Consulting (U.S.), Inc.
st	short ton (2,000 pounds)
S _T	total sulfur
st/d	short tons per day
STD	standard deviation
t/d	metric tonnes per day
TCC	total cash costs
TCR	total core recovery
TCS	triaxial compressive strength
TIC	total inorganic carbon
TSF	tailings storage facility
TV	televIEWer data
UCS	uniaxial compressive strength
UG	underground
U-Pb	Uranium–lead
US\$	United States Dollar
USA	United States of America
USFS	United States Forest Service
V	volts
VFD	variable frequency drive
W	watt
W:O	waste: ore
WAD	weak acid dissociable
WDD	weathered dikes
Wi	work indices
WMS	Weathered metasediment
WMV	weathered metavolcanic
y	year
µm	microns

Appendices

Appendix A: Certificates of Qualified Persons

CERTIFICATE OF QUALIFIED PERSON

I, Jay Newton Janney-Moore, PE do hereby certify that:

1. I am employed as an engineer at NewFields Mining & Technical Services LLC NewFields, 9400 Station Street, Suite 300, Lone Tree, Colorado 80124, USA.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report Feasibility Study Haile Gold Mine Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in Bachelor of Science in Civil Engineering from University of Colorado Denver in 1998. I am a registered professional engineer in the State of South Carolina (No. 28306) and in the State of Colorado (No. 37571). I have worked as an engineer a total of 22 years since my graduation from university. My relevant includes designing heap leach pads, tailings storage facilities, surface water diversions, and other supporting infrastructure.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I visited the Haile Gold Mine property on 24th of September 2019 for 3 days.
6. I am responsible for tailing and overburden storage, Sections 18.1, 18.2, 18.3, 18.4, 18.5, 18.10, the Tailings/Overburden section of 21 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is the engineer of record for the Potentially Acid Overburden Storage Areas and Contact Water Ponds, Fresh Water Storage Dam, and Duckwood Tailings Storage Facility.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September 2020.



Jay Newton Janney-Moore

CERTIFICATE OF QUALIFIED PERSON

I, William Lucas Kingston (MSc, PG) do hereby certify that:

1. I am an Associate Hydrogeologist of NewFields Mining & Technical Services LLC ("NewFields"), 9400 Station Street, Suite 300, Lone Tree, Colorado 80124, USA.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date June 30, 2020 (the "Technical Report").
3. I graduated with a degree in Geology from Tulane University in 1984. In addition, I have obtained a Master of Science degree in Hydrogeology and Hydrology from the University of Nevada – Reno in 1989. I am a professional geologist in the State of South Carolina (No. 2666), in the State of Wyoming (No. 3645), and in the State of California (No. 8679). I have worked as a Hydrogeologist for a total of 30 years since my graduation from university. My relevant experience includes water supply, pit dewatering, and mine water management studies that often include elements of data collection, development of conceptual groundwater flow models, and numerical predictive models.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I visited the Haile Gold Mine property on December 4, 2019 for two days.
6. I am responsible for hydrogeology Sections 16.1.9, 16.2.3, the hydrogeological portion of section of 16.1.2, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is managing prior pit dewatering design and preparation of quarterly groundwater and surface water monitoring reports.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September 2020.



William Lucas Kingston, MSc, PG.



CERTIFICATE OF QUALIFIED PERSON

I, David Read Carr, MAusIMM CP (Met) do hereby certify that:

1. I am Chief Metallurgist of OceanaGold Corporation, 99 Melbourne Street, South Brisbane, Australia.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in Bachelor of Engineering in Metallurgical Engineering (Hons) from the University of South Australia in 1993. I am a Member and Chartered Professional of the Australasian Institute of Mining and Metallurgy. I have worked as a metallurgist for a total of 27 years since my graduation from university. My relevant experience includes base metal flotation, flotation and leaching of gold ores, pressure oxidation of refractory sulphide ores, ultrafine grinding, process plant design, project evaluation and plant commissioning.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I visited the Haile property in 2017, 2018, 2019 and on March 8th 2020 for 17 days.
6. I am responsible for mineral processing, all of Sections 13 and 17, the process plant costs of section 21, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am not independent of the issuer applying all of the tests in section 1.5 of NI 43-101 because I am an employee of OceanaGold Management Pty Limited.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is the preparation of the "NI 43-101 Technical Report Haile Gold Mine Lancaster County, South Carolina" dated August 9, 2017 and in my role as Chief Metallurgist for OceanaGold with involvement in the site commissioning and development since acquisition in 2015.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

A handwritten signature in blue ink, appearing to read "David Read Carr", positioned above a horizontal line.

David Read Carr, MAusIMM CP (Met)



CERTIFICATE OF QUALIFIED PERSON

I, Jonathan Moore, BSc Geology (Hons), MAusIMM(CP) do hereby certify that:

1. I am Chief Geologist of OceanaGold Corporation, Level 3, 99 Melbourne St, South Brisbane Qld 4101, Australia.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in BSc (Hons) Geology from University of Otago in 1985. In addition, I have obtained a Graduate Diploma in Physics from the University of Otago in 1993. I am a member and Chartered Professional of the AusIMM. I have worked as a Geologist for a total of 31 years since my graduation from university; in open pit and underground resource estimation throughout Australia, New Zealand, Philippines, South America and the USA. Commodities include gold, silver, tungsten, lead and zinc.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I visited the Haile property on January 13th for 16 days.
6. I am responsible for open pit and underground Mineral Resources, Section 14 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. Being an OceanaGold employee, I am not independent of the issuer applying all of the tests in section 1.5 of NI 43-101
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement has been ongoing assistance as Chief Geologist with the project since OceanaGold acquired the Haile Gold Mine in 2015.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

Jonathan Moore, BSc Geology (Hons), MAusIMM(CP)



CERTIFICATE OF QUALIFIED PERSON

I, Larry Standridge, PE, MSE, do hereby certify that:

1. I am a Principal Engineer of Call & Nicholas, Inc., 2475 North Coyote Drive, Tucson, AZ, USA, 85750.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a MS in Mining, Geological, and Geotechnical Engineering from The University of Arizona in 2001. In addition, I have obtained a BA in Geology from The University of North Carolina in 1996. I am a registered Professional Engineer (Geological) in the State of Arizona (No. 64435). I have worked as an engineer for a total of 19 years since my graduation from university. My relevant experience includes 15 years of pit slope and waste dump design, prefeasibility and feasibility studies, field mapping, 3D modeling, stability analyses, debris flow analyses, and numerous other geotechnical activities in support of the mining industry.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I visited the Haile Gold Mine property on November 29th, 2017 for 2 days, on October 10th, 2018 for 2 days, and on January 14th, 2020 for 3 days.
6. I am responsible for open pit geotechnical work, co-authoring Section 16.1.2 and portions of Sections 1, 25 and 26 of the Technical Report.
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is providing slope design recommendations for the open pits and waste dumps, develop mitigation options for several geotechnical hazards, and assisting with geotechnical data collection.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.


Larry Standridge, PE




CERTIFICATE OF QUALIFIED PERSON

I, Michael Kirby, PE, MEng Civil do hereby certify that:

1. I am Environmental Superintendent of OceanaGold Corporation, 6911 Snowy Owl Road, Kershaw, SC 29067.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a Masters degree in Civil Engineering from the University of Louisville in 1998. In addition, I have obtained a Professional Engineering license in Kentucky, Alabama, Georgia, North Carolina and South Carolina. I am a member of the Society for Mining, Metallurgy & Exploration. I have worked as an Engineer for a total of 25 years since my graduation from university. My relevant experience includes 20 years as an engineering consultant and 5 years of mining.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I am based at the Haile property.
6. I am responsible for Environmental and Permitting, Section 20 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am not independent of the issuer applying all of the tests in section 1.5 of NI 43-101. I am an employee of OceanaGold.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is that I have been working at this site for 5 years as an employee of OceanaGold.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

Michael Kirby, PE, MEng Civil

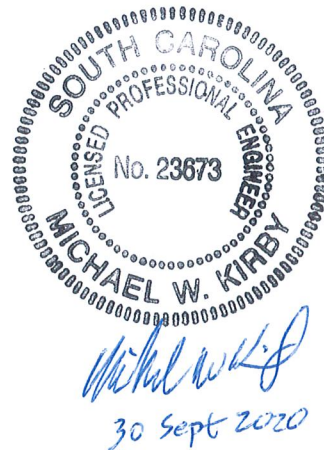




CERTIFICATE OF QUALIFIED PERSON

I, John Jory, MSc, BSc, CPG, AIPG do hereby certify that:

1. I am Director of Exploration of Haile Gold Mine of OceanaGold, 6911 Snowy Owl Road, Kershaw, SC29067, USA
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in Geology from the University of Southampton in 1982. In addition, I have obtained a Masters degree in Mineral Exploration in 1983 from the Royal School of Mines, London, UK. I am a Certified Professional Geologist of the American Institute of Professional Geologists. I have worked as a Geologist for a total of 33 years since my graduation from university. My relevant experience includes 33 years in Mineral Exploration, resource development, open pit production in gold, silver and copper
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I am based at the Haile Property.
6. I am responsible for all of Sections 4, 5, 6, 7, 8, 9, 10, 11, 12, 16.1.5, 23, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am independent of the issuer applying for all of the tests in section 1.5 of NI 43-101.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is qualified person for the geology, drilling and sampling sections (see part 6 above) of the Haile 2017 NI 43-101 technical report.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.



John Jory, MSc, BSc, CPG, AIPG

CERTIFICATE OF QUALIFIED PERSON

I, David Bird, MSc., PG, RM-SME, do hereby certify that:

1. I am an Associate Principal Consultant (Geochemistry) of SRK Consulting (U.S.), Inc., 1125 Seventeenth Street, Suite 600, Denver, CO, USA, 80202.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30th 2020 (the "Technical Report").
3. I graduated with Bachelor's Degrees in Geology and Business Administration Management from Oregon State University in 1983. In addition, I obtained a Master's Degree in Geochemistry/Hydrogeology from the University of Nevada-Reno in 1993. I am a Registered Member of the Society for Mining, Metallurgy, and Exploration (SME). I am a certified Professional Geologist in the State of Oregon (G1438). I have worked full time as a Geologist and Geochemist for a total of 34 years. My relevant experience includes design, execution, and interpretation of mine waste geochemical characterization programs in support of open pit and underground mine planning and environmental impact assessments, design and supervision of water quality sampling and monitoring programs, geochemical modeling, and management of the geochemistry portion of numerous PEA, PFS and FS-level mine projects in the US and abroad.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I have not visited the Haile property.
6. I am responsible for underground geochemistry, Section 16.2.4, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is serving as QP on report titled "NI 43-101 Technical Report, Feasibility Study, Haile Gold Mine, Lancaster County, South Carolina" dated August 9, 2017.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

"Signed"

"Sealed"

David Bird, MSc., PG, RM-SME [4186987RM]

U.S. Offices:

Anchorage	907.677.3520
Clovis	559.452.0182
Denver	303.985.1333
Elko	775.753.4151
Fort Collins	970.407.8302
Reno	775.828.6800
Tucson	520.544.3688

Canadian Offices:

Saskatoon	306.955.4778
Sudbury	705.682.3270
Toronto	416.601.1445
Vancouver	604.681.4196
Yellowknife	867.873.8670

Group Offices:

Africa
Asia
Australia
Europe
North America
South America

CERTIFICATE OF QUALIFIED PERSON

I, Joanna Poeck, BEng Mining, SME-RM, MMSAQP, do hereby certify that:

1. I am a Principal Mining Engineer of SRK Consulting (U.S.), Inc., 1125 Seventeenth Street, Suite 600, Denver, CO, USA, 80202.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in Mining Engineering from Colorado School of Mines in 2003. I am a Registered Member of the Society of Mining, Metallurgy & Exploration Geology. I am a QP member of the Mining & Metallurgical Society of America. I have worked as a Mining Engineer for a total of 15 years since my graduation from university. My relevant experience includes open pit and underground design, mine scheduling, pit optimization and truck productivity analysis.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I visited the Haile property on February 6, 2017 for 2 days and March 12, 2019 for 3 days.
6. I am responsible for underground Mineral Reserves, all of Sections 2, 3, 24, 27, 28, the underground portions of Section 15 and 16.3, Section 16 opening statements, Sections 16.2, 16.2.1, 16.2.5, 16.2.6, 16.2.7, 16.2.8, 16.2.9, 16.2.11, 18.6, 18.7, 18.8, 18.9 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is serving as QP on report titled "NI 43-101 Technical Report Haile Gold Mine Lancaster County, South Carolina" and dated August 9, 2017.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

"Signed"

"Sealed"

Joanna Poeck, BEng Mining, SME-RM[4131289RM], MMSAQP[01387QP]
Principal Consultant (Mining Engineer)

U.S. Offices:

Anchorage	907.677.3520
Clovis	559.452.0182
Denver	303.985.1333
Elko	775.753.4151
Fort Collins	970.407.8302
Reno	775.828.6800
Tucson	520.544.3688

Canadian Offices:

Saskatoon	306.955.4778
Sudbury	705.682.3270
Toronto	416.601.1445
Vancouver	604.681.4196
Yellowknife	867.873.8670

Group Offices:

Africa
Asia
Australia
Europe
North America
South America

CERTIFICATE OF QUALIFIED PERSON

I, Brian Prosser, PE do hereby certify that:

1. I am Principal Consultant of SRK Consulting (U.S.), Inc., 1125 Seventeenth Street, Suite 600, Denver, CO, USA, 80202.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in Mining Engineering from Virginia Polytechnic Institute and State University in 1994. I am a licensed engineer in the states of Virginia, West Virginia, Kentucky, and Nevada. I am a Registered Member of the Society for Mining, Metallurgy, and Exploration and a member of the Mine Ventilation Society of South Africa. I have worked as a mining engineer for a total of 25 years since my graduation from university. My relevant experience includes the development of ventilation systems, network modeling, system troubleshooting, and design evaluation.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I have not visited the Haile property.
6. I am responsible for ventilation, Section 16.2.10 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is serving as QP on report titled "NI 43-101 Technical Report, Feasibility Study, Haile Gold Mine, Lancaster County, South Carolina" and dated August 9th, 2017.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

"Signed"

Brian Prosser

"Sealed"

U.S. Offices:

Anchorage	907.677.3520
Clovis	559.452.0182
Denver	303.985.1333
Elko	775.753.4151
Fort Collins	970.407.8302
Reno	775.828.6800
Tucson	520.544.3688

Canadian Offices:

Saskatoon	306.955.4778
Sudbury	705.682.3270
Toronto	416.601.1445
Vancouver	604.681.4196
Yellowknife	867.873.8670

Group Offices:

Africa
Asia
Australia
Europe
North America
South America

CERTIFICATE OF QUALIFIED PERSON

I, Fernando Rodrigues, BS Mining, MBA, MMSAQP do hereby certify that:

1. I am Practice Leader and Principal Consultant (Mining Engineer) of SRK Consulting (U.S.), Inc., 1125 Seventeenth Street, Suite 600, Denver, CO, USA, 80202.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a Bachelors of Science degree in Mining Engineering from South Dakota School of Mines and Technology in 1999. I am a QP member of the MMSA. I have worked as a Mining Engineer for a total of 22 years since my graduation from South Dakota School of Mines and Technology in 1999. My relevant experience includes mine design and implementation, short term mine design, dump design, haulage studies, blast design, ore control, grade estimation, database management.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I have not visited the Haile property.
6. I am responsible for open pit Mineral Reserves, the open pit portions of Section 15 and 16.3, Sections 16.1, 16.1.1, 16.1.3, 16.1.4, 16.1.6, and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have not had prior involvement with the property that is the subject of the Technical Report.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

"Signed"

"Sealed"

Fernando Rodrigues, BS Mining, MBA, MMSAQP [01405QP]

U.S. Offices:

Anchorage	907.677.3520
Clovis	559.452.0182
Denver	303.985.1333
Elko	775.753.4151
Fort Collins	970.407.8302
Reno	775.828.6800
Tucson	520.544.3688

Canadian Offices:

Saskatoon	306.955.4778
Sudbury	705.682.3270
Toronto	416.601.1445
Vancouver	604.681.4196
Yellowknife	867.873.8670

Group Offices:

Africa
Asia
Australia
Europe
North America
South America

CERTIFICATE OF QUALIFIED PERSON

I, Matthew Sullivan, B.Sc., RM-SME do hereby certify that:

1. I am a Senior Consultant of SRK Consulting (U.S.), Inc., 1125 Seventeenth Street, Suite 600, Denver, CO, USA, 80202.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in Metallurgical and Materials Engineering from Colorado School of Mines in 2009. In addition, I also obtained a degree in Economics and Business from the Colorado School of Mines in 2009. I am an SME Registered Member. I have worked evaluating mining projects for a total of 9 years since my graduation from university. My relevant experience includes economic evaluation of mining projects supporting mining sector investment and economic analysis supporting mining project studies.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I have not visited the Haile property.
6. I am responsible for technical-economics Section 22 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have not had prior involvement with the property that is the subject of the Technical Report.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

"Signed"

"Sealed"

Matthew Sullivan, BEng, RM-SME

U.S. Offices:

Anchorage	907.677.3520
Clovis	559.452.0182
Denver	303.985.1333
Elko	775.753.4151
Fort Collins	970.407.8302
Reno	775.828.6800
Tucson	520.544.3688

Canadian Offices:

Saskatoon	306.955.4778
Sudbury	705.682.3270
Toronto	416.601.1445
Vancouver	604.681.4196
Yellowknife	867.873.8670

Group Offices:

Africa
Asia
Australia
Europe
North America
South America

CERTIFICATE OF QUALIFIED PERSON

I, John Tinucci, PhD, PE, ISRM, do hereby certify that:

1. I am Practice Leader/Principal Consultant (Geotechnical Engineer) of SRK Consulting (U.S.), Inc., 1125 Seventeenth Street, Suite 600, Denver, CO, USA, 80202.
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in B.S. in Civil Engineering from Colorado State University, in 1980. In addition, I have obtained a M.S. in Geotechnical Engineering from University of California, Berkeley, in 1983 and I have obtained a Ph.D. in Geotechnical Engineering, Rock Mechanics from the University of California, Berkeley in 1985. I am member of the American Rock Mechanics Association, a member of the International Society of Rock Mechanics, and a Professional Member of the Society for Mining, Metallurgy & Exploration. I have worked as a Mining and Geotechnical Engineer for a total of 37 years since my graduation from university. My relevant experience includes 34 years of professional experience. I have 20 years managerial experience leading project teams, managing P&L operations for 120 staff, and directed own company of 8 staff for 8 years. I have technical experience in mine design, prefeasibility studies, feasibility studies, geomechanical assessments, rock mass characterization, project management, numerical analyses, underground mine stability, subsidence, tunneling, ground support, slope design and stabilization, excavation remediation, induced seismicity and dynamic ground motion. My industry commodities experience includes salt, potash, coal, platinum/palladium, iron, molybdenum, gold, silver, zinc, diamonds, and copper. My mine design experience includes open pit, room and pillar, (single and multi-level), conventional drill-and-blast and mechanized cutting, longwall, steep narrow vein, cut and fill, block caving, sublevel caving and cut and fill longhole stoping and paste backfilling.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I visited the Haile property on November 29, 2016 for 3 days.
6. I am responsible for underground geotechnical information, Section 16.2.2 and portions of Sections 1, 25 and 26 summarized therefrom, of this Technical Report.
7. I am independent of the issuer applying all of the tests in section 1.5 of NI 43-101.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement is serving as QP on report titled "NI 43-101 Technical Report, Feasibility Study, Haile Gold Mine, Lancaster County, South Carolina" and dated August 9, 2017.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

U.S. Offices:

Anchorage	907.677.3520
Clovis	559.452.0182
Denver	303.985.1333
Elko	775.753.4151
Fort Collins	970.407.8302
Reno	775.828.6800
Tucson	520.544.3688

Canadian Offices:

Saskatoon	306.955.4778
Sudbury	705.682.3270
Toronto	416.601.1445
Vancouver	604.681.4196
Yellowknife	867.873.8670

Group Offices:

Africa
Asia
Australia
Europe
North America
South America

Dated this 30th Day of September, 2020.

"Signed"

John Tinucci, PhD, PE, ISRM

"Sealed"


Tom Cooney

CERTIFICATE OF QUALIFIED PERSON

I, Tom Cooney, BEng (Hons) Mining, MMinMgt, MAusIMM (CP) do hereby certify that:

1. I am General Manager of Project Development and Studies of OceanaGold Corporation, Level 3, 99 Melbourne St South Brisbane Qld 4101 Australia
2. This certificate applies to the technical report titled "NI 43-101 Technical Report, Haile Gold Mine, Lancaster County, South Carolina" with an Effective Date of June 30, 2020 (the "Technical Report").
3. I graduated with a degree in Mining Engineering from The University of Melbourne in 1984. In addition, I have obtained a Masters in Mining Management from the University of New South Wales in 1998. I am a Member and Chartered Professional of the Australasian Institute of Mining and Metallurgy. I have worked as a Mining Engineer for a total of 30 years since my graduation from university. My relevant experience includes operating and technical roles in underground and open pit mining.
4. I have read the definition of "qualified person" set out in National Instrument 43-101 (NI 43-101) and certify that by reason of my education, affiliation with a professional association (as defined in NI 43-101) and past relevant work experience, I fulfill the requirements to be a "qualified person" for the purposes of NI 43-101.
5. I visited the Haile property on November 28, 2018 for 9 days.
6. I am responsible for responsible for the Sections 16.1.1, 16.1.7, 16.1.8, ,19, the open pit, underground, and other costs of section 21 and portions of Sections 1, 25 and 26 summarized therefrom.
7. I am not independent of the issuer applying all of the tests in section 1.5 of NI 43-101 as I am employed by OceanaGold.
8. I have had prior involvement with the property that is the subject of the Technical Report. The nature of my prior involvement has been to undertake and oversee technical studies.
9. I have read NI 43-101 and Form 43-101F1 and the sections of the Technical Report I am responsible for have been prepared in compliance with that instrument and form.
10. As of the aforementioned Effective Date, to the best of my knowledge, information and belief, the sections of the Technical Report I am responsible for contains all scientific and technical information that is required to be disclosed to make the Technical Report not misleading.

Dated this 30th Day of September, 2020.

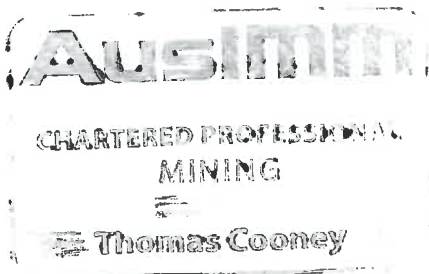

Tom Cooney, BEng (Hons) Mining, MMinMgt, MAusIMM (CP)

Appendix B: LoM Annual Cash Flow Forecast

Technical-Economic Model Summary

Company: OceanaGold																												
YEAR		2020	2021	2022	2023	2024	2025	2026	2027	2028	2029	2030	2031	2032	2033	2034	2035	2036	2037	2038	2039	2040						
Time Before Mine Closure		15	15	14	13	12	11	10	9	8	7	6	5	4	3	2	1	-	-	-	-	-	-	-	-	-	-	-
Production Timeline		1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20	21						
Cumulative Factor	5%	US\$ & Metric Units	1.0000	0.9524	0.9070	0.8638	0.8227	0.7836	0.7462	0.7107	0.6768	0.6446	0.6139	0.5847	0.5568	0.5303	0.5051	0.4810	0.4581	0.4363	0.4155	0.3957	1.0000					
Market Prices																												
Gold	US\$/oz	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	\$1,300	
Silver	US\$/oz	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	\$17.00	
Physicals																												
Total Op Ore Mined	kt	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	48,031	
Total Op Waste Mined	kt	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	407,040	
Total Op Material Mined	kt	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	455,071	
Strip Ratio	wt	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	8.5	
Total LG Ore Mined	kt	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	3,416	
Total Ore Tonnes, Mined	kt	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	51,447	
Total Ore Tonnes, Processed	kt	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	52,785	
Gold Grade, Processed	g/t	1.71	1.84	1.90	1.91	1.92	1.93	1.94	1.95	1.96	1.97	1.98	1.99	2.00	2.01	2.02	2.03	2.04	2.05	2.06	2.07	2.08	2.09	2.10	2.11	2.12	2.13	
Silver Grade, Processed	g/t	2.21	2.31	2.38	2.40	2.41	2.42	2.43	2.44	2.45	2.46	2.47	2.48	2.49	2.50	2.51	2.52	2.53	2.54	2.55	2.56	2.57	2.58	2.59	2.60	2.61	2.62	
Contained Gold, Processed	koz	2,907	3,114	3,246	3,272	3,285	3,296	3,305	3,313	3,320	3,326	3,331	3,336	3,340	3,344	3,347	3,350	3,352	3,354	3,356	3,358	3,360	3,362	3,364	3,366	3,368	3,370	
Contained Silver, Processed	koz	3,346	3,581	3,729	3,751	3,763	3,774	3,784	3,793	3,801	3,808	3,814	3,820	3,825	3,829	3,833	3,836	3,839	3,841	3,843	3,845	3,847	3,849	3,851	3,853	3,855	3,857	
Average Recovery, Gold	%	85.0%	83.6%	82.0%	81.7%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	81.6%	
Average Recovery, Silver	%	81.3%	77.1%	74.7%	74.3%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	74.2%	
Recovered Gold, Dore	koz	2,470	2,612	2,724	2,746	2,758	2,768	2,777	2,785	2,792	2,798	2,803	2,808	2,812	2,815	2,818	2,820	2,822	2,824	2,826	2,828	2,830	2,832	2,834	2,836	2,838	2,840	
Recovered Silver, Dore	koz	3,033	3,205	3,336	3,360	3,373	3,385	3,396	3,406	3,415	3,423	3,430	3,436	3,441	3,445	3,448	3,451	3,453	3,455	3,457	3,459	3,461	3,463	3,465	3,467	3,469	3,471	
Payable Gold, Dore	koz	2,470	2,612	2,724	2,746	2,758	2,768	2,777	2,785	2,792	2,798	2,803	2,808	2,812	2,815	2,818	2,820	2,822	2,824	2,826	2,828	2,830	2,832	2,834	2,836	2,838	2,840	
Payable Silver, Dore	koz	3,032	3,204	3,335	3,359	3,372	3,384	3,395	3,405	3,414	3,422	3,429	3,435	3,440	3,444	3,447	3,450	3,452	3,454	3,456	3,458	3,460	3,462	3,464	3,466	3,468	3,470	
Cash Flow																												
Gross Revenue	\$000s	3,795,121	143,418	306,624	288,481	318,264	492,253	348,177	486,243	338,501	195,586	149,393	231,660	277,623	316,699	358,969	-	-	-	-	-	-	-	-	-	-	-	
OP Mining Cost	\$000s	(627,469)	(24,405)	(87,146)	(28,127)	(87,146)	(28,127)	(87,146)	(28,127)	(87,146)	(28,127)	(87,146)	(28,127)	(87,146)	(28,127)	(87,146)	-	-	-	-	-	-	-	-	-	-	-	
OP Mining Cost	\$/t	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	(13.05)	-	-	-	-	-	-	-	-	-	-	-	
Process Cost	\$000s	(526,811)	(22,490)	(42,289)	(45,023)	(44,811)	(43,403)	(41,760)	(40,684)	(39,903)	(38,343)	(35,555)	(33,343)	(31,670)	(31,558)	(31,558)	-	-	-	-	-	-	-	-	-	-	-	
Site GR&C Cost	\$000s	(176,478)	(9,037)	(17,106)	(16,324)	(16,324)	(16,006)	(15,915)	(15,086)	(14,316)	(14,798)	(14,140)	(12,798)	(12,260)	(12,260)	(12,260)	-	-	-	-	-	-	-	-	-	-	-	
Dore Refining/Freight Costs	\$000s	(657)	(657)	(657)	(657)	(657)	(657)	(657)	(657)	(657)	(657)	(657)	(657)	(657)	(657)	(657)	-	-	-	-	-	-	-	-	-	-	-	
By-Product Credit	\$000s	51,040	1,433	3,163	4,112	3,587	3,997	3,995	3,995	3,995	3,995	3,995	3,995	3,995	3,995	3,995	-	-	-	-	-	-	-	-	-	-	-	
Direct Cash Costs	\$000s	(1,448,864)	(64,793)	(127,891)	(117,289)	(117,289)	(116,389)	(116,389)	(116,389)	(116,389)	(116,389)	(116,389)	(116,389)	(116,389)	(116,389)	(116,389)	-	-	-	-	-	-	-	-	-	-	-	
Capital Expenditure	\$000s	(18,778)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	(1,809)	-	-	-	-	-	-	-	-	-	-	-	
Environmental Bond	\$000s	(7,445)	(499)	(499)	(523)	(523)	(523)	(523)	(523)	(523)	(523)	(523)	(523)	(523)	(523)	(523)	-	-	-	-	-	-	-	-	-	-	-	
Interest Expense - Capital Leases	\$000s	(11,226)	(1,207)	(2,701)	(2,215)	(2,202)	(1,407)	(1,407)	(1,407)	(1,407)	(1,407)	(1,407)	(1,407)	(1,407)	(1,407)	(1,407)	-	-	-	-	-	-	-	-	-	-	-	
Principal Payment - Capital Leases: Sustaining	\$000s	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	(1,638)	-	-	-	-	-	-	-	-	-	-	-	
Principal Payment - Capital Leases: Non-Sustaining	\$000s	(108,810)	(2,743)	(14,842)	(17,781)	(19,118)	(22,759)	(18,781)	(4,794)	(4,542)	(2,422)	(927)	(142)	(142)	(142)	(142)	-	-	-	-	-	-	-	-	-	-	-	
Regional Business Units	\$000s	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	(1,954)	-	-	-	-	-	-	-	-	-	-	-	
Non-Operating Cash Costs	\$000s	(176,880)	(1,471)	(23,652)	(26,289)	(27,623)	(28,463)	(28,463)	(28,463)	(28,463)	(28,463)	(28,463)	(28,463)	(28,463)	(28,463)	(28,463)	-	-	-	-	-	-	-	-	-	-	-	
Total Project Costs	\$000s	(1,624,844)	(66,248)	(161,633)	(144,288)	(146,972)	(152,612)	(147,789)	(156,634)	(149,386)	(135,746)	(134,829)	(105,399)	(72,248)	(47,119)	(23,986)	-	-	-	-	-	-	-	-	-	-	-	
Operating Margin	\$000s	2,169,257	77,173	155,083	143,152	169,283	339,541	200,388	329,609	238,545	159,740	114,564	196,261	265,375	309,580	341,983	-	-	-	-	-	-	-	-	-	-	-	
Earnings																												